

Effective adsorption of Ag–TiO₂ using a Cu-containing solution

ABSTRACT

Titanium dioxide is hard to coat on glass or boehmite at low pH. In this study, a method to coat titanium dioxide functionalized by Ag on the glass surfaces using a Cu-containing solution is proposed. This method facilitated the coating of titanium dioxide functionalized by Ag on glass surfaces using 3-aminopropyltrimethoxysilane (APTMS). Results showed that Ag–TiO₂ nanoparticles can be coated on Al and glass surfaces. Furthermore, they can be coated on boehmite at low pH without using APTMS.

Keywords: 3-aminopropyltrimethoxysilane; Copper (II) nitrate; Boehmite; Glass; Anatase TiO₂ nanoparticles; Ag–TiO₂ nanoparticles

1. Introduction

Titanium dioxide (TiO₂) is an important material because it is widely used in several applications. Typically, TiO₂ has three forms: anatase, rutile, and brookite. Anatase TiO₂ has better photocatalytic properties than rutile TiO₂ [1, 2]. TiO₂ nanoparticles (NPs) are used in several applications such as photocatalysts, self-sustained fuel cells, biocides, solar cells, oxygen reduction catalysts, and optoelectronic devices. The photocatalytic activity of TiO₂ can be improved in Ag-doped TiO₂ NPs. Ag-doped TiO₂ can be used in more applications than TiO₂ (e.g., as a photocatalyst, in solar cells, and to enhance the antibacterial efficiency of sterilization) [3–10]. The enhanced photocatalytic activity of TiO₂ doped with transition metals can be attributed to the increase in its absorption in the visible-light region. Additionally, TiO₂ doping with Ag also increases its disinfection capability [8]. TiO₂ or Ag–TiO₂ can be used for applications, such as bactericidal applications, by coating them on a glass substrate. This method allows the reuse of the material. The resultant solution should be at low pH, which induces a stable dispersion of the nanoparticles. The electrostatic potential on a surface, called zeta potential, is an important factor. Anatase TiO₂ stably disperses in a strongly acidic medium at pH ≤ 2. However, it is difficult to coat anatase TiO₂ on glass using 3-aminopropyltrimethoxysilane (APTMS) at low pH, because the protons in the surface SiAOH groups were not detached and created a negatively charged surface, which is not enough capable of attracting positively charged TiO₂ NPs [11]. This study examines coating anatase TiO₂ on glass surfaces using APTMS. In this study, Cu(NO₃)₂ was added to aid the adsorption of anatase TiO₂ on glass plates treated with APTMS to form a self-assembled monolayer at ~20 °C. Ag–TiO₂ coating on glass surfaces was also investigated. Furthermore adding Cu(NO₃)₂ enabled Ag–TiO₂ NPs to be successfully coated on boehmite without APTMS.

2. Experimental

2.1. Preparation of anatase TiO₂ NPs, Ag–anatase TiO₂ NPs, and solution containing Cu ions

Anatase TiO₂ NPs were prepared using an aqueous anatase TiO₂ suspension (500 mL, 0.02%). This mixture was heated to the boiling stage under vigorous stirring for ~20 min.

Ag–anatase TiO₂ NPs were prepared using an aqueous anatase TiO₂ suspension (500 mL, 0.02%). This mixture was heated to the boiling stage under vigorous stirring for ~20 min before adding an aqueous AgNO₃ solution (5 mL, 1%). Next, sodium citrate (5 mL, 1%) was added after 5 min of the addition of the AgNO₃ solution. Boiling was continued for ~5 min until the particle surfaces turned black.

An aqueous Cu(NO₃)₂ solution (200 mL, 0.01%) was boiled for ~2 min, and a sodium citrate solution (2 mL, 1%) was added to the solution, after which the color of the solution became deep blue. The final product is a Cu-citric complex ion-containing solution.

The pH of the solution was subsequently adjusted to 2–3 by adding diluted HNO₃.

2.2. Preparation of Ag–TiO₂ and TiO₂ adsorbed on substrates

An Al plate which purchased from KENIS LIMITED was cleaned using deionized water, sonicated using a neutral detergent for 15 min to remove grease from its surface, and sonicated again in deionized water for 20 min. To form a boehmite layer on the Al surface, the Al plate was boiled in deionized water for ~15 min.

The Al plate was then functionalized by immersing it in an aqueous APTMS solution (2% (v/v)) for 25 h at ~20 °C. APTMS can dissolve the Al plate because of its alkalinity (pH = 11). To prevent this, the APTMS solution was neutralized using diluted HCl solution before using it to functionalize the Al substrate. The functionalized substrates were then rinsed using deionized water and annealed at 110°C.

The Ag–TiO₂ adsorbed on the substrates was prepared by a chemical assembly of Ag–anatase TiO₂ NPs on the prepared boehmite Al surface. This was conducted by immersing the plate in an Ag–anatase TiO₂ NP solution for 50 h until the NPs were deposited on the surface.

Ag–TiO₂ adsorbed on the substrates was also prepared by a chemical assembly of the Ag–TiO₂ NPs on the APTMS-functionalized Al plates. These plates were immersed in an Ag–anatase TiO₂ NP solution for 50 h until a film of the NPs is formed on the APTMS-modified substrate.

Glass slides were ultrasonically cleaned in deionized water, isopropyl alcohol, acetone, and deionized water for 15 min each followed by immersion in H₂O/H₂O₂/30% NH₄OH (5:1:1) for 16 h. For functionalization, the slides were further cleaned by sonication in deionized water for 15 min and then immersed in an aqueous APTMS solution (2% (v/v)) for 24 h at room temperature. The functionalized substrates were subsequently rinsed using deionized water and annealed at 110 °C [12, 13]. Some of them were then immersed in a TiO₂ NP solution for 75 h. The other substrates were immersed in an Ag–anatase TiO₂ NP solution for 75 h until a film of particles was formed on the APTMS-modified substrate.

2.3. Characterization

Using a field emission microscope (JSM6500F) operated at an accelerating voltage of 15 kV, scanning electron microscopy (SEM) images were obtained. Transmission electron microscopy (TEM) images were obtained using a field emission transmission electron microscope (HD-2300C) operated at an accelerating voltage of 200 kV.

2.4. Materials and methods

1) Materials

AnataseTiO₂ NPs were obtained from anatase TiO₂ (Kanto Chemical Co. Inc, Japan). The particle diameter of the anatase TiO₂ used in this study was 100–300 nm. The following reagents were obtained: 3-aminopropyltrimethoxysilane (Tokyo Chemical Industry Co., Ltd, Japan), sodium citrate (Wako Pure Chemical Corporation, Japan), AgNO₃ (YONEYAMA YAKUHIN KOGYU Co., Ltd, Japan), and Cu(NO₃)₂ (Kanto Chemical Co. Inc, Japan); all reagents were of analytical grades.

2) Methods of preparing Ag–TiO₂

The particle size of anatase TiO₂ decreases during boiling because of the collision of the particles [10]. Thus, the anatase TiO₂ NPs were boiled for ~20 min to decrease their particle size. A part of the solution was then added to a solution containing a mixture of AgNO₃ (1%) and sodium citrate (1%). After ~3 min, the surfaces of the TiO₂ particles turned black. Diluted HNO₃ was then added for adjusting the pH to 2–3 because acidic conditions promote the deposition of Ag NPs on the TiO₂ surfaces. Ag remains stable on the TiO₂ surface for over 5 months [14].

3. Results and discussion

Figure 1(a) shows the TEM images of the prepared Ag–TiO₂ particles after adjusting the pH of the solution to 3 using diluted HNO₃. The X-ray spectroscopy (EDS) pattern in Figure 1(b) confirms a successful adsorption of Ag NPs on all surfaces.

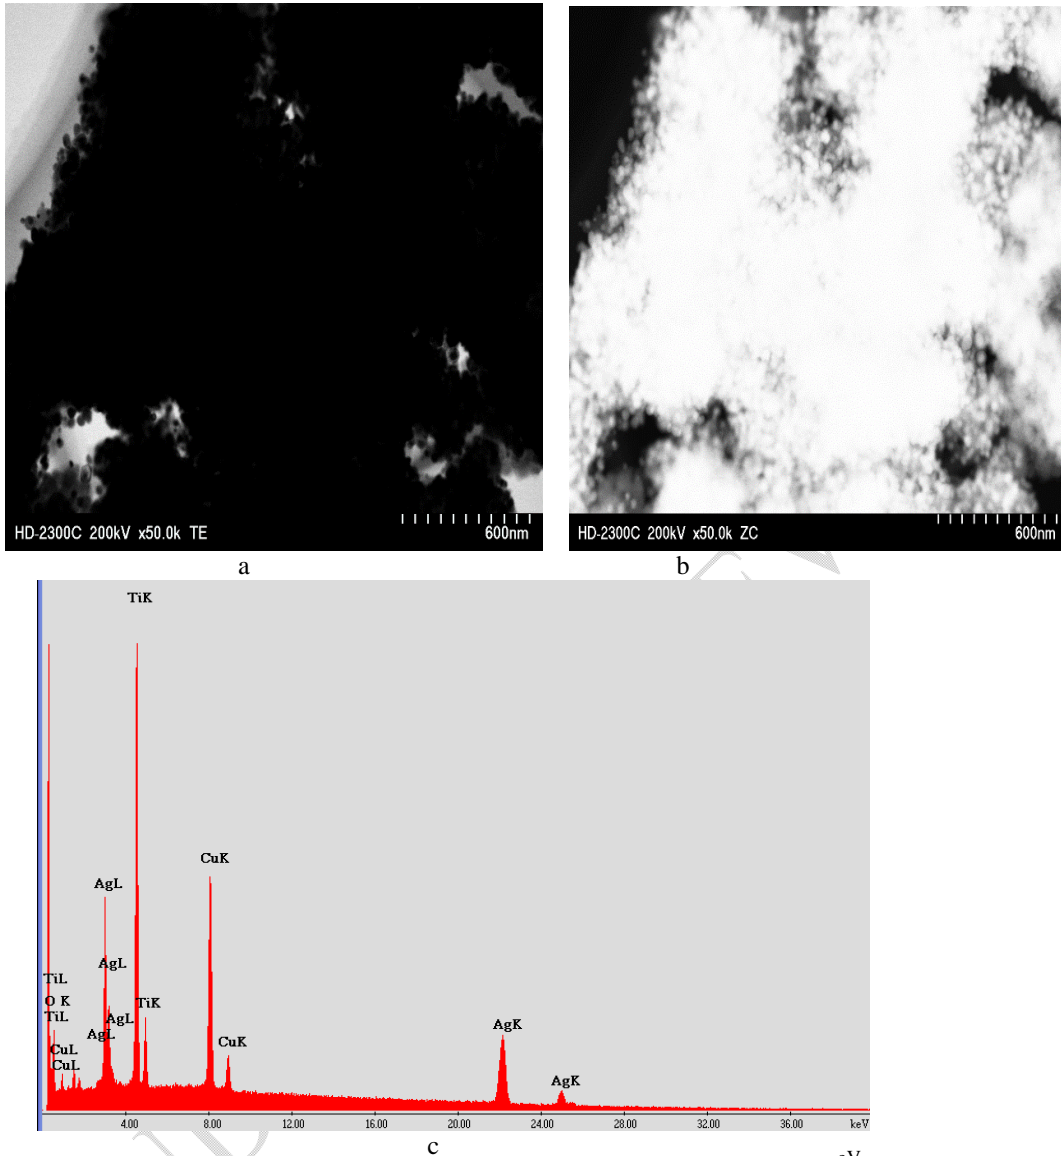


Fig. 1. (a) TEM images of an anatase (TiO_2) surface coated using Ag at pH 3, (b) high-angle annular dark-field image of Ag- TiO_2 , (c) point EDS pattern of the TiO_2 surface. The copper signal is from the TEM sample grid.

Figures 2–5 show that the developed Ag- TiO_2 NPs could be adsorbed on Al or glass surfaces. Because Al dissolves at a pH = 2, the pH was adjusted to 3 using diluted HNO_3 for the synthesis. Figure 2(a) shows the SEM image of the Ag- TiO_2 NP adsorption on the APTMS-modified Al surface. The energy dispersive EDS pattern in Figure 2(b) indicates that Ag- TiO_2 was adsorbed on the Al surface. However, only a small deposit was observed on the Al surface, which was not modified by APTMS, with the boehmite layer.

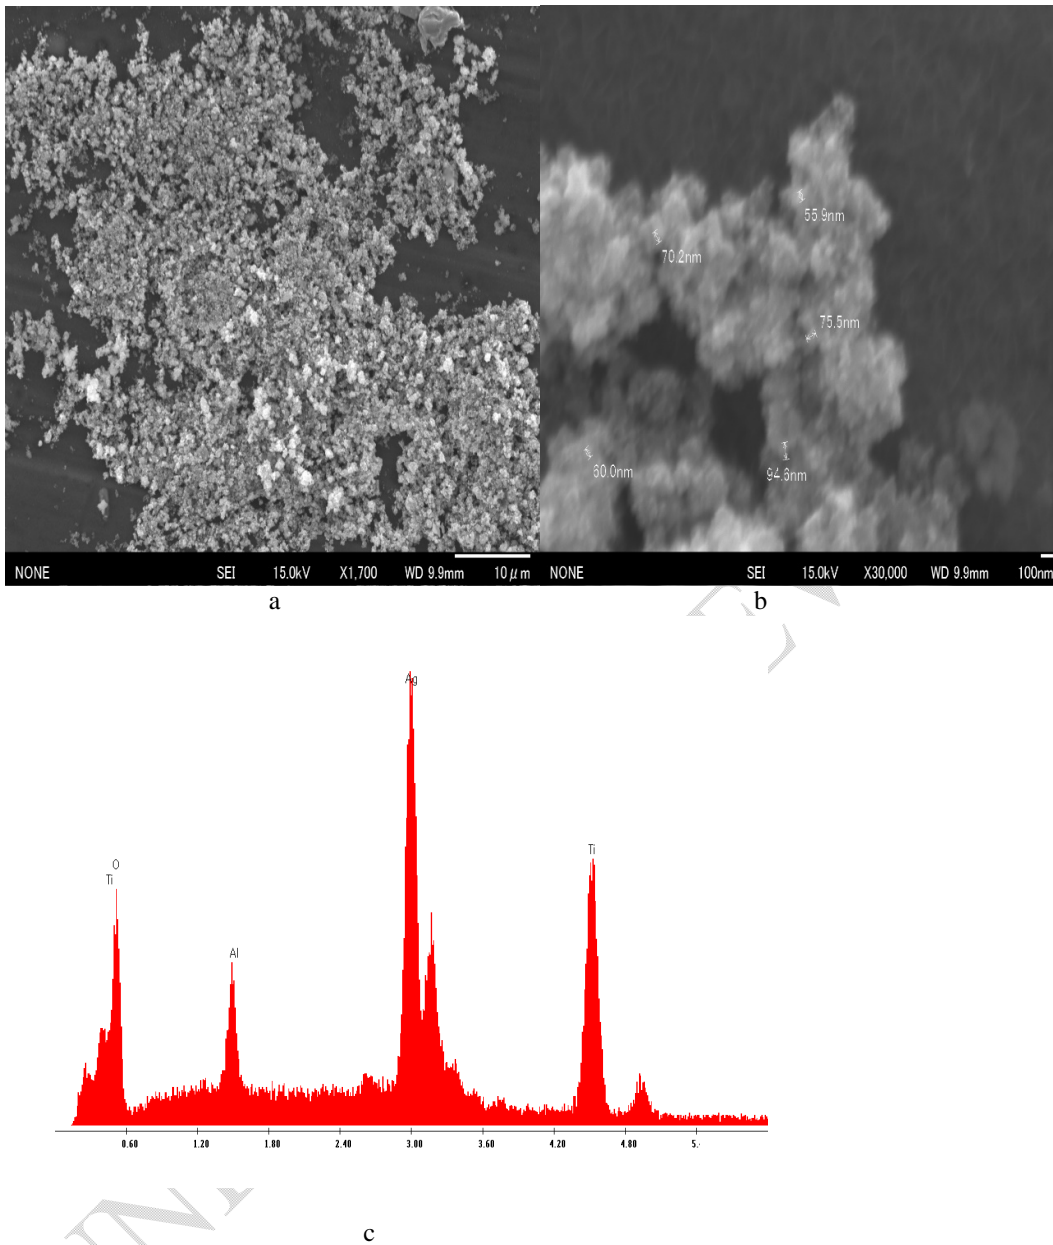


Fig. 2. (a)(b) SEM image of the Al surface functionalized with APTMS at pH 3 adjusted using dilute HNO_3 ; (c) point EDS pattern of the Al surface

Figure 3(a) denotes the SEM image of the Ag-TiO₂ NP adsorption on the Al surface with a boehmite layer. The energy dispersive EDS pattern in Figure 3(b) indicates that only Ag was adsorbed on the Al surface.



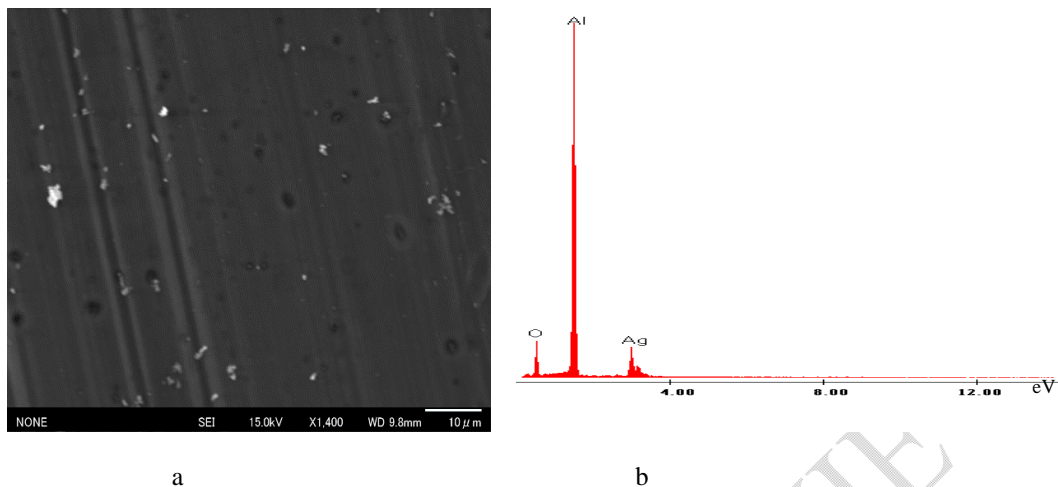


Fig. 3. (a) SEM image of the Al surface at pH 3 adjusted using dilute HNO_3 , which coated by Ag-TiO_2 solution without copper ion. ;(b) point EDS pattern of the Al surface


Next, the Al surface with a boehmite layer that was immersed in a solution containing a mixture of Ag-TiO_2 and $\text{Cu}(\text{NO}_3)_2$ was examined. Figure 4(a) shows the SEM image of the adsorption of Ag-TiO_2 NPs on the Al surface with the boehmite layer. Many Ag-TiO_2 particles were observed on Al surface. The energy dispersive EDS pattern in Figure 4(b) indicates that Ag-TiO_2 was adsorbed on the Al surface.

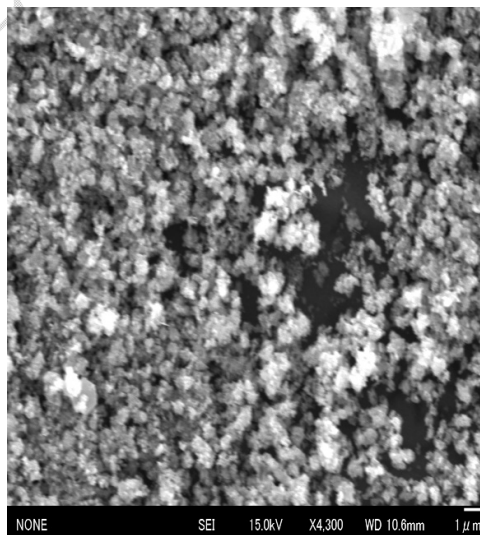

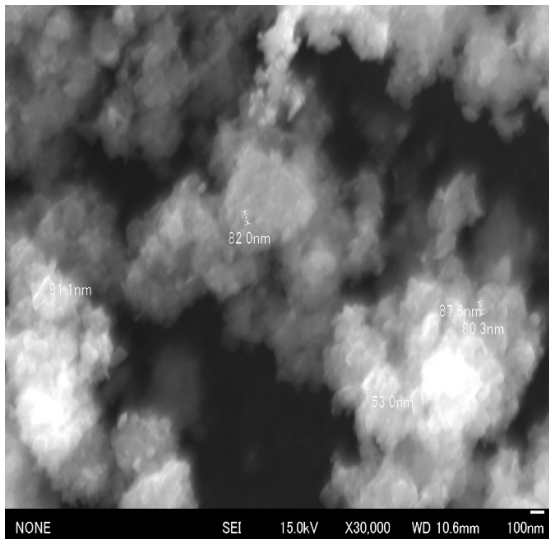

a

b

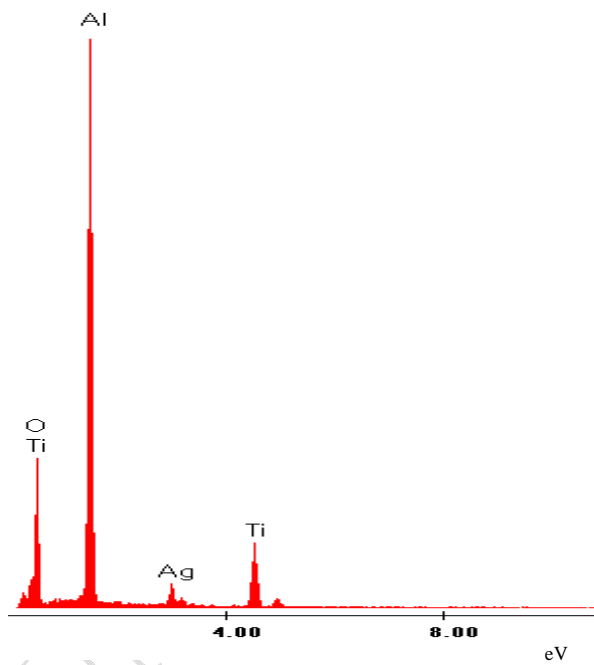


c

Fig. 4. (a)(b) SEM image of the Al surface at pH 3 adjusted using dilute HNO₃, which coated by aqueous Ag-TiO₂ solution including copper ion; (c) point EDS pattern of the Al surface.

As shown in Table 1, taking from the reference [15], the Cu-citric complex ion is changed from a negative charge at pH 5–7 to a positive charge at pH 2–4. At pH 2–4, the Cu-citric complex ion is formed $[\text{CuH}_2\text{C}_6\text{H}_5\text{O}_7]^+$. However, an electron is released from Ag-TiO₂ surface. Then, the following reaction occur $[\text{Cu}(\text{Ligand})] + e^- \rightarrow \text{Cu}^0 + \text{Ligand}^-$. [15] Cu prevents Ag present in Ag-TiO₂ surface from dissolving by the law of ionization tendency (Figure 5).


Table 1. Citric Acid Complexes That Were Formed at Different pH Values and Their Dissociation Constants

pH	complex	Dissociation constant (K_{dis}) ^a [L ² /mol ²]
2-4	[CuH ₂ C ₆ H ₅ O ₇] ⁺	1.0×10 ⁻⁶
4-5	[CuH ₂ C ₆ H ₅ O ₇]	1.0×10 ⁻⁷
5-7	[CuC ₆ H ₅ O ₇] ⁻	7.4×10 ⁻⁶
7-11	[Cu(OH)C ₆ H ₅ O ₇] ²⁻ [CuC ₆ H ₄ O ₇] ²⁻	1.8×10 ⁻¹⁸ 1.5×10 ⁻¹⁶
>11	[Cu(OH)C ₆ H ₄ O ₇] ³⁻	1.8×10 ⁻¹⁸

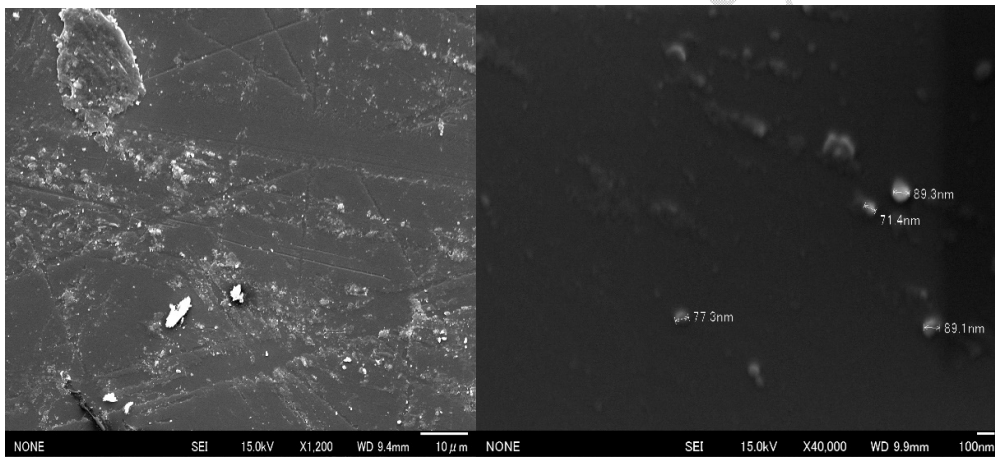

a

b

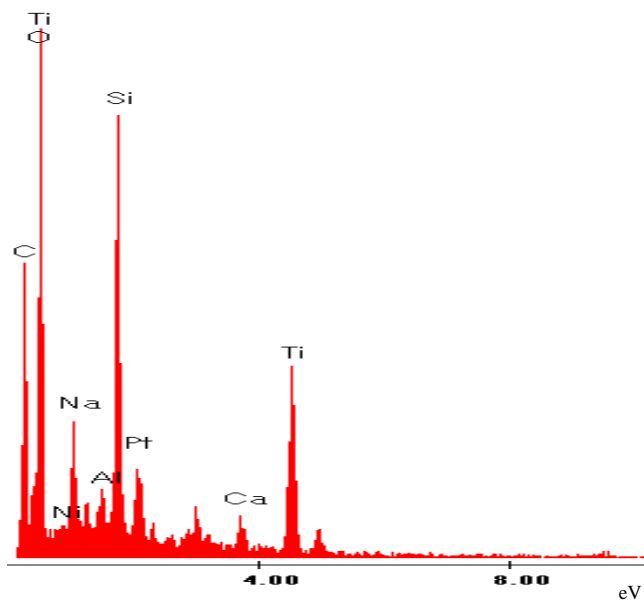

c

Fig. 5. (a)(b) SEM image of the glass surface at pH 2 adjusted using dilute HNO_3 , which coated by aqueous anatase(TiO_2) solution including copper ion; (c) point EDS pattern of the glass surface.

When HNO_3 was added to the solution, the morphology of the Cu-citric complex ion changed; the Cu-citric complex ion changes similar to the abovementioned reason. Several OH groups of the boehmite were present on the surface of the boehmite, which may serve as a proton conductor for the electrochemical reactions in aqueous environments. Cu donated its valence electrons to OH groups ($-\text{OH}_2^+$) and changed to Cu^{2+} . Then, the positively charged Ag- TiO_2 bonded to boehmite. Furthermore, Cu^{2+} was recovered by citric acid and became $[\text{CuC}_6\text{H}_5\text{O}_7]^-$. The color of the mixed solution before adding HNO_3 was deep brown; after adding HNO_3 , the solution first turned light green, and after leaving turned deep brown when the solution was recovered, which reason is considered for gradual recovery of the solutions' original color of dark blue ($[\text{CuC}_6\text{H}_5\text{O}_7]^-$) from light blue ($[\text{CuH}_2\text{C}_6\text{H}_5\text{O}_7]^+$) (Figure 6) [15].

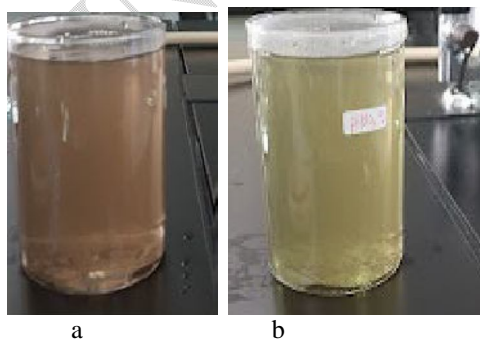



Fig.6. The color of the mixed solution including Cu-citric complex ion.

(a) The color of the mixed solution before adding HNO_3 (b) The color of the mixed solution after adding HNO_3


Thus, the Ag-TiO_2 NPs can be deposited on the surfaces at either $\text{pH} = 3$ or 2 . This suggests that Ag-TiO_2 was bonded to boehmite.

Next, coating anatase TiO_2 on an APTMS-functionalized glass surface was examined. The surface isoelectric point of anatase TiO_2 was observed at a $\text{pH} = 6$ [16]. Hence, under more acidic conditions, hydrogen ions were adsorbed on the OH groups, resulting in a buildup of positive charges. Conversely, under alkaline conditions, the OH groups dissociate from the surface, resulting in a buildup of negative charges. Hence, anatase TiO_2 will be stably dispersed in a strong acidic solution with a $\text{pH} = 2$ or less [17]. However, the anatase TiO_2 NPs were found to slightly deposit on the glass surfaces at a $\text{pH} = 2$. In this case, protons in the surface SiOH groups were not detached, and a complete negatively charged surface was not created, which was incapable of attracting positively charged TiO_2 NPs. [18]. Therefore, the APTMS-functionalized glass surface was immersed in a solution containing a mixture of anatase TiO_2 and $\text{Cu}(\text{NO}_3)_2$. However, TiO_2 that were not coated by Ag cannot irradiate electron. Figure 5(a) illustrates the SEM image of the adsorption of TiO_2 NPs on the glass surface. The energy dispersive EDS pattern in Figure 5(b) indicates that TiO_2 was adsorbed on the APTMS-modified glass surface as some TiO_2 NPs were observed.


Next, Ag-TiO_2 was used instead of TiO_2 . The APTMS-functionalized glass surface was immersed in a solution containing a mixture of Ag-TiO_2 and $\text{Cu}(\text{NO}_3)_2$. Figure 7(a) shows the SEM image of Ag-TiO_2 NP adsorption on the glass surface. The energy dispersive EDS pattern in Figure 7(b) indicates that Ag-TiO_2 was adsorbed on the APTMS-modified glass surface. A considerable amount of Ag-TiO_2 NPs was observed on the surface. Because negative charge accumulates around the positively charged APTMS due to electron released from Cu, such as the reason before. Therefore, positively charged Ag-TiO_2 was deposited on glass surface. For comparison, Figure 7(c) shows the SEM image of Ag-TiO_2 NP adsorption on the glass surface immersed in a solution that does not contain $\text{Cu}(\text{NO}_3)_2$. Ag-TiO_2 NP deposits were few.

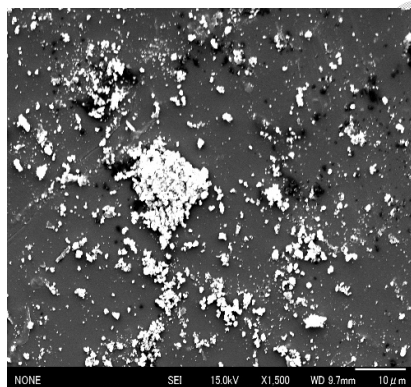

a

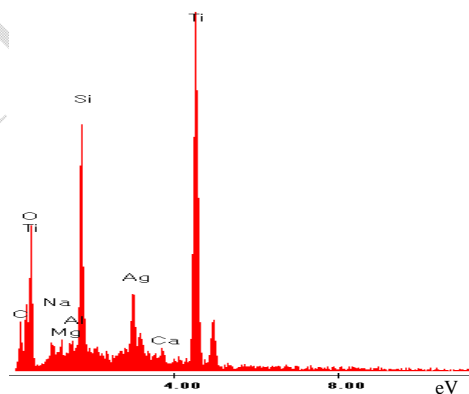

b

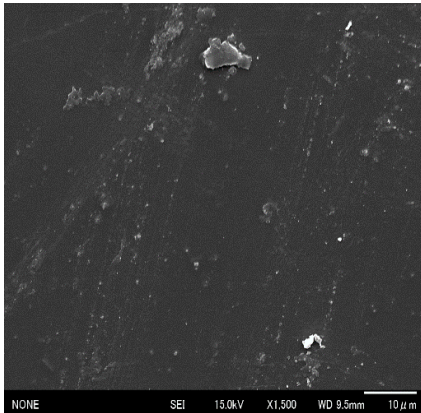

c

Fig. 7. (a) SEM image of the glass surface at pH 2 adjusted using dilute HNO_3 , which coated by Ag-TiO_2 solution including copper ion; (b) point EDS pattern of the glass surface; (c) SEM image of the glass surface at pH 2 adjusted using dilute HNO_3 , which coated by Ag-TiO_2 solution without copper ion.

4. Conclusions

In this study, TiO_2 and Ag-TiO_2 were adsorbed on Al and glass surfaces using a solution containing Cu ions. The Cu ions enhanced the adsorption of Ag-TiO_2 on Al and glass surfaces. Negative charge accumulates around the positively charged APTMS by irradiation electron from Ag-TiO_2 . And Cu acts not to dissolve Ag from Ag-TiO_2 surface by law of ionization tendency, such as the reason before. This can be attributed to the buildup of negative charges, which occurred after the addition of HNO_3 to the solution as a result of its reaction with Cu. Producing substrates that have localized surface plasmon resonance and antibacterial effects is easy using this method.

References

- [1] M. Pelaez; N. T. Nolan, S. C. Pillai; M. K. Seery, P. Falaras, A. G. Kontos, P. S. M. Dunlop, J. W. J. Hamilton; J. A. Byrne, K. O'shea, M. H. Enterazai, D. D. Dionysiou, A review on the visible light active titanium dioxide photocatalysts for environmental applications, *Appl. Catal. B*, 2012; 125;331–349.
- [2] Moges Tsega, F. B. Dejene, Influence of acidic pH on the formulation of TiO_2 nanocrystalline powders with enhanced photoluminescence property, *Heliyon*, 2017; 16;e00246.
- [3] Y. Cui, J. Briscoe, S. Dunn, Effect of ferroelectricity on solar-light-driven photocatalytic activity of BaTiO_3 —influence on the carrier separation and stern layer formation, *Chem. Mater.* 2013; 25;4215–4223.
- [4] Lili Ling, Yawei Feng, Hao Li, Yao Chen, Jieya Wen, Jian Zhu, Zhenfeng Bian,

- Microwave-induced surface enhanced pollutant adsorption and photocatalytic degradation on Ag/TiO₂, *Appl. Surf. Sci.* 2019; 483;772–778.
- [5] Beung-Hoon Jeon, Do-Hyeon Yang, Yong-Dae Kim c, Jae Sup Shin, Chang-Soo Lee, Fabrication of silver nanoparticles in titanium dioxide/poly(vinylalcohol) alternate thin films: A nonenzymatic hydrogen peroxidesensor application, *Electrochim. Acta.* 2018; 292;749–758.
- [6] Hui Mao, Zhengxin Fei, Chaoqun Bian, Leilei Yu, Shengyi Chen, Yongteng Qian, Facile synthesis of high-performance photocatalysts based on Ag/TiO₂ Composites, *Ceram. Int.* 2019; 45; 12586–12589.
- [7] Kairui Liu, Peifang Yan, Hong Jiang, Zhi Xia, Zhanwei Xu, Shi Bai, Z. Conrad Zhang, Silver initiated hydrogen spillover on anatase TiO₂ creates active sites for selective hydrodeoxygenation of guaiacol, *J. Catal.* 2019; 369; 396–404.
- [8] Robert Liu, H. S. Wu, Ruth Yeh, C. Y. Lee, Yungtse Hung, Synthesis and Bactericidal Ability of TiO₂ and Ag-TiO₂ Prepared by Coprecipitation Method, *Int. J. Photoenergy.* 2012; 7.
- [9] Yuyang Sun, Lulu Yang, Fan Liao ↑, Qian Dang, Mingwang Shao, Parameter optimization for Ag-coated TiO₂ nanotube arrays as recyclable SERS substrates, *Appl. Surf. Sci.* 2018; 443; 613–618.
- [10] V. Poornima Parvathi, R. Parimaladevi, Vasant Sathe, M. Umadevi, Environmental photochemistry by plasmonic semiconductor decorated GO nanocomposites: SERS detection and visible light driven degradation of aromatic dyes, *Appl. Surf. Sci.*, 2019; 473; 864–872.
- [11] K.C. Hsu, D.H. Chen, Highly sensitive, uniform, and reusable surface-enhanced Raman scattering substrate with TiO₂ interlayer between Ag nanoparticles and reduced graphene oxide, *ACS Appl. Mater. Interfaces*, 2015; 7; 27571–27579.
- [12] Ming-DeLi, Yan Cui, Min-Xia Gao, Jia Luo, BinRen, and Zhong-QunTian, Clean Substrates Prepared by Chemical Adsorption of Iodide Followed by Electrochemical, Oxidation for Surface-Enhanced Raman Spectroscopic Study of Cell Membrane, *Anal. Chem.* 2008; 80; 5118–5125.
- [13] Masayoshi Kaneko, Long-term stabilization of mixed silver nanoparticles on an Al surface with poly(2-vinylpyridine) films, *Vib. Spectrosc.* 2016; 86; 61–66.
- [14] Masayoshi Kaneko, Coating Ag on an Anatase TiO₂ Surface and Adsorption on a 3-Aminopropyltrimethoxysilane-Modified Al or Glass Surface, *AJOPACS*, 2021;9(1);11-21.
- [15] H.Natter and R.Hempelmann,Nanocrystalline Copper by Pulsed Electrodeposition : The Effects of Organic Additives,BathTemperature,and pH,*J.phys.Chem*,1996;100;19525-19532.
- [16] Kunio Furusawa, Measurement of zeta potential, *BUNSEKI*, 2004; 5 ; 247–254.
- [17] Hidehiro Kamiya, Motoyuki, Iijima, Dispersion, Behavior Control of Nanoparticles and its

|

Applications, FUNSAI, 2012; 55; 12–18.

[18] Masayoshi Kaneko, Anatase TiO₂ adsorption on 3-aminopropyltrimethoxysilane-modified Al or glass surfaces, Heliyon, 2019; 5 ; e01734.

UNDER PEER REVIEW