

Biological preparation, characterization of CaO nanoparticles from egg shell waste and insecticidal activity against seed weevil, *Sitophilus oryzae* L. in maize

ABSTRACT

Calcium oxide (CaO) nanoparticles was biologically synthesized by calcinating egg shells from kitchen waste and characterized using SEM, UV-Vis, XRD and FT-IR. Biosynthesized CaO nanoparticles are found to be an effective insecticide against seed weevil, *Sitophilus oryzae* in maize. The indiscriminate use of already available commercial pesticides has led to develop resistance among the pests and also occurrence of pesticide residues in produce. The SEM study revealed that the particles are granular in shape with a size of 189 nm. The diffraction peaks of XRD were observed at $2\theta = 32.320, 37.48^\circ, 48.40^\circ, 53.96^\circ, 64.18^\circ, 67.52^\circ$ and exhibited polycrystalline nature. In the FTIR spectrum, a broad band at 1410 cm^{-1} , a sign of a C-O bond which indicated the association between the oxygen atom of carbonate and the calcium atom. The insecticidal activity of CaO nanoparticles was assessed against *S. oryzae* by contact toxicity bioassay method. The outcomes of the bioassay studies showed that the lethal dose (LD_{50}) for maize seeds was 72.62 mg/100 g. and within seven days of exposure, 100% death of *S. oryzae* was attained at a dosage of 240 mg/100 gm of maize seeds. The current study came to the conclusion that biosynthesized CaO nanoparticles may be used as an effective management technique to successfully manage the *S. oryzae* under storage conditions as an alternative to chemical pesticides.

Keywords: CaO nanoparticles, storage pest, Sitophilus oryzae, Contact toxicity.

1. INTRODUCTION

To satisfy the human population's need for food, cereals are cultivated to greater extents. Among these, maize (*Zea mays*) is regarded as a crucial crop because it provides both human food and animal feed. It is cultivated all over the world and is widely used in the trade of coarse grains. In the global trade of coarse grains, maize is a key player. The biggest issue with maize cultivation is post-harvest loss, which results in a significant yield loss in terms of production and productivity. Post-harvest losses are caused by both biotic and abiotic causes.

The main cause of damage to the maize seeds is storage insect pests. In storage, more than 37 different species of insects cause harm [1]. The seed weevil, *Sitophilus oryzae* L. is the one that has the most qualitative and quantitative impact on the economy. The use of chemicals insecticides to eradicate the pest caused negative impacts on the ecosystem and the emergence of insect resistance. Botanicals are plant derived products possessing bio-active constituents involving in pest control. The extracts from plants are widely used as repellent, antifeedant and arrestant. They also have effect on insect growth either by affecting the oviposition or feeding behaviour. Common botanicals used in storage ecosystem are sweet flag [2], neem [3], pepper mint [4], sweet basil [5] and bael [6]; despite, botanicals lack immediate mode of action and mortality.

Recently, nanoparticles can be considered as an alternative for chemical insecticides, particularly under storage environments and also improve the germination of seed during

storage. Nanotechnology is an emerging field of science with wide range of applications. It offers new methods for designing novel active ingredients with nanoscale dimensions, as well as their formulation and delivery that are collectively referred to as 'Nanopesticides'.

An interesting fact adding to their insecticidal property is that nanoparticles possess higher surface area to volume ratio [7]. Nanoparticles bring about insect mortality through physical mode of action even at very low concentration. Major advantages include nanoparticles bring quick mortality and eco-friendly too since it can be synthesized from green route, with minimum residues in the produce and wide scale adaptation. In addition to serving as a structural component of cell walls and membranes and regulating plant growth and development, calcium is a crucial macronutrient for plants. The structural integrity of stems that support flowers and fruit, as well as the quality of the generated fruit, are highly influenced by calcium availability. Additionally, calcium improves a plant's resistance to bacterial and viral infections. For treating the calcium deficit in groundnuts, calcium oxide nanoparticles (CaO-Nanoparticles) can be employed. Hence, an attempt has been made to prepare calcium oxides nanoparticle from egg shell waste to assess the insecticide against *S. oryzae*.

2. MATERIAL AND METHODS

2.1 Biological synthesis of CaO Nanoparticles

Egg shell waste were collected from kitchen. Collected egg shell waste was washed using tap water for 3-5 times to clean the shell and remove white membrane which is present inside the egg shell. Egg shells are then dried using hot air oven at 70°C for 2 hours and grinded using pestle and mortar to get fine powders rich in calcium carbonate. The egg shell powder is finally calcinated at 900°C for 4 hrs using muffle furnace to get CaO nanoparticles [8].

2.2 Characterisation of nanoparticles

The size and surface morphology of the CaO nanoparticles was characterized using Scanning Electron Microscope (SEM). The presence of CaO nanoparticles were confirmed by absorbed specific wavelength of the nanoparticles using UV-Vis spectroscopy. The crystalline nature of the biologically synthesized CaO nanoparticle were observed by X-ray Diffractometer (XRD). The functional groups present in CaO nanoparticles were analysed using the Fourier Transform Infrared Spectrometer (FTIR).

2.3 Mass culturing of test insects

S. oryzae weevils were collected from the infested grain products in godowns at the Department of Millets, Tamil Nadu Agricultural University (TNAU), Coimbatore. The weevils were raised on maize grains in a 27±3°C room environment. To ensure a constant supply of insects, subculturing was carried out at intervals of 15 to 20 days. For bioassay studies, uniform aged adults that were one week old were employed.

2.4 Toxicity assessment of test materials against *S. oryzae*

Bioassay was conducted by filling each tiny plastic container with 100g of maize seeds. A control (without any treatment) was maintained while maize seeds were exposed to CaO

Nanoparticles at various concentrations (1 mg, 5 mg, 30 mg, 50 mg, 60 mg, 80 mg, 120 mg, 140 mg, 160 mg, 200 mg and 240 mg) and insecticide treatment (Cypermethrin 0.25%) was used for comparison. To achieve equal dispersion, the containers were then manually shaken for about a minute [9] and then fifteen pairs of adults were placed in each container with four replications in a completely randomized design. The experimentation was done at 27°C and 70% RH and mortality was observed in every 24 hours for seven days (lack of movement and/or responsiveness to repeated probing). Abbott formula was used to calculate the corrected mortality. The observations on the mortality percentage were put through a probit analysis, and the LD50 value was calculated.

Corrected (%) mortality = $(X - Y) / (100 - X) \times 100$

X = Percentage mortality in test material treated treatments

Y = Percentage mortality in the untreated check

2.5 Statistical analysis

Using AGRES statistical software, the data were analysed using a completely randomized design (CRD). Finney's approach (1971) was used to perform the probit regression analysis. Analysis of variance (ANOVA) was carried out to see if there are any treatments that differ significantly from one another.

3. RESULTS AND DISCUSSION

The size and surface morphology of the biologically synthesized CaO nanoparticles was observed by Scanning electron microscope (figure 1). The results are revealed that the particles are granular in shape with 189.0 nm in size. The results of the CaO molecules or atoms absorbing UV light, their electrons are stimulated to higher energy levels. In the present study, a sharp peak in UV-visible spectra at 320 nm suggested the presence of calcium oxide nanoparticle (Figure 2). The diffraction peaks (Figure 3) were observed at $2\theta = 32.320^\circ, 37.48^\circ, 48.40^\circ, 53.96^\circ, 64.18^\circ, 67.52^\circ$. The CaO Nanoparticles' exhibited excellent polycrystalline nature which shown by the XRD pattern's sharp peaks and smaller spectrum width. Similarly, the FT-IR spectrum (Figure 4) of the biosynthesized CaO nanoparticles revealed a broad band at 1410 cm^{-1} , a sign of a C-O bond that indicates an association between the oxygen atom of carbonate and the calcium atom. In addition, a sharp peak around 876 cm^{-1} corresponds to C-O bond denoting the carbonation of biosynthesized CaO nanoparticles. The results are in agreement with the findings of [10] and they have also prepared, characterized CaO nanoparticles from chicken egg shells.

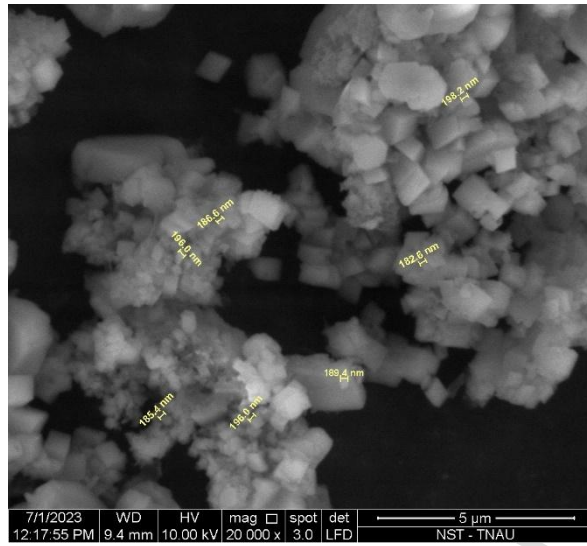


Figure 1: SEM analysis of CaO nanoparticles

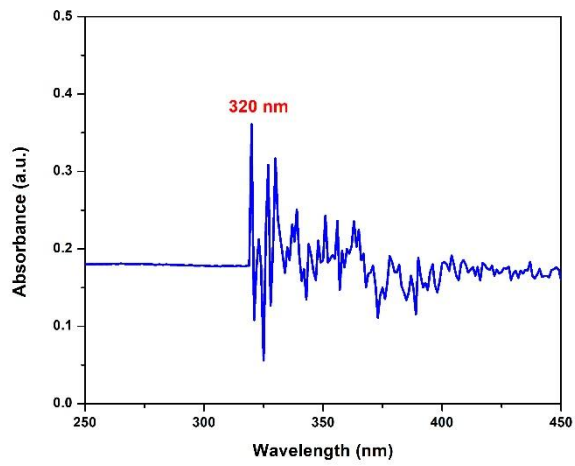


Figure 2: UV-Vis spectra of CaO nanoparticles

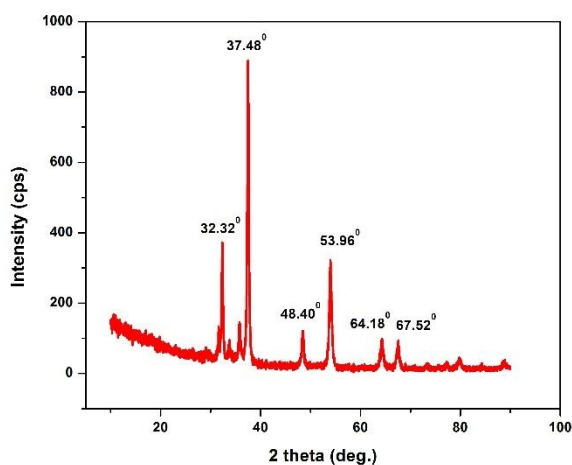


Figure 3: XRD spectrum of CaO nanoparticles

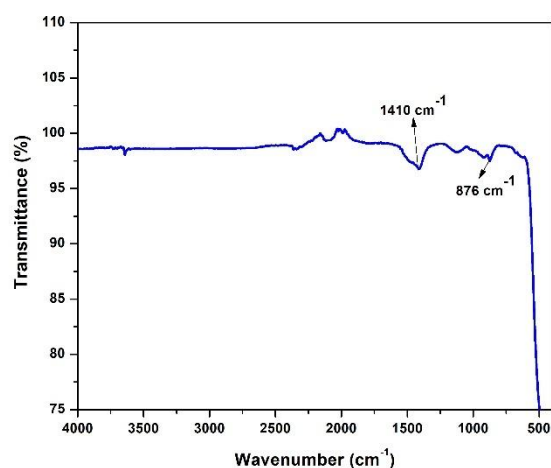


Figure 4: FT-IR spectrum of CaO nanoparticles

3.1 Toxicity assessment against *S. oryzae*

The bioassay results demonstrated the entomotoxic potential of CaO Nanoparticles against *S. oryzae*. The LD₅₀ and LD₉₀ of CaO Nanoparticles (72.62 and 511.10 mg/100 g, respectively) and Cypermethrin 0.25%, (12.63 mg/100 g and LD₉₀ was 543.56 mg/100 g) was determined by probit regression analysis (Table 1). The calculated chi-square value was lower than the tabular value, showing that the data fit the probit model exactly. In 100 g of seeds, 72.62 mg of CaO NP killed 50% of the insect population over the course of 7 days. When rice weevil comes into contact with CaO Nanoparticles treated seeds, Nanoparticles sticks on the surface. *v iz.*, head, thorax, abdomen, and its appendages and causes mortality. The results are in consistent with the results of [11], where CaO Nanoparticles

1	1	0.00 ^d ± 0.00	0.00 ^d ± 0.00	0.00 ^f ± 0.00	0.00 ^e ± 0.00	6.67 ^g ± 0.06	6.67 ⁱ ± 0.10	13.33 ^k ±0.26	13.33
2	5	0.00 ^d ± 0.00	0.00 ^d ± 0.00	0.00 ^f ± 0.00	6.67 ^d ± 0.07	13.33 ^f ±0.25	13.33 ^h ±0.04	20.00 ^j ±0.26	20.00
3	30	0.00 ^d ± 0.00	0.00 ^d ± 0.00	0.00 ^f ± 0.00	6.67 ^d ± 0.12	13.33 ^f ±0.10	20.00 ^g ±0.16	26.67 ⁱ ±0.01	26.67
4	50	0.00 ^d ±0.00	0.00 ^d ± 0.00	6.67 ^e ± 0.15	13.33 ^c ±0.26	20.00 ^e ±0.42	26.67 ^f ±0.32	33.33 ^h ±0.45	33.33
5	60	0.00 ^d ±0.00	0.00 ^d ± 0.00	6.67 ^e ± 0.16	13.33 ^c ±0.06	20.00 ^e ±0.39	33.33 ^e ±0.43	40.00 ^g ±0.94	40.00
6	80	6.67 ^c ± 0.02	6.67 ^c ± 0.09	6.67 ^e ± 0.04	13.33 ^c ±0.05	26.67 ^d ±0.36	40.00 ^d ±0.33	53.33 ^f ±0.11	53.33
7	120	0.00 ^d ± 0.00	6.67 ^c ± 0.05	20.00 ^d ±0.07	40.00 ^b ±0.02	53.33 ^c ±1.28	60.00 ^c ±1.50	66.67 ^e ±1.67	66.67
8	140	0.00 ^d ± 0.00	6.67 ^c ± 0.17	26.67 ^c ±0.04	40.00 ^b ±0.92	53.33 ^c ±0.31	60.00 ^c ±0.53	73.33 ^d ±1.37	73.33
9	160	13.33 ^b ±0.26	20.00 ^b ±0.44	26.67 ^c ±0.04	40.00 ^b ±0.75	53.33 ^c ±0.17	60.00 ^c ±0.00	80.00 ^c ±0.21	80.00
10	200	13.33 ^b ±0.03	20.00 ^b ±0.26	33.33 ^b ±0.03	53.33 ^a ±1.08	60.67 ^b ±1.04	80.00 ^b ±0.62	93.33 ^b ±0.58	93.33
11	240	20.00 ^a ±0.32	33.33 ^a ±0.61	40.00 ^a ±0.27	53.33 ^a ±0.69	73.33 ^a ±1.34	86.67 ^a ±0.05	100 ^a ± 0.31	100
12	Control	0.00 ^d ± 0.00	0.00 ^d ± 0.00	0.00 ^f ± 0.00	0.00 ^e ± 0.00	0.00 ^h ± 0.00	0.00 ^j ± 0.00	0.00 ^l ± 0.00	0.00
	SE(d)	0.14	0.19	0.31	0.30	0.48	0.85	1.17	-
	CD (0.05)	0.40	0.4	0.65	0.63	1.00	1.77	2.43	-

Mean of 30 observations, Means followed by different letters within a column indicate significant differences ($P < 0.05$; LSD (Least significant difference test); DAR= Day(s) after insect release

4. CONCLUSION

An essential inorganic substance known as calcium oxide (CaO) is employed in many different industries as a catalyst, toxic-waste remediation agent, adsorbent, etc. When applied topically to leaves, calcium oxide nanoparticles greatly accelerated germination and growth because they penetrate the phloem more deeply than their bulk counterparts. Biologically synthesized CaO nanoparticles also possessed higher insecticidal activity with LD₅₀ dose of 72.62 mg/100 g of maize seeds. In the current study, we seek to utilize the benefits of nanostructured engineering surfaces that contribute to the effects of metal oxide

nanostructures (CaO) for the creation of alternative and effective pesticides against rice weevil in maize seeds.

REFERENCE

1. Tadesse A. Arthropods associated with stored maize and farmers' management practices in the Bako area, Western Ethiopia. *Pest Management Journal of Ethiopia*. 1997;1(1 & 2):19-27.
2. Paneru RB, Le Patourel GN, Kennedy SH. Toxicity of *Acorus calamus* rhizome powder from Eastern Nepal to *Sitophilus granarius* (L.) and *Sitophilus oryzae* (L.) (Coleoptera, Curculionidae). *Crop Protection*. 1997 Dec 1;16(8):759-63.
3. Islam MS, Talukder FA. Toxic and residual effects of *Azadirachta indica*, *Tagetes erecta* and *Cynodon dactylon* seed extracts and leaf powders towards *Tribolium castaneum*/Direkte und residuale Giftwirkung von Samenextrakten und Blattpulvern aus *Azadirachta indica*, *Tagetes erecta* und *Cynodon dactylon* auf *Tribolium castaneum*. *Zeitschrift für Pflanzenkrankheiten und Pflanzenschutz/Journal of Plant Diseases and Protection*. 2005 Nov 1:594-601.
4. Lashgari A, Mashayekhi S, Javadzadeh M, Marzban R. Effect of *Mentha piperita* and *Cuminum cyminum* essential oil on *Tribolium castaneum* and *Sitophilus oryzae*. *Archives of Phytopathology and Plant Protection*. 2014 Feb 7;47(3):324-9.
5. Mishra BB, Tripathi SP, Tripathi CP. Repellent effect of leaves essential oils from *Eucalyptus globulus* (Mirtaceae) and *Ocimum basilicum* (Lamiaceae) against two major stored grain insect pests of Coleopterons. *Nature and Science*. 2012;10(2):50-4.
6. Kumar R, Kumar A, Prasal CS, Dubey NK, Samant R. Insecticidal activity *Aegle marmelos* (L.) *Correa* essential oil against four stored grain insect pests. *International Journal of Food Safety*. 2008;10:39-49.
7. Debnath N, Das S, Seth D, Chandra R, Bhattacharya SC, Goswami A. Entomotoxic effect of silica nanoparticles against *Sitophilus oryzae* (L.). *Journal of Pest Science*. 2011 Mar;84:99-105.
8. Sree GV, Nagaraaj P, Kalanidhi K, Aswathy CA, Rajasekaran P. Calcium oxide a sustainable photocatalyst derived from eggshell for efficient photo-degradation of organic pollutants. *Journal of Cleaner Production*. 2020 Oct 10;270:122294.
9. Subramanyam B, Roesli R. Inert dusts. In *Alternatives to pesticides in stored-product IPM* 2000 Oct 31 (pp. 321-380). Boston, MA: Springer US.
10. Pasupathy S, Rajamanickam M. Synthesis of pure and bio modified calcium oxide (CaO) nanoparticles using waste chicken egg shells and evaluation of its antibacterial activity. *Int J Pharma Sci Res*. 2019;1:230.
11. Ayoub HA, Khairy M, Elsaid S, Rashwan FA, Abdel-Hafez HF. Pesticidal activity of nanostructured metal oxides for generation of alternative pesticide formulations. *Journal of agricultural and food chemistry*. 2018 May 14;66(22):5491-8.
12. Das S, Yadav A, Debnath N. Entomotoxic efficacy of aluminium oxide, titanium dioxide and zinc oxide nanoparticles against *Sitophilus oryzae* (L.): A comparative analysis. *Journal of Stored Products Research*. 2019 Sep 1;83:92-6.
13. Haroun SA, Elnaggar ME, Zein DM, Gad RI. Insecticidal efficiency and safety of zinc oxide and hydrophilic silica nanoparticles against some stored seed insects. *Journal of Plant Protection Research*. 2020;60(1).
14. Zahir AA, Bagavan A, Kamaraj C, Elango G, Rahuman AA. Efficacy of plant-mediated synthesized silver nanoparticles against *Sitophilus oryzae*. *Journal of Biopesticides*. 2012;5:95.
15. Sankar MV, Abideen S. Pesticidal effect of green synthesized silver and lead nanoparticles using *Avicennia marina* against grain storage pest *Sitophilus oryzae*. *Int J Nanomater Biostruct*. 2015;5(3):32-9.

16. Yerragopu PS, Hiregoudar S, Nidoni U, Ramappa KT, Sreenivas A, Doddagoudar SR. Effect of plant-mediated synthesized silver nanoparticles on pulse beetle, *Callosobruchus chinensis* (L.). *Int. J. Curr. Microbiol. Appl. Sci.* 2019;8:1965-72.

UNDER PEER REVIEW