

Original Research Article

ISOLATION, CHARACTERISATION AND CORROSION INHIBITION EVALUATION OF 1, 3, 5-TRIMETHOYMETHYLBENZENE FROM SEEDS EXTRACT OF *Cola nitida* ON MILD STEEL SURFACE IN HYHROCHLORIC ACID SOLUTION

ABSTRACT

Corrosion inhibition of Mild steel in 1 M hydrochloric acid solution by 1, 3, 5-trimethoymethylbenzene (TMMB) isolated from seeds extract of *Cola nitida* and characterized was studied using weight loss, potentiodynamic polarization and electrochemical impedance spectroscopic methods. The results recorded show that TMMB inhibits corrosion of mild steel in hydrochloric acid solution. The inhibition efficiency by the **weight** method increased with **increase** in TMMB concentration, but decreased with increase in temperature. The inhibition efficiencies by the potentiodynamic polarization and **electrochemical** spectroscopic methods also increased with increase in the concentration of TMMB. The calculated thermodynamic parameters showed that the corrosion inhibition process was endothermic and spontaneous in nature. Potentiodynamic polarization measurements confirmed that TMMB is a mixed – type inhibitor considering the value of E_{corr} being less than the threshold value of 85 mV. Impedance measurement revealed that the charge transfer resistance offered by TMMB to the migration of aggressive ions on the surface of mild steel in acidic solution was enough to impede corrosion. The best line of fit to the adsorption of TMMB onto mild steel surface was found in Temkin isotherm. Formation of protective dense film on the steel surface in the presence of TMMB compared to the blank was revealed by scanning electron microscopy. The molecular **of** structure of TMMB was optimized using Gaussian 09 with density functional theory [DFT/B3LYP/6-31G (d,p)]. Physical adsorption has been proposed for the adsorption of TMMB onto mild steel surface.

Comment [U1]: weight loss

Comment [U2]: the increase

Comment [U3]: electrochemical impedance

Comment [U4]: delete this

Keywords: *Cola nitida*, Mild steel, Acidic solution, Weight loss, Potentiodynamic polarization, Impedance spectroscopy, Density functional theory, Temkin isotherm.

Comment [U5]: Why did the Author/s not include Corrosion and corrosion inhibitor in the keyword?

Comment [U6]: EIS

1 INTRODUCTION

Materials for construction and some components of oil and gas industries made of mild steel rods, sheets and pipes are often exposed to industrial processes involving acidic solutions. This paves the way for industrial processes such as pickling, chemical and electrochemical etching and industrial acid descaling. The metallic components are susceptible to corrosive actions, which are retrogressive and interfacial reactions of a material (metal, ceramic and polymer) with its environment resulting in consumption of the material [1] and they deteriorate on continued usage.

The use of inhibitors in corrosion prevention and control in aggressive environments is the most cost-effective. Most of the efficient inhibitors are organic compounds that contain heteroatoms such as nitrogen (N), sulphur (S), oxygen (O) atoms, π -electrons and suitable functional groups. These atoms are found to have higher basicity and electron density and thus act as corrosion inhibitor and are the active centers for the process of adsorption on the metal surface. The inhibition efficiency conforms to the sequence $O < N < S < P$ [2]. The use of corrosion inhibitors that are biodegradable, in addition to being ecologically acceptable, have made plant products good alternatives to synthesized organic compounds [3]. A number of investigations have been conducted on extracts of different parts of plant materials as potential mild steel corrosion inhibitors in acidic media, thus: cashew waste [4]; *Jatropha tanjorensis* stem bark [5], *Pentaclethra macrophylla Benth* roots [6]; *Cuminum cyminum* extract [7]; Papaya Leaves [8]; Cassava leaf [9]; water melon wastes [10]; coconut shell [11]; *Gmelina arborea* root extract [12] and *Vernonia amygdalina* extract [13].

Comment [U7]: Separate these words into a new sentence since they are not heteroatoms.

Comment [U8]: inhibitors

Comment [U9]: active centers of the corrosion inhibitors

Comment [U10]: has

Cola belongs to the family of *Sterculiaceae* [14]. The five species of edible cola nuts genus include: *C. nitida*, *C. acuminata*, *C. ballayi*, *C. verticillata* and *C. sphaerocarpa*. The latter three species are not known to be cultivated [15]. *C. nitida* is referenced to have phytochemicals that possess extensive conjugation with substantial π – electron systems and as well contain heteroatoms such as N, S, O or heterocyclic ring in their structures that serve as rally points for interaction with the metal surface [16; 1; 15; 17]. These characteristics enhance the potentials of the phytochemicals in the seeds extract of *C. nitida* to inhibit corrosion. Therefore, this research is inclined to investigating the corrosion inhibitory potentials of eco-friendly and less toxic isolated phytochemical from the seeds of *C. nitida*, as a green corrosion inhibitor.

Comment [U11]: Any references in respect to previous study results that inform compound types of Cola or Sterculiaceae family and the use of the Cola or Sterculiaceae family as corrosion inhibitors? Please add the references about it.

Comment [U12]: phytochemicals

Comment [U13]: potential

Comment [U14]: investigate

Comment [U15]: phytochemicals

2 EXPERIMENTAL DETAILS

2.1 PLANT MATERIAL AND EXTRACTION

Pods having fresh and mature seeds of *C. nitida* were harvested from a plantation in Mbikpong, a rural settlement in Ibesikpo/Asutan Local Government Area of Akwa Ibom State and identified by a taxonomist in the Department of Pharmacognosy and Natural Medicine, Faculty of Pharmacy, University

of Uyo, Nigeria with a Voucher No. of UUPH 46. The pods were dissected with a sharp object and the seeds were collected and rinsed with water, cut into pieces, crushed and dried at room temperature (30 ± 2 °C) for 24 hours. It was then put through comparative extraction in which ethanol, acetone, methanol, ethyl acetate and dichloromethane (DCM) were used to macerate 400 g per solvent (2.5 L) in glass extraction jars for 72 hours and re-macerated for another 72 hours for maximum yield. Concentration of the filtrates was achieved using Grant GLS400 water-bath and a preliminary weight loss test was performed on the extracts and DCM extract was affirmed the most active fraction. This was weighed (85 g) and preserved in a refrigerator.

Comment [U16]: add space

Comment [U17]: delete 1 space

Comment [U18]: What is the meaning of this sentence? Fix the sentence

2.2 PURIFICATION OF DCM EXTRACT

Inherent components in DCM fraction of the extract was subjected to vacuum liquid chromatography (VLC) in order to enhance separation using the following solvent systems: 100 % hexane, 70% hexane: 30% DCM, 50% hexane: 50% DCM (re-macerated), 30% hexane: 70% DCM, 100% DCM, 70% DCM: 30% ethyl acetate, 50% DCM: 50% ethyl acetate, 30% DCM: 70% ethyl acetate and 100% ethyl acetate. Based on the spectra of thin layer chromatographic characteristics, the fractions obtained were pooled, thus: $V_1 = 100\% \text{ hexane} + 70\% \text{ hexane}:30\% \text{ DCM}$ (38.7 g); $V_2 = 50\% \text{ hexane}:50\% \text{ DCM}$ (61.5 g); $V_3 = 50\% \text{ hexane}:50\% \text{ DCM} + 30\% \text{ hexane}:70\% \text{ DCM}$ (85.1 g); $V_4 = 100\% \text{ DCM} + 70\% \text{ DCM}: 30\% \text{ ethyl acetate}$ (50.9 g); and $V_5 = 50\% \text{ DCM}: 50\% \text{ ethyl acetate} + 30\% \text{ DCM}: 70\% \text{ ethyl acetate} + 100\% \text{ ethyl acetate}$ (87.3 g). Initial gravimetric tests on the pooled VLC fractions showed that corrosion inhibition efficiencies were in the following order: V_5 (89%) > V_3 (85 %) > V_1 (83 %) > V_4 (77 %) > V_2 (71%).

Comment [U19]: were

Comment [U20]: Why was this sentence not placed in the results and discussion section?

Gradient elution with n-hexane containing increasing quantity of dichloromethane followed by increasing quantities of ethyl acetate and methanol (MeOH) was used on V_5 (87.3 g) loaded on to silica gel column (C1) chromatography (Merck, 60-120 mesh). Eluates of 20 mL were obtained and examined on silica TLC plates (Merck, Germany) in DCM (100%) using p-anisaldehyde-sulphuric acid as spray reagent. Eighty-four (84) eluates were obtained and bulked into eight fractions [A = O_{1-12} (4.9 g), B= O_{13-23} (9.2 g), C = O_{24-31} (8.2 g), D = O_{32-59} (5.8 g), E = O_{60-69} (8.6 g), F = O_{70-77} (16.1 g), G = O_{78-81} (15.9 g) and H = O_{82-84} (10.2 g)] based on their TLC characteristics; silica gel solvent systems were: 100 % DCM, DCM (2): MeOH (8), DCM (8): MeOH (2) and Ethyl acetate(100%). Based on the TLC

Comment [U21]: onto

characteristics, bulk fraction code named G (114.3 g) was subjected to further purification process by means of normal phase column (C2) chromatography and gradient-eluted with ethyl acetate containing increasing quantities of methanol. 20 mL each of the eluates were collected, monitored on silica TLC plates (Merck, Germany) in DCM (100%) and DCM (8): methanol (2) using p-anisaldehyde-sulphuric acid as spray reagent. Thirty-eight eluates were obtained and bulk into five sub-fractions, thus: A1 = O2₁₋₄(2.5 g), B1 = O2₅₋₇ (1.3 g), C1 = O2₈₋₁₅(6.8 g), D1 = O2₁₆₋₃₅(4.1 g) and E1 = O2₃₆₋₃₈(2.1 g) based on their TLC characteristics. Sub-fraction D1 was colorless from column two (C2) gave single spot on TLC plate with R_F of 0.82, confirmed pure and code named D1.

Comment [U22]: giving

2.2.1 CHARACTERISATION OF ISOLATED PHYTOCHEMICAL

The isolated compound code named D1 (with single spot on TLC plate) was subjected to Fourier transform infra-red (FT-IR) spectroscopy, proton (¹H), carbon-13 (¹³C) and distortionless enhancement by polarization transfer-135 (DEPT-135) nuclear magnetic resonance (NMR) spectroscopic studies.

Comment [U23]: infrared

Comment [U24]: spectrometer

Comment [U25]: spectrometers

2.3 MILD STEEL COUPONS

The mild steel sheet used was procured from John & Sons Nigeria Limited, Uyo, Akwa Ibom State. The steel which had the chemical composition (w/w%): C (0.12), Mn (0.85), S (0.06), P (0.05), Si (0.09) and Fe (98.83). Mechanically, the steel was pressed - cut into coupons of 3.0 cm x 2.0 cm x 0.05 cm. At the center of each coupon, a small hole was drilled to facilitate total immersion in the corrodent using glass rod and hook. These coupons were abraded with emery papers of different grades (P60X, 220 and 450) to obtain smooth finished surfaces. The coupons were rinsed with deionized water to get rid of organic impurities, washed in ethanol to remove grease and thereafter in acetone to remove oil. The cleaned coupons were preserved over calcium chloride in desiccators prior to use.

The dimension of the coupons for electrochemical experiment was 1.0 cm x 1.0 cm. They were also polished to a smooth finish.

Comment [U26]: Is the thickness of the coupon not measured?

Can the Author/s displayed the image (in the form of sketch or photo) of the coupon or working electrode or electrochemical cell system for electrochemical experiments?

2.4 WEIGHT LOSS MEASUREMENTS

Weight loss measurements were performed at total immersion condition of the coupons using glass rod and hook in 100 ml of 1M HCl solution containing D1 and blank, respectively, in a beaker maintained at 303 K. One coupon was placed in each beaker. Mild steel coupons were retrieved from the inhibited and blank solutions at intervals of two hours, immersed in 20% NaOH solution containing 200 gL⁻¹ of zinc dust, scrubbed with bristle brush, washed in distilled water, dried in acetone and reweighed [18] to determine weight loss with respect to time. This was done for five consecutive times giving a total of ten hours per temperature. The weight loss was taken to be the difference between the initial weight and the weight of the coupons at a given time for the chosen temperature range. The procedure was repeated at 313 K, 323 K and 333 K. From the data, corrosion rate (CR), surface coverage (θ) and percentage inhibition efficiency (IE %) were determined using the following equations [19].

$$CR = \frac{W_1 - W_2}{S \cdot t} \quad (1)$$

where W_1 is the mass of mild steel coupon before immersion, W_2 is the mass of mild steel coupon after immersion, S is the total surface area of the coupon and t is the corrosion time in hours.

$$\theta = \frac{CR_0 - CR}{CR_0} \quad (2)$$

$$IE \% = \theta \times 100 \quad (3)$$

where CR_0 and CR are corrosion rates of the mild steel coupon in 1.0 M HCl in the absence and presence of the extracts, respectively.

2.4 ELECTROCHEMICAL METHOD

Electrochemical experiments were conducted using the conventional three-electrode cell with a platinum counter electrode (CE) and a saturated calomel electrode (SCE) coupled to a fine lugging capillary as the reference electrode (RE). Ohmic contribution was minimized by placing the lugging capillary closed to the working electrode (WE) which the prepared mild steel coupon was presented in a square form of dimension 1.0 cm x 1.0 cm. The electrode was immersed in the test solution at an open circuit potential (OCP) for thirty minutes to stabilize before measurements could be taken. All electrochemical measurements were taken with the sample immersed in the blank, maximum and minimum concentrations of the test solutions at 303 K using Gamry 600+ Potentiostat/Galvanostat/ZRA Advanced Electrochemical System linked to a computer. The electrochemical set-up was sealed with

Comment [U27]: Do these measurements were conducted by the stirred condition? Give the explanation

Why there is no variation in the concentration of corrosion inhibitor mentioned?

Comment [U28]: What is the CR unit based on Equation 1?

Comment [U29]: unit?

Comment [U30]: unit?

Comment [U31]: Is there unit of this parameter?

butyl stoppers where the electrodes and nitrogen pipe providing N₂ gas for deaeration could pass through. Prior to the electrochemical test, the glass cells were sterilized in an autoclave. Both the working electrode and the counter electrodes were further sterilized using 75% ethanol and kept under ultraviolet rays prior to the experiment.

2.4.1 POTENTIODYNAMIC POLARIZATION MEASUREMENTS

The polarization curve was recorded under potentiodynamic polarization at the condition of air atmosphere and controlled by a personal computer. After the open circuit potential had been established, potentiodynamic polarization curves were obtained at a scan rate of 1mVS⁻¹ in the potential range from -0.25 V to 0.25 V. Application of a small potential drop (ΔE) generates a corresponding current flow (ΔI) [20].

Comment [U32]: Add space

The corrosion rate of the system was determined using corrosion current density, i_{corr} . The linear portions of the anodic and cathodic Tafel curves were extrapolated to the corrosion potential (E_{corr}) and the corrosion current (i_{corr}) axes. All potentials were measured against SCE. The surface coverage (θ) and the percentage inhibition efficiency (% IE), were evaluated by the application of Equations (3.4) and (3.5) (Roy and Sukul, 2015), thus:

$$\theta = \frac{i_{corr}^o - i_{corr}}{i_{corr}^o} \quad 4$$

$$IE\% = \theta \times 100 \quad 5$$

Comment [U33]: it does match with the numbering of the Equations below

Comment [U34]: the citation style is not consistent with others

The values of corrosion current density in the absence and presence of inhibitor are given by i_{corr}^o and i_{corr} , respectively [21; 22].

Comment [U35]: Put the unit of I corr

2.4.2 ELECTROCHEMICAL IMPEDANCE SPECTROSCOPIC MEASUREMENTS

The measurements of electrochemical impedance spectroscopy were carried out over a frequency range of 10 Hz to 100,000 Hz at 303 K using amplitude of 5 mV RMS peak-to-peak with an alternating current signal at the open circuit potential and at air atmosphere. The impedance data were recorded using Nyquist plots and the charge transfer resistance, R_{ct} , was obtained from the diameter of

the semicircle in the plot. The percentage inhibition efficiency (% IE) was calculated from R_{ct} values obtained from the impedance measurements according to the models bellows, thus:

$$\theta = \frac{R_{ct} - R_{ct}^0}{R_{ct}} \quad 6$$

$$IE\% = \theta \times 100 \quad 7$$

charge transfer resistances in the presence and absence of the inhibitor are given by R_{ct} and R_{ct}^0 respectively [23; 24].

Comment [U36]: Put the unit of Rct

2.5 SCANNING ELECTRON MICROSCOPY (SEM)

Samples were ground with SiC paper having 1000 grit, washed in distilled water and then in ethanol, dried in compressed air and placed in a fume hood. Morphological survey was conducted on 1 cm x 1 cm area of the surface of mild steel coupons before and after immersion in both blank and test solutions. Thermo Fisher Scientific Prisma E scanning electron microscopy was used. Measurements were taken at various magnifications and the appropriate ones selected.

Comment [U37]: Solution with inhibitors

Comment [U38]: Fix this sentence

2.6 QUANTUM CHEMICAL STUDIES

Corrosion inhibition mechanism of D1 on mild steel in hydrochloric solution was studied using Gaussian 09 and density functional theory (DFT) with the basis set of B3LYP/6 – 31G (d,p) in aqueous phase. Possible physical properties of D1 that make it prone to corrosion inhibition were evaluated using theoretical study.

Comment [U39]: The aqueous

Comment [U40]: effective as

3 RESULTS AND DISCUSSION

3.1 CHARACTERISATION OF D1

D1 was obtained in a substantial quantity (4.1 g) as a colorless crystalline solid soluble in dimethyl sulphur (II) oxide (DMSO) solvent. Spectroscopic results on D1 revealed, thus: FT- IR (KBr, cm^{-1}): 3153, 3116, 3015 (C-H aromatic), 2829 (C-H aliphatic), 1655 (C=C), 1454 (CH_3 deformation), 1223 (C-O stretching).

^1H NMR (60 MHz, $\text{DMSO}-d_6$): δ 7.95 (s, 3H, Ar-H), 3.85 (s, 6H, 3 x CH_2OCH_3), 1.24 (s, 9H, 3 x CH_2OCH_3) ppm.

C-13 NMR (15 MHz, $\text{DMSO}-d_6$): No information was deduced from the spectra due to absence of visible compound peaks.

Comment [U41]: This is relatively low resolution for ^{13}C NMR apparatus

DEPT-135 (15 MHz, DMSO- d_6): No information was deduced from the spectra due to absence of visible compound peaks.

Comment [U42]: This is relatively low resolution for NMR apparatus

Based on the available pieces of information, the following structure was elucidated, thus:

Comment [U43]: FTIR and NMR spectra should be displayed

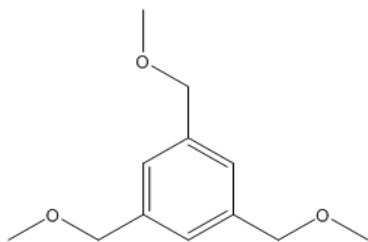


Figure 1: 1, 3, 5-Trimethoxymethylbenzene (TMMB)

Therefore, D1 was elucidated and identified as 1, 3, 5-trimethoxymethylbenzene abbreviated TMMB.

Comment [U44]: How the Author/s believe that TMMB had been isolated without certainty of ^{13}C -NMR and DEPT 135 spectra ?

3.2 WEIGHT LOSS RESULTS

3.2.1 EFFECT OF 1, 3, 5-TRIMETHOXYMETHYLBENZENE (TMMB) CONCENTRATION ON INHIBITION EFFICIENCY

Variation of inhibition efficiency with respect to the concentration of TMMB in 1 M HCl solution is presented in Figure 2. It is observed that the inhibition efficiency increased with increase in TMMB concentration. The highest inhibition efficiency obtained at 303 K was 55.83% at $5.0 \times 10^{-4} \text{ g L}^{-1}$ (Table 1). This implies that there is an interaction between TMMB molecules and the steel surface. The data indicate that there is a higher degree of surface coverage of mild steel surface with increase in the concentration of TMMB, thereby impeding the actions of aggressive ions and of course inhibit corrosion [25].

Comment [U45]: of course,

Comment [U46]: inhibiting

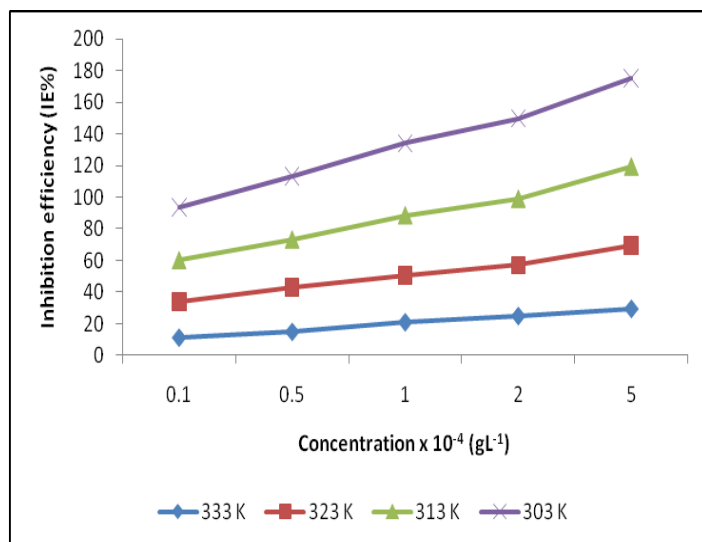


Figure 2: Effect of 1, 3, 5-trimethoxymethylbenzene (TMMB) on the corrosion inhibition efficiency of mild steel at different temperatures.

Table 1: Calculated values of weight loss, corrosion rate and inhibition efficiency for mild steel corrosion in 1 M HCl in the absence and presence of different concentrations of TMMB

Inhibitor Conc. ($\times 10^{-4}$)	Weight loss (g)				Corrosion rate ($\text{mg cm}^{-2} \text{hr}^{-1}$)				Inhibition efficiency (%)			
	303 K	313 K	323 K	333 K	303 K	313 K	323 K	333 K	303 K	313 K	323 K	333 K
Blank	0.150	0.248	0.317	0.421	2.40	3.97	5.07	6.74	-	-	-	-
0.1 g L^{-1}	0.100	0.184	0.214	0.361	1.60	2.94	3.92	5.94	33.33	25.94	22.68	11.42
0.5 g L^{-1}	0.090	0.174	0.198	0.358	1.44	2.78	3.64	5.73	40.00	29.97	28.21	14.99
1.0 g L^{-1}	0.082	0.154	0.184	0.333	1.31	2.46	3.57	5.33	45.42	38.04	29.59	20.92
2.0 g L^{-1}	0.074	0.144	0.156	0.317	1.18	2.30	3.44	5.01	50.83	42.07	32.15	24.78
5.0 g L^{-1}	0.066	0.124	0.132	0.238	1.06	1.98	3.04	4.77	55.83	50.13	50.13	29.23

3.2.2 EFFECT OF TEMPERATURE ON INHIBITION EFFICIENCY

Table 1 displays a pattern of corrosion rate (CR) considering total immersion time of 10 hours in the absence and presence of TMMB at different temperatures. It is seen that CR increases with increase in temperature and decreases with increase in the concentration as it varies, thus: 1.06 $\text{mg cm}^{-2} \text{hr}^{-1}$ at 303K, 1.98 $\text{mg cm}^{-2} \text{hr}^{-1}$ at 313 K, 3.04 $\text{mg cm}^{-2} \text{hr}^{-1}$ at 323 K and 4.77 $\text{mg cm}^{-2} \text{hr}^{-1}$ at 333 K considering 5.0 $\times 10^{-4} \text{ g L}^{-1}$ of TMMB (Table 1). This is because TMMB molecules readily acquire more energy at elevated temperatures and overcame the activation energy barrier than at lower temperatures (Abakedi and Asuquo, 2016). Besides, weight loss trend is seen to decrease as the concentration of TMMB increases. This is linked to the protection of mild steel as the degree of surface coverage (θ) increased proportion to the concentration of TMMB. At the concentration of 0.1 $\times 10^{-4} \text{ g L}^{-1}$ and 5.0 $\times 10^{-4} \text{ g L}^{-1}$ at

Comment [U47]: a total

Comment [U48]: This reason tends to explain that TMBB is effective in higher temperatures. In fact, corrosion rates rise at higher temperatures.

The Author/s can fix the reason.

Comment [U49]: In proportion

303 K, the weight loss by TMMB were 0.100 g and 0.066 g, respectively (Table1). [26] had reported a similar trend.

Comment [U50]: Fix this sentence

Corrosion rate, CR, evaluated from the weight loss measurements in acidic medium is related to temperature by the Arrhenius equation:

$$\log CR = \log A - \frac{E_a}{2.303RT} \quad (8)$$

where E_a is the energy of activation, A is the pre-exponential constant of Arrhenius, R is the universal gas constant and T is the absolute temperature. Energies of activation were evaluated from the slopes of the

Comment [U51]: Put the units for A, R, E_a , T

plot of $\log CR$ versus $\frac{1}{T}$ (Figure 3) and presented in Table 2. It is obvious that the E_a values in the presence of TMMB are higher than the E_a of the blank. These values reveal that the presence of TMMB raised the energy of activation of the metal dissolution reaction. The higher values of energy of activation in the presence of TMMB compared to the blank and the decrease in the percentage inhibition efficiency with increase in temperature are pointers to physical adsorption process [27]. Therefore, the mechanism of adsorption of TMMB on mild steel surface is by physical adsorption.

UNDER PEER REVIEW

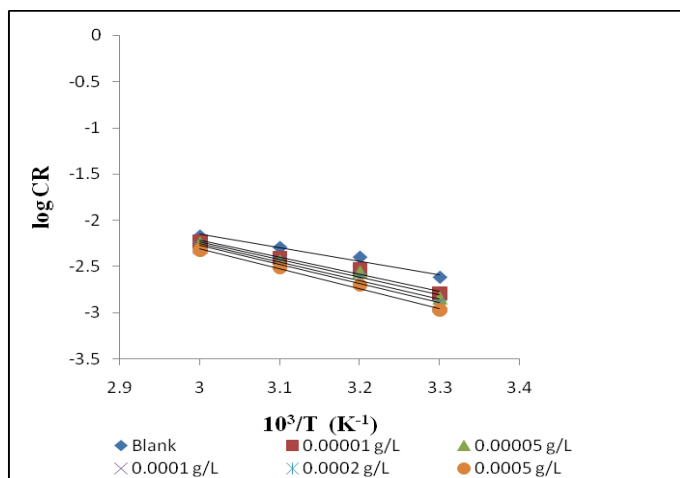


Figure 3: Arrhenius plot for mild steel coupons in 1 M HCl solution in the absence and presence of different concentrations of TMMB.

Table 2: Thermodynamic parameters for mild steel corrosion in 1 M HCl solution in the absence and presence of different concentrations of TMMB at 303 – 333 K.

Inhibitor	Concn.	E_a	ΔH_{ads}°	$-\Delta S_{ads}^{\circ}$
	$M \times 10^{-4}$	$(kJ \text{ mol}^{-1})$	$(kJ \text{ mol}^{-1})$	$(J \text{ K}^{-1} \text{ mol}^{-1})$
	Blank	27.95	25.16	211.63
TMMB	0.1	35.04	32.45	190.94
	0.5	36.76	34.06	186.44
	1.0	38.10	35.46	182.68
	2.0	39.63	36.80	179.03
	5.0	40.78	38.47	174.66

The values of enthalpy change, ΔH_{ads}° , and entropy change of adsorptions, ΔS_{ads}° , were determined from the transition state equation [28] as stated in equation (9), thus:

$$CR = \frac{RT}{Nh} \exp\left(\frac{\Delta S_{ads}^{\circ}}{R}\right) \exp\left(-\frac{\Delta H_{ads}^{\circ}}{RT}\right) \quad (9)$$

where N is the Avogadro's number, h is the Planck's constant, R is the universal gas constant and T is the absolute temperature. Equation (9) is rearranged as follows:

$$\ln\left(\frac{CR}{T}\right) = \left[\ln\left(\frac{R}{Nh}\right) + \frac{\Delta S_{ads}^{\circ}}{R}\right] - \frac{\Delta H_{ads}^{\circ}}{RT} \quad (10)$$

Linear plot of $\log\left(\frac{CR}{T}\right)$ versus $\frac{1}{T}$ (Figure 4) with slope and intercept of $-\frac{\Delta H_{ads}^{\circ}}{R}$ and $\left[\ln\left(\frac{R}{Nh}\right) + \frac{\Delta S_{ads}^{\circ}}{R}\right]$, respectively, were obtained. The slopes were used to determine the enthalpy change of adsorption (ΔH_{ads}°) and intercepts were used to obtain the entropy change of adsorption (ΔS_{ads}°) as presented in Table 3. The positive values of ΔH_{ads}° connote that the adsorption process of TMMB on to the surface of mild steel accompanied heat adsorption and it is endothermic in nature. The negative values of ΔS_{ads}° imply that the adsorption process is linked to a decrease in entropy and this is paramount to the adsorption of TMMB on to the surface of mild steel surface [29; 30]. Similar result had been reported by [25].

Comment [U52]: Put the units of h and N

Comment [U53]: Is accompanied

Comment [U54]: onto

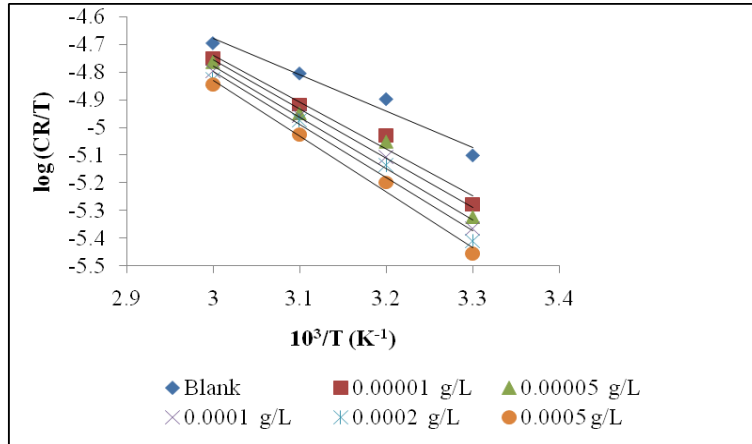


Figure 4: Transition State plot for mild steel coupons in 1M HCl in the absence and presence of different concentrations of TMMB.

3.2.3 ADSORPTION CONSIDERATION

It is imperative to evaluate an experimental best fit adsorption isotherm to the surface coverage data in order to assess the interactions between the molecules of TMMB and the mild steel surface. The best fit was obtained with Temkin adsorption isotherm given as equation (6) [31; 32; 33].

$$e^{f\theta} = K_{ads}C \quad 11$$

where θ is the surface coverage, K_{ads} is the equilibrium constant of adsorption process, C is the inhibitor concentration and f is the factor of energetic inhomogeneity describing the molecular interactions in the adsorption layer ($f = -2a$) [34].

K_{ads} is related to standard free energy of adsorption, ΔG_{ads}° , through the equation (8) [35].

$$\log K_{ads} = 1.744 - \frac{\Delta G_{ads}^\circ}{2.303RT} \quad 12$$

A linear plot of surface coverage (θ) versus logarithm of inhibitor concentration ($\log C$) with correlation coefficients (R^2) within the range $0.930 \leq R^2 \leq 0.996$ obtained for TMMB (Figure 5) indicates that TMMB adsorption best fits to Temkin isotherm. The values of K_{ads} signify the strength of adsorption between adsorbate and adsorbent. Large values of K_{ads} reflect efficient adsorption and hence better inhibition efficiency [36]. The values of K_{ads} from Table 3 are very low and this implies weak interaction (physical

Comment [U55]: Do you evaluate other adsorption isotherms?, If You do, convey it in the manuscript

Comment [U56]: ??

Comment [U57]: Put the units of K_{ads} and C

Comment [U58]: The standard

Comment [U59]: Add degree symbol on ΔG_{ads} for standard condition

Comment [U60]: ?

adsorption) between the molecules of TMMB and the mild steel surface. The negative values of 'a' connote existence of attraction in the adsorption layer [37].

The negative values of Gibbs' free energy change of adsorption, ΔG_{ads} , (Table 3) imply that the adsorption process of TMMB on to the surface of mild steel was spontaneous.

Comment [U61]: onto

Comment [U62]: spontaneous process

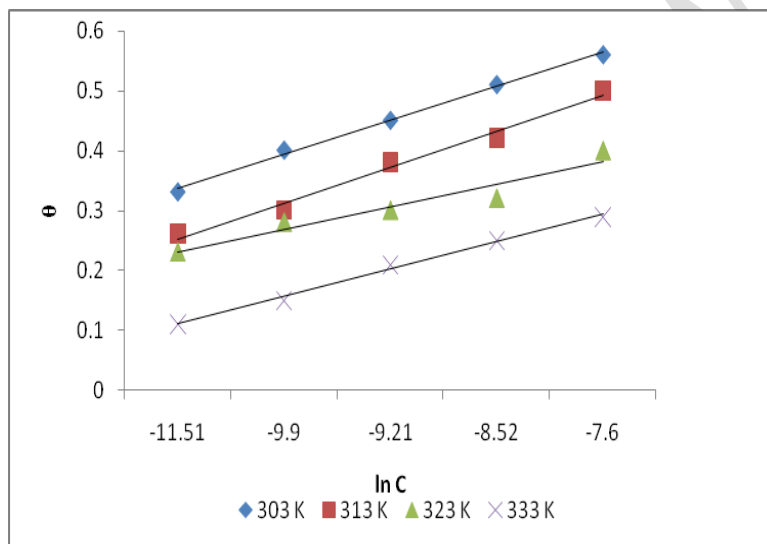


Figure 5: Temkin adsorption isotherm for mild steel corrosion in 1 M HCl solution in the absence and presence of different concentrations of TMMB.

Table 3: Some adsorption parameters from Temkin isotherm for mild steel coupons in 1 M HCl containing different concentrations of TMMB at 303 – 333 K.


Inhibitor	Temp. (K)	Intercept	Slope	K (mol/L)	f	- a	-ΔG (kJ/mol)	R ²
TMMB	303	0.279	0.057	133.44	17.54	8.77	22.45	0.996
	313	0.192	0.060	24.55	16.67	8.33	18.78	0.986
	323	0.192	0.038	156.56	26.32	13.16	24.36	0.930
	333	0.064	0.046	4.02	21.74	10.87	14.97	0.994

Comment [U63]: Fix this unit. Check it again in the adsorption reaction

3.3 POTENTIODYNAMIC POLARIZATION MEASUREMENTS

The presence of TMMB in the test solutions pushed the cathodic and anodic locations to the minimum current magnitudes. This means that corrosion at these locations was retarded by TMMB. Polarization parameters such as corrosion current densities (i_{corr}), corrosion potential (E_{corr}), cathodic Tafel slope (β_c) and anodic Tafel slope (β_a) were generated from the Tafel plot (Figure 6) and used in the calculation of percentage inhibition efficiency (IE%) as presented in Table 4 at different concentrations of TMMB. The values of β_c and β_a were largely affected by the inclusion of TMMB in the blank. When the shift in E_{corr} is higher than 85 mV, the inhibitor can be grouped as either anodic or cathodic, but if the shift is lower than 85 mV, the inhibitor is categorised mixed-type [38]. The E_{corr} values as presented in Table 4 are far less than the threshold value of 85 mV. This confirms that TMMB is a mixed-type corrosion inhibitor with the inhibition of both cathodic and anodic reactions. Similar results had been reported by [39]. Percentage inhibition efficiencies of 67% and 48% were recorded at 5.0×10^{-4} g L⁻¹ and 0.1×10^{-4} g L⁻¹ concentrations of TMMB, respectively. This means that i_{corr} reduces considerably with respect to increase in the concentration of TMMB in the blank (Table 4). Therefore, percentage inhibition efficiency improves upon increase in the concentration of the inhibitor [40].

Comment [U64]: Categorized as inhibitor

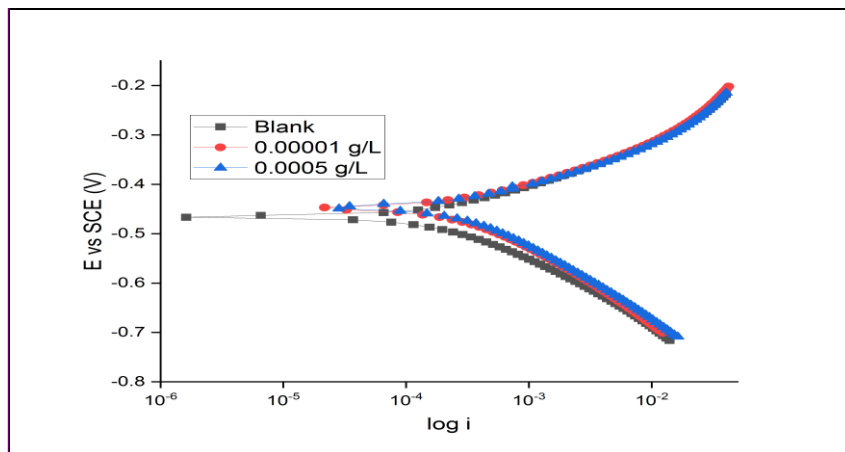

Comment [U65]: Put the unit of i in Figure 6

Figure 6: Polarization curve of mild steel in 1.0 HCl solution in the absence and presence of different concentrations of TMMB at 303 K.

Table 4: Potentiodynamic polarization parameters from Tafel plots for mild steel immersed in 1.0 M HCl solution in the absence and presence of different concentrations of TMMB at 303 K.

Inhibitor	Concn. (g/L)	$-E_{\text{corr}}$ (mV vs SCE)	i_{corr} ($\mu\text{A}/\text{cm}^2$)	β_c (mV dec ⁻¹)	β_a (mV dec ⁻¹)	IE%
	Blank	453.11	365.01	154	65	-
TMMB	0.1×10^{-4}	458.66	190.05	140	98	48
	5.0×10^{-4}	461.54	118.65	124	86	67

3.4 ELECTROCHEMICAL IMPEDANCE SPECTROSCOPY

A one-time constant phase element (CPE) circuit (Figure 7) was used to analyze the electrochemical impedance data generated from a sample area of 1.0 cm^2 at chi squared error of 6.081 x

10^{-6} , relative standard error ranging from 0.084 to 0.788 and the measurement errors in impedance data ≤ 0.2466 . This was achieved using the ZSimpwin software application.

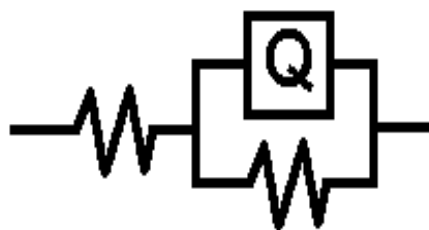


Figure 7: One time constant phase element (CPE) circuit

Impedance measurements were performed to evaluate the characteristics and kinetics of the metal/solution interface and how the corrosion reactions are obstructed by the inhibitor [41].

A plot of Z'_{im} versus Z'_{Re} (Nyquist) of mild steel immersed in the absence and presence of TMMB is presented in Figure 8. It is observed that impedance of the mild steel increases with increase in the concentration of TMMB. The plot shows one incomplete capacitive loop corresponding to the charge transfer reaction which is dependent on either electron transfer at the metal surface or on the electron conduction through the surface film [42]. It is observed that the change in concentration of TMMB had no effect on the shape of the impedance behavior and this suggests that TMMB exhibits similar corrosion inhibition mechanism on mild steel at various concentrations.

The impedance plots (Figure 8) are not perfect semicircles due to frequency dispersion caused by coarseness and surface fractions of the metal [43]. The impedance of the CPE is obtained according to equation (10) [44; 45], thus:

$$Z_{CPE} = Y_0^{-1} (j\omega)^{-n} \quad 13$$

where Y_0 (1.182×10^{-3} at $5.0 \times 10^{-4} \text{ gL}^{-1}$ and 1.250×10^{-3} at $0.1 \times 10^{-4} \text{ gL}^{-1}$ of TMMB) and n ($0.817 \leq n \leq 0.830$) are associated with CPE (Table 6). $j^2 = -1$ regarded as the imaginary axis, ω stands for angular

frequency in rads^{-1} , W denotes the impedance factor and n is the considered shifting factor which explains the surface heterogeneity, impurities and surface fractions of the metal [39].

Chloride ions from the electrolyte (acid used) adsorb onto the metal surface and the presence of TMMB in test solution gradually displaces the chloride ions and their presence at relatively low inhibitor concentration may induce adsorption. More so, chloride ions play a role in the adsorption of protonated inhibitor molecules by specially adsorbing to the metal surface, thus creating a negative charge towards the solution [46]

Introduction of TMMB in the acid solution promoted the radius of the imperfect loop which reflects corrosion inhibition and corresponds to the charge transfer resistance, R_{ct} , of the mild steel surface. Diameter of the depressed incomplete semicircles at high frequency is often regarded as the charge transfer resistance, R_{ct} . The percentage inhibition efficiency, $IE\%$, of TMMB for the mild steel electrode is evaluated using equation (11), thus:

$$IE \% = \frac{R_{ct} - R_{ct}^0}{R_{ct}} \times 100 \quad 14$$

where charge transfer resistances in the presence and absence of TMMB are given by R_{ct} and R_{ct}^0 , respectively [24]. The value of R_{ct} increases in direct proportion to the concentration of TMMB, with percentage inhibition efficiency of 58% at $5.0 \times 10^{-4} \text{ gL}^{-1}$ at 303 K (Table 6).

Comment [U66]: Put the unit

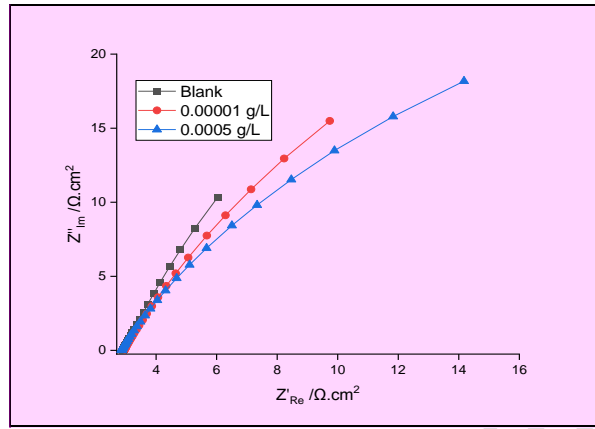


Figure 8: Nyquist plot of mild steel in 1.0 HCl solution in the absence and presence of different concentrations of TMMB at 303 K.

Bode plot of phase angle against logarithm of frequency ($\log f$) in the absence and presence of TMMB is presented in Figure 9 and phase angle peaks at different frequencies of the corrosion media at 303 K are obvious. Asymmetric overlap of peaks for each concentration of TMMB are observed at 37.99 Hz as 52.4° for $5.0 \times 10^{-4} \text{ gL}^{-1}$, at 29.12 Hz as 57.1° for $0.1 \times 10^{-4} \text{ gL}^{-1}$ and at 31.3 Hz as 62.3° for the blank (Figure 8), respectively. This implies that TMMB inhibits mild steel corrosion in acidic media.

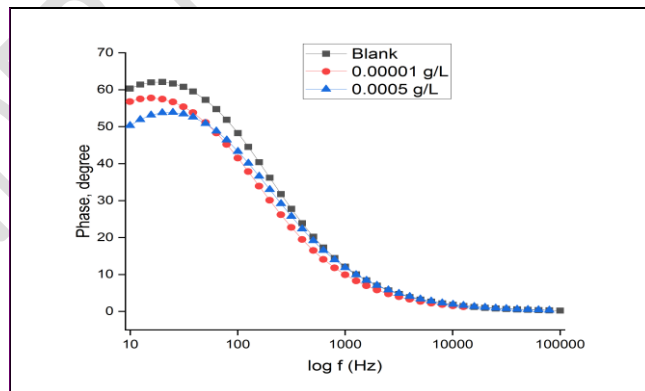


Figure 9: Bode Plot of mild steel in 1.0 M HCl solution in the absence and presence of different concentrations of TMMB at 303 K.

Comment [U67]: Generally, semicircle curves in the Nyquist Plot for the system with inhibitor will be larger than blank solution. How with this plot?

Comment [U68]: is

Comment [U69]: similar question with Nyquist plot, phase of blank solution is usually lower than solution with inhibitor

Table 5: Some Electrochemical Impedance Parameters of Mild Steel in 1M HCl Solutions in the absence and presence of TMMB at 303 K.

TMMB Concn.	R_s	R_{ct}	Q		IE %
	($\Omega \cdot \text{cm}^{-2}$)	($\Omega \cdot \text{cm}^{-2}$)	$Y_o \times 10^{-3}$	n	
Blank	2.914	76.550	0.831	0.856	-
$0.1 \times 10^{-4} \text{ g L}^{-1}$	2.947	125.490	1.250	0.817	40
$5.0 \times 10^{-4} \text{ g L}^{-1}$	2.851	182.260	1.182	0.830	58

3.5 SCANNING ELECTRON MICROSCOPY (SEM)

Micrographs of the mild steel coupons placed in 1 M hydrochloric acid solution in the absence and presence of 1, 3, 5-Trimethoxymethylbenzene (TMMB) were taken at a magnification of 300 μm and are presented in Figure 10 (I – III). Figure 9a exposes localized pitting of the coupon in blank. The aggressive nature of Cl^- and H^+ ions in the interfacial dissolution layer of the steel is responsible for the rough morphology of mild steel in the blank [41]. Similar trend of results were obtained by other workers [47; 25]. The mild steel coupons in the presence of TMMB at $0.1 \times 10^{-4} \text{ g L}^{-1}$ (Figure 10 II) and at $5.0 \times 10^{-4} \text{ g L}^{-1}$ (Figure 10 III) are smoother than that of the blank. The differences in textural properties of the micrographs arise from the formation of dense film at the metal-solution interface by TMMB, hence a reduction in the substrate (mild steel) deterioration rate. Consequently, TMMB at $5.0 \times 10^{-4} \text{ g L}^{-1}$ provided a better protection to the mild steel than TMMB at $0.1 \times 10^{-4} \text{ g L}^{-1}$ as seen in the micrographs (Figure 10: I – III).

Comment [U70]: correct this

Comment [U71]: trends

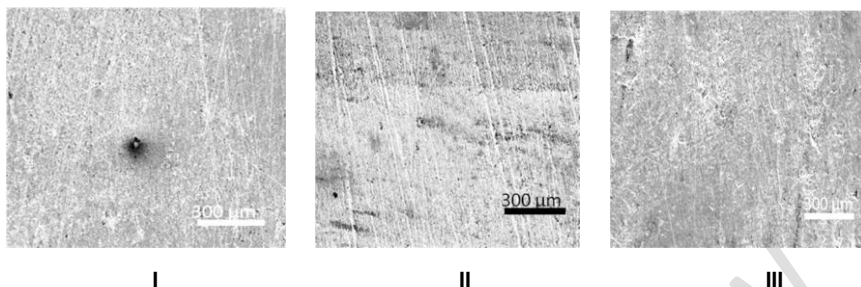


Figure 10: SEM image of mild steel surface exposed to (I) 1.0 M HCl solution (blank), (II) 1.0 M HCl containing $0.1 \times 10^{-4} \text{ gL}^{-1}$ of TMMB, and (III) 1.0 M HCl containing $5.0 \times 10^{-4} \text{ gL}^{-1}$ of TMMB.

3.6 QUANTUM CHEMICAL STUDIES

Optimized structure of 1, 3, 5-trimethoxymethylbenzene (TMMB), lowest unoccupied molecular orbital, E_{LUMO} and highest occupied molecular orbital, E_{HOMO} are presented in Figure 11 (I - III). Quantum chemical assessment reveals that frontier molecular orbital energies, E_{HOMO} and E_{LUMO} , are necessary parameters to determine the reactivity of chemical species by theoretical technique [42]. Quantum chemical parameters were calculated using equations (15 - 19) and are presented in Table 6. Information on the ability of a molecule to donate electrons to appropriate acceptor molecule with empty molecular orbital is obtained from E_{HOMO} and it is -6.570 eV with TMMB. The inhibition efficiency of an inhibitor is linked to the value of E_{HOMO} such that high value of E_{HOMO} reflects on high inhibition efficiency [48]. The energy gap, ΔE_{gap} , determines the reactivity of molecules. Inhibitors with low ΔE_{gap} should have good inhibition efficiencies because the energy required to remove the valence electron in a molecule is low and TMMB with ΔE_{gap} (6.248 eV) is an average corrosion inhibitor. The number of electrons transferred (ΔN) reveals that TMMB ($\Delta N = 0.220$). In view of the positive values of ΔN , it implies that electrons will be donated to the metal surface by TMMB. It is important to note that in as much as the value of ΔN is less than 3.6, the inhibition efficiency increases with the ability of the molecules to donate electrons to the metal surface [49]. The electronegativity, χ , of TMMB is 3.446 eV is lower than the work function of Fe(110) surface given as 4.82 eV and this points to the fact that electrons migrate from the inhibitor to the

Fe surface. Since the value of χ for TMMB is **the low**, movement of electrons from TMMB to the Fe surface is to be expected.

Comment [U72]: lower

Global hardness, η , and global softness, σ , are used to define how an atom resists the deformation of its electron cloud and they are 3.124 eV and 0.320 eV⁻¹, respectively, implying that TMMB is a hard molecule. Therefore, TMMB is an average inhibitor from quantum studies.

$$\text{Energy gap, } \Delta E = E_{LUMO} - E_{HOMO} \quad 15$$

$$\text{Electronegativity, } \chi = -\frac{1}{2} (E_{HOMO} + E_{LUMO}) \quad 16$$


$$\text{Global hardness, } \eta = -\frac{1}{2} (E_{LUMO} - E_{HOMO}) \quad 17$$

$$\text{Global softness, } \sigma = -\frac{1}{\eta} \quad 18$$

Number of transported electrons between metal surface and the inhibitor,

$$\Delta N = \frac{(\phi - \chi_i)}{2\eta_i} \quad 19$$

where ϕ (4.82 eV) is the work function of iron [Fe(110)], a modeled surface configuration of iron used for the evaluation.

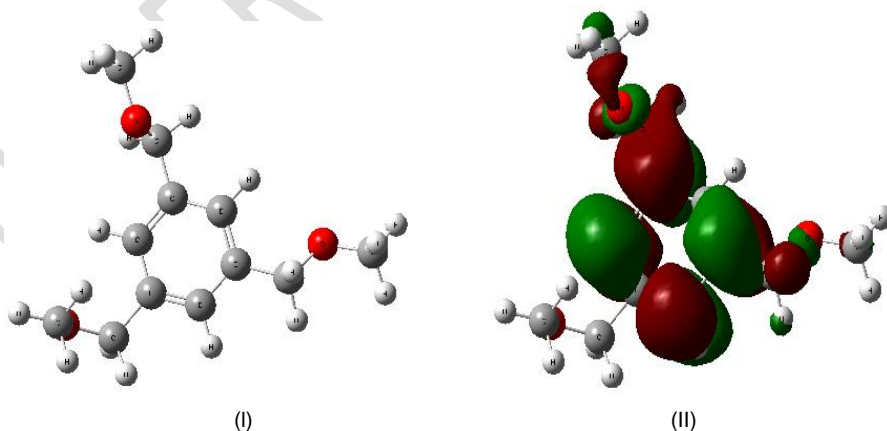

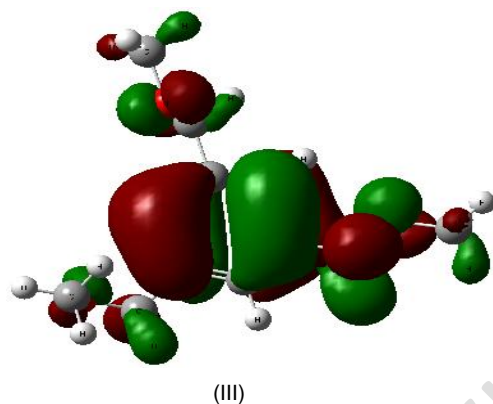


Figure 11: Structure of 1, 3, 5-Trimethoxymethylbenzene (TMMB): (I) optimized, (II) LUMO and (III) HOMO.

Table 6: Quantum chemical parameters for TMMB at geometry optimization

Inhibitor	E_{HOMO} (eV)	E_{LUMO} (eV)	ΔE_{gap} (eV)	IE (eV)	EA (eV)	χ (eV)	η (eV)	σ (eV ⁻¹)	ΔN
TMMB	-6.570	-0.322	6.248	6.570	0.322	3.446	3.124	0.320	0.220

4 CONCLUSION

The study reveals that 1, 3, 5 – trimethoxymethylbenzene (TMMB), a phytochemical isolated from fresh and mature seeds of *Cola nitida* inhibited the corrosion of mild steel in 1 M HCl solution. Inhibition efficiency of TMMB was found to increase with increase in concentration, but decreased with increase in temperature. Adsorption of TMMB onto the mild steel surface fitted to Temkin isotherm. The negative values of $\Delta G_{\text{ads}}^{\circ}$ are indicative of the spontaneity of the corrosion inhibition process and the endothermic nature of TMMB adsorption process is confirmed by the positive values of $\Delta H_{\text{ads}}^{\circ}$. The negative values of $\Delta S_{\text{ads}}^{\circ}$ indicate less disorder of the extract molecules on the mild steel surface and hence a stronger

adsorption of TMMB molecules on mild steel surface. TMMB is a mixed-type inhibitor based on its E_{corr} value. The inhibition efficiency obtained from weight loss, potentiodynamic polarization, electrochemical impedance spectroscopy and quantum chemical studies were in agreement. Dense film formed were seen in the micrographs of the steel and it was responsible for retarding the migration of aggressive ions in the corroder and thereby inhibiting mild steel corrosion in hydrochloric acid solution. Therefore, TMMB is concluded to be an average corrosion inhibitor of steel in hydrochloric acid solution.

REFERENCES

1. Raja PB, Sethuraman MM. Natural Products as Corrosion Inhibitors for Metals in Corrosive Media. A Review, Material letter. 2008; 62: 113-116.
2. Founda AS, Abd El-Aal A, Kandil AB. (2006). The Effect of some Phthalimide Derivatives on Corrosion Behavior of Copper on Nitric Acid. Desalination.2006; 201: 216–222.
3. Perez N. Electrochemistry and Corrosion Science, 2nd Edition, London, Springer. 2016; 243–259.
4. Olawale O, Bello JO, Akinbami P. A Study on Corrosion Inhibitor of Mild Steel in Hydrochloric Acid using Cashew Waste. International Journal of Modern Engineering Research. 2015; 5(8): 25-30.
5. Abakedi OU, Sunday MV, James MA. Mild Steel Corrosion Inhibition in Acidic Medium by *Jatropha tanjorensis* Stem Bark Extract. International Journal of Chemical Studies. 2021; 9(3): 9-13.
6. Lebe N, George N, Justus N, Nneka E, Peter E. Aqueous Extracts of Roots of *Pentaclethra macrophylla*, Bentham, as eco-friendly Corrosion Inhibition for Mild Steel in 0.5 M KOH Medium. International Journal of Materials and Chemistry. 2016; 6(1): 12-18.
7. Sribharathy S, Rajendran S. *Cuminum cyminum* Extracts as Eco-friendly Corrosion Inhibitor for Mild Steel in Seawater. Research Article, 2013; 1-7.
8. Kavitha N, Manjula P, Anandha Kumar N. (2014). Syneristic Effect of Papaya Leaves Extract –Zn²⁺ in Corrosion Inhibition of Mild Steel in Aqueous Medium. Research Journal of Chemical Science. 2014; 4 (8): 88-93.
9. Diah RG, Emriadi AA, Mai E. Water Extracts of Cassava Leaf as Corrosion Inhibitor for Mild Steel in Sulfuric Acid Solution. Journal of Chemical and Pharmaceutical Research.2015; 7(12): 398-405.
10. Odewunmi NA, Umorem SA, Gasem ZM. Watermelon Waste Products as Green Corrosion Inhibitors for Mild Steel in HCl Solution. Journal of EnvironmentalChemical Engineering. 2015; 3 (1): 286-296.

Comment [U73]: Please use up to date references

11. Daramola OO, Adediran AA., Fadumiye AT. Evaluation of the Mechanical Properties and Corrosion Behaviour of Coconut Shell Ash Reinforced Aluminium (6063) Alloy Composites. *Leonardo Electronic Journal and Practices Technologies*. 2015; 27: 107-119.
12. Abakedi OU, Akpan IA, Ekemini NE. (2018). Inhibition of mild steel corrosion by *Gmelina arborea* root extract in 1 M H₂SO₄ solution. *Journal of Materials Science Research and Reviews*. 2018; 1(1):1–9.
13. Olawale O, Adediran AA, Talabi SI, Nwokocho GC, Ameh AO. Inhibitory Action of *Vernonia amygdalina* Extract (VAE) on the Corrosion of Carbon Steel in Acidic Medium. *J. Electrochem. Sci. Eng*. 2017; 7(3): 145-152.
14. IPNI. The International Plant Names Index (IPNI). 2007-2011 data base.
15. Kanoma AI, Muhammad I, Abdullahi S, Shehu K, Maishanu HM, Isah AD. Qualitative and Quantitative Phytochemical Screening of Cola Nuts (*Cola Nitida* and *Cola Acuminata*). *Journal of Biology, Agriculture and Healthcare*. 2014; 4 (5): 2224-3208.
16. Ozcan M, Dehri I, Erbil M. Organic Sulphur-containing Compounds as Corrosion Inhibitors for Mild Steel in Acidic Media: Correlation between Inhibition Efficiency Chemical Structure. *App. Surf. Sci*. 2004; 236: 155-164.
17. Huong DQ, Huong NTL, Nguyet TT, Duong T, Tuan D, Thong NM, Nam PC. Pivotal Role of Heteroatoms in Improving the Corrosion Ability of Thiourea Derivatives. *ACS Omega*. 2020; 42: 27655-27666.
18. National Association of Corrosion Engineers (NACE). Corrosion Basics. An Introduction – official NACE publication: Finland; 2000.
19. Obot IB, Obi-Egbedi NO. Fluconazole as an Inhibitor for Aluminium Corrosion 0.1 M HCl. *Colloid Surface: Physio-chemistry. Engineering Aspects*. 2008; 330: 207-212.
20. Nabuk OE, Ebenso EE, Ibok UJ. Adsorption, Synergistic Inhibitive Effect and Quantum Chemical Studies of Ampicillin (AMP) and Halides for the Corrosion of Mild Steel in H₂SO₄. *Journal of Applied Electrochemistry*. 2010; 40: 445-456.
21. Tsuru T, Haruyama S, Gijutsu B. The Principle of Corrosion and the Mathematical Analysis of Experimental Results. *Japan Society of Corrosion Engineers*. 1978; 27: 573-578.
22. Garai S, Garai, S, Jaiasankai P, Singh JK, Elango A. (2012). A Comprehensive Study on Crude Methanolic Extract of *Artemisia pallens* (Asteraceae) and its Actives Component as Effective Corrosion Inhibitors of Mild Steel in Acid Solution. *Corrosion Science*. 2012; 60: 193-204.
23. Mansfeld F, Kendig MW, Tsai S. Recording and Analysis of ac Impedance Data for Corrosion Studies. *The Journal of Science and Engineering*. 1982; 11 (38): 570-580.


Comment [U74]: adjust to the journal format

24. Da Rocha JC, Gomes JAC, D'Elia E. Corrosion Inhibition of Carbon Steel in Hydrochloric Acid Solution by Fruit Peel Aqueous Extracts. *Corrosion Science*. 2010; 52: 2341-2348.
25. Obodom MI, Akpan IA, Abakedi OU. Gravimetric and Electrochemical Assessments of the Corrosion Inhibition Potential of *Cola nitida* Seeds Extract on Mild Steel Surface in Hydrochloric Acid (HCl) Solution. *Asian Journal of Chemical Sciences*. 2023, 13 (6):118-131.
26. Abakedi OU, Asuquo JE. Mild Steel Corrosion Inhibition by *Eremomastax polysperma* Leaf Extract in Acidic Medium. *Asian Journal of Chemical Sciences*. 2016; 1(1): 1-9.
27. Umoren, S. A., Eduok, U. M. and Oguzie, E. E. Corrosion Inhibition of Mild Steel in 1 M H₂SO₄ by Polyvinyl Pyrrolidone and Synergistic Iodide Additives. *Portugaliae Electrochemica Acta*. 2008; 26(6): 533 – 546.
28. Abdullah A, Hameed KW. Transition State Theory and Reaction Kinetic for the Corrosion of Steel in Acid Media. *AL-Fatih Journal*. 2008; 35: 1 – 9.
29. Emranuzzaman T, Kumar S, Vishwanatham G. (2004). Synergistic Effects of Formaldehyde and Alcoholic Extract of Plant Leaves for Protection of N80 Steel in 15% HCl. *Corrosion Engineering, Science and Technology*. 2004; 39: 327 – 332.
30. Xianghong LI, Shuduan D, Hui FU, Guannan MU. Inhibition Effect of 6-Benzylaminopurine on the Corrosion Cold Rolled Steel in H₂SO₄ Solution. *Corrosion Science*. 2009; 33: 303 – 343.
31. Rozenfeld IL. *Corrosion Inhibitors*. McGraw Hill: New Jersey; 1981.
32. Masel R. *Principles of Adsorption and Reaction on Solid Surfaces*. Wiley InterScience: Hoboken, New Jersey; 1996.
33. Tang L, Li Y. (2007). Phenyl-substituted AminoThiadazoles as Corrosion Inhibitors for Copper in 0.5 M H₂SO₄. *Corrosion Science*. 2007; 49: 4185-5002.
34. Subha R, Saratha R. Naturally occurring substance (*cahendula offinalis* flower) as a Corrosion Inhibitor of Mild Steel in 1 M HCl. *Corrosion Science*. 2006; 53: 556-562.
35. Fiala A, Chibani A, Darchen R, Boulkamh A, Djebbar K. Acetylacetone Complexes as new Corrosion Inhibitor in Phosphoric Media: Inhibition and Synergism Study. *Applied Surface Science*. 2007; 253: 9347 – 9351.
36. Tang L, Li X, Mu G, Liu G, Li L, Liu H, Si Y. The Synergistic Inhibition between Hexadecyltrimethyl Ammonium Bromide (HTAB) and NaBr for the Corrosion of Cold Steel Rolled Steel in 0.5 M Sulfuric Acid. *Journal of Material Science*. 2006; 41: 3063–3069.

Comment [U75]: adjust to the journal format

37. Umoren SA. Inhibition of Aluminium and Mild steel Corrosion in Acidic Medium using Gum Arabic. *Cellulose*. 2008; 15: 751 – 761.
38. Sahakitpichan P, Mahidol C, Disadee W, Ruchirawat S, Kanchanapoom T. Unusual glycosides of pyrrole alkaloid and 4'-hydroxyphenyl ethanamide from leaves of *Moringa oliefera*. *Phytochem*. 2011; 72: 791–795.
39. Dehghani A, Bahlakeh G, Ramezanzadeh B, Ramezanzadeh M. Detailed Macro- /micro Scale Exploration of the Excellent Active Corrosion Inhibition of a Novel Environmentally Friendly Green Inhibitor for Carbon Steel in Acidic Environment. *J. Taiwan Inst. Chem. Eng.* 2019; 100: 239–261.
40. Lowmunkhong P, Ungtharak D, Sulthivaiyakit P. Tryptamine as a Corrosion Inhibitor of Mild Steel in Hydrochloric Acid Solution. *Corrosion Science*. 2010; 52: 30-36.
41. Anadebe VC, Nnaji PC, Okafor NA, Ezeugo JO, Abeng FE, Onukwuli OD. Evaluation of Bitter Kola Leaf Extract as an Anticorrosion Additive for Mild Steel in 1.2 M H₂SO₄ Electrolyte. *S. Afr. J. Chem.* 2021; 75: 6–17.
42. Khaled KF, Al-Qahtani MM. The Inhibitive Effect of some Tetrazole Derivatives towards Al Corrosion in Acid Solution: Chemical, Electrochemical and Theoretical Studies. *Materials Chemistry and Physics*. 2009; 113: 150 -158.
43. Karthick S, Muralidharan S, Lee HS, Kwon SJ, Saraswathy V. Reliability and Long-term Evaluation of GO-MnO₂ Nano Material as a Newer Corrosion Monitoring Sensor for Reinforced Concrete Structures. *Cem. Concr. Compos.* 2019; 100: 74–84.
44. Hao X, Dong J, Etim IN, Wei J, Ke W. Sustained Effect of remaining Cementite on the Corrosion Behavior of Ferrite-Pearlite Steel under the Simulated bottom Plate Environment of Cargo Oil Tank. *Corros. Sci.* 2016; 110: 296 – 304.
45. Hao X, Dong J, Wei J, Etim IN, Ke W. Effect of Cu on Corrosion Behavior of Low Alloy Steel under the Simulated bottom Plate Environment of Cargo Oil Tank. *Corros. Sci.* 2017; 121, 84 – 93.
46. Ikpi ME, Udoh II, Okafor PC, Ekpe UJ, Ebenso EE. Corrosion Inhibition and Adsorption Behaviour of Extracts from *Piper guinensis* on Mild Steel Corrosion in Acid Media. *International Journal of Electrochemical Science*. 2012; 7: 12193 – 12206.
47. Al-Bataineh N, Al-Qudah AA, Abu-Orabi S, Bataineh T, Hamaideh RS, Al-Momani IF, Hijazi AK. Use of *Capparis decdua* Extract as a Green Inhibitor for Pure Aluminium Corrosion in Acidic Media. *Corrosion Science and Technology*. 2022; 21(1): 9-20.
48. Rajendran M, Keerthika K, Kowsalya M, Devapinam D. Theoretical Studies on Corrosion Inhibition Efficiency of Pyridine Carbonyl Derivatives using DFT Method. *Der. Pharma Chem.* 2016; 8(3): 71 – 79.
49. Lukovits I, Kalman E, Zucchi F. (2001). Corrosion Inhibitors—Correlation between Electronic Structure and Efficacy. *Corros. Sci.* 2001; 57(1): 3 – 8.

UNDER PEER REVIEW



UNDER PEER REVIEW

