

Performance Evaluation of Modified Periwinkle Shell-Derived Adsorbent for CO₂ Post-Combustion Capture

ABSTRACT

Seashells and other waste shells are gaining attention as a cost-effective, sustainable, renewable alternative source of CaCO₃ for CO₂ adsorption. Consequently, this study evaluated the performance of periwinkle shell as a potential adsorbent for CO₂ capture. The periwinkle shells were washed, dried, then calcined at 800°C for 2 hrs, crushed, and sieved with 0.25 -1.44 mm sieves. Some portion of the calcined sample were activated with KOH in a 2:1 ratio i.e 240g of KOH to 120g of calcined periwinkle shell. A portion of the activated periwinkle shell was modified with deep eutectic solvent (DES) prepared with 15 ml of choline chloride and 30 ml of glycerol. 20 ml of the deep eutectic solvent was added to 10g of KOH-activated periwinkle shell and later dried in a furnace at 800 °C for 2 hrs to form a DES-modified activated periwinkle shell. Likewise, 60 ml of polyethylene glycol (PEG) was added to 30 g of another portion of the KOH-activated periwinkle shell to form the modified PEG-activated periwinkle shell sample. The result of the SEM and FTIR analysis of the samples showed that the DES and PEG modified samples had similar structure and functional groups. However, the unmodified calcined sample contained more functional groups than the modified samples. The results showed that the unmodified calcined periwinkle shells performed better than the KOH-activated and the DES and PEG-modified APS samples, with a CO₂ adsorption capacity of 0.16 and 0.42 mmol/g after 1 and 3 hours, respectively. The adsorption process of the CPS sample followed the Langmuir monolayer model of adsorption. The relatively low adsorption capacity of the developed adsorbents suggested that they were unsuitable for CO₂ capture. Recommendations for future studies were also highlighted.

Keywords: *Periwinkle shells, bio-adsorbents, CO₂ capture, Deep Eutectic Solvent, post-combustion.*

1. INTRODUCTION

The continuous emissions of greenhouse gases (GHGs), which are the by-products of many industrial and anthropogenic processes, have been identified as the major causes of many environmental problems like an increase in mean global temperature, excessive flooding, wildfires, melting of polar ice caps, droughts, etc. [1], [2]. For a sustainable planet, GHG emissions must be reduced to meet the COP21 Paris Agreement of less than 2 °C [3]. Consequently, various governments around the globe have developed timelines and mitigation measures guided by strict GHG emission policies and regulations to curb the further degradation of the environment. The central focus areas have been increasing the contribution of renewable energy sources like solar, wind, hydro, geothermal, etc., in the total energy mix and the scaling up of carbon capture utilization and storage (CCUS) technologies. These two focus areas are intended to mitigate the adverse effect of GHG emissions on the environment and contribute to our planet's sustainability [4], [5].

Developing and scaling up CCUS has become necessary due to the role fossil fuels are expected to play in providing energy needs for an ever-increasing global population. According to the United Nations report on global population growth, the global population is expected to grow from 8 to 9.7 billion people by 2050 [6], and the energy demand is expected to double. Fossil fuel will continue to play a significant role in meeting the global energy demand. For instance, while crude oil demand is expected to grow at 7%, driven mainly by demand in petrochemical feedstock, the demand for natural gas is expected to increase by 29%, mainly due to the need for lesser GHG emitting fuel (compared

to other fossil fuels). Thus oil and gas alone (excluding coal) are expected to account for more than half of the total energy mix going into 2040 [7]. The continuous use of these fossil fuels will, in no doubt, result in the emissions of GHG that are inimical to a sustainable environment. On the other hand, the mining and processing of the essential metals (cobalt, nickel, copper, lithium, manganese, zinc, etc.) required for developing clean energy technologies like lithium batteries, solar PVs, and wind turbines also contribute to GHG emissions. According to the IEA report [7], the mining and processing of lithium carbonate, class 1 nickel, aluminium, and cobalt sulfate emit about 5, 10, 12, and 17 metric tons of CO₂-equivalent per ton of metal, respectively. Although the CO₂ emissions from clean-tech components and equipment manufacturing are small compared to emissions from fossil fuel sources, it still requires to be sequestered to enable a holistic approach to a sustainable environment.

Carbon capture and storage (CCS) technologies are the established means by which CO₂ from carbon-intensive processes is captured [8], [9]. Incorporating or retrofitting CCS technologies into high carbon footprint processes can help make fossil fuel utilization competitive and safe in the coming decades. The CCS technologies use techniques like oxyfuel combustion, the pre-and post-combustion methods for carbon capture. Details of these processes can be found in the work conducted by Blomen et al. [10], and Osman et al [11]. The prominent technologies used in these CO₂ capture processes are mostly solvents like amines and solid adsorbents like zeolite. Although amines are the most used and mature technologies, their drawbacks, like high regeneration energy requirement, solvent losses, and corrosivity [12], limit their use. These drawbacks have allowed for using relatively efficient and cost-effective solid adsorbents. eg, activated carbons, metal-organic frameworks, and zeolites. However, typical solid adsorbents are still relatively expensive and thermally unstable. To reduce the associated costs of solid adsorbents and improve their thermal stability, attention has shifted to exploring bio-based adsorbents from waste shells (e.g cockle and oysters), for CO₂ capture. Consequently, egg shells and seashells have been investigated and found effective for CO₂ capture [13], [14]. These bio-based shells provide a sustainable source of CaCO₃, comprising about 90 – 96% of the shells [15], the principal component responsible for CO₂ adsorption. During the CO₂ adsorption process, calcined CaCO₃, comprising mainly CaO, reacts with CO₂ to form CaCO₃. The CaCO₃ is then heated to regenerate CaO to continue the adsorption cycle.

Like other waste seashells, Periwinkle (*tympanotonus fuscatus*) shells contain large amounts of sustainable CaCO₃. The use of this waste shell in many applications has been discussed extensively in the open literature [16]. However, studies on their use as adsorbents for CO₂ capture are limited in the available literature. Furthermore, using potentially effective modification agents like deep eutectic solvents (DES) and polyethylene glycol (PEG) for modifying periwinkle shell-based adsorbents are rare. This study, therefore, aims to investigate the performance of adsorbents developed from calcined periwinkle shells, activated with KOH, and modified with DES and PEG for CO₂ capture.

1.1. The Deep Eutectic Solvent (DES) and Polyethylene Glycol (PEG).

DES has numerous bonding hydrogen donors and pairs acceptors for the CO₂ capturing system [17]. These deep eutectic solvents can be formed from the mixtures of choline chloride and glycerols, often called deep eutectic solvent glycerine, usually in their molar ratio using 1mol of choline chloride with 2 mol of glycerol. The DES consists of hydrochloride-ethylenediamine, which possesses a good quality of gravimetric uptake and exhibits suitable performance in the presence of H₂O, with unique tolerance against temperature rise and relative low heat absorption process, which favors regeneration. Those properties aid the DES in CO₂ capture [18]. In the presence of PEG, CO₂ adsorption capacity is expected to increase since PEG acts as a hydrogen ion acceptor for their strong affinity for H⁺. Moreover, the Hydroxyl groups in polyethylene glycol positively influence CO₂ capture [19].

2. MATERIALS AND METHODS

2.1. Calcination of Periwinkle Shell.

Samples of periwinkle shells were collected and washed to remove the dust and other water-soluble materials. The washing process continued until the water was colorless, then dried. Then 500 grams of the periwinkle shell was weighed in a precision electronic balance of model WT 6002A and heated using a muffle furnace with model SXL without air at 800 °C for 2 hrs before crushing to finer particles and sieved with (0.25 mm – 1.4 mm) sieve. The calcined and sieved periwinkle shell was stored in an amber bottle, herein referred to as calcined periwinkle shell (CPS). Figure 1a shows the calcined periwinkle shell sample.

2.2. Activation of Periwinkle Shell.

Chemical activation was done by thoroughly mixing 100 grams of calcined periwinkle shell CPS in 1000 ml of 1M KOH solution until it formed a slurry. It was left for 72 hrs, then washed with de-ionized water and dried in an oven at 110 °C for 2 hrs. Two portions of the calcined sample were activated in the ratios of 2:1 with the KOH solution. The final activated calcined samples were depicted as APS1 and APS 2, respectively. Figure 1b shows the activated periwinkle shell sample.

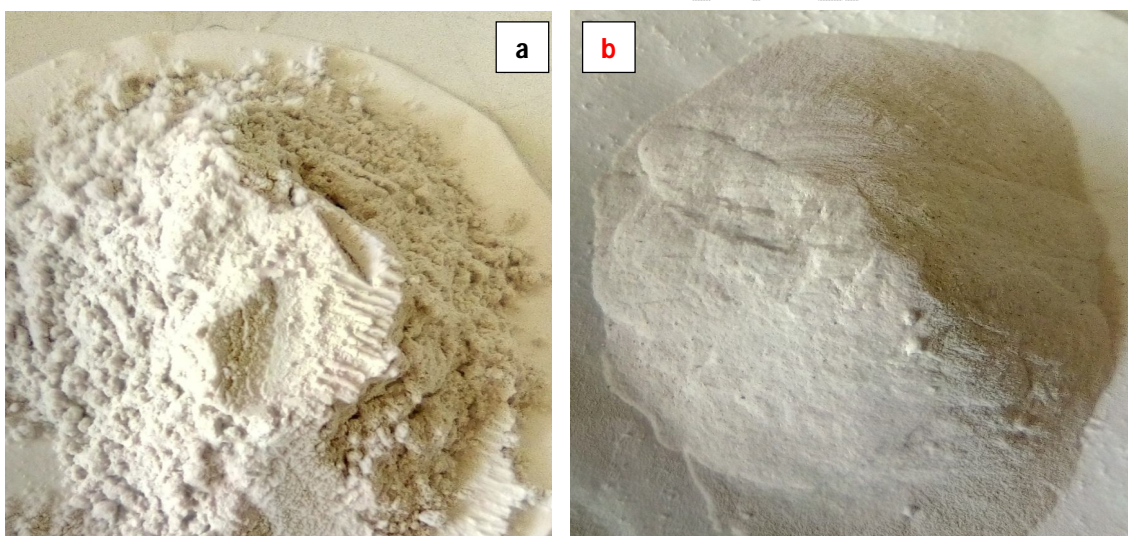


Fig. 1. (a) Calcined and (b) activated periwinkle shell

2.3. Modification of Activated Periwinkle Shell.

The activated periwinkle shell was functionalized with two reagents: the deep eutectic solvent (DES) and polyethylene glycol (PEG). Deep Eutectic solvent (DES) was prepared by adding choline chloride with Glycerol. 15 ml of choline chloride was added to 30 ml of glycerol in a sealed vacuum flask and stirred on a magnetic stirrer for 60 mins at 80 °C until a homogenous and transparent sample was formed. 20 ml of the prepared deep eutectic solvent was then added to 10 ml of APS1 in the ratio of 1:2 for APS1: DES, both introduced into a vacuum flask and placed on a magnetic stirrer for 360 mins at 150 °C, until it formed a slurry. The sample was left in the vacuum flask for 72 hrs, then dried in a furnace for 2 hrs at 800 °C. This modified sample was designated as APS-DES. Also, 30 g of APS 2 was introduced into a flat bottom flask, and 60 ml of polyethylene glycol was added and placed on a magnetic stirrer for 6 hrs at 150 °C. The sample was dried in a furnace for 2 hrs at 800 °C and designated as APS-PEG.

2.4. Characterization of Adsorbents

The formulated APS-DES and APS-PEG adsorbents were characterized using the Infrared spectrometer (Varian 660 MidIR Dual MCT/DTGS Bundle with ATR) for the Fourier transform infrared spectroscopy (FTIR) analysis and the Hitachi SU 3500 scanning electron microscope for the SEM analysis. These analyses were performed to have an in-depth understanding of the surface morphology of the modified periwinkle shell adsorbents and to know the functional groups responsible for the adsorption process.

2.5. CO₂ Adsorption Experiment

The CO₂ adsorption apparatus used for the CO₂ adsorption experiments works on the principles of Sievert's law, as presented by Sadie [20]. Measured amounts of the APS-DES and APS-PEG adsorbents were placed in the reactor, immersed in a water bath for temperature control, and dosed with CO₂ gas. Initial and final (equilibrium) pressures and corresponding temperatures were recorded. Initial pressure ranges were 2 and 15 psia at 26 °C. Adsorption experiments were performed at retention times of 1 and 3 hours. These time frames were chosen to understand the relationship between the adsorption capacity and time. The corresponding adsorption capacity at each condition was also measured. Details of the apparatus and experimental procedures can be found elsewhere [21].

3. RESULTS AND DISCUSSIONS

3.1 Characterization of the Calcined and Modified Periwinkles Samples

The SEM and FTIR images of the calcined, DES and PEG-modified periwinkle shell reveal the surface morphologies and active functional groups of the different periwinkle samples. Figures 2 and 3. The SEM images in figure 2 show that the calcined periwinkle shell (fig 2a) possesses a rigid structure with relatively distributed void spaces, unlike the DES(fig 2b) and PEG (fig 2c) -modified structures. The DES and PEG modified structures' surface area is relatively clogged with little or no void spaces.

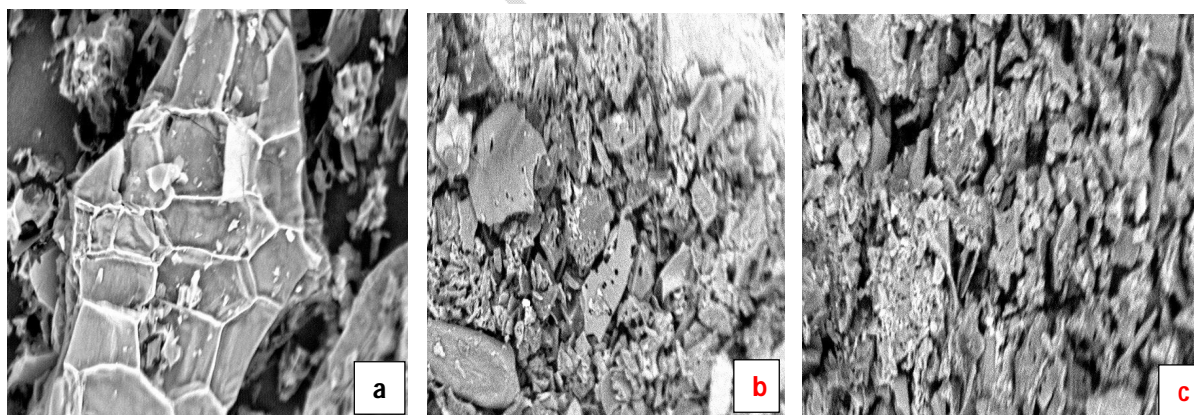


Fig. 2. SEM images of (a) calcined (b) DES modified (c) PEG-modified periwinkle shell

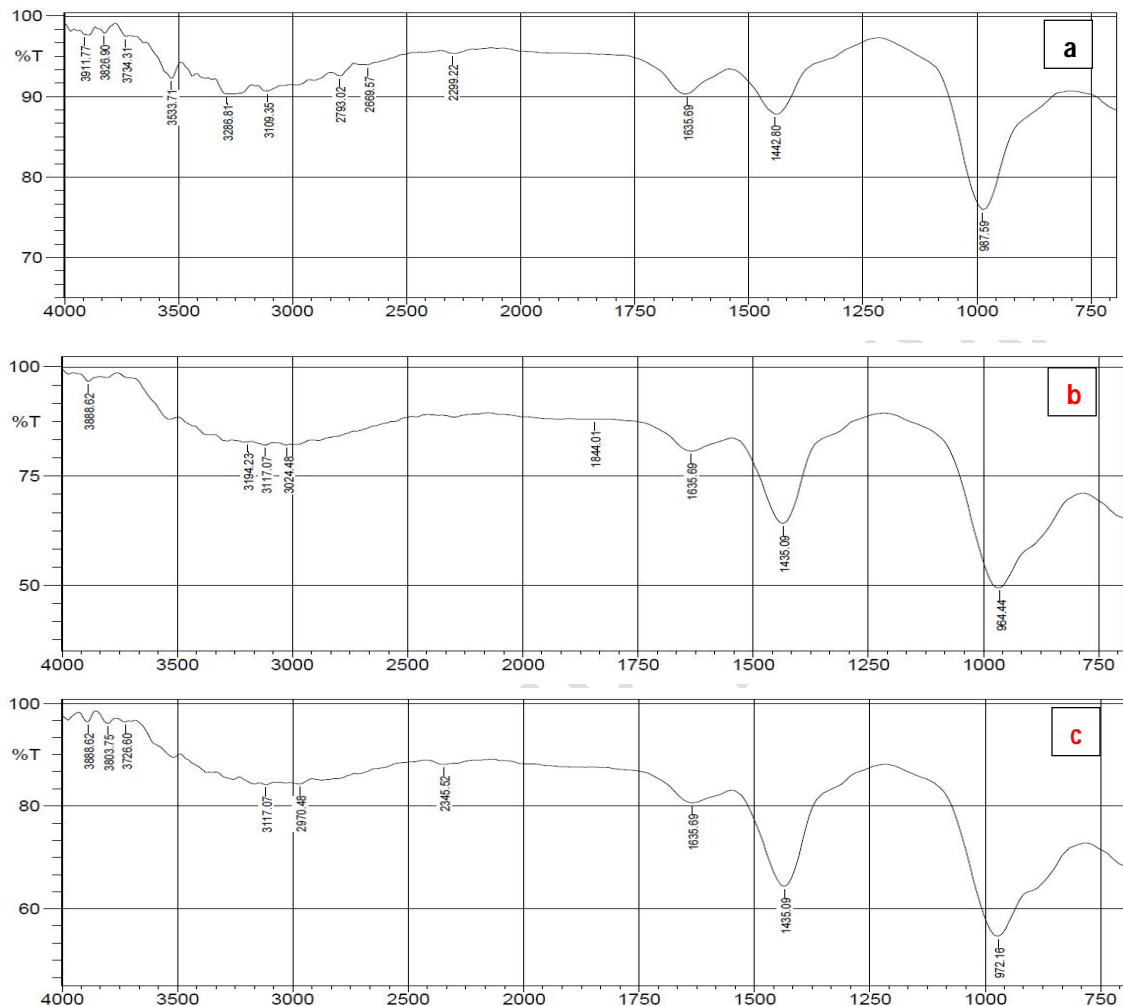


Fig. 3. FTIR spectra of (a) calcined (b) DES modified (c) PEG-modified periwinkle shell

The similarity of the FTIR of the the modified DES and PEG samples in figure 3 may be due to the properties of the alcohol group in both reagents. Likewise, the similarity in the FTIR spectra of the unmodified calcined sample with the modified DES and PEG samples, may be due to inherent functional groups in the periwinkle shell. The clogging of the pore spaces might be due to the viscous nature of DES and PEG, which may block the available pore spaces. The lack of void spaces may affect the samples' adsorption capacities. Furthermore, the FTIR spectra show that the samples are pretty simple structures, with the calcined sample having more functional group bands (12) than the PEG (9) and DES (8) modified samples. All three samples had the double bond C-H stretching of the alkenes group (964 – 987 cm^{-1}), C-C stretching of the aromatic groups (1435-1443 cm^{-1}), N-H bends of primary amines (1635-1636 cm^{-1}), and the –OH stretching corresponding to carboxylic acids (3109-3117 cm^{-1}). However, the unmodified calcined sample had, in addition to the other stated functional groups in the modified samples, the H-C=O stretching of the aldehyde group (2669 and 2793 cm^{-1}) and the –OH stretching of the alcohol and hydroxyl group (3534 cm^{-1}).

3.2 CO₂ Adsorption Capacity of the Samples

Figure 4 shows the results of the CO₂ adsorption experiments after 1 and 3 hours measured at an ambient temperature of 26 °C. All four samples had increasing adsorption capacity with increasing pressure. This can be attributed to the fact that the high impact forces with which CO₂ molecules penetrate the porous structure of the adsorbents cause the molecules to have access to the pore spaces hence, an increase in adsorption capacity [22], [23]. The calcined periwinkle shell, CPS, had a better adsorption capacity than the modified samples. After 1 hour, the CPS sample had an adsorption capacity of about 0.16 mmol/g, while the APS, APS-DES, and APS-PEG samples had adsorption capacities of 0.09 mmol/g, 0.07 mmol/g, and 0.05 mmol/g, respectively. Likewise, the adsorption capacities of the samples CPS, APS, APS-DES, and APS-PEG had adsorption capacities of 0.42 mmol/g, 0.15 mmol/g, 0.11 mmol/g, and 0.21 mmol/g, respectively, after 3 hours.

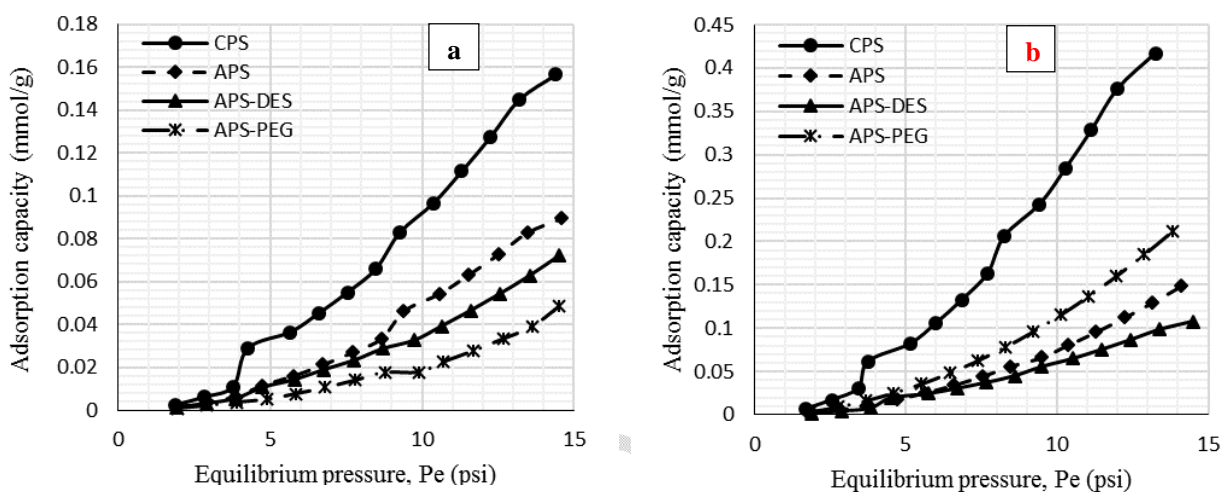


Fig. 4. CO₂ adsorption after (a) 1 hour and (b) 3 hours.

The increase in the retention time from 1 to 3 hours increases the contact time between adsorbent and adsorbate. Hence adsorption capacities of all the samples increased with time [24]. The adsorption capacity of the CPS sample outperformed all the modified samples. This relatively high adsorption compared to the modified samples may be due to the presence of more void spaces as well as nitrogen and oxygen sites of the additional H-C=O stretching of the aldehyde group as well as the -OH stretching of the alcohol and hydroxyl group, in the sample. The presence of more nitrogen and oxygen sites in an adsorbent enhances the CO₂ adsorption process [25], [26]. Furthermore, the adsorption capacities of the modified samples, APS, APS-DES, and APS-PEG, reduced significantly compared to the CPS sample. The reduced adsorption capacity is evident in the relative lack of void spaces, increased logging, and fewer CO₂ reactive functional groups identified in the modified samples, as seen in figures 2 and 3. Also, the increasing viscosity of the modifying agents could be responsible for clogging the available pore spaces required for the adsorption process. The modification of an adsorbent with certain CO₂ reactive agents can reduce their specific surface area available for adsorption and their pore spaces [23], resulting in adsorbent clogging. This clogging due to reduced surface area and pore spaces could be responsible for a decreased adsorption capacity. Figure 5 shows the adsorption isotherms for the various samples. The Langmuir and Freundlich models were used in this study to model the CO₂ adsorption of the samples.

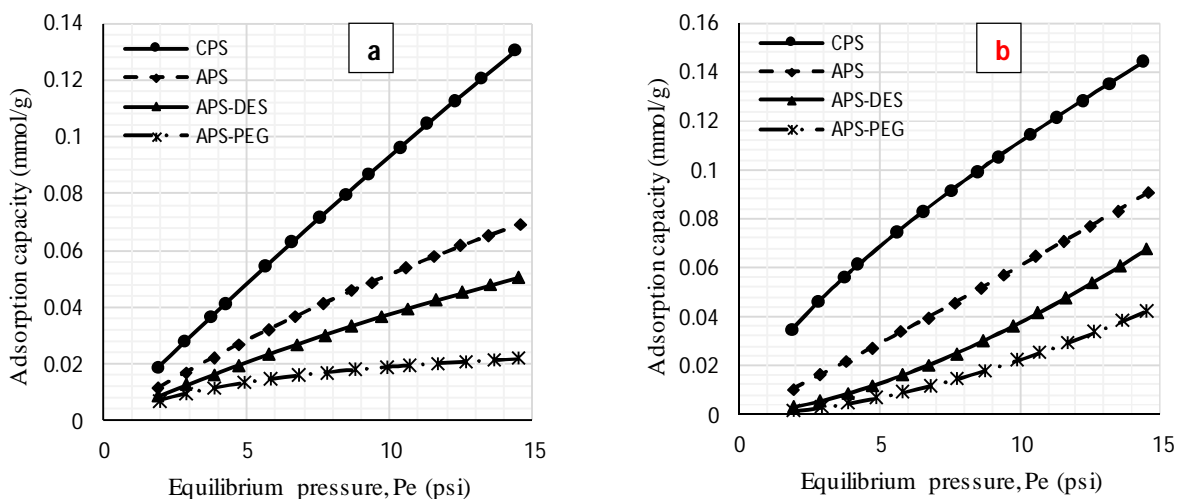


Fig. 5. (a) Langmuir and (b) Freundlich adsorption isotherms

Table 1 shows the isotherm parameters. The table shows that the Langmuir and Freundlich isotherm models can reliably describe the CO₂ adsorption of the CPS sample since both models gave a coefficient of determination of more than 0.95. However, the Langmuir model had the highest R² of 0.98 and thus can best describe the CPS sample CO₂ adsorption process, implying that adsorption is mostly a monolayer phenomenon. Also, the Freundlich isotherm exponent of the CPS sample is greater than 1, indicating a favorable adsorption process. The Langmuir maximum adsorption capacity, Q_m, is observed to decrease from 1.39 mmol/g for CPS to 0.28, 0.21, and 0.03 mmol/g for APS, APS-DES, and APS-PEG samples, respectively. The Langmuir R² value of the adsorbents also showed a decrease in value from 0.98 for the CPS sample to 0.95, 0.94, and 0.79 for APS, APS-DES, and APS-PEG samples, respectively. Similarly, the Freundlich adsorption constant decreased from 0.22 for the CPS sample to 0.005, 0.00098, and 0.00045 for APS, APS-DES, and APS-PEG samples, respectively. This reduction in the Langmuir maximum adsorption capacity and R² and the Freundlich adsorption constant validate the modified adsorbents' poor adsorption performance.

Table 1. Adsorption isotherm parameters for the samples.

Samples	Isotherm Parameters					
	Langmuir	Langmuir			Freundlich	
	Q _m	K _L	R ²	K _f	n	R ²
CPS	1.39	0.007	0.98	0.02200	1.42	0.96
APS	0.28	0.022	0.95	0.00500	0.93	0.98
APS-DES	0.21	0.022	0.94	0.00098	0.63	0.99
APS-PEG	0.03	0.140	0.79	0.000452	0.59	0.98

However, the relatively low adsorption capacities of the investigated samples indicate that periwinkle shells modified with DES and PEG are unsuitable for CO₂ adsorption. This poor adsorption performance could be due to inadequate pre-treatment of the periwinkle shells before calcination. Iyer et al. [13], Sacia et al. [14], and Vonder-Haar [27] showed that the pre-treatment of seashells and other CaCO₃-rich shells like eggshells with an optimized concentration of acetic acid increased the pore structures and surface areas of the shells, which ultimately led to a better adsorption capacity. This improvement in their surface morphology and hence adsorption capacity was attributed to the formation of calcium acetate, which has a greater molar volume than CaCO₃. Thus an improved pore development and surface area. Furthermore, the poor adsorption performance could result from the fact that DES and PEG are unsuitable for modifying periwinkle shells for use as adsorbents. Consequently, the modification suitability of these chemical agents on waste shells should be further

investigated. The periwinkle sizes of 0.25 -1.44 mm could also be a factor. Hence particle size optimization of the shells for maximum adsorption is required. Also, further research should be performed on the suitability of periwinkle shells as adsorbents for CO₂ capture.

4. CONCLUSION

This study evaluated the CO₂ adsorption performance of calcined periwinkle shells (CPS), KOH-activated CPS (APS), DES-modified APS, and PEG-modified APS. The results showed that the unmodified calcined periwinkle shells performed better than the KOH-activated and the DES and PEG-modified APS samples, with a CO₂ adsorption capacity of 0.16 and 0.42 mmol/g after 1 and 3 hours, respectively. The adsorption process of the CPS sample followed the Langmuir monolayer model of adsorption. Further studies on the effect of acetic acid pre-treatment of the periwinkle shells, particle sizes optimization, and the modification suitability of the chemical agents (DES and PEG), were advocated.

REFERENCES

- [1]. Ghorani-Azam, A., Riahi-Zanjani, B., & Balali-Mood, M. Effects of air pollution on human health and practical measures for prevention in Iran. *Journal of Research in Medical Sciences: The Official Journal of Isfahan University of Medical Sciences*, 2016, 21.
- [2]. Spellman FR. Carbon Capture and Sequestration, in: *Sci. Renew. Energy*, Second Ed., CRC Press, 2016: pp. 503–522.
- [3]. COP21 Paris Agreement, European Commission, http://ec.europa.eu/clima/policies/international/negotiations/paris/index_en.htm (accessed 10/07/2020).
- [4]. Khan S.A.R., Zhang Y., Sharif A., Golpîra H. Determinants of economic growth and environmental sustainability in South Asian Association for Regional Cooperation: evidence from panel ARDL, *Environmental Science and Pollution Research*, 2020. <https://doi.org/10.1007/s11356-020-10410-1>
- [5]. Tcvetkov P., Cherepovitsyn A., Fedoseev S. Public perception of carbon capture and storage: A state-of-the-art overview, *Heliyon*, 2019, 5: e02845.
- [6]. United Nations Report on Global Issues of Population (2022). Available at <https://www.un.org/en/global-issues/population>.
- [7]. International Energy Agency (IEA). World Energy Outlook 2020. Available at <https://iea.blob.core.windows.net/assets/a72d8abf-de08-4385-8711-b8a062d6124a/WE02020.pdf>
- [8]. Akash S, Savita V. Carbon Capture and Sequestration- A Review, *IOP Conf. Ser. Earth Environ. Sci. Pap.* 83 (2017). doi:10.1088/1755-1315/83/1/012024.
- [9]. Leung DYC, Caramanna G, Maroto-valer M. An overview of current status of carbon dioxide capture and storage technologies, *Renew. Sustain. Energy Rev.* 2014, 39, 426–443. doi:10.1016/j.rser.2014.07.093.
- [10]. Blomen E, Hendriks C, Neele F. Capture technologies: Improvements and Promising Developments. *Energy Procedia*, 2009, 1, 1505–1512. doi:10.1016/j.egypro.2009.01.197.
- [11]. Osman AI, Hefny M, Maksoud MIA, Elgarahy AM, Rooney DW. Recent advances in carbon capture storage and utilisation technologies: a review. *Environmental Chemistry Letters* 2021, 19:797–849. <https://doi.org/10.1007/s10311-020-01133-3>

- [12]. Hamdy LB, Goel C, Rudd JA, Barronade AR and Andreoli E. The application of amine-based materials for carbon capture and utilization: an overarching view. *Mater. Adv*, 2021, 2, 5843. DOI: 10.1039/d1ma00360g
- [13]. Iyer MV, Sparks A, Vonder-Haar T, Fan L.-S. High Temperature CO₂ Capture using Waste Oyster Shells. (*Bunri Gijutsu*) *Soc of Sep. Proc. Eng. Jpn*, 2005, 35 (4): 235-245.
- [14]. Sacia RE, Ramkumar S, Phalak N, Fan L.-S. Synthesis and Regeneration of Sustainable CaO Sorbents from Chicken Eggshells for Enhanced Carbon Dioxide Capture. *ACS Sustainable Chem. Eng.*, 2013, 1, 903–909.
- [15]. Hart A. Mini-review of waste shell-derived materials' applications. *Waste Management & Research*, 2020, 38 (5): 514 – 527
- [16]. Aimikhe VJ, Lekia GB. An Overview of the Applications of Periwinkle (*Tympanotonus fuscatus*) Shells. *Current Journal of Applied Science and Technology*, 2021, 40(18):31-58
- [17]. Zulkurnai NZ, Mohammad AUF, Ibrahim N, Abdul Manan, NS. Carbon Dioxide CO₂ Adsorption by Activated Carbon Functionalized with Deep Eutectic Solvent (DES). *IOP Conference Series: Materials Science and Engineering*, 2017, 206(1). <https://doi.org/10.1088/1757-899X/206/1/012001>
- [18]. Tushar T, Hoon L, Jeong LH, Kyeong JY, Wook CJ. Deep Eutectic Solvent As Attractive Media for Co₂ Captured. *Journal of green chemistry*, 2016. [Http://doi.org/10.1039/c59c02319j](http://doi.org/10.1039/c59c02319j).
- [19]. Tang YW, Bian J, Hu Z, Liu H. Carbondioxide capture By Amine- Impregnated Mesocellular Foam Containing Template. *Ind Eng Chemical Research* 2012, 51:3653-3662.
- [20]. Stadie NP (2013). Appendix A. Experimental Adsorption Measurements. Accessed on 13th July 2020 from https://thesis.library.calte.ch.edu/7198/77/Stadie_N_2013_Appendices.Pdf
- [21]. Aimikhe VJ, Eyankware OE. Design, Fabrication, and Validation of a Flow Loop for CO₂ Adsorption Studies. *Petroleum and Coal*. 2021. 63(3):824 – 832.
- [22] Sun Y, Li K, Zhao J, Wang J, Tang N, Zhang D, ... Jin Z. Nitrogen and sulfur Co-doped microporous activated carbon macro-spheres for CO₂ capture. *Journal of Colloid and Interface Science*, 2018, 526, 174–183. <https://doi.org/10.1016/j.jcis.2018.04.101>
- [23]. Fatima SS, Borhan A, Ayoub M, Ghani NA. CO₂ Adsorption Performance on Surface-Functionalized Activated Carbon Impregnated with Pyrrolidinium-Based Ionic Liquid. *Processes* 2022, 10, 2372. <https://doi.org/10.3390/pr10112372>
- [24]. Akpasi SO, Isa YM. Effect of operating variables on CO₂ adsorption capacity of activated carbon, kaolinite, and activated carbon – Kaolinite composite adsorbent. *Water-Energy Nexus* 2022, 5, 21–28. <https://doi.org/10.1016/j.wen.2022.08.001>
- [25]. Gu C, Liu Y, Wang W, Liu J, Hu J. Effects of functional groups for CO₂ capture using metal organic frameworks. *Front. Chem. Sci. Eng.* <https://doi.org/10.1007/s11705-020-1961-6>
- [26]. Dong K, Zhai Z, Guo A. Effects of Pore Parameters and Functional Groups in Coal on CO₂/CH₄ Adsorption. *ACS Omega*, 2021, 6 (48), 32395-32407. DOI: 10.1021/acsomega.1c02573.
- [27]. Vonder-Haar TA. Engineering Eggshells for Carbon Dioxide Capture, Hydrogen Production, and as a Collagen Source. B.S. Dissertation, Ohio State University, Columbus, OH, 2007.

UNDER PEER REVIEW