

Original Research Article

Synthesis and characterization of di-metallic zeolite Pt-Co composite as potential catalyst for reforming and hydro-sulphurization of gasoline

Abstract

Synthesis and characterization of di-metallic zeolite-Pt-Co composite was carried out via Hydrothermal Treatment, Acid leaching of Mesoporous-kaolin and Calcination of the acidified mesoporous-kaolin. [Please remove the capital letters in the text behind here](#) Pt and Co metals were impregnated into the zeolite matrix through thermal reduction of $\text{H}_2\text{PtCl}_6 \cdot 6\text{H}_2\text{O}$ and $\text{Co}(\text{CH}_3\text{COO})_2$ at 550°C for 6 hours using (NaBH_4) as reductant with Polyvinylpyrrolidone (PVP) as stabilizer. The results of FTIR indicated absorption bands range of $1062.3\text{-}74.671\text{ cm}^{-1}$ attributed to tetrahedral stretches for AlO_3 and SiO . A peak at 779.0 cm^{-1} stretches assigned to Pt and 650 cm^{-1} due to Co. This may confirm the impregnation of Co and Pt- into the composite. Also, muscovite and quartz interloping where confirmed at $1031\text{-}1038\text{ cm}^{-1}$. The XRD analysis indicated 35% sanidine $[(\text{K}, \text{Na})(\text{Si}, \text{Al})_4\text{O}_8]$, 27% quartz (SiO_2) , 24 % Orthoclase $(\text{KAlSi}_3\text{O}_8)$, 8% Albite $(\text{NaAlSi}_3\text{O}_8)$ and 6.3% Muscovite $(\text{KAl}_2(\text{Si}_3\text{Al})\text{O}_{10}(\text{OH})_2)$ with sharp peaks of quartz at $20.8^\circ 2\theta$, implying crystalline. The results of the Transmission Electron Microscope TEM at 20 nm magnification indicated a uniform morphology with particle size range of 8.22nm - 23.80 nm and average particle size of 16.242 nm. HRTEM result for the synthesized Zeolite Pt-Co composite indicated a particle size range of 3.22 nm -10.27 nm with average particle size of 7.15 nm of disaggregation crystallites morphology. Also, TEM monograph of synthesis Zeolite-Pt-Co indicated a reduced even particle size compared to calcined zeolite clay. Pt enhances isomerization of straight run gasoline with consequent increase in octane number of gasoline while Co aids in hydrosulphurisation.

Key Words: kaolin, Zeolite, catalyst, Calcination, hydrosulphurisation, isomerization

INTRODUCTION

Ample amount of untapped kaolin deposits is scattered in various parts of Akwa Ibom State and other parts of Nigeria. Zeolites could occur natural or as synthesized crystalline aluminosilicate minerals. Zeolite is made up of three-dimensional structures due to its oxygen bonded background ($[\text{SiO}_4]_4^-$ and $[\text{AlO}_4]_5^-$ polyhedral) Victor *et al.*, (2020). Zeolite is well defined as crystalline aluminosilicate with different pore sizes which is classified as microporous (pore size smaller than 2 nm), mesoporous (pore size between 2 to 50 nm) and macroporous (pore size larger than 50 nm) Kumaran *et al.*, (2019); Lateef *et al.*, (2016). Zeolite is ~~used applied~~ in numerous industrial applications including water purification, petroleum refining especially in fluid catalytic cracking. Hydrocarbon refining (cracking and reforming) especially fluid catalytic cracking unit is the major consumer of zeolitic catalyst for ~~increasing ncrease~~ quantity of gasoline , octane number enhancement, upgrading of gasoline structure, and production of environmentally friendly hydrocarbon fuel.

According to U.S. Energy Information Administration database for calendar year 2022, Nigeria is ranked 15th in crude oil production in the world with 1,316,415 bbl/day. Unfortunately, Nigeria imports all her hydrocarbon fuel due to non-operational refineries. Furthermore, refineries are producing at below installed capacities or are not [working functioning](#) at all, which has resulted in the inability to refine enough gasoline to meet local consumption Udo *et al.*,(2023), (Udo *et al.*, 2020). Hydrocarbon based fuel are non-biodegradable and non-renewable which may be exhausted Udo *et al.*,(2020).

Also, Nigeria untapped zeolitic kaolin are scattered in different locations in Nigeria. Low-cost silica-alumina such as kaolinite Zeolites can be synthesized from kaolinite kaolin via “Hydrogel process”. The structural pattern could be confirmed by the presence of a single characteristic broad band associated with O-H stretching vibrations of the catalytic centers (Si-OH-Al sites) located in the region between 3700-3500 cm⁻¹ Victor *et al.*,(2020); Isernia, (2013). Highest isomer production was archived with ensemble of Rh bounded with Pt atoms Musselwhite *et al.*,(2013). The Platinum catalysts exhibit high activity and selectivity. Olajire reported that a bimetallic Pt-Cu nanostructure poses greater catalytic oxidative action in desulfurization process

Synthesis of zeolite from clay as a source of silica and alumina from Nigerian kaolin clay has been successfully studied Adeoye *et al.*,(2017); Olaremu *et al.*,(2019); Yusuf *et al.*,(2019). Naturally occurring zeolite is important in many industrial processes due to its environmentally benign nature, low cost and its relative abundance compared to deleterious, expensive and, imported synthetic zeolite. Nigeria has numerous untapped natural kaolin deposits. Unfortunately, for many years now we experience protracted increase in prices of petroleum products especially premium motor spirit (PMS) in Nigeria, with attendant adversative economic consequences. This is because of malfunctioning of all the local refineries in Nigeria, importation of all petroleum products which are sometime adulterated. Pt and Co have high selectivity and catalytic activities with enhance isomerization ability of straight run gasoline and hydrosulphurization respectively. Also, Pt-based bimetallic catalysts display great improved activity, selectivity, and stability compared to monometallic catalyst Shilina *et al.*(2023). Hence, the objective of this study was to design a low cost, ecofriendly, high performance zeolite-Pt-Co composite with enhance isomerization and hydrosulphurization potentials. Pt based catalysts possess a great selectivity to multi branched isomers, with low aromatic compounds production Ghaderi *et al.*,(2021)

MATERIALS AND METHODS

Sample Collection

The kaolin sample used in this study was collected from clay deposits in Ikot Uso Akpan Itam, Itu L.G.A, Akwa Ibom State, using a clean garden fork. The sample was pulverized to enable its usability stored in clean dry plastic container. Ikot Uso Akpan Itam is in Itu Local Government Area, Akwa Ibom State, Nigeria. The study area is bounded in the North and North-East by Odukpani in Cross River State and Arochukwu in Abia State, in the West by Ibiono Ibom and Ikono L.G.A, in the South and South-east by Uyo and Uruan Local Government Areas respectively. Itu has a latitude of 5.203624(5°12'13.05°N) and a longitude of 7.968822(7°58'7.76°E)

Hydrothermal Treatment of Kaolin Clay

In hydrothermal process, 50 g of dried clay sample was added into a 200 ml conical flask containing 100 ml of deionized water. The mixture was heated at 150 °C for one (1) hour with

constant stirring using hot plate with magnetic stirrer, the resulting mixture was filtered and oven dried at 120°C stored in lid tight containers for further use.

Acid leaching of Mesoporous-kaolin

The dried (mesoporous-kaolin) (50 g) prepared ~~in from~~ the hydrothermal step was added to a 200 ml conical flask containing 100 ml of 11% hydrochloric acid (HCl). The resulting mixture was heated electrically at 150°C with constant stirring using magnetic stirrer for one (1) hour and filtered. The solid residue was washed with deionized water until no chloride was detected using AgNO₃.

Calcination of the acidified mesoporous -kaolin

The acidified mesoporous -kaolin was oven dried at 120°C for one (1) hour and calcined at 550°C for two (2) ~~hours~~ in a muffle furnace and later cooled. The calcined kaolin was stored in a lid tight container and properly ~~labeled~~. The heating process ~~eliminates~~ ~~drives~~ ~~off~~ water from the mineral kaolinite (Al₂O₃·2SiO₂·2H₂O), the main constituent of kaolin clay, and collapses the material structure, resulting in an amorphous aluminosilicate (Al₂O₃·2SiO₂), metakaolinite. The process is known as dehydroxylation $\text{Al}_2\text{O}_3 \cdot 2\text{SiO}_2 \cdot 2\text{H}_2\text{O} \rightarrow \text{Al}_2\text{O}_3 \cdot 2\text{SiO}_2 + 2\text{H}_2\text{O} \uparrow$

Preparation of Zeolite-dimetallic (Zeolite-Pt-Co) Composite

The calcined kaolin prepared from acidified mesoporous -kaolin was used to form Zeolite Pt-Co composite according to Olajireet *al*, (2017) in the following steps. In the first step, the synthesis of zeolite Pt-Co composite was prepared by mixing 30 mL of 1 M aqueous H₂PtCl₆·6H₂O solution, and 30 mL of 1 M aqueous Co(CH₃COO)₂ solution with magnetic stirring in a flask. Thirty (30 ml) of 0.002 sodium borohydride (NaBH₄) was subsequently added to the flask, placed in an ice bath on a stir plate and stirred with addition of 5 g of Polyvinylpyrrolidone (PVP) as stabilizer to prevent aggregation, Olajireet *al*, (2017). In the second step, Ten grams (10 g) of the prepared calcined kaolin catalyst was added into 200 ml conical flask containing 50 ml of deionized water and mixed with the ~~content~~ in the conical flask in step 1. The mixture was heated for 1 hour at 150 °C using hot plate and oven-dried at 120°C for 1 hour for reduction process. The dried mesoporous clay composite Zeolite-Pt-Co composite was further calcined at 550 °C for 5 hours in a muffle furnace to and stored in a labeled lid tight container.

Characterization of the synthesized Zeolite-Pt-Co

The functional groups profile and molecular finger print of the synthesized zeolite-Pt-Co composite was analyzed using Agilent Technologies Cary 630 FTIR, Benchtop FTIR Spectrometer with depth 26 cm, height 16 cm, power requirement-100-240 VAC, 50/60 Hz, Resolution-≤ 2 cm⁻¹, sample type-powder couple with MicroLab Pharma Software. Unique Ux-30 XRF spectrophotometer was ~~used to analyze in~~ ~~analyzing~~ individual elementals and compound present in the composite. The crystalline phase identification (phase ID), quantification and percent (%) crystallinity, of the synthesized zeolite-Pt-Co composite were carried out using Rigaku Miniflex Benchtop powder X-ray Diffraction (XRD) instrument. Core attribute-600 W X-ray tube, D/teX Ultra silicon strip detector, Core dimensions-620 (W) x 722 (H) x 460 (D) mm, Power requirements-1Ø, 100-240 V 50/60 Hz mounted with External PC, MS Windows OS, SmartLab Studio-II software.

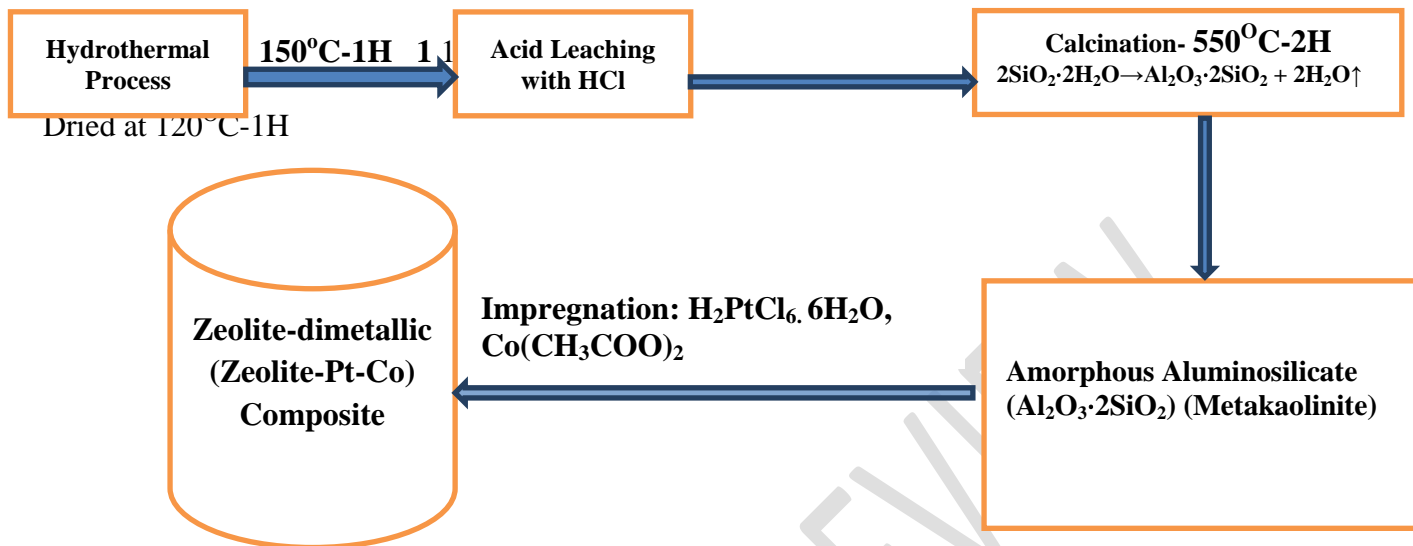


Figure 1: Flow chart for synthesis of Zeolite-dimetallic (Zeolite-Pt-Co) Composite

[Figure 1 is not cited in the text](#)

RESULTS AND DISCUSSIONS

The results of XRD, FTIR, TEM and XRF are as presented in Figure 2- Figure 7 and Table 1. XRD analysis of the Zeolite-Pt-Co. From the results of XRD data Fig. 2 -Fig 3, the Zeolite-Pt-Co composite produced contained 35% sanidine [(K,Na)(Si,Al)₄O₈] Haldar and Josip (2014), 27% quartz (SiO₂), 24% Orthoclase (KAlSi₃O₈), 8% Albite (NaAlSi₃O₈) and 6.3% Muscovite (KAl₂(Si₃Al)O₁₀(OH)₂). Also, the X-ray diffraction patterns of the Zeolite-Pt-Co composite indicated sharp peaks for quartz at 20.8° 2θ, implying that the composite is crystalline. The peak at 2θ = 3.4° is associated with d220 reflection the peaks 6.16°, 15.88°, 26.08°, and 30.7° depict the HY zeolite Anbia *et al.*, (2015), Peng *et al.*, (2016), Ghaderi *et al.*, (2021). In a similar study by Yusuf *et al.*, (2019) XRD data indicated two peaks corresponding to the kaolinite and quartz in Elefun Kaolin.

Phase Data View

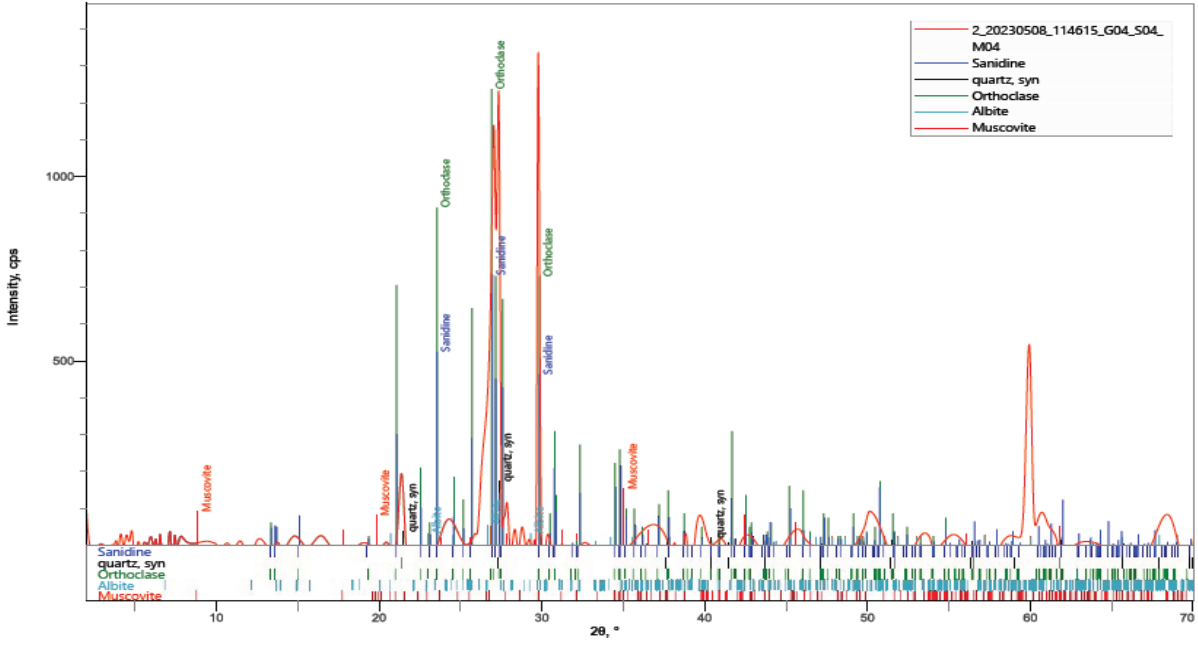


Figure 2: XRD phase data view of Zeolite-Pt-Co composite

Plot of results

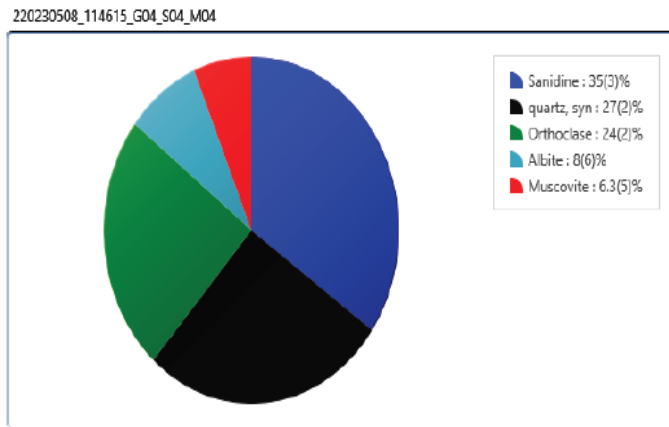


Table of results

Dataset / Weight Fraction, wt%	Value, Unit	Sanidine	quartz, syn	Orthoclase	Albite	Muscovite
2_20230508_114615_G04_S04_...	0	35(3)	27(2)	24(2)	8(6)	6.3(5)

Figure 3: Percentage composition of Sanidine, quartz, Orthoclase, Albite and Muscovite

FTIR spectroscopy Analysis.

The results of FTIR spectroscopy analysis of the synthesized Zeolite-Pt-Co composite are as presented in Figures 4-5. From the FTIR data results, the absorption bands ranges observed at $1062.3\text{-}74.671\text{ cm}^{-1}$ is attributed to tetrahedral stretches for AlO_3 and SiO Kumaran *et al*, (2019). Ezra *et al*, (2021) reported 1067.44 cm^{-1} absorption band for symmetric stretching vibration of Si-O-Si bond. The 1062.3 cm^{-1} stretches could also be attributed to Si-O quartz. The result of FTIR of the calcined kaolin clay was in line with the research of Bhaskar *et al*,(2010) who confirmed that “the main peaks in the infrared spectra reflected Al-OH, Al-O and Si-O functional groups in the high frequency stretching and low frequency bending modes”. $4000\text{-}650\text{ cm}^{-1}$ stretches could be associated with Co-O and Pt vibrations. ~~This~~ may confirm the impregnation of Co and Pt into the synthesis Zeolite-Pt-Co composite Abubkaret *al*,(2023). Shilina *et al*,(2023), Eurovet *al*,(2022) observed a Co small band near 669 cm^{-1} due to stretching vibrations of the metal–oxygen bond in Co_3O_4 . Cobalt serves catalyst for hydrodesulfurization in petroleum refining. The wave number 3678.9 cm^{-1} and 3596.5 cm^{-1} may be assigned to Al–O–H stretching and OH Stretching - Crystalline hydroxyl respectively Saikia *et al*,(2010). The obtained FT-IR spectra in this study was consistent with the work of Nguyen *et al*, 2019 who recorded 3382 , 3269 , and 3236 cm^{-1} for PtNPs/CTS samples with CTS concentration of 2.0, 1.0, and 0.5%, respectively. Muscovite and possibly quartz interference could be observed at $1031\text{-}1038\text{ cm}^{-1}$ for the studied kaolin Saikia *et al*,(2010). In this paragraph I can sother pepe material that corresponds to Introduction Section, for example when you indicate the work and results obtained by other people, and I would expect in this section to see your results and a discussion of your results eventually supported by other people’s results.



Agilent Technologies

Sample ID:A1
Sample Scans:30
Background Scans:16
Resolution:8
System Status:Good
File Location:C:\Program Files\Agilent\MicroLab PC\Results\A1_3-6-2023T8-21-21 PM.a2r

Method Name:Transmittance
User:Admin
Date/Time:2023-03-06T20:21:21.146-08:00
Range:4000 - 650
Apodization:Happ-Genzel

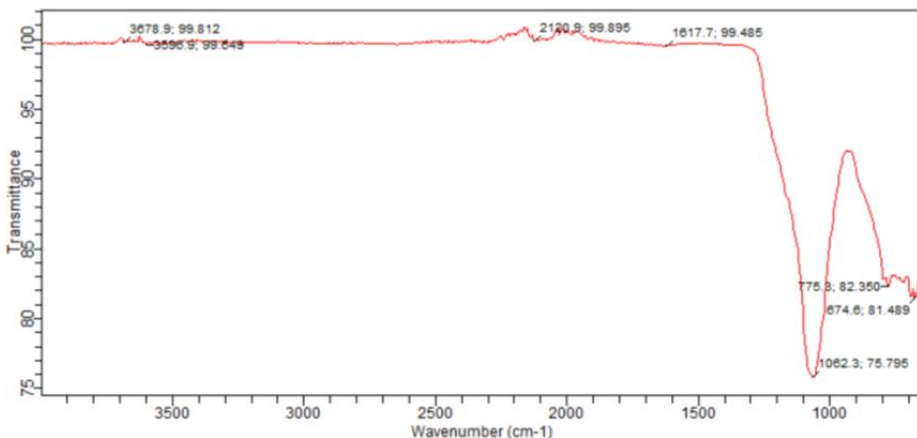


Figure 4: FTIR of calcined kaolin clay



Sample ID:2
Sample Scans:30
Background Scans:16
Resolution:8
System Status:Good
File Location:C:\Program Files\Agilent\MicroLab PC\Results\2_5-9-2023T9-33-15 AM.a2r

Method Name:Transmittance
User:Admin
Date/Time:2023-05-09T09:33:15.262-07:00
Range:4000 - 650
Apodization:Happ-Genzel

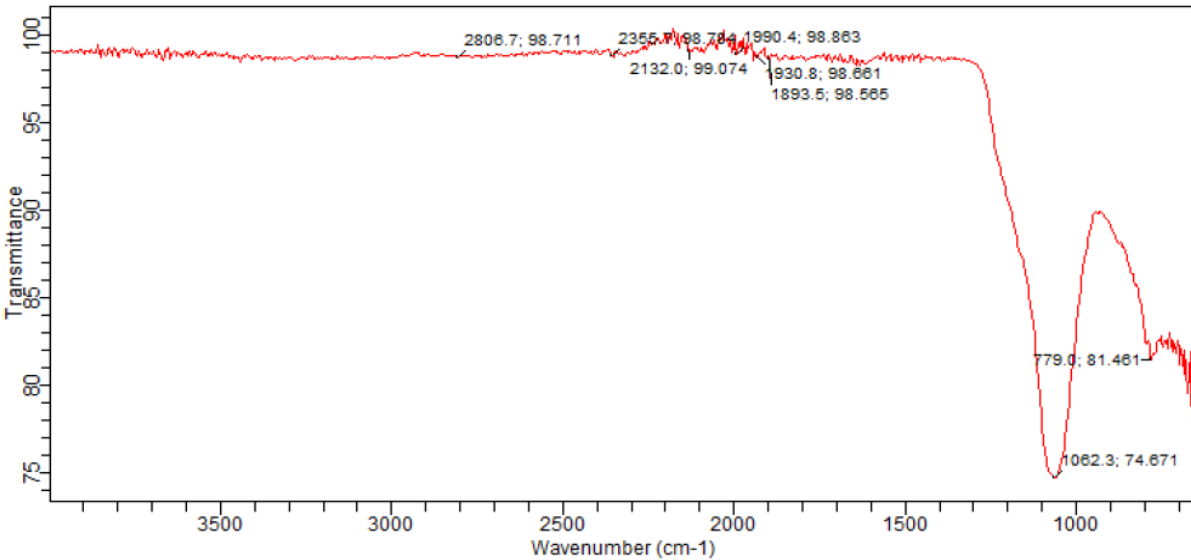


Figure 5: FTIR of Zeolite-Pt-Co composite

High Resolution Transmission Electron Microscopy (HRTEM) of the Calcined zeolite and synthesis zeolite-Pt-Co composite:

High Resolution Transmission Electron Microscopy (HRTEM) was used to characterize the lattice arrangement and crystallinity of the calcined zeolite and synthesis Zeolite-Pt-Co composite structures. The results are as presented in Figure 6 and Figure 7. The results of the Transmission Electron Microscope TEM at 20nm magnification indicated a uniform morphology with particle size range of 8.22nm - 23.80 nm and average particle size of 16.242 nm. Comparatively, the HRTEM result for the synthesized Zeolite Pt-Co composite indicated a particle size range of 3.22 nm -10.27 nm with average particle size of 7.15 nm with

disaggregation crystallites. The TEM monograph of synthesis Zeolite-Pt-Co indicated a smaller particle size Figure 7 compared to calcined zeolite clay Figure 6. The reduction in average particle size of 16.242 nm for calcined zeolite to 7.15 nm in synthesized Zeolite-Pt-Co composite could implies that Pt and Co were successfully impregnated into the synthesized composite. In related study by Bingxue *et al.*,(2022) PtCo/C nanoparticle size was less than 5 nm, showing its high oxygen reduction reaction activity potential. The TEM image of the Zeolite-Pt-Co composite Figure 7 indicates that Co and Pt are evenly distributed on the synthesized zeolite composite. In a related research by Olajire *et al.*, (2017), it was reported that The Pt and Cu nanostructures revealed exceedingly even morphology with sizes range between 1.87 and 2.38 nm and average particles size of 2.12 ± 0.21 nm. Yesmurzayeva *et al.*,(2016) reported a reduced particle size using of 0.235 nm and 0.208 nm using gold and the copper nanoparticle respectively. Platinum (Pt) atoms can function as catalyst for isomerization of hydrocarbons Musselwhite *et al.*,(2013). Also, in similar work by Nandhi and Gajendran (2017). TEM image revealed well-dispersed platinum nanoparticles with a narrow size distribution from 1.6 nm to 2.5 nm. [This section contain material that corresponds to introduction section, for example when the work and results of other authors are cited.](#)

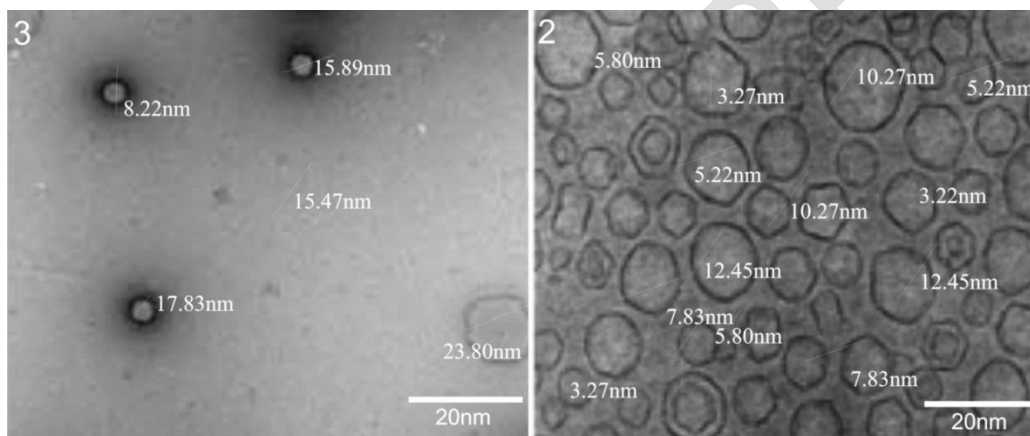


Figure 6: TEM monograph of Calcined kaolin

Figure 7: TEM monograph of Zeolite-Pt-Co

composite

The result of the XRF analysis of the calcined kaolin revealed SiO_2 (63.001 %), Al_2O_3 (31.017 %), K_2O (2.163 %), TiO_2 (2.220 %) and Fe_2O_3 (1.850) as major chemical compositions with 1.850 %, 2.220 %, 2.163 % of Fe_2O_3 , TiO_2 , K_2O as trace impurities. In a related work by Abiodun *et al.*, (2023), 48.62 % SiO_2 , 31.45% Al_2O_3 and 4.08 Fe_2O_3 were recorded in a metakaolin at 500 °C . Percentages of the major individual element present in calcined clay were oxygen 49.250, aluminium 15.956 and silicon 28.314 % Table 1. Comparatively, the XRF analysis recorded SiO_2 (63.001%), Al_2O_3 (31.017%), PtO_2 (6.011%), with trace amount of Cr_2O_3 , (0.770%), Co_3O_4 (0.002%), Fe_2O_3 (0.770 %), V_2O_5 (0.106%). The concentrations of individual elements in the synthesized Zeolite-Pt-Co composite were Zn (11.134 %). Fe(34.158), Sb (4.571%), Si (30.280%), Al (18.010%), Pt (29.674 %), O (37.000 %), S (1.015), K (1.267%) and Co (32.834 %) respectively. Table1. The result of XRF together with XRD and FTIR indicated that Pt and Co were successfully impregnated in the synthesis Zeolite-Pt-Co composite Table 1,

Figures 2 and 3. In related research, Shilina *et al.*, (2023) deposited ~~Pt~~ and Co Pt-Co/ZSM-5 Catalysts using laser electrodispersion on Co-modified ZSM-5 prepared by the $\text{Co}(\text{CH}_3\text{COO})_2$ impregnation.

Table 1: XRF results of calcined and Zeolite-Pt-Co composite

Calcined Kaolin		Zeolite-Pt-Co Composite	
components	concentrations	Components	Concentrations
SiO ₂	63.001	SiO ₂	63.001
V ₂ O ₅	0.106	V ₂ O ₅	0.106
Cr ₂ O ₃	0.069	Cr ₂ O ₃	0.069
MnO	0.013	MnO	0.013
Fe ₂ O ₃	1.850	Fe ₂ O ₃	0.770
Co ₃ O ₄	0.005	Co ₃ O ₄	0.002
NiO	0.007	NiO	0.007
CuO	0.028	CuO	0.028
Nb ₂ O ₃	0.010	Sn	11.134
MoO ₃	0.002	Fe	34.158
WO ₃	0.000	Sb	4.571
P ₂ O ₅	0.000	Mn	ND
SO ₃	0.198	Ni	ND
CaO	0.336	Co	32.834
MgO	0.000	Cr	34.158
K ₂ O	2.163	Pt	29.674
BaO	0.113	Al ₂ O ₃	31.017
Al ₂ O ₃	31.017	PtO	6.011
Ta ₂ O ₅	0.027	Cl	1.000
TiO ₂	2.220	Si	30.280
ZnO	0.010	Al	18.010
Ag ₂ O	0.007	O	37.000
Cl	0.686	Mg	0.012
ZrO ₂	0.131	S	1.015
SnO ₂	0.000	K	1.267
O	49.250		
Al	15.956		
Si	28.314		

CONCLUSION

Synthesis and characterization of di-metallic zeolite Pt-Co composite was carried out via Hydrothermal Treatment, Acid leaching of Mesoporous-kaolin and Calcination of the acidified mesoporous –kaolin. The Pt and Co metals were impregnated into the zeolite matrix through reduction of $\text{H}_2\text{PtCl}_6 \cdot 6\text{H}_2\text{O}$ and $\text{Co}(\text{CH}_3\text{COO})_2$ at 550oC for 6 hrs using (NaBH_4) as reductant with Polyvinylpyrrolidone (PVP) as stabilizer. The results of FTIR indicated absorption bands

range of 1062.3-74.671 cm^{-1} attributed to tetrahedral stretches for AlO_3 and SiO . A peak at 779.0 cm^{-1} stretches assigned to Pt and 650 cm^{-1} due to Co. This may confirm the impregnation of -Co and Pt- into the synthesis Zeolite-Pt-Co composite. Muscovite and quartz interlocking might remain at 1031-1038 cm^{-1} . The XRD analysis indicated 35% sanidine $((\text{K,Na})(\text{Si,Al})_4\text{O}_8)$ 27% quartz (SiO_2), 24 % Orthoclas (KAlSi_3O_8), 8% Albite ($\text{NaAlSi}_3\text{O}_8$) and 6.3% Muscovite ($\text{KAl}_2(\text{Si}_3\text{Al})\text{O}_{10}(\text{OH})_2$) with sharp peaks of quartz at $20.8^\circ 2\theta$, implying crystalline. The results of the Transmission Electron Microscope TEM at 20nm magnification indicated a uniform morphology with particle size range of 8.22nm - 23.80 nm and average particle size of 16.242 nm. HRTEM result for the synthesized Zeolite Pt-Co composite indicated a particle size range of 3.22 nm -10.27 nm with average particle size of 7.15 nm of disaggregation crystallites morphology. Also, TEM monograph of synthesis Zeolite-Pt-Co indicated a reduced even particle size compared to calcined zeolite clay. Pt enhances isomerization of straight run gasoline with consequent increase in octane number of gasoline while Co aids in hydrosulphurisation. [This paper is a technical report where the experimental results are described by I do not see generation of scientific knowledge.](#)

References

- Abiodun, Y.O ;Orisaleye, J.I. and Adeosun, S.O. (2023).** Effect of Calcination Temperatures of Kaolin on Compressive and Flexural Strengths of Metakaolin-Concrete . Nigerian Journal of Technological Development, 20 (1): 33-43.
- Anbia, M.; Kargosha, K. and Khoshbooei, S. (2015).** Heavy metal ions removal from aqueous media by modified magnetic mesoporous silica MCM-48. Chem Eng Res Des. 93:779–88.
- Abubakar, S. Y.; Alhassan, M.; Lawal, I S.; Shehu, Y. and Muhammad H. (2023).** Studies of neat kaolin and cobalt (iii) oxide doped kaolin for Heterogeneous Catalysts Development Using Fourier Transform Infrared Spectroscopy. Science World Journal 18(1), 1597-6343
- Bingxue, H.; Xinlei, L.; Ziheng Zheng, R. T.; Qi Zhang, M. G.; Chengcheng, W.; and Zanxiong T. (2022).** An Efficient Electrocatalyst (PtCo/C) for the Oxygen Reduction Reaction, Catalyst12 (794). [https:// doi.org/10.3390/catal12070794](https://doi.org/10.3390/catal12070794)
- Bhaskar J. S. and Gopalakrishnarao, P.(2010).**Fourier Transform Infrared Spectroscopic Characterization of Kaolinite from Assam and Meghalaya, Northeastern India. J. Mod. Phys. 1: 206-210
- Eurov, D.A.; Rostovshchikova, T.N.; Shilina, M.I.; Kirilenko, D.A.; Tomkovich, M.V.; Yagovkina, M.A.; Udalova, O.V.; Kaplin, I.Y.; Ivanin, I.A. and Kurdyukov, D.A. (2022).**Cobalt oxide decorated porous silica particle Structure and activity relationship in the catalytic oxidation of carbon monoxide. Appl. Surf. Sci. 579 (152121).

Ezra, A.; Zaccheus.; Shehub, D.; Wilson, L.; Kennedy, P.; Yoriyoa, R. K. and Nsor, C.A.(2021). Novel developments of ZnO/SiO₂ nanocomposite: a nanotechnological approach towards insect vector control. *J. Nig. Soc. Phys. Sci.* 3, 262–266

Peng, R.; Wu, C.M.; Baltrusaitis, J.; Dimitrijevic, N.M.; Rajh, T. and Koodali, R.T. (2016). Solar hydrogen generation over CdS incorporated in Ti-MCM-48 mesoporous materials under visible light illumination. *Int J Hydrogen Energy.* 41(7):4106–19.

Ghaderi, Z.; Peyrovi, M. H. and Parsafard, N. (2021). n-Heptane isomerization activities of Pt catalyst supported on micro/mesoporous composites. *BMC Chemistry*, 15(61): 1-8.

Musselwhite, N.; Alayoglu, S. and Melae, G. (2013). Isomerization of n-Hexane Catalyzed by Supported Monodisperse PtRh Bimetallic Nanoparticles. *Catal Lett* 143: 907–911
<https://doi.org/10.1007/s10562-013-1068-5>

Yesmurzayeva, N.; Tursunova, R.; Nakypova, S.; Selenova B. and Kudaibergenov S. (2016). Synthesis and Characterization of Catalysts Based on Bimetallic Nanoparticles 6th International Conference on Nanomaterials: Applications and Properties (NAP) 1-4.

Prabhu, N Gajendran, T. (2017). Green Synthesis of Noble Metal of Platinum Nanoparticles from *Ocimum sanctum* (Tulsi) Plant- Extracts. *IOSR Journal of Biotechnology and Biochemistry*, 3(1): 107-112.

Olajire, A. A.; Kareem, A. and Olaleke, V (2017). Green synthesis of bimetallic Pt-Cu nanostructures for catalytic oxidative desulfurization of model oil. *J Nanostruct Chem*, 7:159–170.

Shilina, M.; Krotova, I.; Nikolaev, S.; Gurevich, S.; Yavsin, D.; Udalova, O. and Rostovshchikova, T. (2023). Highly Effective Pt-Co/ZSM-5 Catalysts with Low Pt Loading for Preferential Co Oxidation in H₂-Rich Mixture. *Hydrogen* 4, 154–173. <https://doi.org/10.3390/hydrogen4010011>

Thi, K. L. N.; Ngoc, D. N.; Van, P. D.; Dinh, T. P.; Thai, H. T. and Quoc, H. N. (2019). Synthesis of Platinum Nanoparticles by Gamma Co-60 Ray Irradiation Method Using Chitosan as Stabilizer. *Advances in Materials Science and Engineering*, 2019:1-5
<https://doi.org/10.1155/2019/9624374>

Palanivel, S. and Natarajan, S.(2012). Cobalt Recovery from Waste Catalysts (Petroleum Refining Industry from Gujarat) *Open Journal of Metal*, 2: 24-30 [DOI:10.4236/ojmetal.2012.21004](https://doi.org/10.4236/ojmetal.2012.21004)

Udo,G.J.;Awaka-Ama, J.J.;Nyong, A.E.; Ekanem, A.N. and Igwe, R.C. (2023).GC-MS Analysis of Artisanal Refined and Regular Automotive Gasoline: Comparative Study of Quality. International Journal of Novel Research and Development. 8(1): 2456-4184

Udo,G.J.;Awaka-Ama, J.J.;Uwanta, E.J.; Ekwere, I.O.; and Chibueze, I.R. (2020).Comparative Analyses of Physicochemical Properties of Artisanal Refined Gasoline and Regular Automotive Gasoline.Front. Chem. 8:753. doi: 10.3389/fchem.2020.00753

Udo, G. J.; Etteson, U.M.; Awaka-Ama J.J.,Nyong, A.E. and Uwanta, E.J. Uwanta (2020). GCMS and FTIR Spectroscopy Characterization of Luffa Cylindrica Seed Oil and Biodiesel Produced from the oil. Communication in Physical Sciences 2020, 5(3): 378-390

Yusuf, E.O; Efevbokhan, V. E. and Babalola,R. (2019). Development and Characterization of Zeolite-A from Elefun Kaolin Journal of Physics: Conference Series 1378,1-8 doi:10.1088/1742-6596/1378/3/032016

UNDER PEER REVIEW