

EFFECTS OF CALCINATION TEMPERATURE ON THE PHYSICOCHEMICAL BEHAVIOUR OF CATALYSTS PRODUCED FROM EGG SHELL AND RICE HUSK

ABSTRACT

The production, security, sustainability, and affordability of energy are crucial factors in various industries and physical and chemical processes. To address environmental concerns and promote energy production, solid waste materials can serve as catalysts. This research specifically investigates the influence of different calcination temperatures on the properties of two solid wastes, namely Eggshell and Rice husk, as heterogeneous catalysts in Biodiesel production. The results of the study revealed notable changes in various properties such as color, mass, chemical transformation, crystallinity, and functional groups as the calcination temperatures increased for both raw materials. X-ray diffractometer (XRD) analysis was used to characterize the calcined Eggshells and Rice husks. It was observed that increasing the calcination temperature from 600 °C to 700 °C led to enhanced crystallinity, with the highest average crystal size being 278.0374 nm, and chemical transformation in the eggshells. Conversely, the Rice husks exhibited decreased crystallinity (274.793 nm to 16.723 nm) but increased chemical transformation with higher calcination temperatures increasing from 600 °C to 800 °C. The presence of a small amount of K₂O in the calcined Rice husk was attributed to leaching with HCl after roasting and quenching before calcination. Furthermore, the Fourier Transform Infrared Spectroscopy (FT-IR) analysis indicated the formation of desirable functional peaks with increasing calcination temperatures in both materials. Additionally, the presence of CO₃²⁻ was observed in KA and KB due to the incomplete decomposition of CaCO₃. Notably, the highest formation of CaO occurred at 700°C for Eggshell, while the Rice husk calcined at 800°C exhibited the highest formation of silicon (IV) oxide and lower impurity content (lignin, cellulose, and hemicellulose). Overall, this research provides valuable insights into the effects of calcination temperatures on the properties of Eggshell and Rice husk as catalysts for Biodiesel production. The findings highlight the potential of utilizing solid waste materials as catalysts for energy production while also considering the optimization of calcination temperatures to enhance their performance.

Keywords: *Characterization, physicochemical, chemical transformation, calcination temperature.*

INTRODUCTION

Energy is widely recognized as a fundamental factor in economic growth and essential for various aspects of human life, including sustainable industrial development, transportation, and electricity generation. However, the depletion of fossil fuel reserves, coupled with environmental concerns and high costs associated with fossil fuel combustion, has highlighted the need for alternative energy sources. One promising alternative is biofuels, such as biodiesel (Olutoye et al., 2016). To address potential fuel crises, high costs, and environmental challenges linked to fossil fuels, the search for environmentally friendly energy substitutes is essential. One potential source of such substitutes is biofuels, with biodiesel being a particularly promising option (Olutoye et al., 2016). Among the abundant

solid waste materials generated daily, eggshells have emerged as a potential resource with economic value. Instead of incurring costly disposal methods, eggshells can be economically transformed into valuable products. Eggshell waste can serve as a solid base catalyst in biodiesel production, leading to reduced pollutants, lower production costs, and environmentally friendly processes. Eggshells contain bioactive chemicals, primarily calcium carbonate (CaCO_3), magnesium carbonate (MgCO_3), and calcium phosphate ($\text{Ca}_3(\text{PO}_4)_2$). They also contain trace amounts of other elements like sodium (Na^+), potassium (K^+), zinc (Zn^{2+}), manganese (Mn^{2+}), iron ($\text{Fe}^{2+}/\text{Fe}^{3+}$), and copper (Cu^{2+}). Furthermore, eggshells can be used as absorbents for heavy metals in wastewater treatment and as biomaterials for bone tissue replacement (Faridi and Arabhosseini, 2018). Rice husk, another abundant waste product, has significant potential as a biomass source for various applications. It contains chemical compositions such as silicon oxide (SiO_2), aluminum oxide (Al_2O_3), ferric oxide (Fe_2O_3), calcium oxide (CaO), magnesium oxide (MgO), sodium oxide (Na_2O), potassium oxide (K_2O), manganese oxide (MnO_2), and sulfur trioxide (SO_3) (Abdullahi et al., 2018). Extracting silica from rice husk and producing value-added silicon-based compounds is one of the potential uses. Currently, a substantial amount of rice husk is burned for energy generation, leading to the production of rice husk ash. However, only a small portion of rice husk is utilized for silica extraction. Transforming rice husk into a heterogeneous catalyst for biofuel production has gained attention in research. Catalysts play a vital role in various reactions, making research on their application essential. In the context of biodiesel production, base catalysts have shown superior performance compared to acid catalysts, particularly in alkaline catalysis. Heterogeneous catalysis, which involves solid surfaces facilitating chemical interactions between molecules, offers advantages over homogeneous catalysis in terms of regeneration, activity, selectivity, and ease of separation from reactants. Metal oxide catalysts like CaO , SiO_2 , and MgO are commonly employed in reactions (Mohadi et al., 2016). The use of solid-based catalysts, particularly in renewable energy industries, has gained attention as a means to reduce reliance on fossil fuels and meet increasing energy demands. Heterogeneous catalysts offer advantages such as easy

separation, catalyst recycling, reduced energy requirements, and lower water consumption, contributing to a reduction in biodiesel production costs and addressing corrosion and toxicity challenges (Faruque et al., 2020; Mat.R et al., 2012). The need for environmentally friendly and renewable energy sources is driven by rising petroleum prices, population growth, and environmental concerns. Biodiesel, derived from mono-alkyl esters of long-chain fatty acids found in vegetable oils or animal fats, offers a viable solution. It aligns with renewable energy objectives and can be used as a drop-in biofuel in existing diesel engines and infrastructure (Chakraborty et al., 2010; Gerhard, 2010).

2.0 MATERIALS AND METHODS

2.1 Experimental Method

This shall involve Pretreatment of Samples, Size Reduction, Rice Husk Ash (RHA) formation, Calcination of the Eggshell and Rice Husk (RH) and Characterization of the calcined Materials.

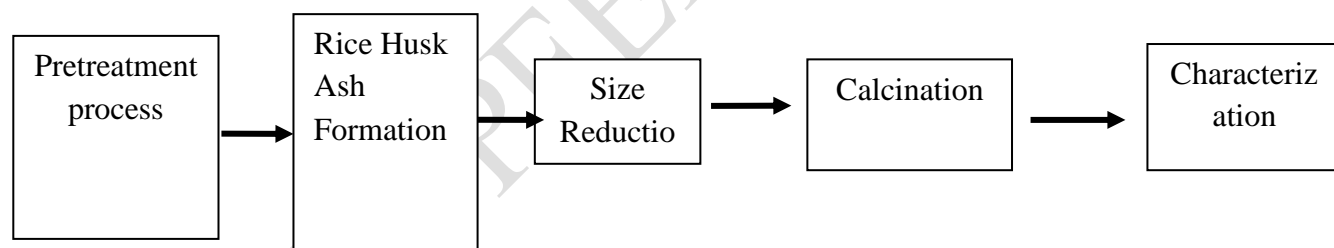


Fig 1: Flowchart of the Synthesis of Eggshell Rice Husk Ash Catalyst

2.1.1 PRETREATMENT AND CALCINATION OF SAMPLES

2.1.1.1 Rice Husk

Rice Husk was obtained from a rice milling factory and underwent a cleaning process using distilled water to eliminate soil particles and impurities. It was then naturally dried in sunlight and stored in an airtight container (Andrea et al., 2023). Subsequently, 450g of the cleaned rice husk (RH) was roasted in a heating pot on a heat plate. The resulting roasted rice husk was then quenched in room temperature distilled water and separated from the water through

filtration. The roasted and quenched rice husk was subjected to leaching. This involved immersing 300g of the roasted and quenched rice husk in 900ml of diluted hydrochloric acid (HCl) for a duration of 3 hours. The mixture was filtered using filter paper and washed three times with distilled water. Finally, the residue was dried at 100 °C for several hours in a controlled air environment and labeled as LRQRH (Leached-Quenched-Roasted Rice Husk). The LRQRH sample was divided into three equal parts, each weighing 80g and labeled as KD, KE, and KF. These divided LRQRH samples were then subjected to calcination in a muffle furnace. The samples were heated to temperatures of 600 °C, 700 °C, and 800 °C, respectively (Bello et al., 2021). Once the desired temperatures were reached, the samples were left inside the furnace to complete the calcination process. Afterward, they were cooled down and stored for characterization (Alhassan et al., 2016).



fig2: roasted rice husk

2.1.1.2 Eggshell

The sample was obtained from a merchant located in Bosso Minna, Niger State, Nigeria. It was washed thoroughly to eliminate any impurities and subsequently dried using sunlight. The dried sample was ground into a powder using an electric grinder and sieved to remove some of the white membrane present. The ground samples were then divided into three equal portions, each weighing 250g. These portions were labeled as KA, KB, and KC, respectively.

They were loaded into ceramic crucibles and subjected to calcination in a furnace at temperatures of 600 °C, 650 °C, and 700 °C, respectively(Iyayosa Andrea et al., 2023). Each crucible was left inside the furnace for a duration of 3 hours after reaching the desired temperature. Following the calcination process, the samples were cooled down, and subsequently stored for further characterization.



fig3washed and dried eggshell



fig4: calcined eggshells

2.2 Characterization of the calcined Eggshell and Rice Husk

The elemental and physical properties of the prepared samples were assessed through analysis methods including Fourier Transform-Infrared Ray (FT-IR) and X-ray Diffraction (XRD) analysis.

2.2.1 X-ray diffraction Analysis for Mineral Identification

The powdered samples were formed into pellets and sieved to a size of 0.074mm. Each sample was subjected to analysis using the Rigaku D/Max-III C X-ray diffractometer, developed by Rigaku Int. Corp. in Tokyo, Japan. The instrument was configured to generate diffractions at a scanning rate of 2 0/min within the 2 to 500 range, at room temperature, using CuK α radiation set at 40kV and 20mA. The obtained diffraction data, including d values and relative intensity, were compared to the standard data of minerals from the mineral powder diffraction file, ICDD.

3.0 RESULT AND DISCUSSION

Table 1. Change in physical properties of the materials used (colour change)

Material Used	Color Change after calcination
Calcined waste eggshell (whitish-brown)	
1. 600 °C	black
2. 650 °C	black-gray
3. 700 °C	gray
Calcined Rice husk (brown)	
1. 600 °C	light-ash
2. 700 °C	black-ash
3. 800 °C	Ash

The eggshells underwent decomposition through calcination in a furnace at various temperatures (600 °C, 650 °C, and 700 °C), resulting in a color change. Table 1 illustrates the observed color changes at different calcination temperatures. At 600 °C, the eggshells transformed into black powder, while a small amount of black-colored ash was produced at

650 °C. Finally, at 700 °C, a significant amount of black powder with a higher ash content was obtained. The results indicate that as the calcination temperature increases, there is a corresponding increase in the formation of metal oxide, as evidenced by the color change in the chicken eggshell powder (Mohadi et al., 2016). Also the calcined rice husks underwent decomposition during the calcination process in a furnace at varying temperatures (600 °C, 700 °C, and 800 °C). The samples exhibited an increasing change in color as the calcination temperature rose, as depicted in table 1. At 600 °C, the rice husks resulted in a light ash powder, while a black-ash colored powder was obtained at 700 °C. Finally, at 800 °C, an ash-colored powder was obtained. The results indicate that as the calcination temperature increases, there is an increased formation of metal oxide, as evidenced by the color change in the rice husk powder (Sekifuji et al., 2021).

3.1 Loss in mass of the raw materials used.

Table 2. Loss in mass of the raw materials used.

S/N	Material Used	Calcination temp °C	Mass loss after calcination			
			Initial mass(g)	Final mass(g)	Mass loss(g)	% loss
1.	Eggshell	1) 600 °C	250	188.25	61.75	24.7%
		2) 650 °C	250	171.75	78.25	31.3%
		3) 700 °C	250	160.75	89.25	35.7%
2.	Rice husk	1) 600 °C	80	19.84	60.16	75.2%
		2) 700 °C	80	12.32	67.68	84.6%
		3) 800 °C	80	8.56	71.44	89.3%

Table 2. shows that there was loss in masses of calcined eggshells rice husks during each calcination due to thermal decomposition of CaCO_3 to CaO and Ca(OH)_2 , which is as a result of loss in CO_2 and other impurities, and loss of some volatile materials in Rice husk increases as calcination temperature increases and decomposition of Ca_2SiO_4 to SiO_4 When

calcined Rice husk at different calcination temperatures from 600 °C to 700 °C to 800 °C. As shown in table 2. 24.7% was loss when Eggshell was calcined at 600 °C, at 650 °C there was 31.3% loss in mass of Eggshell and highest loss in mass of eggshell at 700 °C of about 35.7%. RH loss its mass up to 75.2% by weight at 600 °C, and loss its mass up to 84.6% at 700 °C while at 800 °C there was mass loss up to 89.3% as shown in Table 2. due to presence of physically absorbed moisture and water content in the RH, the removal of organic group by oxidation reaction and the decomposition of hemicellulose and cellulose followed by total decomposition of lignin.

3.2 Characterization of the Calcined Eggshells and Rice husks

The samples produced were characterized to know the chemical transformation, crystallinity and functional groups presence X-ray diffractometer and FT-IR Spectrometer respectively.

3.2.1 X-ray diffraction

Samples were analyzed using Cu- K source equipped with an Inel CPS 120 hemispherical detector (RigakuD/Max-IIIC Co., Japan). at scanning rate of 2°/min in the 10° to 55°

3.2.1.1 calcined eggshell

X-ray diffraction is a non-destructive analytical technique which reveals information about crystallographic structure. This technique is widely used in the characterization of shell. The XRD patterns for calcined eggshells.

3.2.1.1.1 KA (eggshell calcined at 600 °C)

Sample	: K-A	File	: Sg2~1.ASC	Date	: Feb 16 9:50:10	Operator	:
Comment	: Qualitative	Memo					
Method	: 2nd differential	Typical width	: 0.065 deg.	Min. Height		2800:00 c p s	

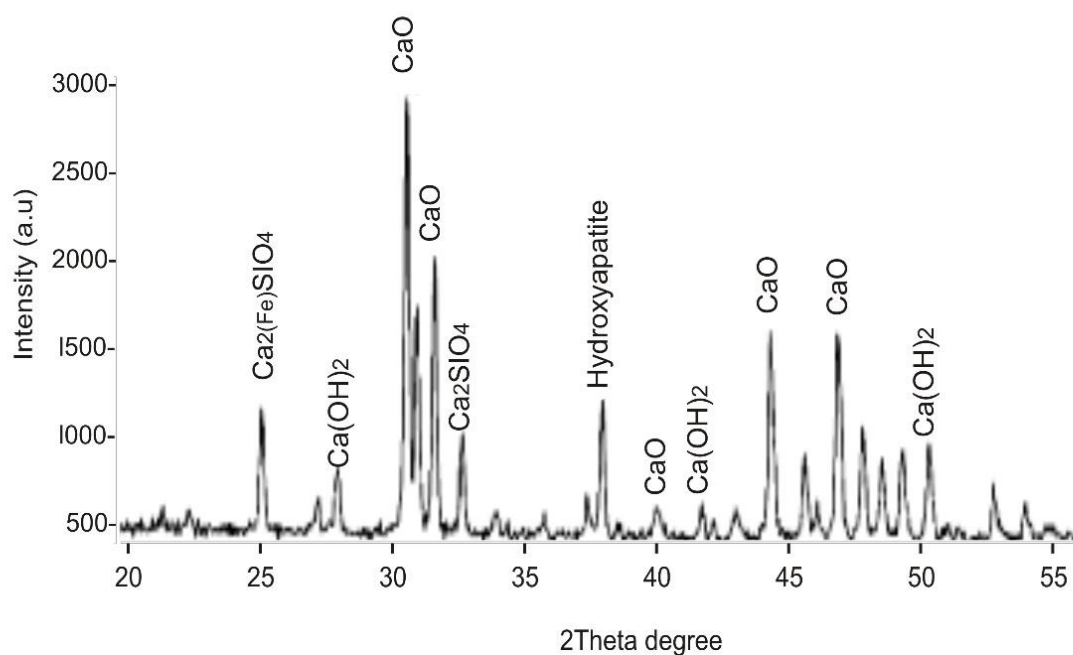


fig 5. Eggshell Calcined at 600 °C (KA)

Fig5 showed the highest peak is at $2\theta = 30^\circ$ shows presence of CaO as crystalline form, there are more CaO at $2\theta = 31^\circ, 40^\circ, 44^\circ$ and 47° at difference phases. There is presence of Ca(OH)_2 at $2\theta = 28^\circ, 42^\circ$ and 50° as a result of moisture content of the calcined sample. $\text{Ca}_2(\text{Fe})\text{SiO}_4$ exists at $2\theta = 25^\circ$ shows incomplete decomposition of the eggshell while hydroxyapatite occurs at $2\theta = 37.5^\circ$ (Pornchaiet *al.*, 2016).

3.2.1.1.2 KB (eggshell calcined at 650°C)

Sample	: K-B	File	: Sg2~1.ASC	Date	: Feb 16 10:05:30	Operator	:
Comment	: Qualitative	Memo					
Method	: 2nd differential	Typical width	: 0.065 deg.	Min. Height		3200:00 c p s	

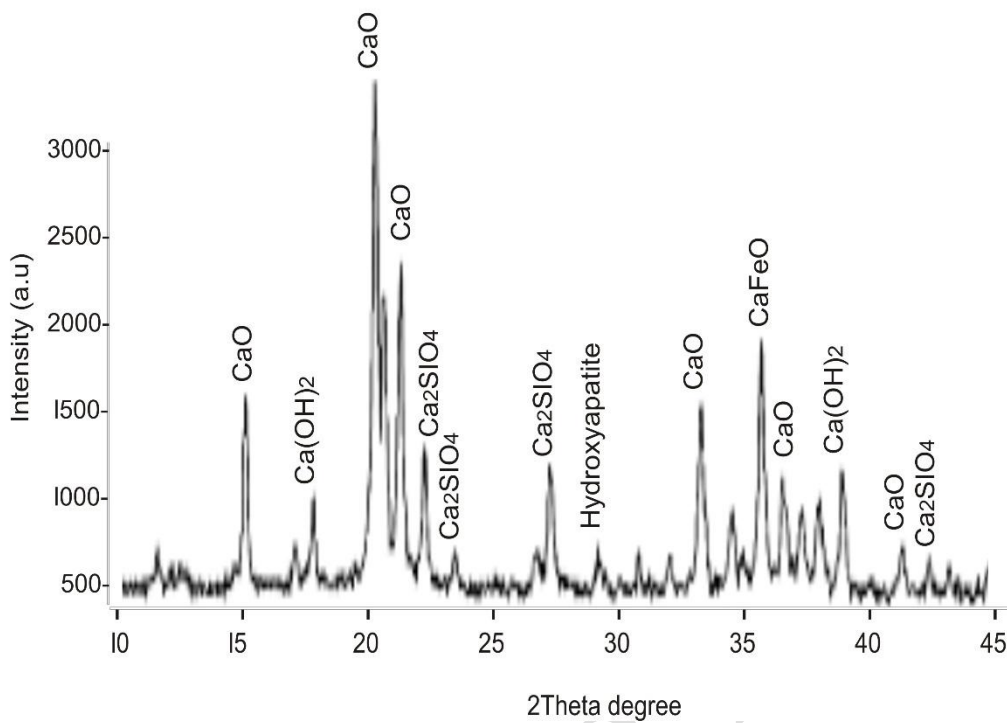


Fig6 Eggshell Calcined at 650 °C (KB)

Fig6 showed the highest peak is at $2\theta = 22^\circ$ shows presence of CaO being most abundance in a crystalline form, there are more formation of as compared to KA, other formation of CaO at $2\theta = 15^\circ, 22^\circ, 34^\circ, 37^\circ$ and 42° at difference phases.

There is presence of Ca(OH)_2 at $2\theta = 17^\circ, 44^\circ$ and 39° where the amount is small as in KA.

$\text{Ca}_2(\text{Fe})\text{SiO}_4$ has decomposed to Ca_2SiO_4 at $2\theta = 22^\circ, 24^\circ, 27^\circ$ and 42° .

there is small amount of hydroxylapatite at $2\theta = 30^\circ$ (Pornchaiet *al.*, 2016).

3.2.1.1.2 KC (Eggshell Calcined at 700°C)

Sample	: K-C	File	: Sg2~1.ASC	Date	: Feb 16 10:10:40	Operator	:
Comment	: Qualitative	Memo					
Method	: 2nd differential	Typical width	: 0.065 deg.	Min. Height		3000:00 c p s	

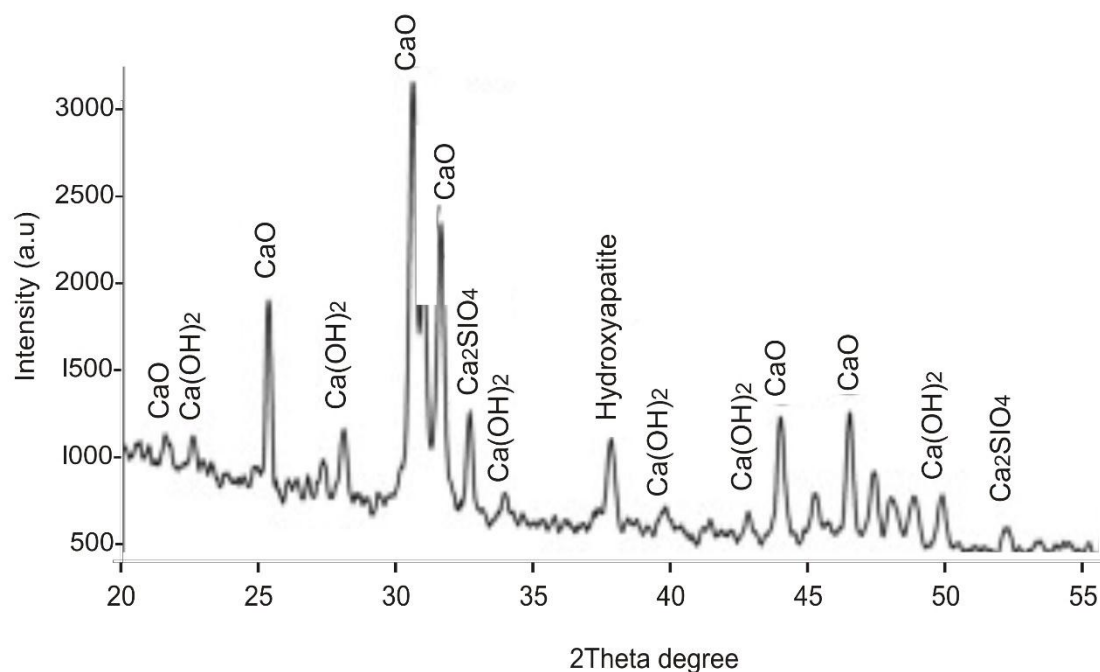


Fig7 Eggshell Calcined at 700 °C (KC)

Fig7 showed the highest peak is at $2\theta = 32^\circ$ with strong crystalline nature as sharp the band shows presence of CaO being most abundance, there are more formation of CaO as compared to KA and KC, other formation of CaO at $2\theta = 26^\circ, 32^\circ$ in small quantity and at $2\theta = 44^\circ, 47^\circ$ and 42° at amorphous-like indicated that the sample is getting from crystalline to amorphous.

There is presence of $\text{Ca}(\text{OH})_2$ at $2\theta = 28^\circ, 34^\circ, 40^\circ$ and 50° in small amount as a result of decreased in moisture content as temperature increased where.. $\text{Ca}_2(\text{Fe})\text{SiO}_4$ has decomposed to Ca_2SiO_4 at $2\theta = 33^\circ$ and 52° there is smaller amount of hydroxylapatite at $2\theta = 38^\circ$ (Mohadiet *al.*, 2016).

3.2.1.2 calcined rice husk

X-ray diffraction is a method of analysis that provides insights into the crystal structure without causing damage. It is extensively employed in the examination of shells to understand their crystallographic arrangement. The XRD patterns for processed rice husks can be obtained using this technique.

3.3.1.2.1 KD (rice husk calcined at 600 °C)

Sample	: K-D	File	: Sg2~1.ASC	Date	: Feb 16 10:23:20	Operator	:
Comment	: Qualitative	Memo					
Method	: 2nd differential	Typical width	: 0.065 deg.	Min. Height		3000:00 c p s	

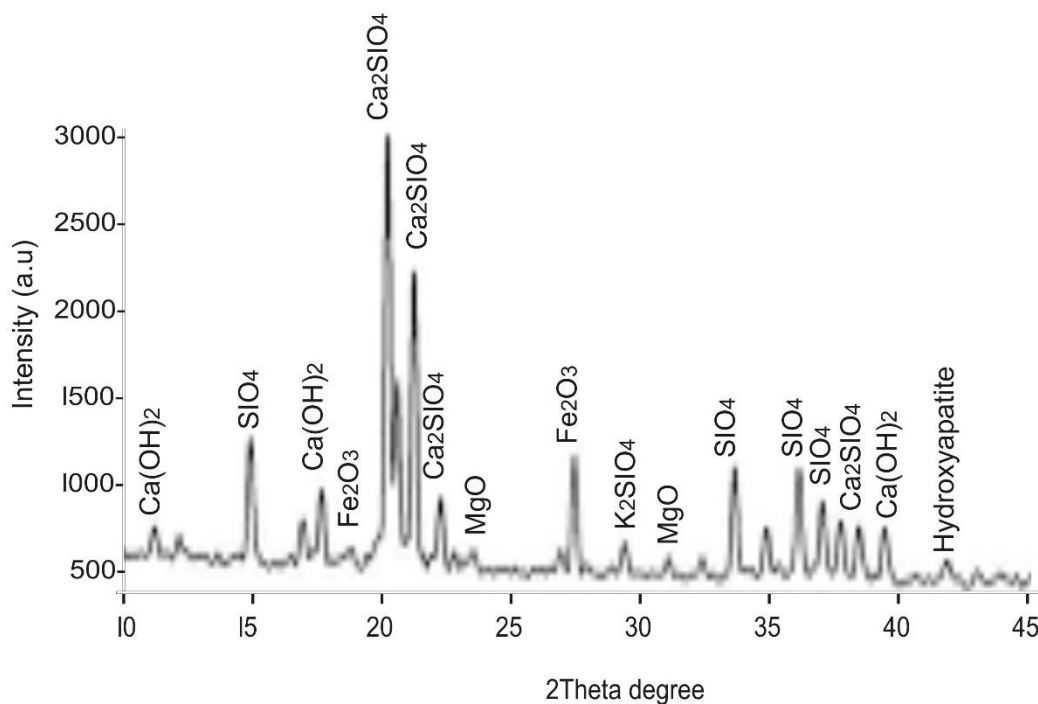


Fig8. Rice Husk Calcined at 600 °C (KD)

The highest peak is at $2\theta = 21^\circ$ being the abundance component shows presence of Ca_2SiO_4 it exists at $2\theta = 22^\circ, 28^\circ$ and 37° and SiO_4 is at $2\theta = 15^\circ, 34^\circ, 36^\circ, 37^\circ$ in small amount.

Ca(OH)_2 occurred in small amount and there is a trace of hydroxylapatite at 42° also trace of MgO and Fe_2O_3 .

4.3.1.2.2 KE (rice husk calcined at 700 °C)

Sample	: K-E	File	: Sg2~1.ASC	Date	: Feb 16 10:35:13	Operator	:
Comment	: Qualitative	Memo					
Method	: 2nd differential	Typical width	: 0.065 deg.	Min. Height		2500:00 c p s	

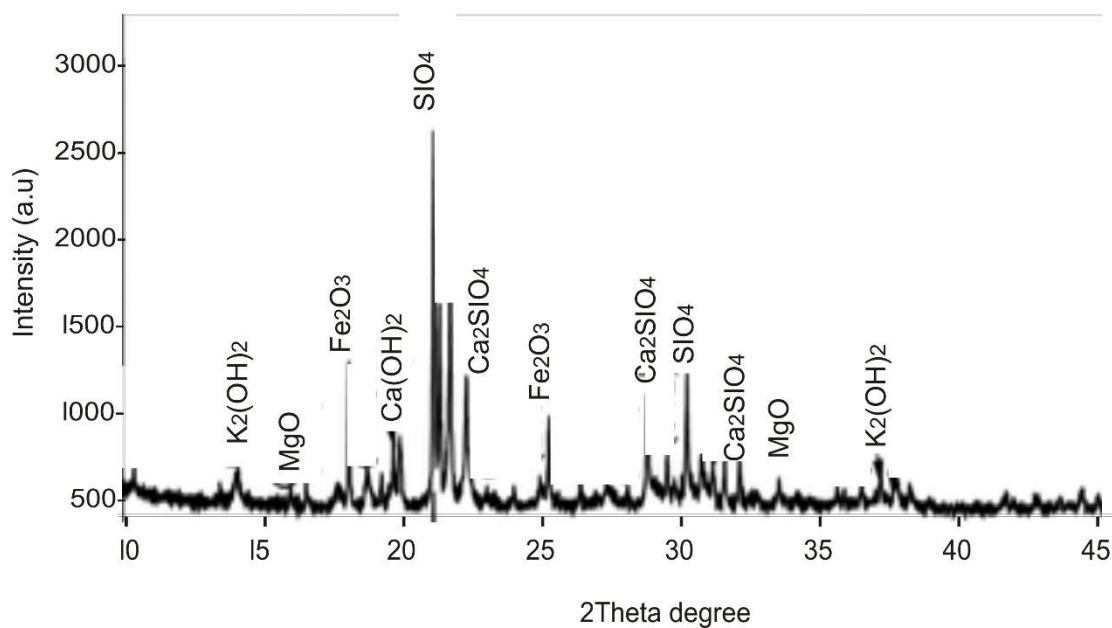


Fig9. Rice Husk Calcined at 700 °C (KE)

The highest peak is at $2\theta = 22^\circ$ and 31° being the abundance component shows presence of SiO_4 in crystalline state. At $2\theta = 22^\circ$, 38° and 37° there is Ca_2SiO_4 formation there is absence of hydroxylapatite, also trace of MgO and Fe_2O_3 .

4.3.1.2.3 KF (rice husk calcined at 800°C)

Sample : K-F **File** : Sg2~1.ASC **Date** : Feb 16 10:42:50 **Operator** :
Comment : Qualitative **Memo**
Method : 2nd differential **Typical width** : 0.065 deg. **Min. Height** **2700:00 c p s**

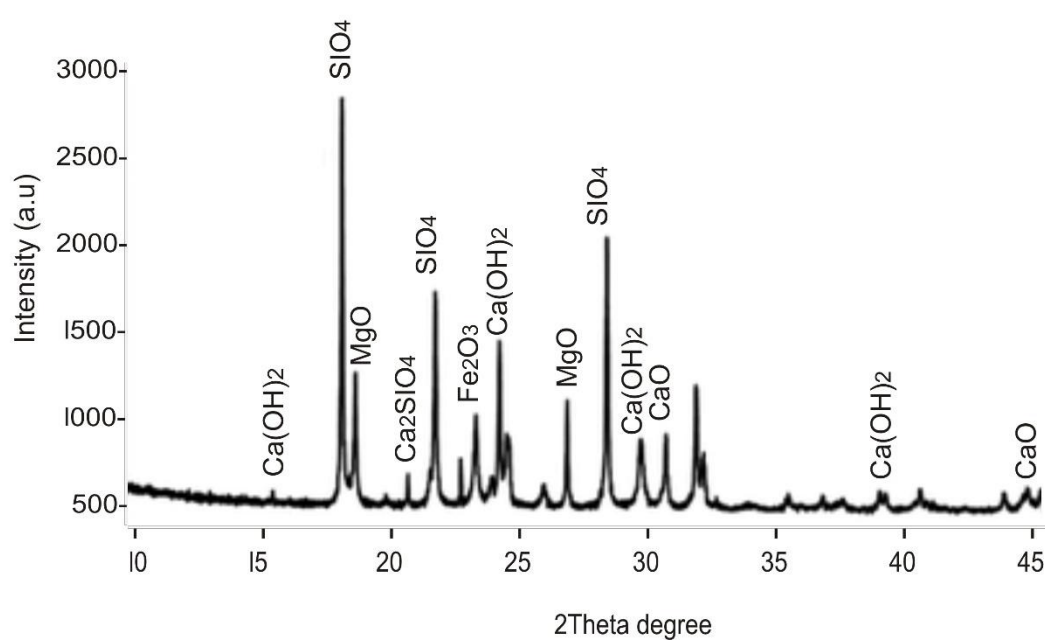


Fig 10. Rice Husk Calcined at 800 °C (KF)

The highest peak is at $2\Theta = 18^\circ$, 22° and 28° showed SiO_4 present in highest composition, Ca_2SiO_4 exists at $2\Theta = 21^\circ$ in small amount due to more decomposition of the sample at this temperature. Ca(OH)_2 occurred in small amount and there is a trace of hydroxylapatite at 24° also trace of MgO , CaO and Fe_2O_3 were observed.

Table 3. Crystallite size (nm) using Scherrer equation

Sample	Average Crystallite size (nm)
KA	177.3967207
KB	274.7932751
KC	278.0374549
KD	274.7932751
KE	238.7086417
KF	16.72281279

An examination of crystallite size changes with increasing temperature using the Scherrer equation reveals that the size of the crystallites in calcined Eggshell increases between 600 °C and 700 °C. Among the samples, KC exhibits the largest crystallite size. On the other hand, the crystallite size of calcined Rice Husk decreases as the calcination temperature rises. Among them, KD, calcined at 600 °C, has the highest crystallite size, while KF exhibits the smallest crystallite size among all the samples.

3.3.2 FT-IR RESULTS

The samples were characterized to know functional groups present using Perkin Elmer Spectrum 100 Series, Nicolet iS10 FT-IR Spectrometer.

3.3.2.1 Eggshell

Eggshell was characterized by FTIR. This technique could be used to identify the major functional groups consisting Calcined eggshell. From the wave number of the molecular vibration modes, a good explanation of the chemical structure could be obtained.

3.3.2.1.1 KA (eggshell calcined at 600 °C)

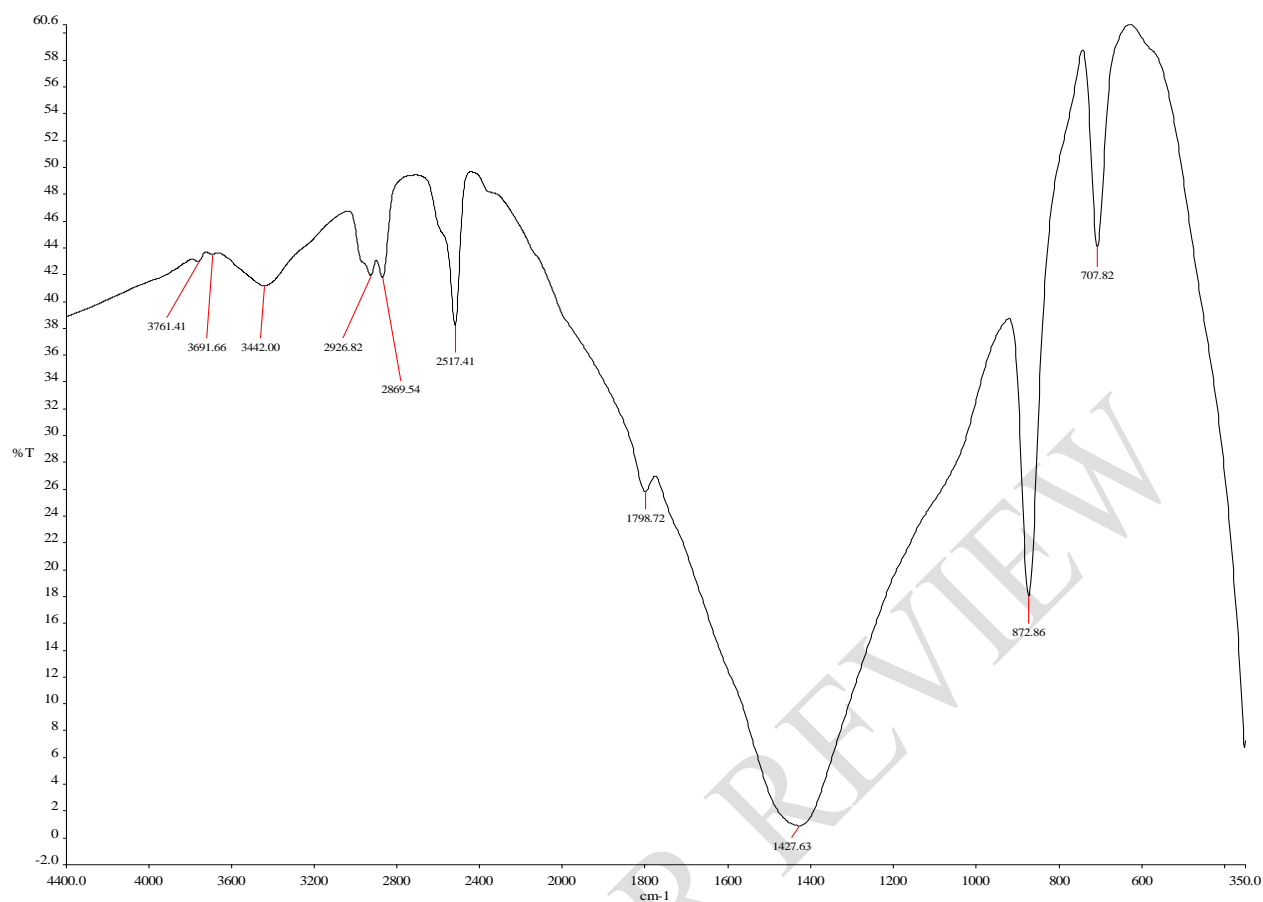


Fig11. Eggshell Calcined at 600 °C (KA)

The highest band is at 707.82 cm^{-1} indicates presence of symmetric stretching vibrations of CO_3^{2-} bond due to presence of CaCO_3 , -OH group presents at 3761.41 cm^{-1} , 3691.66 cm^{-1} and 3442.00 cm^{-1} due to presence of hydroxyapatite, Ca-OH, -OH-Si, and Ca-OH-Si units in the octahedral layer. There was a broad band at 1460 cm^{-1} due to bending vibrations of the Si-O bond and sharp band at 872.86 cm^{-1} due to presence of CaO bond.

3.3.2.1.2 KB (eggshell calcined at 650 °C)

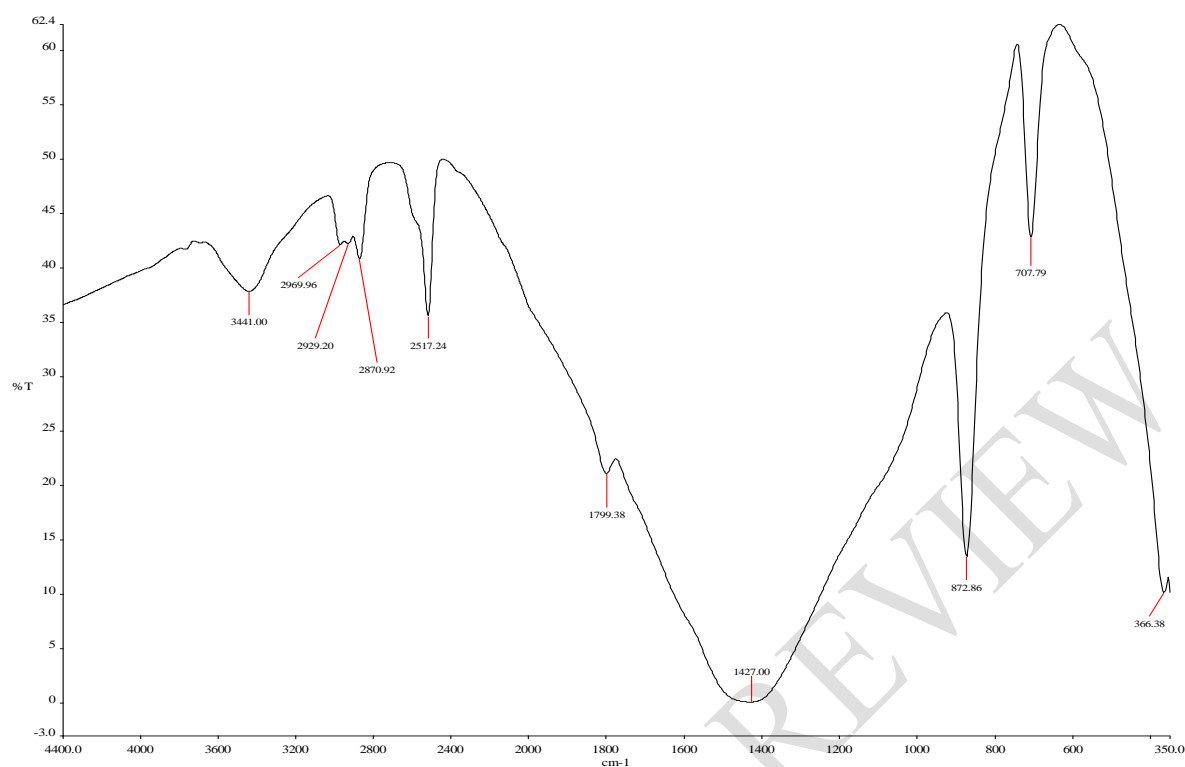


Fig12. Eggshell Calcined at 650 °C (KB)

The highest band is at 707.79 cm^{-1} indicates presence of symmetric stretching vibrations of CO_3^{-2} bond due to presence of CaCO_3 , -OH group presents at 3441.00 cm^{-1} due to presence of Ca(OH)_2 and small hydroxylapatite as compared to KA. There was a broad band at 1427 cm^{-1} due to bending vibrations of the Si-O-Si group and sharp band at 872.86 cm^{-1} due to presence of Ca-O bond.

3.3.2.1.3 KC (eggshell calcined at 700 °C)

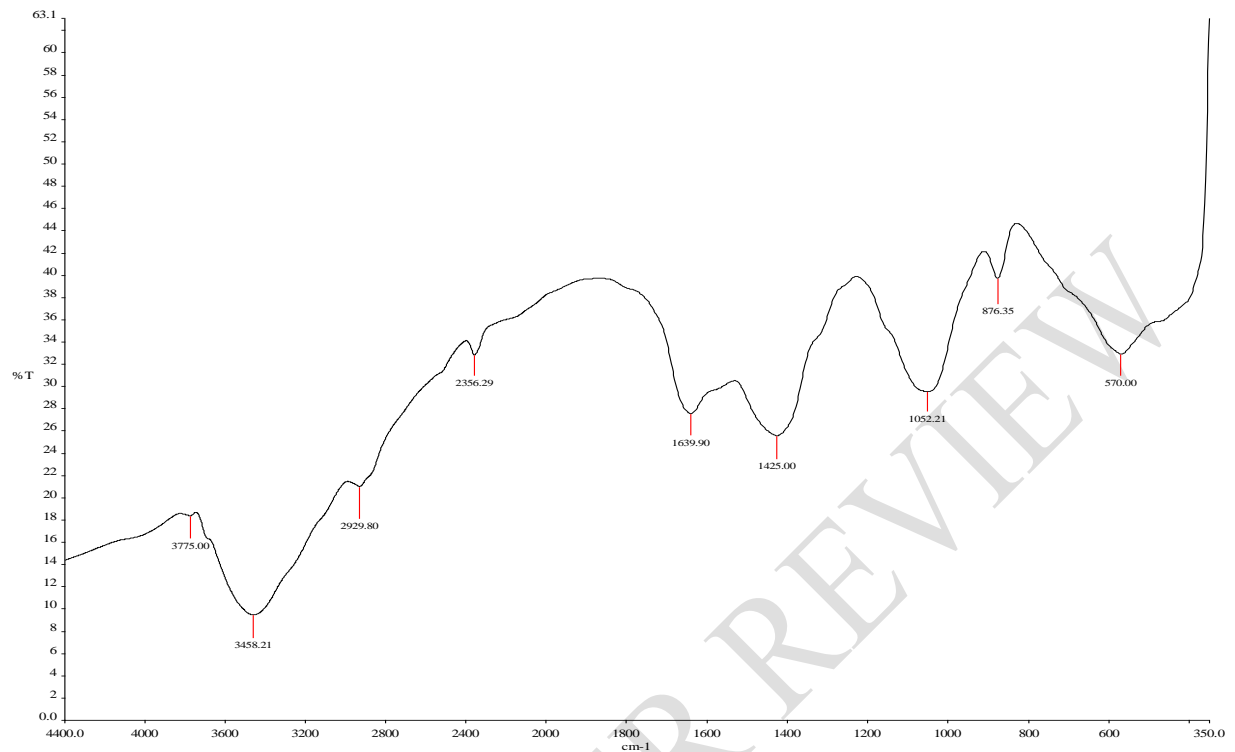


Fig13. Eggshell Calcined at 700 °C (KC)

The characteristic IR band of eggshell appeared at 3775.00 cm^{-1} and 3458.21 cm^{-1} represent the fundamental stretching vibrations of different -OH groups present in Ca-OH , -OH-Si , and Ca-OH-Si units in the octahedral layer (Abdulsalam, Alhaji Yaro, et al., 2023). The strong peak appears at 876.35 cm^{-1} is related to the stretching vibrations of Ca-O , while the bands at 525 and 466 cm^{-1} are due to Ca-O-Si and Ca-O-Ca bending vibrations, respectively. This shows highest formation of CaO (Pornchai et al., 2016).

3.3.2.2 Rice husk

KD, KE and KF consist of mixture of CaO and silicate mineral. SiO_2 are present as dominant mineral in all patterns. Fig.17 shows that the percent of SiO_2 increase significantly after purification process while the percent of CaO in purified eggshell is increased. K-E and K-F shows similar pattern for the calcined eggshell with SiO_2 as the main mineral (Abdulsalam, Ibrahim, et al., 2023).

3.3.2.1.4 KD (rice husk calcined at 600 °C)

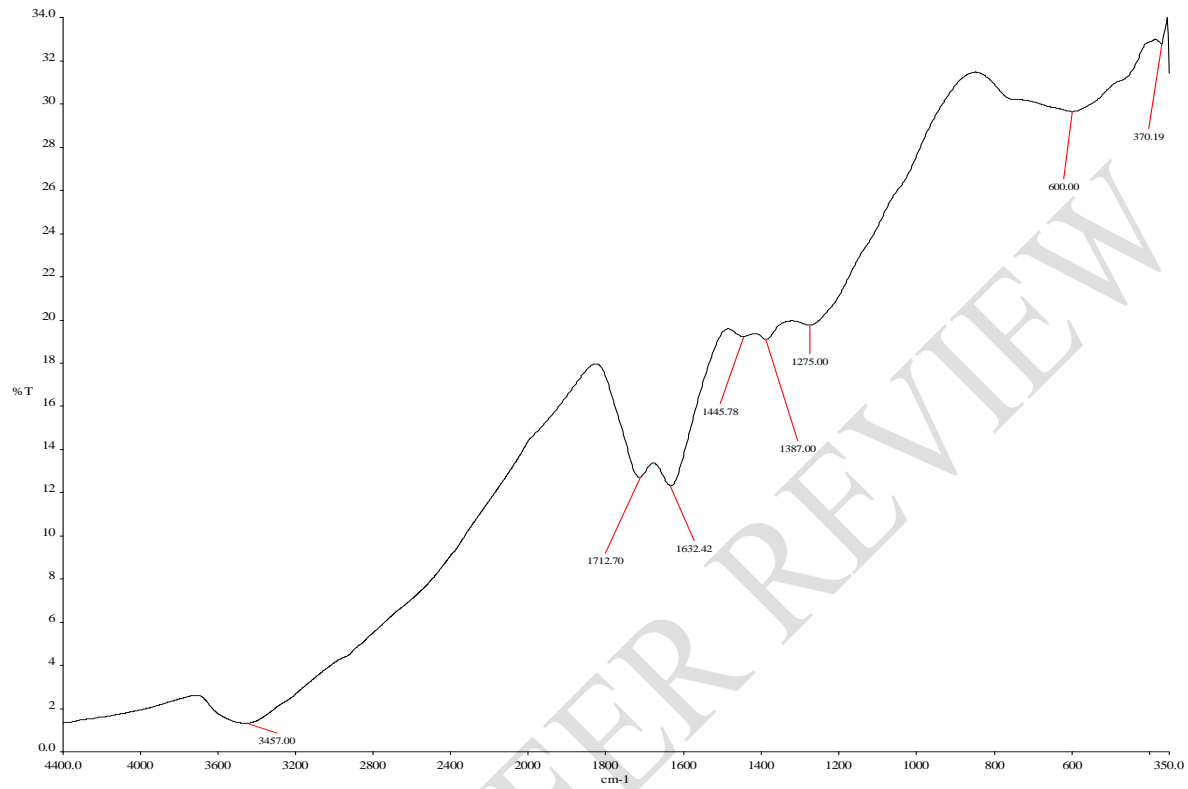


Fig14. Rice Husk Calcined at 600 °C (KD)

There is -OH group at 3457.00 cm⁻¹ indicated presence of Ca(OH)₂ in small amount. The highest peak at 370.19 cm⁻¹ and 600 cm⁻¹ are due to presence of bending vibration of Si-O-Si bond and band 1387.00 cm⁻¹ is because of bending vibration of the CH₃ group in cellulose as a residue and 1712.70 cm⁻¹ can be because of C=O bond in carbonyl group Hemicellulose.

3.3.2.1.5 KE (rice husk calcined at 700 °C)

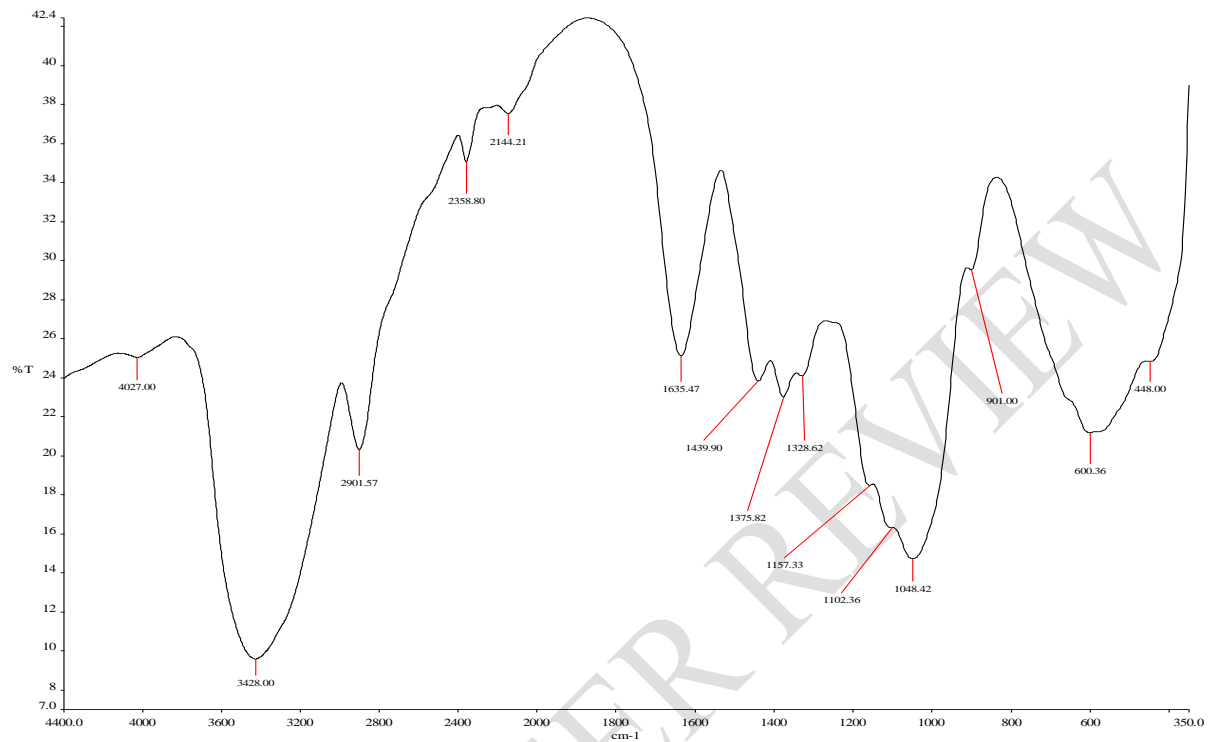


Fig15. Rice Husk Calcined at 700 °C (KE)

The spectrum is a complex one with more than 5 bands, the 4027.00 cm^{-1} and 3428.00 cm^{-1} are because of -OH group in Ca-OH and Ca-OH-Si. bands at 600.36 cm^{-1} and 448.00 cm^{-1} are due to bending vibration of Si-O-Si bond C-H bond in lignin could be at the 901.00 cm^{-1} as shown in small amount, at 1048.42 and 1102.36 could be accounted for presence of Si-O-Si bond in another phase.

3.3.2.1.6 KF (Eggshell Calcined at 800 °C)

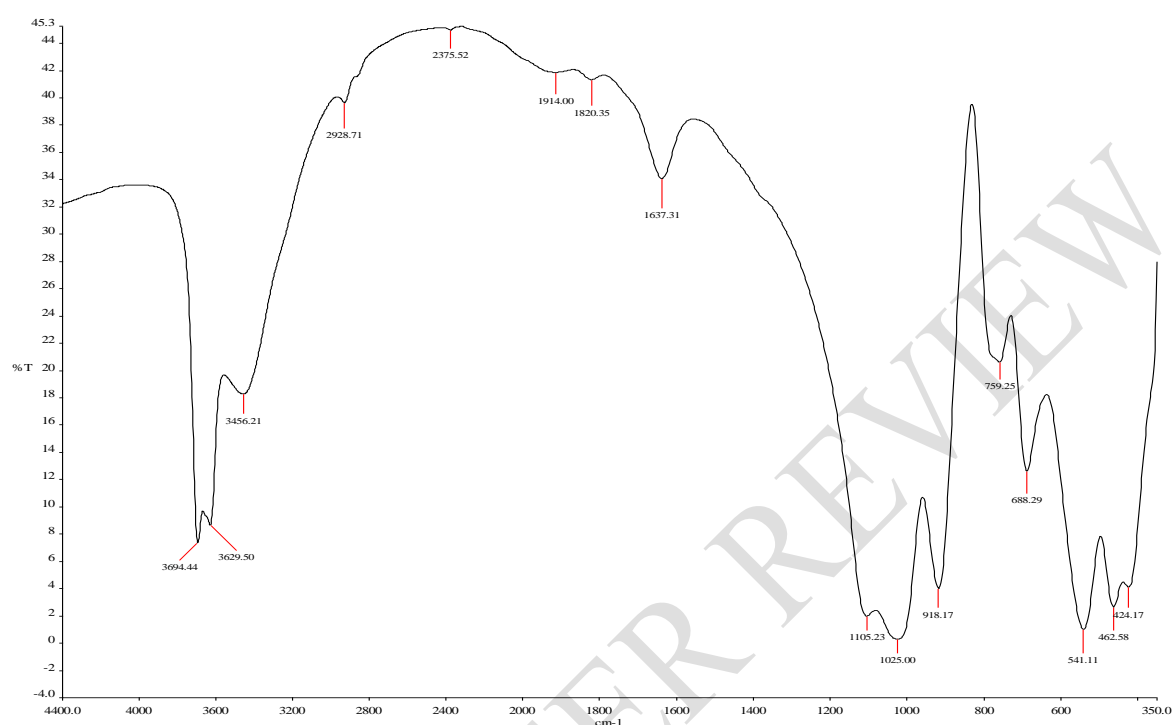


Fig16. Rice Husk Calcined at 800 °C (KF)

The -OH group vibration is shown at 3694.44 cm^{-1} and 3456.21 cm^{-1} and the band at 424.17 cm^{-1} , 462.58 cm^{-1} and 541.11 cm^{-1} are all due to stretching vibration of Si-O-Si bond. Lignin compound having C-H bending vibration formed at 688.29 cm^{-1} .

4.0 CONCLUSION

The study successfully investigated the effects of calcination on the physiochemical properties of solid wastes, namely Eggshell and Rice husk, used as heterogeneous catalysts. The results showed significant changes in properties such as color, weight, crystallinity, chemical transformation, and functional groups with increasing calcination temperature. XRD analysis revealed the presence of potassium compounds in roasted rice husk due to leaching effects. The highest amounts of **CaO** and silicon (IV) oxide were observed at the highest calcination temperatures for eggshell and rice husk, respectively. Crystallite size increased for

calcined Eggshell between 600 °C and 700 °C, with KC having the largest size, while the size decreased for calcined Rice Husk with increasing temperature. FT-IR analysis indicated the presence of $(\text{CO}_3)^{-2}$ in certain samples, suggesting higher decomposition and impurities. Based on the findings, KC (calcined at 700 °C) was identified as the best catalyst for eggshell, and KD (calcined at 600 °C) for rice husk, due to high crystallinity and low impurities.

REFERENCES

- Abdullahi, A., Alhassan, M., Isah, A. G., Sani, K. A., & Olalekan, O. A. (2018). Comparative studies on the kinetics of biogas purification using activated Carbon and Zeolite. *IOP Conference Series: Earth and Environmental Science*, 173(1). <https://doi.org/10.1088/1755-1315/173/1/012046>
- Abdulsalam, A., Alhaji Yaro, N., Mohammed, A., Saleh Ibrahim, Y., Mustapha Yakasai, K., Iyayosa Andrea, D., & Alhassan, B. (2023). Kinetic Studies of Emerging Contaminants Removal from Wastewater using Organo Modified Activated Carbon. In *International Journal of Innovative Science and Research Technology* (Vol. 8, Issue 10). www.ijisrt.com
- Abdulsalam, A., Ibrahim, Y. S., Yaro, N. A., Olanrewaju, O. A., Alhassan, B., Iyayosa, D. A., & Lawal, K. (2023). Emerging Contaminants Removal from Wastewater Using Organo-Modified Bentonite Clay. *Journal of Engineering Research and Reports*, 25(10), 121–144. <https://doi.org/10.9734/jerr/2023/v25i101006>
- Alhassan, M., Auta, M., Sabo, J., Umaru, M., & Kovo, A. (2016). CO₂ Capture Using Amine-impregnated Activated Carbon from *Jatropha curcas* Shell. *British Journal of Applied Science & Technology*, 14(4). <https://doi.org/10.9734/bjast/2016/24253>
- Andrea, D. I., Abdulsalam, A., Aboje, A. A., & Azeez, O. S. (2023). Application of Activated Rice Husk for Adsorptive Bleaching of Groundnut Oil: Kinetic, Equilibrium and Thermodynamic Study. *International Research Journal of Pure and Applied Chemistry*, 24(6), 52–72. <https://doi.org/10.9734/irjpac/2023/v24i6840>
- Bello, A., Mohammed, A., Manase, A., & Abdullahi, A. (2021). Ascertaining Optimum Pyrolysis Conditions for Biochar Production from Maple Sawdust. *Current Journal of Applied Science and Technology*. <https://doi.org/10.9734/cjast/2021/v40i4031597>
- Chakraborty, R., Bepari, S., & Banerjee, A. (2010). Transesterification of soybean oil catalyzed by fly ash and egg shell derived solid catalysts. *Chemical Engineering Journal*, 165(3), 798–805. <https://doi.org/10.1016/j.cej.2010.10.019>.
- Faridi, H. and Arabhosseini, A. (2018) Application of Eggshell Wastes as Valuable and Utilizable Products: A Review. *Research in Agriculture Engineering*, 64, 104-114.
- Faruque, M. O., Razzak, S. A., & Hossain, M. M. (2020). *Application of Heterogeneous Catalysts for Biodiesel Production from Microalgal Oil — A Review*.
- Gerhard Knothe, (2010). The History of Vegetable Oil Based Diesel Fuels. *The Biodiesel Handbook*, Chapter 2, ISBN 978-1-893997-79-0.

- Iyayosa Andrea, D., Abdulsalam, A., Uthman, H., & Sarafa Azeez, O. (2023). Article no.JMSRR.110513 Original Research Article Andrea et al. In *Journal of Materials Science Research and Reviews* (Vol. 6, Issue 4). <https://www.sdiarticle5.com/review-history/110513>
- Mat, R., Samsudin, R. A., Mohamed, M., & Johari, A. (2012). Solid catalysts and their application in biodiesel production. *Bulletin of Chemical Reaction Engineering and Catalysis*, 7(2), 142–149. <https://doi.org/10.9767/bcrec.7.2.3047.142-149>
- Mohadi, R., Anggraini, K., Riyanti, F., & Lesbani, A. (2016). Preparation Calcium Oxide From Chicken Eggshells. *Sriwijaya Journal of Environment*, 1(2), 32–35. <https://doi.org/10.22135/sje.2016.1.2.32-35>
- Mohadi, R., Anggraini, K., Riyanti, F., & Lesbani, A. (2016). Preparation Calcium Oxide From Chicken Eggshells. *Sriwijaya Journal of Environment*, 1(2), 32–35. <https://doi.org/10.22135/sje.2016.1.2.32-35>
- Olutoye, M.A., Adeniyi, O. D., & Yusuff A. S. (2016). Synthesis of Biodiesel from Palm Kernel Oil using Mixed Clay-Eggshell Heterogeneous Catalysts. (2016). *Iranica Journal of Energy and Environment*, 7(3) <https://doi.org/10.5829/idosi.ijee.2016.07.03.14>
- Pornchai, T., Imkum, A., & Apipong, P. (2016). *Effect of Calcination Time on Physical and Chemical Properties of CaO- catalyst Derived from Industrial-eggshell Wastes*. March, 2–6.
- Sekifuji, R., Chieu, L. Van, Tateda, M., & Takimoto, H. (2021). *Solubility and physical composition of rice husk ash silica as a function of calcination temperature and duration*. 19–27. <https://doi.org/10.30486/IJROWA.2021.1899156.1069>
- Zou, L., & Yang, H. (2019). Heterogeneous catalysts from biomass wastes for biodiesel production. *Catalysts*, 9(11), 916.