

Piper nigrum Leaf Extract-Mediated Synthesis of Copper Oxide Nanoparticles and Their Antimicrobial Activity Against Soil Phytopathogens

Abstract:

Bio-inspired synthesis of copper oxide nanoparticles using *Piper nigrum* leaf extract (BP- CuONPs) is reported in this study. The rapid reduction of copper (Cu²⁺) ions was preliminarily confirmed using UV–Vis spectrophotometer with peak formation at 270 nm. Further-ray diffraction(XRD) pattern confirmed the crystalline phase of copper oxide with monoclinic crystal structure. Fourier Transformed Infrared (FTIR) spectroscopy of the nanoparticles revealed the presence of various functional groups, including alcohol, phenols, carboxylic acids, and amino groups, which serve as reducing and capping agents for the metal nanoparticles and indicate the presence of metal oxide nanoparticles. Energy dispersive X-ray (EDX) spectroscopy revealed weight percentage of copper was found to be approximately 68.29%. Scanning electron microscopy (SEM) and Transmission electron microscopy (TEM) showed theformation spherical shaped formation of BP-CuONPs NPs with an average particle size of 5nm- 24.5 nm. The BP-CuONPs exhibited complete inhibition against four soil borne fungal phytopathogens at 1500ppm.

Keywords : Bio- inspired synthesis, CuO NPs, *Piper nigrum* , Electron microscopy, Phytopathogens

1. Introduction

Soil is filled with countless microorganisms, many of which benefit both the soil and plants. However, some microorganisms can harm crops by damaging their roots and crowns, thereby causing significant

economic loss. These persistent pathogens in the soil or on its surface are known as soil-borne plant pathogens, and can be caused by fungi, bacteria, nematodes, oomycetes, protozoa, and viruses. Soil-borne diseases can greatly affect crop yields, and when these pathogens form synergistic associations, they can cause significant economic losses that are difficult to manage. Soil-borne plant pathogens, such as *Fusarium* spp., *Rhizoctonia* spp., *Pythium* spp., *Sclerotinia* spp., *Verticillium* spp., and *Phytophthora* spp., can result in yield losses of up to 50-75% for important crops, such as wheat, maize, cotton, vegetables, and fruits (Mihajlovic *et al.*, 2017). *Fusarium oxysporum* strains can infect over 150 agricultural crop species, including bananas, tomatoes, melons, and cotton, causing severe vascular wilt disease (Bertoldo *et al.*, 2014). In cucurbitaceous crops, the pathogen is responsible for yield losses of approximately 30-80% (Lüet *et al.*, 2011). *Fusarium* wilt of bananas, caused by *F. oxysporum* f. sp. *cubense*, is a major threat to banana cultivation worldwide, with Tropical Race 4 causing significant losses in Southeast Asian countries, affecting the lives of small producers. Additionally, some strains of *Fusarium oxysporum* can cause root/foot rot and damping-off (Michielse and Rep, 2009). *F. solani* mainly causes collar and root rot in economically important crops, such as beans and peas. *F. graminearum* and *F. verticillioides* cause cob rot in maize, both species are known to produce mycotoxins (Nelson *et al.*, 1981). In *Brassica napus* and oil seed rape, the prevalent population of *Rhizoctonia solani* AG2-1 isolate is responsible for severe seedling diseases, establishment losses of up to 80-100%, and final yield losses of up to 30% (Tahvonena *et al.*, 1984; Kataria and Verma, 1992; Khangura *et al.*, 1999). *Rhizoctonia* presents with a variety of symptoms including stem lesions, damping-off, crown rot, root rot, stem rot, and aerial web blight. Infections ultimately lead to wilting, stunting, and plant death. *Phytophthora* and *Pythium*, two species, cause damping-off and root rot disease under cool and wet conditions, affecting 5-80% of seedlings and resulting in significant economic losses for farmers (Alcala *et al.*, 2016). Late blight, caused by *Phytophthora* spp., is one of the most destructive soil-borne diseases affecting potatoes and tomatoes, worldwide (Son *et al.*, 2008). Globally, it causes an estimated \$5 billion in annual losses (Latijnhouwers *et al.*, 2004). Conventional methods

of disease control include the use of chemical pesticides, which provide quick and reliable disease control, as well as significant drawbacks such as environmental pollution, health risks to humans and animals, and the development of increased resistance to pathogens. These issues necessitate exploration of safer and more sustainable alternatives. Nanotechnology, particularly phyto-nanotechnology, has emerged as a promising alternative. Nanotechnology leverages the unique properties of nanoparticles, including their small size, large surface-area-to-volume ratio, and high reactivity, thereby making them highly effective in various applications. Phyto-nanotechnology, which involves the use of plant-derived phytochemicals such as polyphenols and flavonoids to synthesize nanoparticles, offers several advantages over traditional chemical pesticides and can be engineered to have high specificity towards target pathogens, thereby minimizing the impact on non-target organisms and reducing environmental contamination. Nanoparticles alone can be directly utilized as antimicrobial agents and have been found to be effective against numerous soil-borne pathogens. They can be applied to the soil, seeds, roots, and foliage to provide protection against a variety of pests and pathogens, including fungi, bacteria, and viruses. Nanoparticles can penetrate plant systems and either act directly against pathogens or function as elicitor molecules, inducing local and systemic defense responses in plants. Metallic nanoparticles, including gold, silver, titanium oxide, zinc oxide, and copper oxide, have garnered significant attention owing to their potential antimicrobial properties. Studies have demonstrated that these particles possess potent antifungal, antibacterial, and antiviral properties (Gogos *et al.*, 2012; Kah and Hofmann, 2014; Kim *et al.*, 2018). The increased surface area to volume ratio of nanoparticles facilitates enhanced interaction with microbial cells, resulting in improved efficacy at lower concentrations compared to conventional chemical pesticides. Among these, Copper oxide NPs possess unique crystal structures and high surface areas, making them highly valuable antimicrobial agents. These NPs are robust and stable and have a longer shelf life than other organic antimicrobial agents (Perreault *et al.*, 2012). Many researchers have already reported using plant extracts such as *Punica granatum* (Al-Askar *et al.*,

2023), *Ficus sycomorus* (Elkobrosy et al., 2023), *Eugenia caryophyllata* (Hassan et al., 2019), *Stachys lavandulifolia* and *citrus medica* (Rajesh et al., 2018) and *Ocimum basilicum* (Abdelkhalek et al., 2022) for the synthesis of oxide NPs. Cu has been utilized to inhibit the growth of microorganisms for over two centuries, with reports indicating that it can reduce microbial concentrations by 99.9% (Krithiga et al., 2013; Subhankari and Nayak, 2013). Numerous studies have demonstrated that copper nanoparticles exhibit broad-spectrum antimicrobial activity against a wide range of fungus. Specifically, nano copper oxide (CuO) has been identified as an effective antimicrobial agent against various pathogens, including *Pythium aphanidermatum*, *Fusarium solani*, *Rhizoctonia solani*, *Phytophthora infestans*, *A. alternata* and *Botrytis cinerea* (Rai et al., 2023; Khatami et al., 2019; Ismail, 2021; Giannousi et al., 2013; Ouda, 2014). This study found that *Piper nigrum* leaves may effectively synthesize bioactive copper nanoparticles without negatively impacting the environment or the budget. *Piper nigrum* or Black pepper is a perennial woody climbing liana belonging to the family Piperaceae. It is native to India, Indonesia, Malaysia, South America and West Indies but is also widely cultivated in the tropical regions. It is considered as the 'King of Spices'. The presence of a pungent alkaloid piperine (C₁₇H₁₉N₃O₃) attributes a spicy taste to the seeds, leaves and other parts of *Piper* (Khajuria et al. 2002). It also contains small amount of safrole (C₁₀H₁₀O₂), pinene (C₁₀H₁₆), sabinene (C₁₀H₁₆), limonene (C₁₀H₁₆), caryophyllene (C₁₅H₂₄) and Linalool (C₁₀H₁₈O) compound (Augustine et al., 2013). Shanmugapriya et al. (2012) extracted alkaloids, phenolic compounds, saponins and flavonoids from the leaves of black pepper. They have also shown the antioxidant potential of these compounds. These alkaloids may act as reducing agents, free radical scavengers or potential complexers of pro-oxidant metals.

The present study was designed with a novel, rapid, and cost-effective route for biosynthesis of copper oxide nanoparticles (CuONPs) using *Piper nigrum* Leaf Extract extract. The synthesized copper oxide nanoparticles obtained by the green method are under investigation of their

effect on soil phytopathogens viz., *Rhizoctonia solani*, *Fusarium oxysporum*, *Pythium aphanidermatum*, *Phytophthora capsici*.

2. Experimental

2.1. Materials

Copper sulphate pentahydrate [CuSO₄·5H₂O] is analytical grade purchased from Merck, Darmstadt, Germany and used without further purification. Deionized distilled water was used in all experimental work. The pathogens like *Rhizoctonia solani*, *Fusarium oxysporum*, *Pythium aphanidermatum*, *Phytophthora capsici*, and *Sclerotium rolfsii* procured from repository of Department of Plant Pathology, CoA. Kerala agriculture university, Vellanikkara. Agar and dextrose were purchased from Hi-Media Private Limited, Nagpur (India). Without any further purification all chemicals were used for experiment.

2.2. Preparation of *Piper nigrum* leaf extract

Fresh leaves of black pepper (*P. nigrum*) were collected from Thrissur district, Kerala during the month of December 2022 and the specimens was authenticated by an expert of Department of medicinal and aromatic plants of College of Agriculture Vellanikara, KAU. Leaves of plants were thoroughly washed in tap water and air dried by keeping for seven days. Dried leaves were ground into fine powder using mixer grinder. The powder thus obtained was stored in airtight glass jars for further use. Ten grams of dried powder was mixed in 100 ml deionised water and was kept in water bath at temperature at 60°C for 20 min (Chahandeet *et al.*, 2020). After cooling at room temperature, the extracts were filtered through a muslin cloth to remove debris. The filtrate was centrifuged at 5000 rpm for 15 min (Eppendorf SE Centrifuge 5430 R Barkhausenweg 1 22339 Hamburg, Germany) and thereafter filtered through a Whatman No.1 filter paper (Gabriela *et al.*, 2017). The final filtrate was then stored at 4 °C for further experiments.

2.3. Biosynthesis of copper oxide nanoparticles

The prepared plant extracts of black pepper were mixed with 5 ml of 0.3M copper sulphate solution. The pH of the reaction mixture was adjusted to 8 by adding 1M NaOH and was stirred using a magnetic stirrer (LABQUEST by BOROSIL) at 80°C for 40 minutes. The reaction mixture was centrifuged at 7830 rpm for 10 min to obtain black pepper mediated copper oxide nanoparticles (BP-CuONPs), which were washed in deionised water for twice. Further CuO nanoparticles were dried in hot air oven at 70°C and were transferred to a ceramic crucible and heated in muffle furnace which was maintained at 500 °C for 2 h. The BP-CuONPs thus obtained were dissolved in di methyl sulfoxide (DMSO) and was analysed in UV spectrophotometer.

2.4. Characterization techniques

The external and internal morphology of the synthesized BP- CuONPs was examined using Field Emission Scanning Electron Microscopy (FESEM) coupled with Energy Dispersive X-ray (EDX) spectroscopy with a TESCAN Brono s.r.o Czech machine (Model: MAIA3 XMH) at the Sophisticated Analytical Instrument Facility (SAIF), Mahatma Gandhi University, Kottayam. Transmission Electron Microscopy (TEM) analysis was conducted using a JEOL JEM 2100 with a LaB6 electron source operating at 200 kV from the International and Inter University Centre for Nanoscience and Nanotechnology (IIUCNN), MG University, Kottayam. The crystalline nature of the BP- CuONPs was assessed through Powder X-ray diffraction using an AERIS research bench top pan analytical rayon X-ray diffractometer at the Physics Department of St. Thomas College, Thrissur, Shimadzu, with CuK radiation at 1.5405 Å over a Bragg angle range of $20^\circ \leq 2\theta \leq 80^\circ$. Surface functional groups were confirmed by Fourier-transformed infrared (FT-IR) spectra. The purified powder of plant-mediated metal nanoparticles was mixed with potassium bromide (KBr) to form a pellet and analyzed by FTIR (Thermo Nicolet iS50, 4000 cm^{-1} to 100 cm^{-1}) at the Sophisticated Test and Instrumentation Centre (STIC), CUSAT, Kochi. The

UV-vis spectrum of copper oxide nanoparticles was recorded using a Shimadzu UV-1780 spectrophotometer in the wavelength range of 200–800 nm at a resolution of 1 nm. For this, 3 mg of the sample was diluted with 3 ml of dimethyl sulfoxide, and the measurements were taken as a function of reaction time at the Department of Nano Science and Technology.

2.5. Antimicrobial activity

The biosynthesized BP-CuONPs were evaluated against soil borne pathogens viz., *Rhizoctonia solani*, *Fusarium oxysporum*, *Pythium aphanidermatum* and *Phytophthora capsici* separately under *in vitro* condition by poisoned food technique using Potato Dextrose Agar (PDA) as basal medium. A 3000-ppm stock solution of the synthesized metal nanoparticles were prepared by dispersing 600mg of powder form in 200 ml of deionised water. Different concentration was prepared by mixing 33.33 ml, 50 ml and 66.6 ml of metal nanoparticles from stock with 66.7 ml, 50 ml and 33.4 ml of double strength PDA (Potatoes-400 g, Dextrose- 40g, Agar 40g, dist. Water-1000 ml) medium to obtain 1000 ppm ,1500 ppm, 2000 ppm respectively. The PDA medium with the required concentration was poured into Petriplate. A control was maintained without metal nanoparticles and a 7 mm mycelial disc of five-day old fungal pathogen culture was inoculated at the centre of the plate and incubated at $23 \pm 10^{\circ}\text{C}$, until full growth was observed in control plates. Three replications were maintained for each treatment. Observations on colony diameter of the test isolates were recorded at an interval until the continued till untreated control plates showed complete growth of the test pathogen. Per cent mycelial growth inhibition of the test pathogens over untreated control was calculated by following formula.

$$\text{Per cent inhibition (I)} = \frac{\text{C}-\text{T}}{\text{C}} \times 100$$

T

where, I = Per cent inhibition, C= Radial growth (mm) of test pathogen in control and T= Radial growth (mm) of test pathogen in treatments.

3. Result and discussion

3.1. Confirmation of BP-CuONPs by X-ray diffraction and Fourier-transmission infrared spectroscopy

X-ray diffraction analysis serves as a valuable tool for identifying phases and characterizing the crystal structure of nanoparticles. The X-ray diffraction pattern of synthesized BP- CuONPs, displayed in figure 1, revealed several Bragg reflection peaks at 2θ values of 32.45° , 35.57° , 38.69° , 48.77° , 53.57° , 58.75° , 61.72° , and 75.16° , assigned to the corresponding (110), (002), (111), (112), (020), (202), (113), (310), (220), and (004) planes, respectively. These obtained XRD patterns indicated the highly crystalline nature of the synthesized nanoparticles with the monoclinic structure of CuO, as confirmed by JCPDS (Card No: 89-5895).

FTIR analyses were conducted to ascertain the presence of diverse functional groups in biomolecules accountable for the reduction and stabilization of metal nanoparticles. Intense bands in the observed spectra were cross-referenced with standard infrared chart values to validate the functional groups. Figure 2 showcased the FTIR spectra of BP-CuONPs. The absorption peaks at 3419.2 cm^{-1} of BP-CuONps corresponds to hydrogen bonded O-H groups of alcohols and phenols (Ghidan et al.,2016).The bands at 1612 cm^{-1} can be allocated to the stretching vibration of C- OH bond from proteins (amide I). Presence of peak at 1384.91 cm^{-1} and 1100.70 cm^{-1} of BP- CuONps may be attributed to the presence of carboxylic acids and amino group.Strong peak around 793.11 and 617.89 cm^{-1} of BP- CuONPs corresponds to the Cu-O stretching vibrations copper oxide nanoparticles in monoclinic state (Berra et al.,2018).

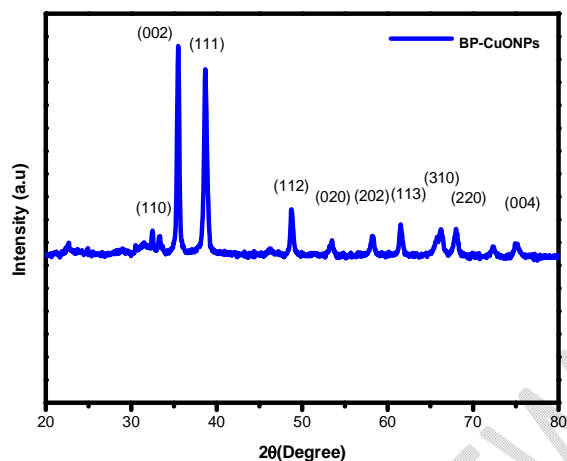


Fig. 1 : XRD pattern of BPCuONPs

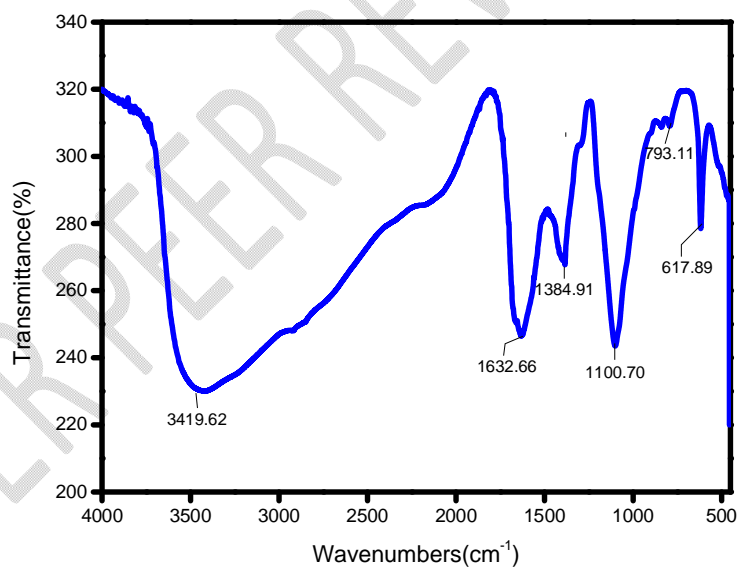


Fig. 2 : FTIR spectrum of BPCuONPs

3.2 UV–vis spectroscopy analysis

The addition of *P.nigrum* leaf extract to copper sulphate pentahydrate [CuSO₄·5H₂O] solution resulted in color change of the solution from blue to green. The color changes arise from the excitation of surface plasmon vibrations with the copper oxide nanoparticles (Yugandhar

et al., 2018). The surface plasmon resonance (SPR) of CuO nanoparticles produced a peak centered near 270 nm as shown in Fig 3, indicating the reduction of copper sulphate pentahydrate into CuONPs. Similar results were found in the study conducted by Atri *et al.*, 2023 on green synthesis of copper oxide nanoparticles using *Ephedra alata* plant extract, it was found that absorption peak at about 272 nm, confirmed good formation and pure phase of CuONPs

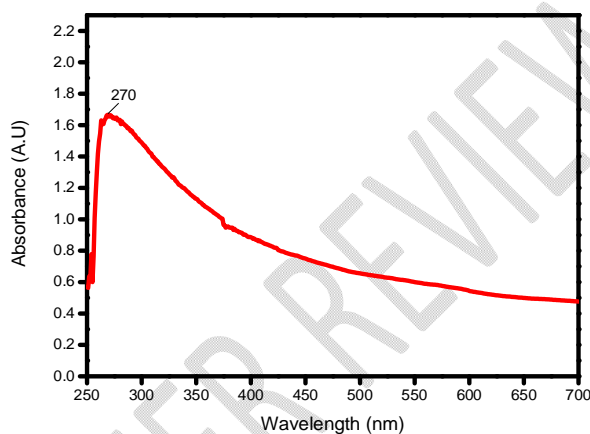


Fig. 3 : UV Vis spectrum of BPCuONPs

3.3 Scanning Electron Microscopy and Elemental Analysis of metal nanoparticles

The particle size distribution and microstructure of the green synthesized metal and metal oxide nanoparticles were studied by the field emission scanning electron microscopy (FESEM) coupled with Energy Dispersive X-ray (EDX) spectroscopy. In the examination of BP-CuONPs, the FESEM analysis revealed the formation of spherical copper oxide nanoparticles with average diameters of 28.75 nm, respectively (Fig 4). In the EDX analysis, copper peaks were detected at 1 keV, 8 keV and 9 keV while the oxygen peak was centered at 0.5 keV (Fig 5). The weight percentage of copper and oxygen were found to be approximately 68.29% and 19.21% for BP-CuONPs (Table 1). Additionally, peaks corresponding to elemental constituents such as carbon, silicon, potassium, sulphur, and

sodium were also detected, which may come along with plant extract which sometimes acted as a capping agent to nanoparticles. When we observe the table, we can clearly notice the major element as copper which comprises more than 50% of total constituent along with oxygen, which clearly confirms the formation of pure copper oxide nanoparticles. This indicates the nanoparticles synthesis can be made easily by biological synthesis method

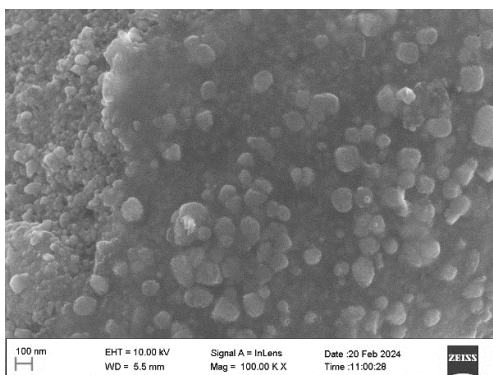


Fig. 4 : SEM image of BPCuONPs

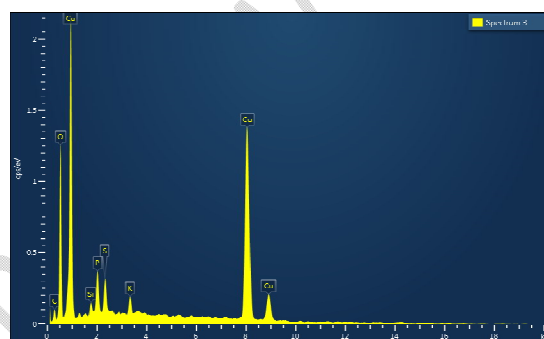


Fig. 5 : EDAX spectrum of BPCuONPs

Element	Weight (%)	Atomic (%)
C K	5.5	15.52
O K	19.21	40.7
Si K	0.9	1.08
P K	2.62	2.87
S K	2.08	2.2
K K	1.4	1.21
Cu K	68.29	36.42
Total:	100	100

Table 1 : Elemental composition of BPCuONPs

3.4 High Resolution Transmission Electron Microscopy (HRTEM)

HRTEM images of these BP-CuO NPs are depicted in Fig 6.a, 6.b and 6.c. The analysis confirmed that the BP-CuO NPs were spherical or roughly spherical in shape with mean diameter 20 nm varied from 5nm – 24.95 nm.

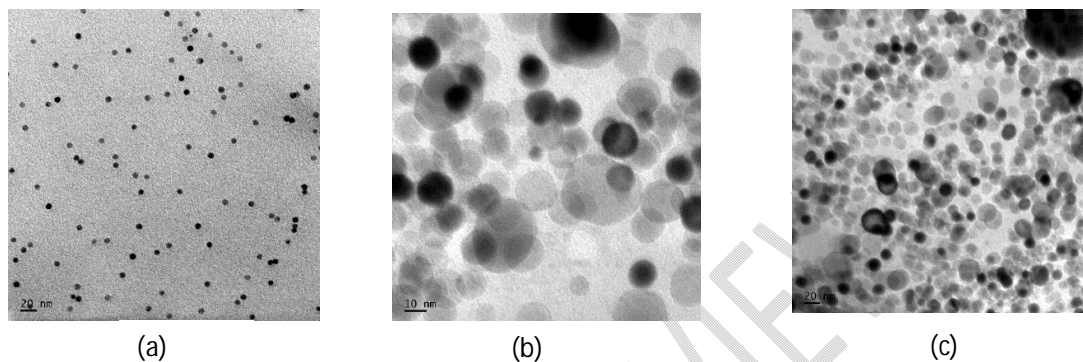


Fig. 6(a,b,c) : TEM images of BPCuONPs

3.5 Antimicrobial Activity

The poisoned food technique was used to evaluate the antimicrobial potential of BP-CuONPs. The results of the antimicrobial activity of BP-CuONPs tested at concentrations of 1000 ppm and 1500 ppm against *Rhizoctonia solani*, *Fusarium oxysporum*, *Pythium aphanidermatum*, *Phytophthora capsici*, and *Sclerotium rolfsii* were shown in fig 7.. At both concentrations, *Pythium aphanidermatum* and *Phytophthora capsici* were completely inhibited, as shown in figures 8.a and 8.b and figures 9.a and 9.b. At 1000 ppm, *Rhizoctonia solani* showed partial inhibition at 22.22%, as seen in figure 10.a, while *Fusarium oxysporum* did not exhibit any inhibitory response, as shown in figure 11.a. At 1500 ppm, *Fusarium oxysporum* was completely inhibited, as seen in figure 11.b, and *Rhizoctonia solani* demonstrated significant inhibition at 100 per cent, as shown in figure 10.b. This study indicates that BP-CuONPs have promising efficacy against the tested organisms. These results align with findings by Shende et al. (2016), where copper oxide nanoparticles were effective against eleven fungal pathogens, including *Alternaria carthami*, *Aspergillus niger*, *Colletotrichum gloeosporioides*, *Fusarium oxysporum* f. sp. *carthami*, *Fusarium oxysporum* f. sp. *ciceri*, *Macrophomina phaseolina*, *Rhizoctonia bataticola*, *Colletotrichum lindemuthianum*, *Drechslera sorghicola*,

Rhizopus stolonifera, and *Fusarium oxysporum*.sp. *udum*. Similarly, Vanati et al. (2016) reported that *Eichhornia*-mediated copper oxide nanoparticles inhibited *Fusarium culmorum* and *Aspergillus niger* at 100 µg/ml.

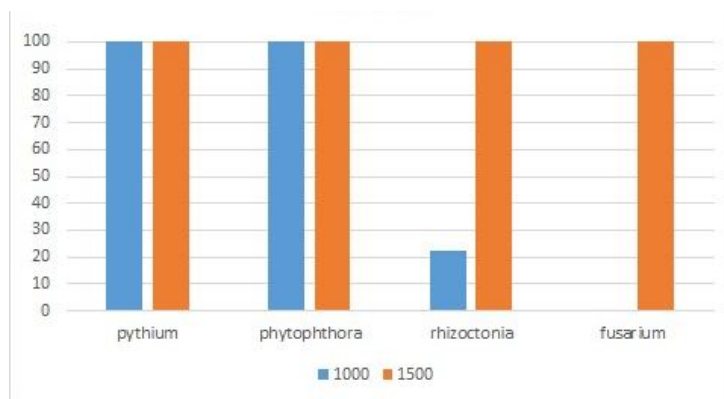


Fig. 7 : Percent incubation at different concentration of synthesized BPCuONPs

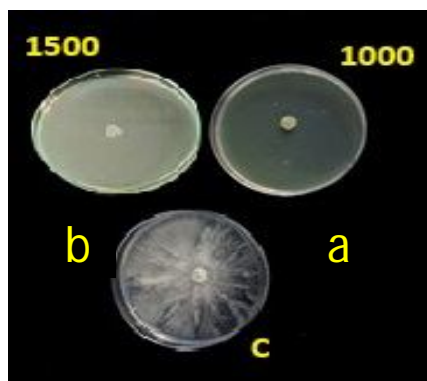


Fig. 8 : Anti microbial activity of BPCuONPs against *Phytophthora capsica* at a) 1000 ppm b) 1500ppm c) control

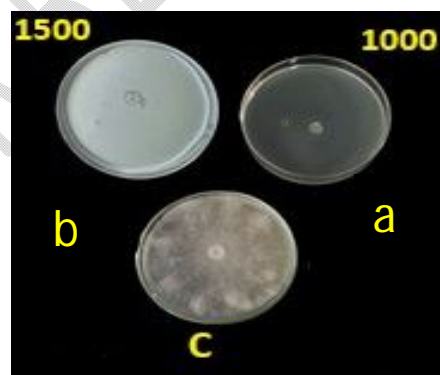


Fig. 9 : Anti microbial activity of BPCuONPs against *Pythium aphanidermatum* at a) 1000 ppm b) 1500ppm c) control

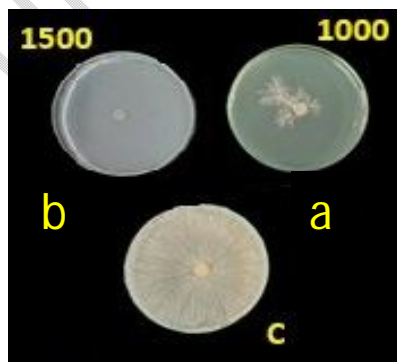


Fig. 10 : Anti microbial activity of BPCuONPs against *Rhizoctonia solani* at a) 1000 ppm b) 1500ppm c) control

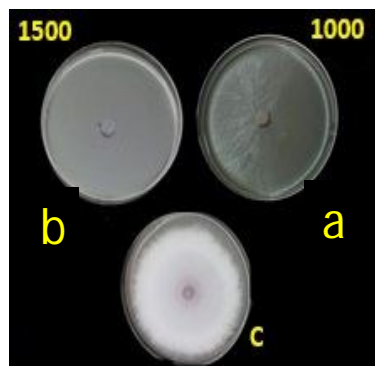


Fig. 11 : Anti microbial activity of BPCuONPs against *Fusarium oxysporum* at a) 1000 ppm b) 1500ppm c) control

4. Conclusion

The synthesis of copper oxide nanoparticles (CuONPs) through green methods is a more environmentally friendly and safer option compared to chemical and physical methods. Our study has developed a quick, eco-friendly, and practical technique for producing CuO nanoparticles using copper sulfate pentahydrate and *P. nigrum* leaf extract. The colour change resulting from surface Plasmon resonance during the reaction with the extract's ingredients confirms the formation of CuO nanoparticles, as demonstrated by XRD, FT-IR, UV-vis spectroscopy, SEM, and TEM. FTIR spectroscopy of the nanoparticles revealed the presence of various functional groups, including alcohol, phenols, carboxylic acids, and amino groups, which serve as reducing and capping agents for the metal nanoparticles and indicate the presence of metal oxide nanoparticles. In vitro studies have shown that these nanoparticles are effective against most soil-borne plant pathogens. Future research should focus on scaling up this green technique to an industrial level while also considering its environmental and health impacts.

Compliance with ethical standards

Authors declares that they have no conflict of interest.

Highlights :

- Copper oxide nanoparticles were bio synthesized by precipitation method.
- Spherical shaped morphology was observed for the synthesised nanoparticles.
- Antimicrobial studies of copper oxide nanoparticles was conducted for *Rhizoctoniasolani*, *Fusarium oxysporum*, *Pythium aphanidermatum* and *Phytophthora capsicaat* different ppm.
- A complete inhibition of all the tested phytopathogens were observed at 1500ppm.

Reference

1. Atri, A., Echabaane, M., Bouzidi, A., Harabi, I., Soucase, B.M. and Chaâbane, R.B., 2023. Green synthesis of copper oxide nanoparticles using Ephedra Alata plant extract and a study of their antifungal, antibacterial activity and photocatalytic performance under sunlight. *Heliyon*, 9(2).
2. Abdelkhalek A, El-Gendi H, Alotibi FO, Al-Askar AA, Elbeaino T, Behiry SI, et al. Ocimumbasilicum-mediated synthesis of silver nanoparticles induces innate immune responses against cucumber mosaic virus in squash. *Plants*. 2022;11:2707.
3. Al-Askar AA, Aseel DG, El-Gendi H, Sobhy S, Samy MA, Hamdy E, et al. Antiviral activity of biosynthesized silver nanoparticles from pomegranate (*Punica granatum L.*) peel extract against tobacco mosaic virus. *Plants*. 2023;12:2103.
4. Alcala, A.V.C., Paulitz, T.C., Schroeder, K.L., Porter, L.D., Derie, M.L. and du Toit, L.J., 2016. Pythium species associated with damping-off of pea in certified organic fields in the Columbia Basin of central Washington. *Plant disease*, 100(5), pp.916-925.
5. Berra, D., Laouini, S.E., Benhaoua, B., Ouahrani, M.R., Berrani, D. and Rahal, A., 2018. Green synthesis of copper oxide nanoparticles by Pheonix dactylifera L leaves extract. *Digest Journal of Nanomaterials and Biostructures*, 13(4), pp.1231-1238.
6. Bertoldo, C., Gilardi, G., Spadaro, D., Gullino, M.L. and Garibaldi, A., 2015. Genetic diversity and virulence of Italian strains of *Fusarium oxysporum* isolated from *Eustoma grandiflorum*. *European Journal of Plant Pathology*, 141, pp.83-97.
7. Chahande, R.K., Mehere, B.A., Pantawane, P.K., Chouke, P.B. and Murai, S.R., 2020. Bio-inspired synthesis of silver nanoparticles assisted *Murrayakoneigii* leaf extract and its antimicrobial activity. *Materials Today: Proceedings*, 29, pp.923-928.
8. Elkobrosy D, Al-Askar AA, El-Gendi H, Su Y, Nabil R, Abdelkhalek A, et al. Nematocidal and bactericidal activities of green synthesized silver nanoparticles mediated by *Ficus sycomorus* leaf extract. *Life*. 2023;13:1083
9. Gabriela, Á.M., Gabriela, M.D.O.V., Luis, A.M., Reinaldo, P.R., Michael, H.M., Rodolfo, G.P. and Roberto, V.B.J., 2017. Biosynthesis of silver nanoparticles using mint leaf extract (*Mentha piperita*) and their antibacterial activity. *Advanced Science, Engineering and Medicine*, 9(11), pp.914-923.

10. Ghidan, A.Y., Al-Antary, T.M. and Awwad, A.M., 2016. Green synthesis of copper oxide nanoparticles using *Punica granatum* peels extract: Effect on green peach Aphid. *Environmental Nanotechnology, Monitoring & Management*, 6, pp.95-98.
11. Giannousi, K.; Avramidis, I. and DendrinouSamara, C. 2013. Synthesis, characterization and evaluation of copper-based nanoparticles as agrochemicals against *Phytophthora infestans*. *RSC Adv.*, 3: 21743-21752.
12. Gogos, A., Knauer, K. and Bucheli, T.D., 2012. Nanomaterials in plant protection and fertilization: current state, foreseen applications, and research priorities. *Journal of agricultural and food chemistry*, 60(39), pp.9781-9792.
13. Hassan, S.E.D., Fouda, A., Radwan, A.A., Salem, S.S., Barghoth, M.G., Awad, M.A., Abdo, A.M. and El-Gamal, M.S., 2019. Endophytic actinomycetes *Streptomyces* spp mediated biosynthesis of copper oxide nanoparticles as a promising tool for biotechnological applications. *JBIC Journal of Biological Inorganic Chemistry*, 24, pp.377-393.
14. Ismail, A.M., 2021. Efficacy of copper oxide and magnesium oxide nanoparticles on controlling black scurf disease on potato. *Egyptian Journal of Phytopathology*, 49(2), pp.116-130.
15. Kah, M. and Hofmann, T., 2014. Nanopesticide research: current trends and future priorities. *Environment international*, 63, pp.224-235.
16. Kataria, H.R. and Verma, P.R., 1992. *Rhizoctonia solani* damping-off and root rot in oilseed rape and canola. *Crop Protection*, 11(1), pp.8-13.
17. Khajuria A, Thusu N, Zutshi U (2002) Piperine modulates permeability characteristics of intestine by inducing alterations in membrane dynamics: influence on brush border membrane fluidity, ultra-structure and enzyme kinetics. *Phytomedicine* 9(3):224–23.
18. Khangura, R.K., Barbetti, M.J. and Sweetingham, M.W., 1999. Characterization and pathogenicity of *Rhizoctonia* species on canola. *Plant disease*, 83(8), pp.714-721.
19. Khatami, M., Varma, R.S., Heydari, M., Peydayesh, M., Sedighi, A., Agha Askari, H., Rohani, M., Baniasadi, M., Arkia, S., Seyedi, F. and Khatami, S., 2019. Copper oxide

nanoparticles greener synthesis using tea and its antifungal efficiency on *Fusarium solani*. *Geomicrobiology Journal*, 36(9), pp.777-781.

20. Kim, D.Y., Kadam, A., Shinde, S., Saratale, R.G., Patra, J. and Ghodake, G., 2018. Recent developments in nanotechnology transforming the agricultural sector: a transition replete with opportunities. *Journal of the Science of Food and Agriculture*, 98(3), pp.849-864.
21. Krithiga, N., Jayachitra, A. and Rajalakshmi, A., 2013. Synthesis, characterization and analysis of the effect of copper oxide nanoparticles in biological systems. *Ind J Ns*, 1, pp.6-15.
22. Latijnhouwers, M., Ligterink, W., Vleeshouwers, V.G., Van West, P. and Govers, F., 2004. A *Gα* subunit controls zoospore motility and virulence in the potato late blight pathogen *Phytophthora infestans*. *Molecular microbiology*, 51(4), pp.925-936.
23. Lü, G., Guo, S., Zhang, H., Geng, L., Song, F., Fei, Z. and Xu, Y., 2011. Transcriptional profiling of watermelon during its incompatible interaction with *Fusarium oxysporum* f. sp. *niveum*. *European journal of plant pathology*, 131, pp.585-601.
24. Michielse, C.B. and Rep, M., 2009. Pathogen profile update: *Fusarium oxysporum*. *Molecular plant pathology*, 10(3), p.311.
25. Mihajlovic, M., Rekanovic, E., Hrustic, J., Grahovac, M. and Tanovic, B., Methods for management of soil-borne plant pathogens. *PesticPhytomed (Belgrade)* 2017; 32: 9-24.
26. Nelson, P.E., Toussoun, T.A. and Cook, R.J. eds., 1981. *Fusarium: diseases, biology and taxonomy* (pp. xi+-457).
27. Ouda, S.M. 2014. Antifungal activity of silver and copper nanoparticles on two plant pathogens, *Alternaria alternata* and *Botrytis cinerea*. *Res. J. Microbiol.*, 9: 34-42
28. Perreault F, Melegari SP, da Costa CH, Rossetto AL, de OF, Popovic R, et al. Genotoxic effects of copper oxide nanoparticles in Neuro 2A cell cultures. *Sci Total Env.* 2012;441:117-24.

29. Rai, M., Ingle, A.P., Paralikar, P., Anasane, N., Gade, R. and Ingle, P., 2018. Effective management of soft rot of ginger caused by *Pythium* spp. and *Fusarium* spp.: emerging role of nanotechnology. *Applied microbiology and biotechnology*, 102, pp.6827-6839.
30. Rajesh, K.M., Ajitha, B., Reddy, Y.A.K., Suneetha, Y. and Reddy, P.S., 2018. Assisted green synthesis of copper nanoparticles using *Syzygium aromaticum* bud extract: Physical, optical and antimicrobial properties. *Optik*, 154, pp.593-600.
31. Shanmugapriya K, Saravana PS, Payal H, Mohammed P, Williams SB (2012) Antioxidant potential of pepper (*Piper nigrum* Linn.) leaves and its antimicrobial potential against some pathogenic microbes. *Indian J Nat Prod Resour* 3(4):570–577
32. Shende, S., Gaikwad, N. and Bansod, S., 2016. Synthesis and evaluation of antimicrobial potential of copper nanoparticle against agriculturally important phytopathogens. *Synthesis*, 1(4), pp.41-47.
33. Son, S.W., Kim, H.Y., Choi, G.J., Lim, H.K., Jang, K.S., Lee, S.O., Lee, S., Sung, N.D. and Kim, J.C., 2008. Bikaverin and fusaric acid from *Fusarium oxysporum* show antioomycete activity against *Phytophthora infestans*. *Journal of applied microbiology*, 104(3), pp.692-698.
34. Subhankari, I. and Nayak, P.L., 2013. Antimicrobial activity of copper nanoparticles synthesised by ginger (*Zingiber officinale*) extract. *World Journal of Nano Science & Technology*, 2(1), pp.10-13.
35. Tahvonen, R., Hollo, J. and Hannukkala, A., 1984. *Rhizoctonia solani* damping-off on spring turnip rape and spring rape (*Brassica* spp.) in Finland. *Agricultural and Food Science*, 56(2), pp.143-154.
36. Vanathi, P., Rajiv, P. and Sivaraj, R., 2015. Eichhornia mediated copper oxide nanoparticles: in vitro analysis of antimicrobial activity. *International Journal of Pharmacy and Pharmaceutical Sciences*, pp.422-424.

UNDER PEER REVIEW