

## Assessing the Sustainability and Performance of Hempcrete: A Study on Physical and Mechanical Properties

Commented [DAH1]: ... Physical and Mechanical Properties of what?

### Abstract

#### Aim:

Buildings contribute significantly to GHGs emissions, accounting for around 39% of total energy-related emissions. Traditional construction materials like cement, concrete, glass, asphalt, and steel have high GHGs emissions. Thus, researchers are focusing on solutions to tackle carbon emissions, with hempcrete emerging as a less polluting construction material. Hempcrete is a bio-composite of hemp shiv (hardwood core of the hemp stem) and hydrated lime. The aim of the study is to determine the physical and mechanical properties of hempcrete.

#### Study Design

This paper is a part of the ongoing research on hempcrete at G.B. Pant University of Agriculture & Technology, Pantnagar, Uttarakhand, India. The present study adopted an experimental research design.

#### Methodology

The results of this paper are presented in two sections: sustainability and performance. The sustainability aspect of hempcrete was assessed through a review of relevant literature, while the performance section involved conducting experiments in laboratory settings. In the experimental phase, five different hemp shiv and lime concrete mixes were formulated through a series of iterative trials and adjustments. At the time of experimental phase, the researcher manually casted all the cubes with sizes measuring 10 cm.

#### Results

During the specified time intervals of 28, 56, 84, and 112 days, the cubes exhibited a range in weight density from 506 to 674 Kg/m<sup>3</sup>. In parallel, the compression test results demonstrated varying values, spanning from 0.510 Mpa to 0.810 Mpa across the same time points.

**Conclusion** The results pertaining to weight density highlight the lightweight nature of hempcrete, to the extent that the cubes have the propensity to float in water. Due to its relatively low compressive strength values, hempcrete is deemed suitable for non-load bearing applications within building constructions.

Keywords: Sustainability, Hempcrete, GHGs, non-structural applications, lightweight

### 1. INTRODUCTION

As per Inter-governmental Panel on Climate Change's (IPCC) Sixth Assessment Report (AR6), 2023, IPCC reported that there is a more than 50% chance that global temperature rise will reach or surpass 1.5 degrees C (2.7 degrees F) between 2021 and 2040 across studied scenarios, and under a high-emissions pathway, specifically, the world may hit this threshold even sooner between 2018 and 2037.

Reports consistently highlight [that emissions](#) [those emissions](#) from the construction and building sector

represent approximately one-third of total global emissions. This alarming statistic underscores the urgent need for humanity to explore sustainable building materials as alternatives to traditional construction materials. Some examples of sustainable building materials are bamboo, recycled plastic, hempcrete, rammed earth, cork and straw bale construction and many others. These days, Lime-Hemp Composites (LHC) or Hempcrete—which were initially created and tested in the early 1990s—are the most advanced bio aggregate-based building material in Eastern Europe. When lime is mixed with hemp hurd /shiv (woody chips of hemp stem), it is called hempcrete. Due to its good thermal properties and lightweight characteristics, it is gaining popularity among civil engineers, researchers and academicians. Hemp (*Cannabis Sativa L.*) is a multipurpose crop that can be cultivated for either fibre, seed or cannabidiols and building material. The 21<sup>st</sup> century has seen an increase in the demand for hemp and its products. Over the past 20 years, most countries have legalized the growing of industrial hemp, which has sparked a lot of research into the health advantages of hemp and products derived from it. Uttarakhand is the first state of India to legalise the industrial and horticultural growing of hemp.

The temperate zone, which spans from 1200 meters to more than 2200 meters, has the ideal climate for hemp cultivation. It requires soil that is well-aerated, has a pH of six, and is wet. Owing to space constraints in Uttarakhand's mountainous regions, hemp is typically grown in cropping patterns with other crops. It is an extremely valuable resource for industrial application, especially in developing nations, due to its greater potential for carbon absorption and cheap cultivation capital requirements [1]. Concrete, in general, is a solid mass made of various aggregates bound together by a binder, or "glue." It has many types of aggregates and binders. Hemp wood act as an aggregate and lime as binder, to form hemp-lime, also known as hempcrete. For various applications, such as plaster, walls, floors, and roofs, different formulations of hempcrete are required [2]. Hemp buildings were used by ancient Indians as early as the sixth century, as evidenced by the Ellora caves. They investigated the sample of clay plaster taken from Buddhist cave number 12. After the hemp was extracted from the lime plaster, it was analysed using a variety of microscopic techniques. The sample was then compared to a fresh specimen of *C. sativa* that had been taken from Jalna in the Aurangabad area of Maharashtra, and the results verified the similarities between the two [3]. France is linked to the use of hempcrete in more recent times. Charles Rasetti, a historical building expert, originally created this method in 1986 for restoring oak-framed structures that were filled with straw, lime, and rubble and were typical of the Champagne area of France. Rasetti discovered that hempcrete worked far better than cement because the infill of these buildings deteriorated even more when cement was used to fix them [4]. Because of its lower mechanical strength, hempcrete is not a load-bearing material. It is used as a filling material for single-layer walls with a structural frame and as insulation material for existing walls, floors and roofs. Construction techniques include forming monolithic walls by compacting the mix in a formwork, spraying, bricklaying from precast blocks and prefabrication of entire wall elements [5]. The quantity of shiv in hemp concrete affects density and thermal conductivity. The density drops from 611 to 369 kg/m<sup>3</sup> and the thermal conductivity drops from 140.8 to 94.7 W/ (m K) for hemp percentages in weight between 20% and 40% [6].

## 2. METHODOLOGY

**Commented [DAH2]:** The Introduction has not been able to specifically capture or point out the major "research problem", its "objective" and "significance".

The results of the present paper are structured into two sections: the first section focuses on the experimental findings, while the second part delves into the sustainability aspect of hempcrete through a review of relevant literature. All experimental work for this study was conducted at the Department of Civil Engineering of G.B. Pant University of Agriculture & Technology, located in Pantnagar, Uttarakhand, India. This division of the paper allows for a comprehensive exploration of both the practical applications and theoretical implications of hempcrete.

**Commented [DAH3]:** It is improper for findings to come before the empirical review. A review is first done to assist in locating the "research problem".

## 2.1. Materials Used for The Study

### 2.1.1. Hemp shiv

Small woody chips of hemp stem are called hemp hurd or shiv shown in figure 1. it was procured from Gohemp Agroventures Pvt Ltd., based in Roorkee, Uttarakhand. The hemp plant used for the shiv was naturally grown locally. Figure 2 illustrates the composition of shiv, indicating that it consists of 2% dust, 7% fibre, and the remaining percentage is shiv by weight.



Figure.1 Shiv sample

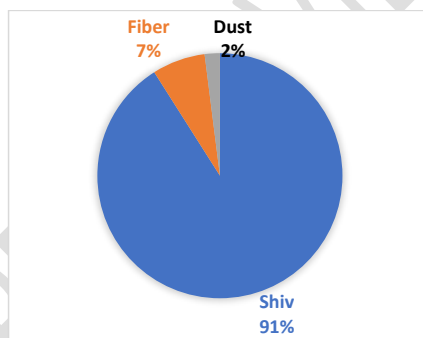


Figure.2 Composition of Shiv by weight percent

### 2.1.2. Quick lime: a binding agent

Lime is a traditional building material. Naturally available limestone ( $\text{CaCO}_3$ ), when heated up, releases  $\text{CO}_2$ , and the resulting white powder is referred to as quicklime ( $\text{CaO}$ ). The quicklime was sourced from **ONGC Additions Ltd. (OPAL)** based in taluka Vaghra, Bharuch, Gujarat. Before use quicklime was slaked for 24 hours thus convert it into hydrated form. Lime has the ability to collect and release moisture by maintaining humidity levels, this lowers the moisture damage and makes the living area comfortable.

### 2.1.3. Water

Locally available, good-quality potable water was used for the slaking of lime and all other experiments. The amount of water used in the lime process totally depends on the outside temperature. Compared to winters, summers require a greater quantity of water as water evaporates quickly through exothermic reactions.

## 2.2 Properties of Materials Used

### 2.2.1. Hemp shiv

#### 2.2.1.1. Physical properties of shiv

The physical properties of the shiv are moisture content, ash content and dry matter. these are measured without changing the chemical composition of it. Preliminary test results shows that moisture content of hemp shiv was 4.5 %, ash content was found 1.94 % and rest was dry matter percentage. shown in table 1.

**Table 1. Physical Properties of hemp shiv**

Moisture Content	4.5 %
Ash content	1.94 %
Dry matter	95.5%

#### 2.2.1.2 Sieve analysis of hemp shiv

In the present study, hemp shiv was used as coarse aggregate. Traditional examples of coarse aggregates are sand, gravel, and crushed stone. Sieve analysis was used to obtain the particle size distribution of solid material by determining the amount of shiv retained on a series of sieves with different size apertures.

The sieve analysis procedure is carried out in accordance with **IS 383-1970**, and the total sample size was 1 kg. it was sieved manually. Minimum i.e. approx. 16 percent particle retained on sieve size 10 and maximum about 23 percent retained on 2.36 mm sieve displayed in **table 2**.

**Table 2. Shiv analysis of shiv particles**

Sieve Sizes (mm)	Retained (gms)	Retained Percentage	Cumulative Percentage Retained	Percentage Passing/ Percent Fine
10	155.58	15.57	15.57	84.42623
8	90.10	9.01	24.59	75.40984
5.6	223.60	23.36	47.95	52.04918
4.75	65.55	6.55	54.50	45.4918
2.36	229.50	22.95	77.45	22.54098
Pan	225.54	22.54	100	0

<b>Total</b>	<b>1000</b>			
--------------	-------------	--	--	--

## 2.2.2 Lime

### 2.2.2.1 Physical properties of quick lime

Physical properties of lime discussed here are specific gravity, fineness modulus and compressive strength. Specific gravity refers to the ratio of the density of building material to the density of water. It means how heavy is material with respect to the water. Quick lime used in the study has specific gravity of 2.61 it means it is 2.61 times heavier than water. Fineness modulus value was 3.26 and compressive strength of lime at 28 days was 1.29 MPa presented in table 3.

**Table 3. Physical Properties of Quick Lime**

Properties	Results	Methods
Specific Gravity	2.61	IS-2386 Part: III, 1963
Fineness Modulus	3.26	IS 1514:1990
Compressive Strength	1.29 MPa	IS: 6932 Part: VII

## 2.3 Mix Proportions of Ingredients

Several trials were carried out to determine a suitable base concrete mix consisting solely of the fundamental ingredients of hempcrete, namely shiv and quicklime. The quicklime was slaked for 24 hours, and the following day, it was utilized for mix preparation in accordance with BIS regulation. The amount of water needed for the slaking process couldn't be set definitively because it varied based on the external temperature and humidity.

The objective of mix proportioning is to achieve a concrete mixture that meets the requirements of being lightweight, providing good insulation, and exerting minimal environmental impact. In this study, five distinct combinations of hemp and lime ratios illustrated in table 4, were selected for examination or analysis. Following mix proportions was used for the entire study.

**Commented [DAH4]:** Could this be your objective?


**Table 4. Composition for making 10 cm<sup>3</sup> cube**

Specimen Code	H/L	Shiv (in grams)	Slaked Lime (in grams)
HC0.30	3:10	231	770
HC0.35	7:20	238	660
HC0.40	2:5	238	595
HC0.45	91:200	237	520
HC0.50	1:2	238	476

## 2.4 Production of Concrete

The production of hemp-based concrete entails a four-step process, as illustrated in the flow chart depicted in Figure 3, and is elaborated upon below. In the production of concrete, weigh batching is adopted instead of volume batching. This method is chosen because each cube is cast manually, and using a pan mixer would necessitate larger quantities of concrete. Lime was slaked in a 20-liter iron bucket for the slaking process for 24 hours. The next day, excess water was removed from it, and the slurry was stirred with a wooden rod for 1-2 minutes before being left to settle for 5-10 minutes. Any extra water that rose to the surface was then removed by tilting the bucket to one side. This process was repeated 3-4 times depending on the amount of excess water, resulting in the formation of a thick paste of slaked lime. Water was sprinkled on Shiv to moisten it, enabling the lime to adhere easily to its surface and enhance the workability of the mixture. Lime was poured onto the moistened Shiv and thoroughly mixed until a homogeneous mixture was obtained.

The cast iron cubes were oiled before being filled with mixture. The mixture was filled in four layers. In each layer, a handful of the mix was taken, filled, and then compacted with a 3.5 kg weighted iron rod with a diameter of 5.5 cm for 30 blows. All the cubes were dried in open air in laboratory conditions. The pictorial representation, figure 4, provides a visual guide to the production sequence, outlining each key step involved in the creation of hempcrete construction elements.

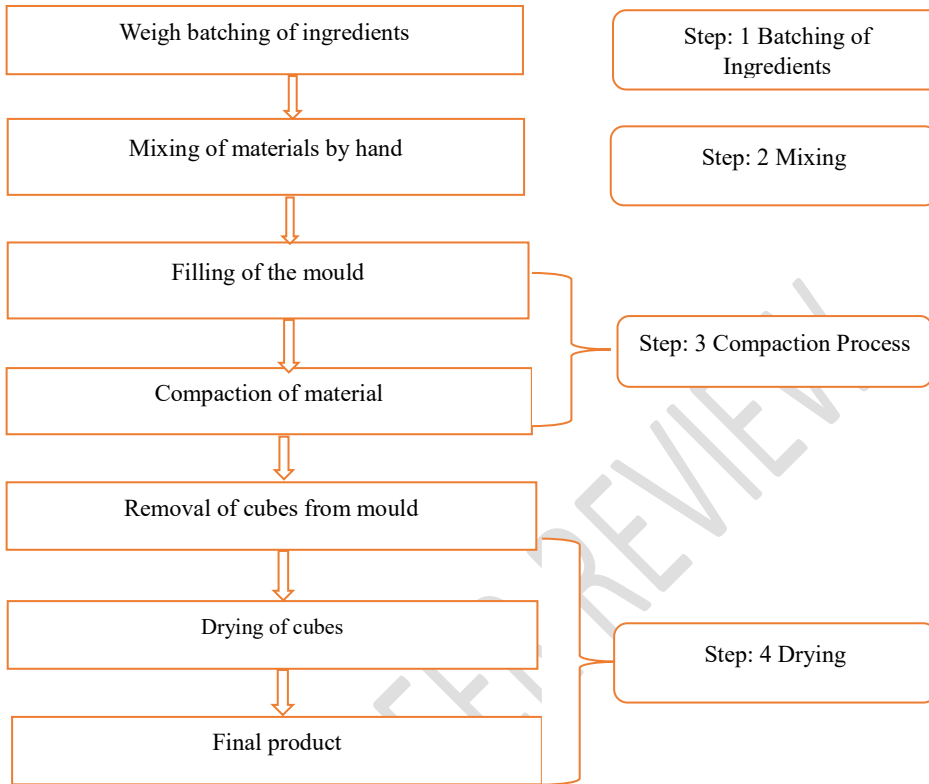

**Figure 3** Flow chart of the manufacturing process of concrete based on hemp shiv





**Figure 4. Pictorial presentation of production of concrete (a). Slaked lime paste (b) Weight batching of hemp shiv (c) Mixing of lime and shiv (d) Iron rod used for compaction (e) Compaction of concrete into the cube mould (f) Final view of hempcrete cubes.**

### 3. RESULTS & DISCUSSION

In the initial segment of the results and discussions section, the focus is directed towards the outcomes derived from the experimental phase. Subsequently, the latter portion delves into the exploration of sustainability aspects within the context of existing literature.

#### 3.1 Experimental Results & Properties of Concrete

##### 3.1.1. Weight density

The weight of cube is defined as the ratio of the weight of the cube to the volume of cube in  $\text{Kg/m}^3$ . For each cube mix composition, a set of 3 bricks was tested after 28, 56, 84 & 112 days. The size of the cube taken for weight density was  $100\text{mm} \times 100\text{mm} \times 100\text{mm}$ . The weight of the cube noted from a weighing scale with a sensitivity of 0.5 gm. The assessment of weight density plays a crucial role in evaluating both the strength and durability of concrete structures. A denser concrete typically exhibits higher strength by minimizing voids and porosity within its structure. In the context of Hempcrete, as shown in Figure 5, the weight density ranges from 651 to 511 for the H0.30 mix and 632 to 506 for the HC0.50 mix over the 28 to 112-day drying period. Notably, all these density measurements fall below the density of water. In the realm of lightweight concrete, the practical density range is typically considered to be between 500 and  $1850 \text{ kg/m}^3$ . The cube mix composition HC0.30 exhibits maximum density, while the lowest density is observed in HC0.50. As the quantity of shiv increases and lime decreases in successive mixes, the density decreases. A crucial observation is that over time, there is minimal reduction in weight density attributable to lime's slower setting rate.


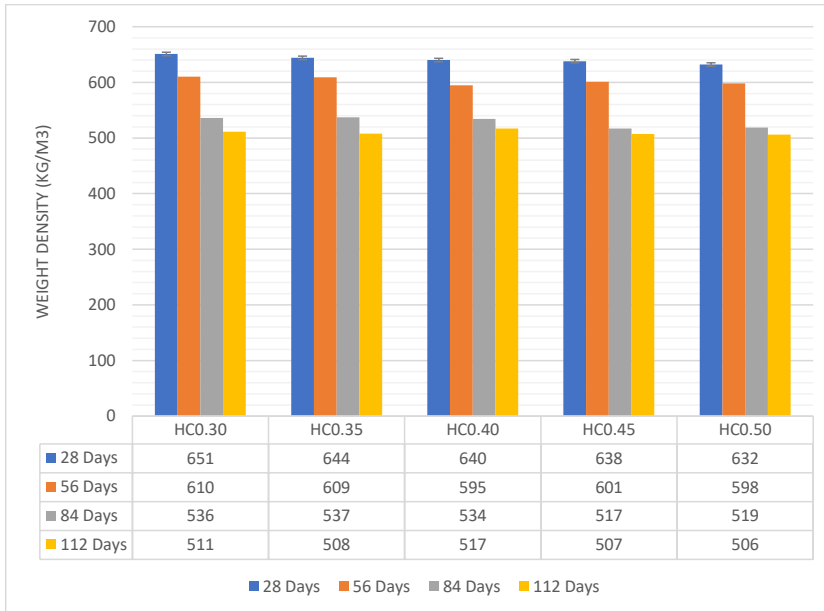


Figure 5. Demonstrate the weight density of concrete at different days

### 3.1.2. Water Absorptions

The water absorption test provides insights into the internal structure of concrete. Typically, materials with higher porosity tend to absorb more water. Hempcrete is a very porous material, hence its results for water absorption were quite high. The test results revealed that the hempcrete mix HC 0.30 resulted in a minimum absorption rate of 86%, whereas the HC 0.50 mix showed a maximum water absorption rate of 117%, as displayed in Figure 6.

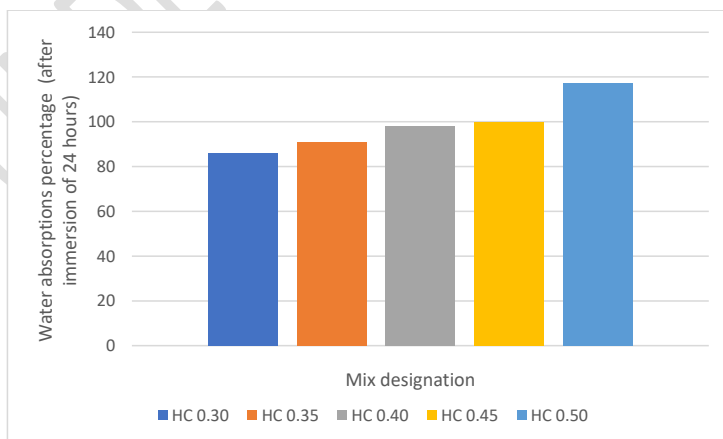


**Figure 6. Water absorptions of hempcrete**

### 3.1.3. Compressive strength

The ability of a material to support weight and withstand deformation in the presence of compressive stress is known as its compressive strength. The samples were dried in natural condition at 28, 56, 84, and 112 days and then tested in compression mode using a Universal Testing Machine SERVO 200 kN at loading rate of 0.10kN/min. The HC0.30 mix with the highest content of lime showed a maximum compressive strength of 0.810 MPa for 112 days. At 28 days' time period, mix HC0.50 exhibited minimum strength of 0.51 MPa shown in table 5. Hempcrete displayed ductile properties by avoiding brittle cracking (shown in figure 7).

**Table 5. Compressive strength of cube at different days**

Specimen Code	28D	56D	84D	112 D
HC 0.30	0.617	0.791	0.717	0.810
HC 0.35	0.584	0.591	0.634	0.765
HC 0.40	0.594	0.677	0.680	0.735
HC 0.45	0.526	0.555	0.593	0.663
HC 0.50	0.510	0.548	0.619	0.673

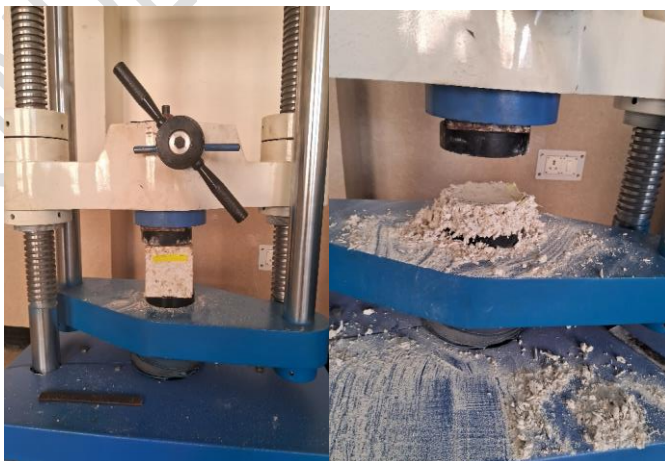

**Figure 7. Cube under compression (b) Cube after compressive test**

### **3.2 Review of Literature on Sustainability of Hempcrete**

Assessing the sustainability of hempcrete involves initially examining the individual benefits of hemp and lime. Subsequently, it entails exploring the unique advantages of combining hemp and lime in hemp concrete.

#### **3.2.1. Hemp**

Hemp (*Cannabis Sativa L.*) is a multipurpose crop that can be cultivated for either [fiber](#), seed or cannabidiols and building material. The 21<sup>st</sup> century has seen an increase in the demand for hemp and its products. Over the past 20 years, most countries have legalized the growing of industrial hemp, which has sparked a lot of research into the health advantages of hemp and products derived from it. In India, the states of Uttarakhand and Uttar Pradesh currently allow the cultivation of hemp; Madhya Pradesh, Manipur, and Himachal Pradesh will follow suit. Hemp is a multidimensional crop or plant, as all the parts can be used commercially. Its [fibers](#) are strong and pliable. And hemp seeds are valued for their high content of micro- and macronutrients such as potassium, iron, and zinc [7]. Hemp cultivation can be achieved with minimal or no reliance on chemical pesticides or fertilizers, offering the potential to substantially decrease the environmental carbon footprint. The rise in public health awareness during the COVID-19 pandemic has [fuelled](#) the growth of the hemp industry. Hemp is versatile, with its stalks, seeds, and leaves being utilized to create a wide range of products such as building materials, fabrics, paper, food, furniture, cosmetics, and medical supplies. Moreover, bioplastics, biofuels, and biopesticides are among the most extensively researched and discussed applications of the hemp plant [8]. bio-based building materials derived from hemp offer several advantages over traditional building materials. These advantages include being lightweight, fireproof, self-insulating, pest-resistant, and cost-effective in production [9].

#### **3.2.2. Lime**

Lime is a naturally occurring material found in the form of limestone ( $\text{CaCO}_3$ ). When heated in a lime kiln at approximately  $900^\circ\text{C}$ , it transforms into quicklime (calcium oxide,  $\text{CaO}$ ), which can be used directly from the kiln or slaked to produce hydrated lime [ $\text{Ca}(\text{OH})_2$ ] or lime putty, depending on the amount of water added. Lime mortar offers several eco-friendly advantages over conventional options like cement. In the realm of environmentally friendly construction materials, lime emits fewer greenhouse gases during production due to lower energy requirements compared to cement. Additionally, through a process known as carbonation, lime absorbs  $\text{CO}_2$  throughout its lifespan, a phenomenon referred to as carbon sequestering. This process helps offset the initial carbon emissions from the production stage.

In the earliest construction work, lime was used as mortar to join building blocks, such as bricks, stones, and concrete masonry units. Among all the binders available in the past, the oldest one was lime mortar

[10]. Lime-based mortars are well known for their excellent performance in conserving buildings. Currently, they are popularly used in restoring old buildings and rehabilitating historic masonry [11].


Rich lime (calcium oxide) is more appropriate for use in hemp than cement. The Ph of lime protects the hemp shives from mould and bacteria (antiseptic) for a long time [12]. One of the limitations of lime is its slow setting rate, leading to gradual solidification and strength development. Consequently, with urbanization, industrialization, and advancements in the construction industry, cement gained popularity in the 12<sup>th</sup> century due to its rapid setting rate and superior mechanical strength. This led to a reduced demand for lime [13].

### 3.2.3. Hempcrete

Hempcrete offers numerous sustainable advantages as a building material, but it is non-load-bearing and should be used in conjunction with a load-bearing wooden frame. The sustainability aspects of hempcrete can be further explored in terms of thermal conductivity, hygrothermal properties, and environmental credibility. Thermal conductivity (k value) describes a material's capacity to conduct heat. Heat transfer by conduction happens when energy passes within a material without any motion of the material. Lower k values indicate lower conductivity and higher insulating properties for the material. Hempcrete typically exhibits a thermal conductivity ranging from 0.06 to 0.18 W/m.K for densities of 200 to 800 kg/m<sup>3</sup> [14], whereas traditional concrete has thermal conductivity values between 1.33 W/mK and 1.95 W/m.K at 20°C, which is significantly higher [15].

Hempcrete present excellent hygrothermal behaviour or properties. The term "hygrothermal properties" of a material pertain to the alterations in its physical characteristics resulting from the combined absorption, retention, and release of heat and moisture in either liquid or vapor form. Hempcrete demonstrates a high specific heat capacity value of approximately 1500 J/kg.K in a dry state, which can increase to over 2900 J/kg.K at 95% relative humidity [16]. The elevated specific heat capacity values of hempcrete indicate that more energy is needed to alter its temperature. This property enables hempcrete to offer thermal comfort indoors even when external temperatures rise.

One square meter of lime hemp concrete wall stores between 14 and 35 kg of Co<sub>2</sub> over its lifespan of 100 years. This is due to Co<sub>2</sub> storage in the hemp and construction wood, but also in the lime, which catches up Co<sub>2</sub> as it sets [17]. Another significant finding concerning hempcrete blocks reveals that the net carbon emission of hempcrete blocks was recorded at -48.36 kg CO<sub>2</sub>eq/m<sup>3</sup> illustrated in figure 8. [18].

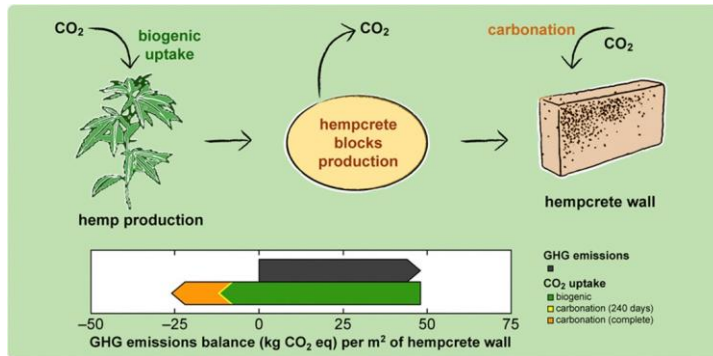

**Figure 8: Illustration of the carbon emissions and sequestration of hempcrete, showcasing a net emissions balance that demonstrates carbon negativity**

#### 4. CONCLUSION

The present paper discusses the physical and mechanical properties of hempcrete through a series of experiments. It highlights that hempcrete is a lightweight, porous material with a higher water absorption ratio. Additionally, the study indicates that the compressive strength of hempcrete does not exhibit significant improvement over time, suggesting that it may not be suitable for direct use as a load-bearing material in building construction.

The sustainability aspect of hempcrete is further illuminated through a literature review, offering valuable insights into its environmental benefits. The examination reveals that hempcrete boasts a low thermal conductivity and a high specific heat capacity, enhancing its thermal insulation properties and ensuring comfortable indoor environments. Moreover, the lifecycle assessment of hempcrete classifies it as a carbon-negative material, indicating that it has minimal impact on the environment. These findings underscore the eco-friendly attributes of hempcrete and its potential to contribute positively to sustainable construction practices.

**Commented [DAH5]:** Good for sustainable development

#### 5. REFERENCES

1. **Pandey M, Nautiyal BP and Kumar N.** Sustainability improvement of traditional cropping system in Uttarakhand, India, through intercropping with medicinal and aromatic plants. *Current Science*. 2019;117(8): 1281-1285.
2. **Busbridge R and Rhydwen R.** An investigation of the thermal properties of hemp and clay monolithic walls. 2010. In '5<sup>th</sup> Annual Conference of Advances in Computing and Technology (AC&T)' at University of East London, during September 25-28:163-170.

**Commented [DAH6]:** If the "Referencing" is not unique to specialized areas in sciences, I think APA style is more standard.

3. Singh M, & Sardesai M.M. Cannabis sativa (Cannabaceae) in ancient clay plaster of Ellora Caves, India. *Current Science*. 2016;110(5): 884-891 <https://doi.org/10.18520/cs/v110/i5/884-891>.
4. **Steve Allin**. *Building with Hemp*. 2<sup>nd</sup> ed. Seed press, Kerry, Ireland; 2005.
5. **Pietruszka B et al**. Characterization of Hemp-Lime Bio-Composite. 2019. In 'IOP Conference Series: Earth and Environmental ~~Science:CentralScience: Central~~ Europe towards Sustainable Building (CESB-2019) at Prague, Czech Republic during July 2–4.
6. **Benfratello S, Capitano C, Peri G, Rizzo G, Scaccianoce G, & Sorrentino G**. Thermal and structural properties of a hemp–lime bio composite. *Construction and Building Materials*. 2013; 48:745–754.
7. **Rehman MSU, Rashid N, Saif A, Mahmood T, & Han J**. Potential of bioenergy production from industrial hemp (Cannabis sativa): Pakistan perspective. *Renewable & Sustainable Energy Reviews*, 2013;18: 154 164. <https://doi.org/10.1016/j.rser.2012.10.019>
8. **Nath MK**. Benefits of Cultivating Industrial Hemp (Cannabis sativa ssp. sativa)—A Versatile Plant for a Sustainable Future. *Chemistry Proceedings*. 2022;10(1):14. doi:<https://doi.org/10.3390/IOCAG2022-12359>.
9. Crini G, Lichtfouse E, Chanet G, & Morin-Crini N. Applications of hemp in textiles, paper industry, insulation and building materials, horticulture, animal nutrition, food and beverages, nutraceuticals, cosmetics and hygiene, medicine, agro-chemistry, energy production and environment: a review. *Environmental Chemistry Letters*. 2020;18(5):1451–1476. <https://doi.org/10.1007/s10311-020-01029-2>
10. Veiga R. Air lime mortars: What else do we need to know to apply them in conservation and rehabilitation interventions? A review. *Construction & Building Materials*. 2017;157: 32–140. <https://doi.org/10.1016/j.conbuildmat.2017.09.080>
11. Maravelaki-kalaitzaki P, Bakolas A, Karatasios I, & Kilikoglan V. Hydraulic lime mortars for the restoration of historic masonry in Crete. *Cement & Concrete research*. 2005;35(8):1577-1586.
12. Evard A & De Herde A. Bioclimatic Envelops made of lime and hemp concrete. 2005. In 'International Scientific Conference Cycle for a Sustainable Energy Transition in the built environment' at Lausanne, Switzerland, during. September 3-5.
13. Olaniyan SA. Towards reviving lime-based mortar utilisation as a sustainable building material: An imperative for review of the existing building standards. *International Journal of Scientific & Engineering Research*. 2018;9(9):1901-1910.
14. Laurent A & Etienne G. Mechanical and thermal properties of hemp concretes. 2012. In 'International Inorganic-bonded ~~fiber~~ composites conference at Acton, Australia, during September 10-14.
15. Misri Z, Ibrahim MHW, Awal ASMA, Desa MSM, & Ghadzali NS. Review on factors influencing thermal conductivity of concrete incorporating various type of waste materials. *IOP Conference Series. Earth and Environmental Science*. 2018;140: 012141. <https://doi.org/10.1088/1755-1315/140/1/012141>

16. Arnaud Evard. \_Transient Hygrothermal Behaviour of Lime-Hemp Material. Thesis, Doctor of philosophy. 2008. Universite Catholique de Louvine, Belgium. French.
17. Boutin MP, Flamin C, Quinton S, Gosse G, & Inra L. Étude des caracteristiques environnementales du chanvre par l'analyse de son cycles de vie. Ministère de l'Agriculture et de la Pêche. 2006. French.
18. Arrigoni A, Pelosato R, Melià P, Ruggieri G, Sabbadini S, & Dotelli G. Life cycle assessment of natural building materials: the role of carbonation, mixture components and transport in the environmental impacts of hempcrete blocks. Journal of Cleaner Production. 2017;149:1051–1061. <https://doi.org/10.1016/j.jclepro.2017.02.161>

UNDER PEER REVIEW