

1
2
3
4
5
6
7
8
9

Evaluation of Bond Strength of a Bioactive Adhesive System Associated with Ozonated Water on Enamel Preconditioned with Phosphoric Acid

10
11

ABSTRACT

Aims: To evaluate the effectiveness of ozonated water as a cavity cleaning solution in combination with a bioactive adhesive system on bond strength to enamel, compared to distilled water, after different storage times.

Study Design: Experimental in vitro study.

Place and Duration of Study: Department of Restorative Dentistry, State University of West Parana, Cascavel, Parana, Brazil, between September 2022 and August 2023.

Methodology: Bovine anterior teeth were divided into four groups: AD24h (distilled water and 24-hour storage), AO24h (ozonated water and 24-hour storage), AD30D (distilled water and 30-day storage), and AO30D (ozonated water and 30-day storage). After cavity cleaning, a bioactive adhesive system and composite resin were applied. Three bioactive composite resin cylinders were light-cured on each tooth using a LED light device. Microshear bond strength was tested with a testing machine (EMIC) at a speed of 1 mm/min using a 50N load cell. Statistical analysis was performed using the non-parametric Wilcoxon test ($p < 0.05$).

Results: Ozonated water significantly increased bond strength to enamel after 24 hours ($p < 0.05$). However, after 30 days, no significant differences in bond strength were observed between ozonated water and distilled water groups.

Conclusion: Ozonated water enhances initial bond strength to enamel but its effect diminishes over time. These findings suggest the need for improved adhesion techniques to achieve long-term durability in dental restorations.

12
13
14
15
16
17
18
19

Keywords: Bond Strength, Bioactive Adhesive System, Ozonated Water, Acid Conditioning, Microshear Bond Strength, Dental Restorations, Adhesion Durability.

20
21

1. INTRODUCTION

22
23
24
25

Before the advent of adhesive systems, the success of dental restorations was directly related to mechanical retention mechanisms. The development of bonding systems, coupled with the rise of minimally invasive dental procedures, has led to restorative techniques that allow greater preservation of healthy dental structure. Consequently, these materials have become highly relevant in various clinical applications [1].

26 Adhesive systems are responsible for promoting the adhesion of restorative materials to dental substrates
27 (Oliveira et al., 2010). These compounds can be classified according to the different adhesive strategies used on dental
28 structures into three main categories: conventional adhesives, self-etching adhesives, and, more recently, universal
29 adhesives [1].

30 Conventional adhesives, also known as total-etch adhesives, are characterized by the preliminary and isolated
31 application of phosphoric acid on dental structures. In enamel, conditioning with this strong acid promotes
32 demineralization and the consequent creation of microporosities, which are then filled by hydrophobic resin monomers
33 contained in the adhesive [1]. This technique facilitates optimal adhesion of the material to the substrate, making the
34 restoration in enamel durable and effective [2].

35 Adhesion of conventional systems to dentin, however, is hindered by the more organic composition of this
36 substrate, the intrinsic moisture in dentinal tubules, and the presence of the smear layer, a layer of residual microparticles
37 accumulated on dentin, which can obstruct dentinal tubules [3]. Therefore, acid conditioning in dentin must promote
38 complete removal of the smear layer, as well as demineralization of this substrate, exposing collagen fibers and allowing
39 hybridization. However, it is necessary to maintain dentin moisture to ensure efficient penetration of resin monomers
40 between collagen fibers [4].

41 Self-etching adhesives, on the other hand, do not require phosphoric acid application as they feature an acidic
42 primer that simultaneously acts as a conditioner. Although this adhesive system shows superior adhesion to dentin
43 compared to conventional systems, its effectiveness in enamel is significantly reduced. In this context, the selective acid
44 etching technique of enamel, which involves applying phosphoric acid to dental enamel, is used to promote selective
45 demineralization of this substrate, optimizing the adhesion of self-etching adhesives [4]. Additionally, universal adhesives
46 have a pH similar to mild and very mild self-etching adhesives, providing lower adhesion strength in enamel, and have a
47 composition similar to adhesives that contain functional monomers that chemically bond to calcium in hydroxyapatite
48 [1,10,11].

49 Furthermore, cavity cleaning is a crucial procedure for the success of restorative treatments. Removal of residual
50 debris from cavity preparation promotes better interaction between the material and the dentin substrate, increasing bond
51 strength and reducing microleakage of the restoration, thus prolonging its durability [5]. Among the main dentin cleaning
52 agents used in clinical practice are 2% chlorhexidine, EDTA, and saline solution. Chlorhexidine is an extensively used oral
53 antiseptic due to its broad antibacterial spectrum and low toxicity. Ethylenediaminetetraacetic acid (EDTA) is a chelating
54 agent that forms a stable, soluble complex with dentin calcium, making it useful in removing the smear layer [6]. In this
55 context, the use of ozonated water for dentin cleaning is an emerging strategy in dentistry. The performance of this
56 solution compared to traditional cleaning agents shows similar results in bond strength with adhesive systems [7].

57 The recent advent of bioactive adhesives represents an interesting alternative for increasing the longevity of
58 dental restorations. These materials have the ability to neutralize metalloproteinases, enzymes involved in the
59 degradation of collagen fibers in the hybrid layer. Thus, bioactive adhesive systems biologically modify the dentin
60 structure, promoting remineralization of the substrate and controlling microbial growth, enhancing the stability of the
61 adhesive interface [8].

62 In conclusion, the clinical relevance of adhesive systems in dental practice is clear. However, despite correct
63 methodology, the use of these materials presents intrinsic limitations [7]. Therefore, the rising use of ozonated water as a
64 dentin cleaning agent and the development of bioactive resins present potential alternatives to improve bonding
65 interfaces, extending the longevity of restorative treatments. Thus, the hypothesis of this project is that the use of a
66 bioactive adhesive system associated with ozonated water may yield superior results compared to conventional systems
67 when applied to enamel with prior phosphoric acid conditioning. Therefore, the aim of this study is to evaluate the bond
68 strength using microshear testing of a bioactive adhesive system associated with ozonated water in enamel conditioned
69 with phosphoric acid.

72 2. METHODOLOGY

74 2.1 Sample Size Calculation

75
76 Using a randomized design with the Bioestat 5.3 software, a minimum sample size of 6 teeth per group was
77 determined, considering a power analysis of 90% and a standard error of 0.01. To ensure result reliability, a total of 40
78 teeth were randomly distributed among four groups based on the cleaning solution.

79 2.2 Sample Preparation

Forty bovine anterior teeth, sourced from a local slaughterhouse, were freshly extracted and sectioned with high-speed rotation and abundant refrigeration using a diamond tip, No. 4138 (KG Sorensen), separating the crowns from the roots. The crowns were fixed in standardized PVC tubes with a diameter of 25 mm and a height of 15 mm using acrylic resin, leaving the vestibular surface exposed. The materials used were:

Table 1. Description and Composition of Materials Used

Material	Composition	Method of use
FL Bond II Adhesive – SHOFU	Two-step self-etch adhesive system, consisting of an acidic primer and adhesive.	Step 1: Apply the primer carefully to the dentin and enamel surfaces. Allow it to sit for 10 seconds and dry with an oil-free air jet for 5 seconds (no rinsing). Step 2: Apply a homogeneous layer of the adhesive over the entire surface. Light-cure for 10 seconds with a halogen light or 5 seconds with LED.
Beautifil Bulk Flowable Composite – SHOFU	Bulk injectable composite resin with Giomer bioactive technology.	Apply in 2 mm layers and light-cure for 20 seconds with LED.

2.3 Preparation of Ozonated Water

Ozonated water at 4 ppm was prepared at room temperature ($25^{\circ}\text{C} \pm 1.0^{\circ}\text{C}$) and used within 5 minutes \pm 1.0 minute of preparation, using an ozone generator (Ozone&Life®/O&L3.0RM, São José dos Campos, SP, Brazil) that uses pure oxygen from a cylinder, connected to a glass tower (1L/min). The amount of ozone in the water was measured by direct iodometric titration, as recommended by the International Ozone Association (IOA), which involves adding 50 ml of 1 N potassium iodide (KI) solution to the ozonated water. The chemical reaction results in the oxidation of KI by ozone, releasing iodine (I₂), as per the equation $\text{O}_3 + 2 \text{KI} + \text{H}_2\text{O} \leftrightarrow \text{I}_2 + 2 \text{KOH} + \text{O}_2$. To ensure iodine production, it was necessary to acidify the solution by adding 2.5 mL of 1 N sulfuric acid (H₂SO₄) to the KI solution. The titration was then performed with 0.01 N sodium thiosulfate (Na₂S₂O₃) until the yellow color of iodine was barely perceptible. Subsequently, 1 mL of 1% starch solution was added, and titration was continued until the blue color of the solution disappeared.

2.4 Adhesive Procedure

The FL Bond II Adhesive System (SHOFU Dental ASIA-Pacific Pte. Ltd., Kyoto, Kyoto, Japan) was used for all groups according to the manufacturer's instructions. Three composite resin cylinders were then created on the crowns of each sample. A Tygon matrix (Tygon tubing, TYG-030, Saint-Gobain Performance Plastics, Miami Lakes, FL, USA) with an internal diameter of 2 mm and a height of 2 mm was used. The matrix was positioned with the help of a clinical tweezer on the surface, and its interior was filled with Beautifil Flow Plus - F03 Composite Resin (SHOFU Dental ASIA-Pacific Pte. Ltd., Kyoto, Kyoto, Japan) in a single increment using a spatula (Thompson No. 6). Light-curing was performed with a Valo Cordless light unit (Ultradent, Indaiatuba, São Paulo, Brazil) at 1200 mW/cm² for 30 seconds.

2.5 Storage

The specimens were stored for 24 hours and 30 days at 37°C in saline solution in a bacteriological incubator. The matrix was then removed using a No. 11 scalpel blade, and microshear bond strength testing was conducted.

2.6 Microshear Testing

The samples were subjected to microshear bond strength testing using a universal testing machine (EMIC DL200MF, São José dos Pinhais, Paraná, Brazil) at a speed of 1 mm/min with a 50 N load cell. The maximum force applied to the base of the cylinders was 45 N, corresponding to 10% less than the load cell's value. The microshear bond strength was evaluated by dividing the force applied at the moment of failure by the adhesive area. The data obtained were expressed in Newtons and then converted to MegaPascals (MPa). Post-test, the maximum load values supported by the composite resin-enamel interface were used for statistical analysis.

2.7 Statistical Analysis

The obtained results were tabulated and subjected to statistical analysis using Jamovi software, version 1.2.24. Initially, the data were tested for normality using the Shapiro-Wilk test, which indicated a non-normal distribution. Subsequently, statistical tests were performed to assess the presence of statistically significant differences between groups using the Wilcoxon test ($p < 0.05$).

2.8 Fracture Pattern Analysis

The fractured composite resin-enamel interface was examined under a stereomicroscope with 100x magnification (Olympus SZ40, Shinjuku, Tokyo, Japan). The analysis of the fractures revealed three distinct types of failures. Adhesive failures (A) were characterized by the detachment occurring at the composite resin-enamel interface. Mixed (M) failures involved failures at the composite resin-adhesive-enamel interface, which included both adhesive and cohesive failures. Cohesive (C) failures were those occurring exclusively within the composite resin itself.

3. RESULTS

3.1 Bond Strength Evaluation

The obtained results were subjected to statistical analysis using the non-parametric Wilcoxon test ($p < 0.05$). Generally, the use of ozonated water resulted in higher fracture resistance when subjected to the micro-shear bond strength test at the 24-hour period compared to distilled water. However, no statistically significant difference was observed between the groups in the 30-day period.

Furthermore, an intra-group analysis showed no significant differences within the ozonated water group. In contrast, for the distilled water group, a significant difference was found in the middle third between the 30-day analysis and all 24-hour analyses, as well as in the incisal third at the 30-day analysis. Detailed results are presented in Table 2. The fractured composite resin-enamel interface was examined under a stereomicroscope with 100x magnification (Olympus SZ40, Shinjuku, Tokyo, Japan). The analysis of the fractures revealed three distinct types of failures. Adhesive failures (A) were characterized by the detachment occurring at the composite resin-enamel interface. Mixed (M) failures involved failures at the composite resin-adhesive-enamel interface, which included both adhesive and cohesive failures. Cohesive (C) failures were those occurring exclusively within the composite resin itself.

Table 2. Median values and interquartile range of micro-shear bond strength (N) over time, comparing the use of ozonated water and distilled water for cavity cleaning on enamel.

Time	24 hours			30 days		
	Cervical	Middle	Incisal	Cervical	Middle	Incisal
Distilled Water	5.71 (\pm 2.26) Aa	5.71 (\pm 4.33) Aa	3.81 (\pm 3.61) Aa	11.1 (\pm 2.4) Aab	11.6 (\pm 7.12) Ab	8.91 (\pm 9.66) Aa
Ozonated Water	11.3 (\pm 11.05) Ba	15.8 (\pm 12.85) Ba	11.7 (\pm 7.44) Ba	14.7 (\pm 8.8) Aa	10.9 (\pm 4.8) Aa	10.6 (\pm 4.57) Aa


*Different lowercase letters within the same row indicate significant differences with $P < 0.05$ in intra-group analysis using the Wilcoxon test.

**Different uppercase letters in the same column indicate significant differences with $P < 0.05$ in inter-group analysis using the Wilcoxon test.

3.2 Fracture Pattern Evaluation

A higher incidence of adhesive fractures was observed, followed by mixed and cohesive fractures. Figure 1 illustrates the types of fractures for each experimental group, considering the storage time.

Figure 1. Graph of fracture types based on the experimental group and storage time.

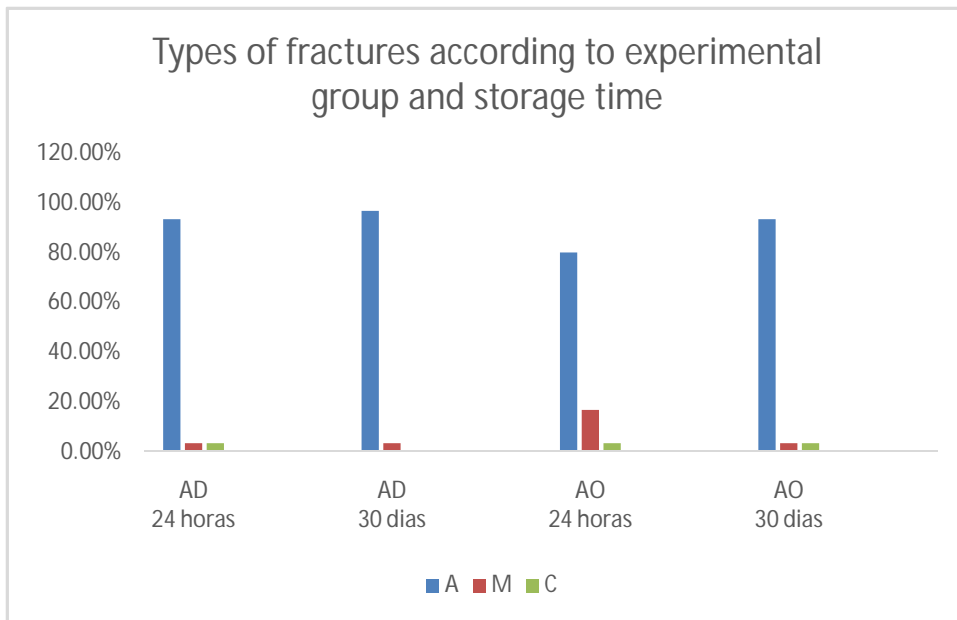

170

171

172 4. Discussion

173

174

175

176

177

178

179

180

181

182

Cavity cleaning solutions play a crucial role in the success of restorative treatment by removing debris from the tooth preparation, enhancing the adhesion of the restorative material to the tooth, and reducing microleakage of the restoration [5]. Common cavity cleaning agents in clinical practice include 2% chlorhexidine, EDTA, and saline solution. Recently, ozonated water has gained attention for its strong antibacterial action, which plays a significant role in preventing secondary carious lesions and enhancing the longevity of adhesive restorations [9]. Additionally, ozonated water has significant analgesic properties, reducing postoperative sensitivity and providing additional benefits over other cavity cleaning materials. However, recent studies indicate that despite these additional properties, ozonated water does not negatively influence the bond strength of adhesive restorations. Its performance in terms of bond strength is similar to that of traditional cleaning agents [9].

183

184

185

186

187

188

189

190

191

192

193

194

195

196

The analysis of the obtained results shows that the use of ozonated water provided significantly higher bond strength when subjected to the micro-shear bond strength test at the 24-hour period compared to distilled water. This finding suggests that ozone may have a positive effect on the initial adhesion of bioactive composite resins to dental enamel. The increase in bond strength could be attributed to the antimicrobial and oxidative properties of ozone, which may facilitate more effective cleaning of the tooth surface and thus improve the interaction between the adhesive and enamel. Moreover, the adhesive system used promotes bonding to the tooth structure through chelation with the calcium present on its surface. Therefore, the calcium exposure provided by cavity cleaning with ozonated water may have favored the formation of a more resistant adhesive interface, contributing to the superior results observed at the initial 24 hours. However, it is noteworthy that extending the storage period to 30 days did not reveal any statistically significant difference between the groups. This result corroborates findings by Celiberti et al. (2006), where the use of ozonated water as a cavity cleaning solution did not affect fracture resistance over time. Thus, the results suggest that the beneficial influence of ozone on bond strength may be more pronounced in the initial stages of adhesion but may diminish over time. This decrease could be due to degradation of adhesive components or reactivation of chemical interactions between the adhesive and the tooth substrate.

197

198

199

200

201

Additionally, intra-group analysis revealed a significant difference in the middle third between the 24-hour and 30-day analyses, as well as in the incisal third at the 30-day analysis in the distilled water group. This difference may indicate a variation in bond strength of the bioactive resin over time, specifically in the distilled water group. The variation in bond strength could be attributed to factors such as hydrolytic degradation of the adhesive or changes in the mechanical properties of the resin over time.

202

203

204

The data suggest that selecting ozonated water as a cleaning agent during the adhesion procedure may play a critical role in the initial bond strength of bioactive composite resins, with potential influence on restoration longevity. Furthermore, the antibacterial effect of ozonated water is noteworthy, as it significantly contributes to the reduction of

205 recurrent dental caries. This effect can be attributed to the oxidation potential of ozone, capable of damaging the bacterial
206 cell wall and cytoplasmic membrane.

207 The analysis of fracture types revealed that adhesive fractures were the most common across all groups, followed
208 by mixed and cohesive failures. This pattern offers valuable insight into how the tested materials responded to the use of
209 distilled water and ozonated water, as well as the impact of storage time. The predominance of adhesive fractures
210 highlights a critical area for improvement in material adhesion, emphasizing the need for advancements in adhesive
211 technologies for dental applications. The prevalence of adhesive fractures also underscores the vulnerability of the
212 adhesive interface in restorations, suggesting a need for further development of techniques and materials to enhance
213 adhesion.

214

215 **5. CONCLUSION**

216 Although the results provide valuable information on the efficacy of ozonated water as a cavity cleaning agent on
217 the bond strength of a bioactive adhesive system, this study has limitations that should be considered. The experiment
218 was conducted under controlled laboratory conditions, which may not account for the potential variabilities of clinical
219 practice. Additionally, the bond strength and fracture pattern analyses were limited to 24-hour and 30-day storage periods,
220 not allowing for an assessment of results over extended periods. Therefore, further studies are needed to evaluate the
221 longevity of these restorations over longer periods and under variable clinical conditions. This will contribute to the
222 development of more effective solutions for adhesive dental applications.

223

224 **COMPETING INTERESTS**

225 No competing interests exist.
226

227

228

229 **AUTHORS' CONTRIBUTIONS**

230

231 Maria Ritha Veiga Colognese designed the study, conducted the research, and wrote the first draft of the
232 manuscript. Poliana Maria de Faveri Cardoso and Juliana Furlan performed the statistical analysis and assisted with data
233 interpretation. Julio Katuhide Ueda and Veridiana Camilotti supervised the research activities and provided critical
234 revisions of the manuscript. All authors read and approved the final manuscript.

235

236 Disclaimer (Artificial intelligence)

237 Option 1:

238 Author(s) hereby declare that NO generative AI technologies such as Large Language Models (ChatGPT,
239 COPILOT, etc) and text-to-image generators have been used during writing or editing of manuscripts.

240 Option 2:

241 Author(s) hereby declare that generative AI technologies such as Large Language Models, etc have been used
242 during writing or editing of manuscripts. This explanation will include the name, version, model, and source of the
243 generative AI technology and as well as all input prompts provided to the generative AI technology

244 Details of the AI usage are given below:

245 1.

246 2.

247 3.

248

249

250 **REFERENCES**

251

252

253

254

1. Arinelli AMD, Pereira KF, Prado NAS, Rabello TB. Current adhesive systems. *Rev Bras Odontol.* 2016;73(3):242. Portuguese.

255

256

257

2. Detogni AC, Silva MP, Sinhoreti MAC, Ueda JK, Camilotti V. Influence of Ozonated Water Prior to the Use of Two Universal Adhesive Systems on the Bonding Strength of Bulk Fill Flow Composite Resins: In Vitro Study. *Rev Focus.* 2023;16(8)–e2758. Portuguese.

258

259

3. Rodrigues LS, Assis PSM, Martins AC, Finck N. Current adhesive systems and main challenges in adhesion: narrative review. *Res Soc Dev.* 2021;10(10). Portuguese.

260

261

4. Froehlich L, Rosin M, Mazur N, Boffo BS, Oliveira HP De, Zanchin C, et al. Adhesive Systems: A Literature Review. *Res Soc Dev.* 2021;10(2). DOI: 10.33448/Rsd-V10i2.12612.

262

263

5. Celiberti P, Pazera P, Lussi A. The impact of ozone treatment on enamel physical properties. *Am J Dent.* 2006;19(1):67–72.

264

265

266

6. Macedo PAS, Favarão J, Ueda JK, Castro ED, Detogni AC, Menolli RA, et al. Influence of Ozonated Water as an Irrigant and Dentin-cleaning Solution on the Bond Strength of Fiberglass Pins. *J Contemp Dent Pract.* 2021;22(8):876-881.

267

268

7. Froehlich L, Rosin M, Mazur N, Boffo BS, Oliveira HP De, Zanchin C, et al. Adhesive Systems: A Literature Review. *Res Soc Dev.* 2021;10(2). DOI: 10.33448/Rsd-V10i2.12612.

269

270

271

8. Neri JR. Influence of dentin biomodification strategies on the physicochemical properties of adhesive systems. UFC Institutional Repository. 2015. Accessed 12 August 2023. Available: <http://repositorio.ufc.br/handle/riufc/15521>.

272

273

274

9. Laurindo BM. Ozonated water as a dentin cleaning solution: antibacterial action and analysis of bond strength. State University of Western Paraná. 2019. Accessed 12 August 2023. Available: <https://tede.unioeste.br/handle/tede/4498>. Portuguese.

275

276

10. Akturk E, Bektas OO, Ozkanoglu SE, Akin EG. Do ozonated water and boric acid affect the bond strength to dentin in different adhesive systems?. *Nigerian journal of clinical practice.* 2019 Dec 1;22(12):1758-64.

277

278

279

11. Santos M, Leandro F, Barroso H, Delgado AH, Proença L, Polido M, Vasconcelos e Cruz J. Antibacterial Effect of Ozone on Cariogenic Bacteria and Its Potential Prejudicial Effect on Dentin Bond Strength—An In Vitro Study. *Pharmaceutics.* 2024 May 2;16(5):614.