

# **Effects of Nano-sized Particles on Mechanical Properties of Resin Dental Composites: A Review Article**

---

## **ABSTRACT**

Nanomaterials have unique physical and mechanical characteristics. The addition of nanoparticles advances the mechanical performance of polymers, because the ratio of surface area-to-volume is high. Nanoparticles are utilised to produce materials with different behaviour because of interfacial reactions. The current review compiles and discusses the available literature on the positive impact of nanoparticles on the mechanical behaviour of resin-based dental composites, in addition to the recent advancements. The effects of different types of fillers in nano-ranged size have been studied. It also presents appropriate filler quantity for the enhancement of some mechanical properties. Finally, the important role of energy dissipation mechanisms in dental composites has been emphasised.

*Keywords: Dental composites; nanoparticles; nanocomposites; mechanical properties; energy dissipation mechanisms.*

## **1. INTRODUCTION**

Composite restorative materials were evolved to overcome the shortages of silicate cement and methyl methacrylate-based resins [1]. Since the first application of dental composites in the early 1960s, numerous advances have been made [2]. Resin-based composites (RBCs) are extensively utilised in dentistry due to their satisfactory mechanical and biocompatibility properties, aesthetics and bonding ability [3]. The increased utilisation and popularity of these materials is attributed to the continuous improvements in strength, abrasion resistance, translucency, ease of manipulation and polishability [4, 5]. RBCs are used as restorations, cavity liners, sealants, core buildups, inlays, onlays, crowns, cements, orthodontic devices, root canal sealers and posts, fixed and removable dentures, and implants [6, 7]. Although the advancements of RBCs, there are multiple drawbacks continue to exist such as low mechanical properties. However, insufficient strength may lead to bulk fracture that is a common cause for short lifespan and failure of resin composite restorations [8-10].

In recent years, nanotechnology has been applied for the manufacturing of restorative materials (dental nanocomposites) [11], since the incorporation of nanoparticles (NPs) into polymers will produce new materials with advanced properties, such as hardness, diametral tensile strength, resistance to wear, fracture toughness, modulus of elasticity and flexural strength [12, 13]. These improvements are owing to the large specific surface area and rich surface functional groups of NPs [14]. In addition, due to their high free surface energy, bonds between nanoparticles themselves and other particles are very strong. Agglomeration could be eliminated by functionalising NPs which produce same surface charge and hence they repel each other [15]. The main purpose of the present review is to highlight the

research improvements made in determining the effects of the NPs on the mechanical properties of RBCs. Surface hardness, flexural strength and fracture toughness of dental nanocomposites are discussed. This review also addresses related factors (i.e., energy dissipation mechanisms) that affect the effectiveness of NPs to obtain the desired mechanical properties of the targeted composite materials.

## 2. COMPOSITION OF DENTAL RESIN COMPOSITES

Dental resin composites (DRCs) are typically consists of the following major ingredients: organic resin matrix (polymer), inorganic filler particles (such as glass, fused quartz, and silica), coupling agents, and the initiator–accelerator system. The components of the matrix include monomers, an initiator–activator system, stabilisers, and pigments. The fillers are interconnected with the matrix by a coupling agent. These basic components play a vital role in determining the performance of DRCs [16-18].


### 2.1 Resin matrix

The resin is a monomer but is activated chemically and transformed to a hard polymer through a radical addition reaction [19]. The matrix in most DRCs contains a blend of dimethacrylate monomers such as bisphenol A glycidyl dimethacrylate (Bis-GMA) and urethane dimethacrylate (UDMA) [20]. Due to the high viscosity of Bis-GMA and to facilitate handling during manipulation, it is mixed with diluents such as triethylene glycol dimethacrylate (TEGDMA), UDMA and bisphenol A polyethylene glycol diether dimethacrylate (BisEMA) [21]. The addition of the diluents improves the degree of conversion, facilitates filler addition and mixing, and thus contributing to improvement of the mechanical properties [22]

### 2.2 Filler systems

Different types of fillers have been used such as silica ( $\text{SiO}_2$ ), glass, carbon nanotubes (CNTs), alumina ( $\text{Al}_2\text{O}_3$ ), zirconia ( $\text{ZrO}_2$ ) and titania ( $\text{TiO}_2$ ) [23]. The inorganic phase in current dental composites composed of silica, quartz, borosilicate, and aluminum silicates. The filler loading usually varies between 35–70% volume percent (vol.%) or 50–85% weight percent (wt.%) [24]. The presence of filler has a positive impact on various properties, such as hardness, wear resistance, translucency, strength, coefficient of thermal expansion, overall curing shrinkage, fluids absorption, handling properties and aesthetic [25-27].


In order to improve the mechanical properties of restorative composites, changes on filler particles size and size distribution have been made [28]. Over the years, the particle size of fillers used in dental restorations has decreased from the conventional composites to the nanocomposite materials [29]. Based on the filler particle size, DRCs are classified as macrofilled (10–50  $\mu\text{m}$ ), microfilled (40–50 nm) and hybrid (10–50  $\mu\text{m}$  and 10–50 nm) [30]. Hybrid composites are classified as microhybrids and nanohybrids. Microhybrids are then divided into two types, midfill (1–10  $\mu\text{m}$  to 40 nm) and minifill (0.6–1  $\mu\text{m}$  to 40 nm) [31, 32]. Nanohybrids contain NPs and microparticles (0.1 to 2  $\mu\text{m}$  and  $\leq$  100 nm). Finally, nanofilled composites were introduced. These composites contain NPs with more even distribution (<100 nm) [33, 34]. **Error! Reference source not found..**

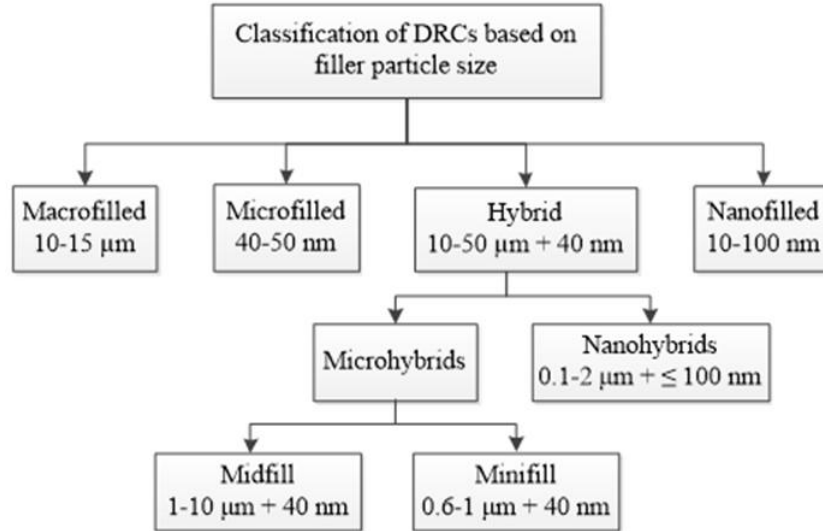

**Fig. 1. Classification of DRCs according to filler particle size**

### 2.3 Coupling agents

Due to the high surface energy of NPs, they exhibit higher tendency to agglomeration and inhomogeneous distribution [15, 35]. However, the filler dispersion and adhesion at interface have a strong impact on the mechanical properties [36]. Therefore, the treatment of filler surface with coupling agents is essential to improve the adhesion between filler and matrix [37], giving better stress distribution from matrix to fillers [38], thus improving the mechanical performance [39]. 3-methacryloxypropyltrimethoxysilane ( $\gamma$ -MPS) is the commonly applied silane coupling agent (Figure 2) in the DRCs [40].

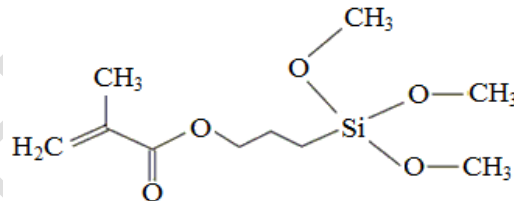

**Fig. 2. Silane coupling agent**

During silanation, the  $\gamma$ -MPS molecules bond chemically with the surface of filler particles via direct condensation between  $-OCH_3$  groups and the surface hydroxyl groups on the particles surface to form covalent bonds [41]. Another condensation occurs between the  $-OCH_3$  groups on neighbouring molecule to give a siloxane-coated particles [42]. Silanation must involve the whole surface of inorganic particles to promote improved mechanical properties. However, reduced mechanical performance has been reported due to incomplete coating of silanated fillers, which leads to agglomeration. In clinical practice, the interfacial bonding among the composite's phases is susceptible to degradation in the humid mouth environment [43].

## 3. EFFECTS OF NPS ON MECHANICAL PROPERTIES OF DENTAL COMPOSITES

### 3.1 Surface hardness

Hardness is the surface resistance to deformation caused by external load [44]. It is indication of the material's ability to resist scratching, and its ease of finishing [45]. The achievement of esthetic is based on the proper finishing and polishing. However, the presence of scratches acts to decrease the fatigue life and cause failure of restoration [46]. The hardness of resin composites is determined by their ability to resist abrasion and stay stable in the mouth fluids [47].

In general, the addition of filler particles enhances the mechanical properties of resin composites [48] due to their high rigidity and stiffness as compared to polymer matrices [27, 49]. However, the integration of a high filler content leads to particles aggregation that reduces the crosslinks between the polymer chains, and causes plastic flow in the polymer matrix, which decreases the mechanical properties [50]. Several factors could influence the hardness such as size of filler particles, weight fraction of fillers [51], type and volume of silane, method of surface treatment, degree of dispersion, and hardness of fillers, because the addition of harder particles can significantly enhance the hardness of composites [35].

A previous study evaluated the hardness of micro and nanodental composites. The results displayed that the hardness of nanocomposites filled with 40 and 50 wt% nanoparticles was higher than the microcomposites, and the highest value was recorded for the group containing 50 wt% nanoparticles [52]. Others compared the hardness of three dental composites, i.e., Filtek Z350 XT (Nanofilled, aggregated  $ZrO_2/SiO_2$  cluster and  $SiO_2$  with particle size 5–20 and 20 nm, respectively, at filler loading of 78.5 wt%), Grandio (Nanohybrid, ceramic glass and spherical  $SiO_2$  with particle size 1 $\mu$ m and 20–60 nm, respectively, at filler loading of 87.0 wt%), and Esthet X (Nanohybrid, barium boron fluoralumino silicate glass and  $SiO_2$  with particle size 0.6–0.8  $\mu$ m and 40 nm, respectively, at filler loading of 77.0 wt%). The findings showed that Grandio exhibited the highest value of hardness due to the filler particle size and filler loading, in addition to the high contact surface that observed between nanofillers and organic phase [53]. Another comparison has been performed to estimate the hardness of four dental composites, i.e., Feeling Lux (Microhybrid), Amelogen Plus (Microhybrid), Filtek Z350 (Nanohybrid) and Te-Econom Plus (Hybrid). Filtek Z350 composites presented the highest mean values of hardness due to their smallest filler particles size (5–20 nm) [54]. In another work, the hardness of nanohybrid and microhybrid composites, light cured nanoionomer, and conventional glass ionomer materials has been examined. The hardness value of nanocomposite was higher than the others owing to NPs and increased filler content [55]. These outcomes are in agreement with others who found that nanocomposites exhibited higher hardness value compared to microcomposites due to the addition of high surface area particles at high filler content [56–58].

Furthermore, the effects of surface modification of nanofillers on hardness of acrylic dental resin have been investigated. Modified and unmodified nano- $ZrO_2$  (100 nm) at different percentages (1, 3 and 5 wt%) were added to poly(methyl methacrylate) (PMMA). Surface functionalisation has been done by two types of silanes, i. e., Vinyltris(2-methoxyethoxy)silane and 3-Methacryloxypropyltrimethoxysilane. The modified particles were efficiently dispersed with an increment in cross-linking, and thus hardness increased by 46.3% and 50.7%, respectively, while the addition of unmodified particles improved hardness by 24% [59].

In a recent study, treated  $Al_2O_3$  (20 nm) and marble dust (70 nm) have been added to dental composites at concentrations of 5, 10, 15, and 20 wt%. The hardness elevated by 86% and 61% upon the inclusion of 20 wt% treated  $Al_2O_3$  and marble dust, respectively. This enhancement is due to the high percentage of hard filler, which stiffened the matrix elasticity and improved the indentation resistance. More hardness of the nano- $Al_2O_3$  composite was attributed to the stronger bonding between nano- $Al_2O_3$  and silane as compared to the bonding between marble and silane. Moreover, the strong filler-matrix interfacial adhesion is

attributed to the improved dispersion, which resulted from the reduced particle size [60]. Zidan et al. [61] attained similar results when they added ZrO<sub>2</sub> nanoparticles (30 and 60 nm) at different percentages (1.5, 3, 5, 7 and 10 wt%) to PMMA denture base. The highest value was obtained at 10 wt%. Table 1 displays the effect of nanoparticles on hardness of DRCs.

**Table 1. The improvements in hardness of nanoparticles filled dental composites**

Material	Filler	Particle size (nm)	Filler loadings (wt%)	Optimum loading	Reference
Dental composite	SiO <sub>2</sub>	20 - 50	20, 30, 40 & 50	40 & 50	(Hosseinipour et al. 2010)
	Al <sub>2</sub> O <sub>3</sub>	20	5, 10, 15 & 20	20	(Meena et al. 2019)
		20	0.5, 1, 3 & 5	5	(Alqahtani 2020)
PMMA	ZrO <sub>2</sub>	100	1,3 & 5	5	(Elmadani et al. 2018)
		30 & 60	1.5, 3, 5, 7 & 10	10	(Zidan et al. 2019)

### 3.2 Flexural strength

The flexural strength can be enhanced by incorporating ceramic fillers into the polymer matrix [62]. Increasing the inclusion content resulted in improving flexural strength [63]. In general, the mechanical characteristics of polymer composites could be affected by the filler particle size [64]. Other factors may play a role in promoting the flexural strength such as filler/matrix bonding, filler ratio [65] and conversion degree of the polymer matrix [66, 67]. Although the stiffness and strength are increased in traditional dental composites, the dimensional changes are decreased [68]. Salination can also promote filler/polymer bonding and deviate the crack propagation which leads to better flexural strength [65]. Moreover, the inclusion of nanoparticles in dental composite materials exhibited a remarkable improvement in flexural strength [69]. Previous work was performed to study the flexural strength of three dental composite materials (Filtek Z350 XT, Grandio, and Esthet X) [53]. The highest value was achieved by Filtek Z350 XT. The results suggest that the flexural strength is positively affected by the filler particle size and concentration. Another study was conducted to measure the flexural strength of UDMA dental composite materials mixed with glass (140 nm) at loadings of 5, 7.5 and 10 wt%. The flexural strength increased by 17.2% at filler loading of 10 wt% [70]. Nano-ZrO<sub>2</sub> particles were also added to the dental composite at different percentages (1, 2 and 3 wt%). The maximum filler level (3 wt%) displayed higher flexural strength [71]. Alqahtani [57] investigated the effect of adding various ratios (0.5, 1, 3 and 5 wt%) of hexagonal boron nitride particles (70 and 800 nm) on flexural strength of self-cured PMMA. An amount of 550% increment was recorded for PMMA composite filled with 800 nm hexagonal boron nitride at 5 wt%. **Error! Reference source not found.** shows the improvements in flexural strength of dental polymer composites filled with various ratios of nanoparticles. Overall, low NPs loadings could enhance the flexural strength of dental polymer composite. Selection of filler particle size should be done according to the characteristics influenced by the filler content e.g., curing contraction and viscosity. Polymer structure turns out to be another factor that has a marked impact on flexural strength.

**Table 2. Improvements in flexural strength with increasing nanoparticles loading**

Material	Filler	Particle size (nm)	Filler loadings (wt%)	Optimum loading	Reference
Dental composite	Al <sub>2</sub> O <sub>3</sub>	25 - 40	10, 20 & 30	30	(Foroutan et al. 2011)
	Glass	140	5, 7.5 & 10	10	(Monfared & Bahrololoom 2016)
	ZrO <sub>2</sub>	-	1, 2 & 3	3	(Kumar et al. 2018)
PMMA	Hexagonal boron nitride	800	0.5, 1, 3 & 5	5	(Alqahtani 2020)

However, reduced flexural strength with the further rise in filler ratio has been reported. Hosseinalipour et al. [52] compared the flexural strength of dental composites mixed with nano-sized SiO<sub>2</sub> (20–50 nm) at different concentrations (20, 30, 40 and 50 wt%) and dental composite mixed with micro-sized SiO<sub>2</sub> (10–40 μm) at a concentration of 60 wt%. They inferred that the nanocomposites showed greater flexural strength than the microcomposite. However, the highest value was obtained at 40 wt%, then decreased at 50 wt%. In another study, Liu et al. [72] added nano-SiO<sub>2</sub> to dental composite at concentrations of 0.5, 1, 1.5 and 2 wt%. The highest flexural strength was obtained via 1 wt% nanofiller. When a higher amount of nanoparticles were impregnated, the flexural strength was reduced. This behaviour was also observed by Kundie et al. [73], who added Al<sub>2</sub>O<sub>3</sub> nanoparticles (7 nm) at different loadings (0.13, 0.25 and 0.5 wt%) to the PMMA denture base. The maximum value was reached at 0.13 wt% and then dropped. Another study also stated that the incorporation of 1 wt% TiO<sub>2</sub> nanoparticles into PMMA improved the flexural strength, and then decreased at a filler ratio of 2 wt% [74]. The decreases in flexural strength of dental composites beyond optimum nanoparticles loading are summarised in **Error! Reference source not found.** Inferior flexural strength with high filler content can be ascribed to aggregation of NPs which leads to stress concentration and alterations in the elastic modulus of the matrix and accelerating the crack pathway due to partial embedding of the fillers in the polymer [74, 75].

**Table 3. Decreases in flexural strength of dental composites beyond optimum nanoparticles loading**

Material	Filler	Particle size (nm)	Filler loadings (wt%)	Inferior loadings	Reference
Dental composite	SiO <sub>2</sub>	20 - 50	20, 30, 40 & 50	50	(Hosseinalipour et al. 2010)
		30	0.5, 1, 1.5 & 2	1.5 & 2	(Liu et al. 2014)
PMMA	TiO <sub>2</sub>	15 - 40	1 & 2	2	(Chen et al. 2019)
	Al <sub>2</sub> O <sub>3</sub>	7	0.13, 0.25 & 0.5	0.25 & 0.5	(Kundie et al. 2018)

### 3.3 Fracture toughness

Fracture toughness ( $K_{IC}$ ) is an essential characteristic of a material to anticipate the strength in the existence of a crack [76]. It is assigned to be one of the most crucial mechanical attributes of any dental material [77]. It can be defined as the energy absorbed by the material during deformation before fracture due to crack propagation [78]. In another word, it is a measure of the energy required to propagate a crack from an existing defect [79].

However, it differs from strength, in that it is an inherent property of a material, and therefore its value should be independent of testing modality or specimen geometry [80].

The inclusion of fillers in the polymer matrix improves tensile strength, modulus of elasticity and fracture toughness [81]. The influence of filler on the  $K_{IC}$  probably happens due to the cracks propagation around filler particles through the polymer matrix. A higher filler ratio encourages larger compression of the polymer, leading to a decrease in the force applying on filler particles thereby inhibiting the crack propagation [63]. Accordingly, greater  $K_{IC}$  could be attained by increasing the filler content [79].

In addition, the size of the filler particles has a distinctive influence on the mechanical behaviour of polymer composite materials [64]. Fu et al. [82] stated that particle size considerably influenced the  $K_{IC}$  of polymer composite materials. The incorporation of nanofillers into RDCs leads to substantial changes in mechanical properties [83]. Nanofillers can be uniformly distributed in the polymer matrix, which enhances  $K_{IC}$  in comparison with micro-composites [84]. As stated by Yeli et al. [85], dental nanocomposites displayed improved  $K_{IC}$ . This is in agreement with Zhou et al. [32], who revealed that nanocomposites exhibit remarkably greater fracture toughness than micro-composites. Another work was carried out to compare the  $K_{IC}$  of nanohybrid and microhybrid composites, light-cured nanoionomer, and conventional glass ionomer materials. The result was 1.75, 1.52, 1.27 and 0.83 MPa.m<sup>1/2</sup>, respectively. The  $K_{IC}$  of the nanocomposites was greater than other dental composites. The fracture toughness of nanohybrid is improved because of the higher filler level and nanoparticle constituents [55].

Salination and NPs increase the  $K_{IC}$  of dental composite materials by enhancing the bonding between the NPs and organic matrix through a greater surface area and superior particle strength [86]. In addition to the crack extension that occurs via several possible toughening mechanisms, like, crack deflection and crack bridging [84, 86, 87]. An earlier study by Hosseinalipour et al. [52] evaluated the fracture toughness of dental polymer composites containing silanated SiO<sub>2</sub> particles (20–50 nm) at different loadings (20, 30, 40 and 50 wt%). The control group was containing 60 wt% SiO<sub>2</sub> particles with sizes ranging from 10–40 µm. The fracture toughness values increased gradually as filler loading increased, then decreased when reached 50 wt%. The maximum fracture toughness value was 1.43 MPa.m<sup>1/2</sup> that obtained at 40 wt% filler content, whereas the control group achieved 1.07 MPa.m<sup>1/2</sup>. Another study indicated that the impregnation of 70 wt% of silanated porous SiO<sub>2</sub> (12 nm) to dental polymer composite, substantially enhanced the fracture toughness [88]. One study found that adding silanated SiO<sub>2</sub> particles with the average size of 12 nm, at different percentages (0.25, 0.50, 0.75 and 1 wt%) considerably improved the  $K_{IC}$  of PMMA for fixed interim restorations. The fracture toughness was reduced steadily by raising the nano-SiO<sub>2</sub> ratio. The highest value was recorded at a filler content of 0.25 wt% [12]. Similarly, other researchers found that adding silanated nano-SiO<sub>2</sub> particles (12 and 40 nm) with loadings of 15, 20, 25, 30 wt% and 25, 35, 45, 50, 53 wt%, respectively, improved the  $K_{IC}$  of dental polymer composites. The findings revealed the  $K_{IC}$  is improved due to a higher filler level. The optimal increase is reached by both groups, i.e., 12 and 40 nm (25 and 50 wt%, respectively), and then decreased with an increase in nanofiller content up to 30 and 53 wt%, respectively. In general, the fracture toughness of the composite group filled with 12 nm SiO<sub>2</sub> was higher than the composite group filled with 40 nm SiO<sub>2</sub>. They concluded that the  $K_{IC}$  of the dental composite could be affected by the filler size. Rougher materials can be attained by using a smaller filler size [89]. A similar occurrence was observed when nano-Al<sub>2</sub>O<sub>3</sub> particles (7 nm) mixed at different loadings (0.13, 0.25, 0.5, 1, 2 and 5 wt%) with a PMMA denture base. The fracture toughness improved with a higher filler level to a maximum and then dropped. The composite loaded with 0.5 wt% filler exhibited the highest fracture toughness [73]. The improvements in  $K_{IC}$  of dental nanocomposite are shown in Table 4. The  $K_{IC}$  of nanocomposites depends on the filler levels and the particle size. Composites with lower aspect ratio NPs have higher fracture toughness than that of higher aspect ratio NPs.

**Table 4. The improvements in fracture toughness of nanoparticles filled dental composites**

Material	Filler	Particle size (nm)	Filler loadings (wt%)	Optimum loading	Reference
Dental composite	SiO <sub>2</sub>	20 - 50	20, 30, 40 & 50	40	(Hosseinipour et al. 2010)
		12	70	70	(Atai et al. 2012)
		12 & 40	(15, 20, 25 & 30) and (25, 35, 45, 50 & 53)	25 & 50	(Barghamadi et al. 2018)
PMMA	SiO <sub>2</sub>	12	0.25, 0.50, 0.75 & 1	0.25	(Topouzi et al. 2017)
	Al <sub>2</sub> O <sub>3</sub>	7	0.13, 0.25, 0.5, 1, 2 & 5	0.5	(Kundie et al. 2018)

#### 4. ENERGY DISSIPATION MECHANISMS

Some energy dissipation mechanisms have a remarkable effect on crack suppression [90]. The possibility of a particle being hit by a crack in a favourable direction for energy dissipation rises with a greater level of the filler [91]. The fracture toughness increases due to the good filler/matrix interfacial strength and high mechanisms of energy dissipation like the deflection of the crack and filler/matrix detachment [92]. The composite material becomes tougher as the crack grows, and resists the catastrophic failure [80]. The inclusion of micro- and nanofillers enhanced fracture toughness. The particles of the filler offer toughening via improved energy dissipation through crack propagation like, crack bridging, pinning and deflection [93].

##### 4.1 Crack bridging

The fracture toughness of polymer nanocomposites can be enhanced by one of the principal mechanisms such as crack bridging [94]. When nanofiller link both sides of the fracture, it might either fracture or pull out from one of the surfaces. Such criteria depend on the interfacial strength, embedded length, flexibility of nanofiller and angle to fracture surface. Therefore, the bridging mechanism is very crucial in promoting the  $K_{IC}$  of polymer composite materials. Lohbauer et al. [91] stated that crack bridging is one of the toughening methods that active in dental composite materials.

##### 4.2 Crack pinning

The stress at the crack tip can be less localised due to the existence of adjoining particles in polymer composites. Energy dissipation can happen by a crack pinning leading to a greater fracture resistance [95]. Alternatively, a propagating crack can be pinned by the particles which results in the crack front to "bow" among the filler particles, thus enhancing the  $K_{IC}$  [96]. Yadav and Gangwar [97] reported that the increase in the  $K_{IC}$  is related to the crack pinning and crack deflection effect of NPs. The energy dissipation methods advanced through crack propagation provides developed fracture toughness.

##### 4.3 Crack deflection and branching

Deflection of crack at particle was recommended to have a prominent effect in the toughening. According to the theory proposed by Faber and Evans [98], when a crack approaches an obstacle, it is tilted and twisted out of the initial plane [99]. This increases the

roughness of the fracture surface due to non-planar cracks, thus resulting in increased fracture toughness [100]. For fracture toughness and initial fracture strength, dental composite materials reinforced with greater particle size proved superior products because of the deflection of the crack [101]. According to Lohbauer et al. [91], the underlying energy-dissipating mechanisms in dental resin composites are crack branching and crack deflection.

#### **4.4 Particle–matrix interface**

The interface has a critical effect on deformation behaviour so that under the strong bonding conditions high amounts of energy will be consumed at the interface of the particle and matrix [70]. The strong interfacial allows load transfer leading to the improved mechanical performance of the dental polymer composite. The impact property and crack propagation resistance are affected by the interface adhesion strength. These failure mechanisms led to high energy absorption as a result of dissipation during the propagation of the crack [102].

### **5. CONCLUSIONS**

The effects of the size of filler particles on the mechanical behaviour of dental composite materials are quite challenging because most studies were performed to determine the influence of varying one parameter. Though from the cited literature, it could be concluded that the addition of nanofillers produces improved mechanical characteristics for DRCs. Enhancing the bond strength between filler particles and the matrix is the main point for promoting mechanical performance, which could be attained with the functionalisation of the filler surface by a coupling agent. Energy dissipation mechanisms can take place in DRCs. Filler particles offer toughening via improved energy dissipation mechanisms through the propagation of the crack. These toughening mechanisms ensure better mechanical properties of dental composites.

#### **COMPETING INTERESTS DISCLAIMER:**

Authors have declared that no competing interests exist. The products used for this research are commonly and predominantly use products in our area of research and country. There is absolutely no conflict of interest between the authors and producers of the products because we do not intend to use these products as an avenue for any litigation but for the advancement of knowledge. Also, the research was not funded by the producing company rather it was funded by personal efforts of the authors.

#### **REFERENCES**

1. Nikolaidis AK, Koulaouzidou EA, Gogos C, Achilias DS. Synthesis and characterization of dental nanocomposite resins filled with different clay nanoparticles. *Polymers*. 2019;11(4):730.
2. Fugolin APP, Pfeifer CS. New Resins for Dental Composites. *J Dent Res*. 2017;96(10):1085-91.
3. Razali R, Rahim N, Zainol I, Sharif A. Preparation of Dental Composite Using Hydroxyapatite from Natural Sources and Silica. *J Phys: Conference Series: IOP Publishing*; 2018. p. 012050.
4. Fleisch AF, Sheffield PE, Chinn C, Edelstein BL, Landrigan PJ. Bisphenol A and related compounds in dental materials. *Pediatr*. 2010;126(4):760-8.

5. Arun D, Adikari Mudiyansele D, Gulam Mohamed R, Liddell M, Monsur Hassan NM, Sharma D. Does the Addition of Zinc Oxide Nanoparticles Improve the Antibacterial Properties of Direct Dental Composite Resins? A Systematic Review. *Mater*. 2021;14(1):40.
6. Furtos G, Silaghi-Dumitrescu L, Lewandowska K, Sionkowska A, Pascuta P. Biocomposites for orthopedic and dental application. *Key Eng Mater: Trans Tech Publ*; 2015. p. 261-75.
7. Petropoulou A, Pantzari F, Nomikos N, Chronopoulos V, Kourtis S. The use of indirect resin composites in clinical practice: A case series. *Dent*. 2013;3(3).
8. Subramani K, Ahmed W. *Nanobiomaterials in Clinical Dentistry*. 2nd ed: Elsevier; 2019.
9. Chen L, Yu Q, Wang Y, Li H. BisGMA/TEGDMA dental composite containing high aspect-ratio hydroxyapatite nanofibers. *Dental materials: official publication of the Academy of Dent mater*. 2011;27(11):1187-95.
10. Powers JM, Wataha JC. *Dental Materials - E-Book: Properties and Manipulation*. Elsevier Health Sciences; 2015.
11. Khurshid Z, Zafar M, Qasim S, Shahab S, Naseem M, AbuReqaiba A. Advances in nanotechnology for restorative dentistry. *Mater*. 2015;8(2):717-31.
12. Topouzi M, Kontonasaki E, Bikiaris D, Papadopoulou L, Paraskevopoulos KM, Koidis P. Reinforcement of a PMMA resin for interim fixed prostheses with silica nanoparticles. *J Mech Behav Biomed Mater*. 2017;69:213-22.
13. Seehra M. *Nanostructured Materials: Fabrication to Applications*. BoD-Books on Demand; 2017.
14. Wang X, Cai Q, Zhang X, Wei Y, Xu M, Yang X, et al. Improved performance of Bis-GMA/TEGDMA dental composites by net-like structures formed from SiO<sub>2</sub> nanofiber fillers. *Mater Sci Eng: C*. 2016;59:464-70.
15. Pratap B, Gupta RK, Bhardwaj B, Nag M. Resin based restorative dental materials: characteristics and future perspectives. *Jpn Dent Sci Rev*. 2019;55(1):126-38.
16. Ravi RK, Alla RK, Shammam M, Devarhubli A. Dental Composites-A Versatile Restorative Material: An Overview. *Indian J Dent. Sci*. 2013;5(5):111-5.
17. Alizadehgharib S, Östberg AK, Dahlgren U. Effects of the methacrylate/acrylate monomers HEMA, TEGDMA, DEGDA, and EMA on the immune system. *Clin Exp Dent Res*. 2017;3(6):227-34.
18. Subramani K, Ahmed W. *Nanobiomaterials in clinical dentistry*. 1st ed. Waltham, USA: William Andrew Publishing; 2013.
19. Noort RV, Barbour ME. *Introduction to dental materials*. 2nd ed. London, United Kingdom: Mosby Ltd.; 2015.
20. Stencel R, Pakielna W, Barszczewska-Rybark I, Żmudzki J, Kasperski J, Chladek G. Effects of Different Inorganic Fillers on Mechanical Properties and Degree of Conversion of Dental Resin Composites. *Arch Metall Mater*. 2018;63(3):1361-9.
21. Bourbia M, Finer Y. Biochemical Stability and Interactions of Dental Resin Composites and Adhesives with Host and Bacteria in the Oral Cavity: A Review. *J Can Dent Assoc*. 2018;84(i1):1488-2159.
22. Emami N, Söderholm K. Young's modulus and degree of conversion of different combination of light-cure dental resins. *Open Dent J*. 2009;3:202-7.
23. Chaugule R, Raorane D, Pednekar S, Dashaputra R. Nanocomposites and Their Use in Dentistry. In: Chaugule RS, ed. *Dental Applications of Nanotechnology*. Mumbai, India: Springer; 2018.
24. Szczesio-Włodarczyk A, Sokolowski J, Kleczewska J, Bociog K. Ageing of Dental Composites Based on Methacrylate Resins—A Critical Review of the Causes and Method of Assessment. *Polym*. 2020;12(4):882.
25. Bhattacharya M, Seong W-J. Carbon Nanotube-Based Materials—Preparation, Biocompatibility, and Applications in Dentistry. In: Subramani K, Ahmed W, Hartsfield JK,

- eds. Nanobiomaterials in Clinical Dentistry. Waltham, USA: William Andrew Publishing; 2013.
26. García AH, Lozano MAM, Vila JC, Escribano AB, Galve PF. Composite resins. A review of the materials and clinical indications. *Med Oral Patol Oral Cir Bucal*. 2006;11(2):E215-20.
  27. Mousavinasab, Mostafa S. Effects of filler content on mechanical and optical properties of dental composite resin. In: Cuppoletti J, editor. *Metal, Ceramic and Polymeric Composites for Various Uses*: IntechOpen; 2011.
  28. Puoci F. *Advanced Polymers in Medicine*. Springer International Publishing; 2014.
  29. Ilie N, Hickel R. Resin composite restorative materials. *Aust Dent J*. 2011;56:59-66.
  30. Alzraikat H, Burrow M, Maghaireh G, Taha N. Nanofilled resin composite properties and clinical performance: a review. *Oper Dent*. 2018;43(4):E173-E90.
  31. Souza JCM, Hotza D, Henriques B, Boccaccini AR. *Nanostructured Biomaterials for Cranio-Maxillofacial and Oral Applications*. Elsevier; 2018.
  32. Zhou X, Huang X, Li M, Peng X, Wang S, Zhou X, et al. Development and status of resin composite as dental restorative materials. *J Appl Polym Sci*. 2019;136(44):48180.
  33. Kishen A. *Nanotechnology in Endodontics: Current and Potential Clinical Applications*. Springer International Publishing; 2015.
  34. Kenneth J. Anusavice D, Shen C, Rawls HR. *Phillips' Science of Dental Materials*. 12 ed. China: Elsevier Health Sciences; 2012.
  35. Rodríguez HA, Casanova H. Effects of Silica Nanoparticles and Silica-Zirconia Nanoclusters on Tribological Properties of Dental Resin Composites. *J. Nanotechnol*. 2018;2018.
  36. Felemban NH, Ebrahim MI. The influence of adding modified zirconium oxide-titanium dioxide nano-particles on mechanical properties of orthodontic adhesive: an in vitro study. *BMC Ora Heal*. 2017;17(1):1-8.
  37. Mohseni M, Atai M, Sabet A, Beigi S. Effect of plate-like glass fillers on the mechanical properties of dental nanocomposites. *Iran Polym J*. 2016;25(2):129-34.
  38. Hasratiningsih Z, Takarini V, Cahyanto A, Faza Y, Asri L, Purwasasmita B. Hardness evaluation of PMMA reinforced with two different calcinations temperatures of ZrO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub>-SiO<sub>2</sub> filler system. *IOP Conference Series: Mater Sci Eng*. IOP Publishing; 2017. p. 012067.
  39. Hasratiningsih Z, Cahyanto A, Takarini V, Karlina E, Djustiana N, Febrida R, et al. Basic properties of PMMA reinforced using ceramics particles of ZrO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub>-SiO<sub>2</sub> coated with two types of coupling agents. *Key Eng Mater. Trans Tech Publ*; 2016. p. 93-8.
  40. Saen P, Atai M, Nodehi A, Solhi L. Physical characterization of unfilled and nanofilled dental resins: Static versus dynamic mechanical properties. *Dent Mater*. 2016;32(8):e185-e97.
  41. Mirjalili A, Zamanian A, Hadavi SMM. The effect of TiO<sub>2</sub> nanotubes reinforcement on the mechanical properties and wear resistance of silica micro-filled dental composites. *J. Compos. Mater*. 2019;53(23):3217-28.
  42. Karabela MM, Sideridou ID. Synthesis and study of properties of dental resin composites with different nanosilica particles size. *Dent Mater*. 2011;27(8):825-35.
  43. Matinlinna JP, Lung CYK, Tsoi JKH. Silane adhesion mechanism in dental applications and surface treatments: A review. *Dent Mater*. 2018;34(1):13-28.
  44. Karimzadeh A, Ayatollahi M, Shirazi HA. Mechanical properties of a dental nano-composite in moist media determined by nano-scale measurement. *Inter J Mater Mech Manufact*. 2014;2(1):67-72.
  45. Porwal A, Khandelwal M, Punia V, Sharma V. Effect of denture cleansers on color stability, surface roughness, and hardness of different denture base resins. *J Indian Prosthodont Soc*. 2017;17(1):61-7.

46. Joseph AM, Joseph S, Mathew N, Koshy AT, Jayalakshmi NL, Mathew V. Effect of incorporation of nanoclay on the properties of heat cure denture base material: An In vitro study. *Contemp Clin Dent*. 2019;10(4):658-63.
47. Rastelli AN, Jacomassi DP, Faloni APS, Queiroz TP, Rojas SS, Bernardi MIB, et al. The filler content of the dental composite resins and their influence on different properties. *Microsc Res Tech*. 2012;75(6):758-65.
48. Culhaoglu AK, Park J. A comparison of the wear resistance and hardness of two different indirect composite resins with a ceramic material, opposed to human enamel. *European J Gen Dent*. 2013;2(3):274-80.
49. Martinez-Garcia JC, Serraiña-Ferrer A, Lopeandía-Fernández A, Lattuada M, Sapkota J, Rodríguez-Viejo J. A Generalized Approach for Evaluating the Mechanical Properties of Polymer Nanocomposites Reinforced with Spherical Fillers. *Nanomater*. 2021;11(4):830.
50. Liu Y, Wu X, Sun Y, Xie W. POSS Dental Nanocomposite Resin: Synthesis, Shrinkage, Double Bond Conversion, Hardness, and Resistance Properties. *Polym*. 2018;10(4):369.
51. Monfared M, Mirdamadi S, Khavandi A. Synthesis of new dental nanocomposite with glass nanoparticles. *Nanomed J*. 2014;1(2):107-11.
52. Hosseinalipour M, Javadpour J, Rezaie H, Dadras T, Hayati AN. Investigation of mechanical properties of experimental Bis-GMA/TEGDMA dental composite resins containing various mass fractions of silica nanoparticles. *J Prosthodont. Implant, Esthetic and Reconstructive Dentistry*. 2010;19(2):112-7.
53. Rosa RS, Balbinot C, Blando E, Mota E, Oshima H, Hirakata L, et al. Evaluation of mechanical properties on three nanofilled composites. *Stomatol*. 2012;14(4):126-30.
54. Contreras RG, Vilchis RJS, Torres LSA, Arenas-Arrocena C, García-Garduño R, de la Fuente Hernández J. Vickers microhardness comparison of 4 composite resins with different types of filler. *J Oral Res*. 2015;4(5):313-20.
55. Peskersoy C, Culha O. Comparative evaluation of mechanical properties of dental nanomaterials. *J Nanomater*. 2017;2017.
56. Nayyer M, Zahid S, Hassan SH, Mian SA, Mehmood S, Khan HA, et al. Comparative abrasive wear resistance and surface analysis of dental resin-based materials. *Eur J Dent*. 2018;12(01):057-66.
57. Alqahtani M. Mechanical properties enhancement of self-cured PMMA reinforced with zirconia and boron nitride nanopowders for high-performance dental materials. *J Mech Behav Biomed Mater*. 2020;110:103937.
58. Elshereksi NW, Ghazali MJ, Muchtar A, Azhari CH. Effect of Nanobarium Titanate Addition on the Surface Characteristics of Denture Base Resin. *Int J Mech Prod Eng*. 2017;5(5):1-8.
59. Elmadani A, Tomić N, Petrović M, Stojanović D, Mirjanić V, Heinemann R, et al. Influence of surface modification to mechanical and thermal properties of nanomodified acrylic dental resin. *Dig J Nanomater Biostruct*. 2018;13(1):23-9.
60. Meena A, Mali HS, Patnaik A, Kumar SR. Investigation of wear behavior of nanoalumina and marble dust-reinforced dental composites. *Sci Eng Compos Mater*. 2019;26(1):84-96.
61. Zidan S, Silikas N, Alhotan A, Haider J, Yates J. Investigating the mechanical properties of ZrO<sub>2</sub>-impregnated PMMA nanocomposite for denture-based applications. *Mater*. 2019;12(8):1344.
62. Shawi HK, Younis AM, Ahmad ZA, Akil HM. Influence of Environmental Exposure on Absorption, Solubility and Flexural Properties of cordierite Filled Denture Base Poly (Methyl Methacrylate). *Libyan J Med Res*. 2018;12(1).
63. Esteves RA, Boaro LCC, Gonçalves F, Campos LMP, Silva CM, Rodrigues-Filho LE. Chemical and Mechanical Properties of Experimental Dental Composites as a Function of Formulation and Postcuring Thermal Treatment. *Biomed Res Int*. 2018;2018.

64. Omar MF, Akil HM, Ahmad ZA. Particle size–Dependent on the static and dynamic compression properties of polypropylene/silica composites. *Mater Des.* 2013;45:539-47.
65. Marovic D, Tarle Z, Hiller K-A, Müller R, Rosentritt M, Skrtic D, et al. Reinforcement of experimental composite materials based on amorphous calcium phosphate with inert fillers. *Dent Mater.* 2014;30(9):1052-60.
66. Srivastava R, Liu J, He C, Sun Y. BisGMA analogues as monomers and diluents for dental restorative composite materials. *Mater Sci Eng C.* 2018;88:25-31.
67. Srivastava R, Sun Y. Silver sulfadiazine immobilized glass as antimicrobial fillers for dental restorative materials. *Mater Sci Eng C.* 2017;75:524-34.
68. Garoushi S, Säilynoja E, Vallittu PK, Lassila L. Physical properties and depth of cure of a new short fiber reinforced composite. *Dent Mater.* 2013;29(8):835-41.
69. Foroutan F, Javadpou J, Atai M, Rezaie H. Mechanical properties of dental composite materials reinforced with micro and nano-size  $Al_2O_3$  filler particles. *Iran J Mater Sci.* 2011;8(2):25-33.
70. Monfared M, Bahrololoom M. Fractography and Mechanical Properties of Urethane Dimethacrylate Dental Composites Reinforced with Glass Nanoparticles. *J Dent Biomater.* 2016;3(4):327-34.
71. Kumar SR, Patnaik A, Bhat I, Singh T. Optimum selection of nano-and micro-sized filler for the best combination of physical, mechanical, and wear properties of dental composites. *Proceedings of the Institution of Mechanical Engineers, Part L: J Mater Des Appl.* 2018;232(5):416-28.
72. Liu Y, Sun Y, Zeng F, Xie W, Liu Y, Geng L. Effect of nano  $SiO_2$  particles on the morphology and mechanical properties of POSS nanocomposite dental resins. *J Nanopart Res* 2014;16(12):1-8.
73. Kundie F, Azhari CH, Ahmad ZA. Effect of nano-and micro-alumina fillers on some properties of poly (methyl methacrylate) denture base composites. *J Serb Chem Soc.* 2018;83(1):75-91.
74. Chen S-G, Yang J, Jia Y-G, Lu B, Ren L.  $TiO_2$  and PEEK reinforced 3D printing PMMA composite resin for dental denture base applications. *Nanomater.* 2019;9(7):1049-67.
75. Aparna P, Kumar KH, Ravichandran R, Nair VV, Zeenath H, Manjuran NG. Comparison of Thermal Conductivity, Flexural Strength, and Surface Hardness of Alumina Incorporated and Conventional Heat-Activated Denture Base Resins. *Int J Sci Study.* 2020;8(2):64-71.
76. Petterson RW, Bodig J. Prediction of fracture toughness of conifers. *Woo Fibe Sci.* 2007;15(4):302-16.
77. Asiri AM, Inamuddin, Mohammad A. Applications of Nanocomposite Materials in Dentistry. Sawston: Woodhead Publishing; 2019.
78. Swallowe GM. Mechanical Properties and Testing of Polymers: An A–Z Reference. Dordrecht: Springer 2013.
79. Passos SP, Freitas AP, Jumaily S, Santos MJM, Rizkalla AS, Santos Jr GC. Comparison of mechanical properties of five commercial dental core build-up materials. *Compend Contin Educ Dent.* 2013;34(1).
80. Ilie N, Hilton T, Heintze S, Hickel R, Watts D, Silikas N, et al. Academy of dental materials guidance—resin composites: Part I—mechanical properties. *Dent Mater.* 2017;33(8):880-94.
81. Belli R, Kreppel S, Petschelt A, Hornberger H, Boccaccini AR, Lohbauer U. Strengthening of dental adhesives via particle reinforcement. *J Mech Behav Biomed Mater.* 2014;37:100-8.
82. Fu S-Y, Feng X-Q, Lauke B, Mai Y-W. Effects of particle size, particle/matrix interface adhesion and particle loading on mechanical properties of particulate–polymer composites. *Compos B Eng.* 2008;39(6):933-61.

83. Safaee S, Yasrebi B. Effect of an increase in nano-filler content on the mechanical properties of high-leucite composite resins useable in dentistry. *Cresc J Med Biol Sci.* 2017;4(3):144-9.
84. Chen M-H. Update on dental nanocomposites. *J Dent Res.* 2010;89(6):549-60.
85. Yeli M, Kidiyoor K, Nain B, Kumar P. Recent advances in composite resins-A review. *J Oral Res Rev.* 2010;2(3):134-6.
86. Chan K, Lee Y-D, Nicoletta D, Furman B, Wellinghoff S, Rawls R. Improving fracture toughness of dental nanocomposites by interface engineering and micromechanics. *Eng Fract Mech.* 2007;74(12):1857-71.
87. De Souza J, Goutianos S, Skovgaard M, Sørensen BF. Fracture resistance curves and toughening mechanisms in polymer based dental composites. *J Mech Behav Biomed Mater.* 2011;4(4):558-71.
88. Atai M, Pahlavan A, Moin N. Nano-porous thermally sintered nano silica as novel fillers for dental composites. *Dent Mater.* 2012;28(2):133-45.
89. Barghamadi H, Atai M, Imani M, Esfandeh M. Effect of Amorphous Silica Nanoparticle Size and Content on fracture toughness of a Highly-Filled Dental Composite. *J Res Dent Sci.* 2018;15(1):5-12.
90. Wu D, Lu F, Zhao D, Ma G, Li C, Ding J, et al. Effect of doping SiC particles on cracks and pores of Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> eutectic ceramics fabricated by directed laser deposition. *J Mater Sci.* 2019;54(13):9321-30.
91. Lohbauer U, Belli R, Ferracane JL. Factors involved in mechanical fatigue degradation of dental resin composites. *J Dent Res.* 2013;92(7):584-91.
92. Saravanakumar K, Arumugam V, Souhith R, Santulli C. Influence of Milled Glass Fiber Fillers on Mode I & Mode II Interlaminar Fracture Toughness of Epoxy Resin for Fabrication of Glass/Epoxy Composites. *Fibe.* 2020;8(6):36.
93. Ferracane JL, Pfeifer CS, Hilton TJ. Microstructural features of current resin composite materials. *Curr Ora Heal Rep.* 2014;1(4):205-12.
94. Shadlou S, Ahmadi-Moghadam B, Taheri F. Nano-enhanced adhesives. *Rev Adhes Adhes.* 2014;2(3):371-412.
95. Arsecularatne JA, Chung NR, Hoffman M. An in vitro study of the wear behaviour of dental composites. *Biosurf Biotrib.* 2016;2(3):102-13.
96. Ferracane JL, Antonio RC, Matsumoto H. Variables affecting the fracture toughness of dental composites. *J Dent Res.* 1987;66(6):1140-5.
97. Yadav S, Gangwar S. Mode-I Fracture Toughness Analysis of n-HAPs Filled Dental Restorative Composites. *Silic.* 2020;13(5):1347-58.
98. Zamanian M, Mortezaei M, Salehnia B, Jam J. Fracture toughness of epoxy polymer modified with nanosilica particles: Particle size effect. *Eng Fract Mech.* 2013;97:193-206.
99. Wetzell B, Rosso P, Hauptert F, Friedrich K. Epoxy nanocomposites—fracture and toughening mechanisms. *Eng Fract Mech.* 2006;73(16):2375-98.
100. Dittanet P. Fracture behavior of silica nanoparticle filled epoxy resin [Dissertation], Lehigh University; 2011.
101. Ornaghi BP, Meier MM, Lohbauer U, Braga RR. Fracture toughness and cyclic fatigue resistance of resin composites with different filler size distributions. *Dent Mater.* 2014;30(7):742-51.
102. Elmadani A, Radović I, Tomić N, Petrović M, Stojanović D, Heinemann RJ, et al. Hybrid denture acrylic composites with nanozirconia and electrospun polystyrene fibers. *PLoS One.* 2019;14(12):e0226528.

## ABBREVIATIONS

γ-MPS: 3-methacryloxypropyltrimethoxysilane

Al<sub>2</sub>O<sub>3</sub>: Alumina

BisEMA: Bisphenol A polyethylene glycol diether dimethacrylate

Bis-GMA: Bisphenol A glycidyl dimethacrylate

CNTs: Carbon nanotubes  
DRCs: Dental resin composites  
NPs: Nanoparticles  
PMMA: Poly(methyl methacrylate)  
RBCs: Resin-based composites  
SiO<sub>2</sub>: Silica  
TEGDMA: Triethylene glycol dimethacrylate  
TiO<sub>2</sub>: Titania  
UDMA: Urethane dimethacrylate  
ZrO<sub>2</sub>: Zirconia

UNDER PEER REVIEW