

Adsorption and Thermodynamic studies of *Carica papaya* leaves extract (yellow) as Corrosion Inhibitor for mild steel in acidic medium

Abstract: The inhibitive effects of plant leaf, *Carica papaya* leaves extract (yellow), CPLE (yellow) was studied on mild steel in 1.0 M HCl solution at 30°C using the gravimetric and electrochemical methods as well as Fourier transform infrared spectroscopy, FT-IR technique. The analysis of spectra obtained from FT-IR revealed that some functional groups present in the original spectrum were missing in the spectra of the corrosion products, an indication of interaction between the mild steel and inhibitor. The corrosion rate decreases noticeably with increase in inhibitor concentrations, that is, the inhibition efficiency (% IE) increases with increase in the inhibitor concentration. The progressive increase of the extract shows greater reduction of corrosion rate, given maximum inhibitive efficiency of 94.68% at 0.5g L⁻¹ at 30°C. The Tafel and potentiodynamic polarization studies revealed that the CPLE (yellow) functioned as mixed-type inhibitor. The adsorption mechanism of the extract on the mild steel surface was found to obey El-Awady isotherm model. The thermodynamic evaluation deduced proposed a physisorption with the mild steel surface and spontaneous adsorption of CPLE (yellow). FT-IR was used to confirm the formation of a protective layer on the mild steel surface.

Keywords: Mild steel, CPLE (yellow), Hydrochloric Acid, Adsorption, Thermodynamic

1. INTRODUCTION

The impact of corrosion of materials, particularly, metallic structures (e.g mild steel and aluminium) on the economy have continued to generate interest, not only among the scientific community, but globally. A substantial economic loss and sometimes, loss of lives are incurred by the industries concerned as a result of rapid corrosion of these structures, due to the aggressiveness of the acidic media involving pickling, chemical cleaning, oil-well acidizing and descaling among others [1, 2]. Unmitigated corrosion has the negative effects of causing rigidity weakening of mild steel based installations, thereby compromising the mechanical properties and ultimately, facility breakdown [3]. Among various techniques adopted to control this menace, corrosion inhibitors have proven excellently in regard to cost, availability, processing, reproducibility and environmentally-benign. However, due to their high cost and stringent environmental laws because of health awareness and ecological risks, focus has continually drawn towards finding highly efficient, affordable and non-toxic inhibitors. The use of green corrosion inhibitors has, therefore, taken a focal stage in the present research due principally to their non-toxicity, environmental friendliness and good performance [4, 5].

The natural plant products as corrosion inhibitors have been utilized and proven to be good with higher prospect viz-a-viz the synthetic or chemical inhibitors. Corrosion inhibitors represent the advanced trends of managing corrosion based on green chemistry and research efforts are still ongoing to discover higher performance corrosion-inhibiting additives with optimum concentration [1, 6-8]. These green plants inhibitors molecules consist of heterocyclic compounds with polar functional groups such as O, N, S, P and π electrons with double rings [9]. However, specific areas that are crucial in regard to the nature of active constituents, the chemical structures of the extract and, the use of density functional theory to correlate the extract active components and inhibitive effects on the basis of the molecular parameters are still few and require further elucidation. In the present study, the investigation of *Carica papaya* leaves extract, CPLE, (yellow), on the inhibition of mild steel in 1M HCl acid solution is another attempt towards contributing to the growing interest of exploring green corrosion inhibitors. The aim of this research therefore, is the adsorption and corrosion inhibition of *Carica papaya* leaves extract, CPLE, (yellow), on mild steel in the presence of 1M HCl acid solution at room temperature (30°C).

2. MATERIALS & METHODS

Commercially available mild steel was used for all experiments of average nominal composition; 98.3% Fe, 0.128% C, 0.010% P, 0.030% S, 0.820% Cr, 0.292% Mn, 0.115% Ni, 1.420% Ar, 0.092% Pb, 0.074% Cu and 0.066% N respectively. *Carica papaya* leaves extract (yellow), CPLE (yellow) is the inhibitor used. The *Carica papaya* leaves were sourced from the Federal Polytechnic Ado-Ekiti campus, Nigeria. The leaves samples were washed; oven dried at 90°C for 4 hours and pulverized using an electrically powered blender. About 50g of the pulverized leaves was weighed and soaked in 250ml of ethanol for 48 h. The solution of the sample was then filtered to obtain the extract. The filtrates were furthered subjected to evaporation at 352K to remove excess ethanol. CPLE (yellow) was prepared in volumetric concentration of 0.1, 0.2, 0.3, 0.4, 0.5g L⁻¹ per 200ml of the acid solution respectively. Solution of 1.0M HCl of analytical grade was used as the corrosion test media. Mild steel specimen of the required size was used for measurement of weight loss study. The strips were mechanically polished using emery papers of grade numbers 220, 320, 400, 600, 800, and 1000; washed thoroughly with distilled water, degreased with acetone and dried in air before immersion in the corrosive medium.

The corrosion tests were carried out at 30°C and the conditions under which they were done are as follows: the Fourier transform infrared spectroscopic, FTIR analysis of the *Carica papaya* leaves extract (yellow) and that of the corrosion products in the presence of the extracts were prepared utilizing Perkin-Elmer-1600 Fourier transform infra-red spectrophotometer. The corrosion product from the mild steel specimen for the analysis was obtained following the procedures in accordance with [3]. This entailed the immersion of the powdered mild steel inside 150ml of 0.5g CPLE (yellow) concentration.

The mixture was left for 6hrs after which it was filtered. The residue was allowed to dry and then analyzed using FTIR. The sample was prepared using KBr.

The weight loss measurements were carried out by weighing the specimens in triplicate before use and after immersion in 200ml for 24hrs in 1.0M HCl in the absence and presence of 0.1, 0.2, 0.3, 0.4, 0.5g/l of inhibitor CPLE (yellow) at 30°C. Each of the test specimens was taken out every 24hrs, washed thoroughly with liquid soap (Morning fresh), rinsed with distilled water, cleaned with acetone, dried and re-weighed. The test was also carried out progressively for 168hrs (7days). The corrosion rate (C_R), inhibition efficiency (%IE) and surface coverage (θ) were calculated from the following equations in accordance with ASTM G31 standard [10].

$$CR (mmpy) = \frac{87.6 W}{DAT} \quad (1)$$

$$\% IE = 1 - \frac{CR_{inh}}{CR_{blank}} \times 100 \quad (2)$$

$$\theta = 1 - \frac{CR_{inh}}{CR_{blank}} \quad (3)$$

Where W is the weight loss in grammes, D is the density in g/cm³, A is the surface area in cm², T is the immersion time in hrs, CR_{inh} and CR_{blank} are corrosion rates of mild steel with and without inhibitor respectively. The procedure was utilized for all the 168hrs (7days), using thermostat to study the inhibition efficiency of inhibitor. The study gives details about the rate of adsorption and thermodynamic parameters of the corrosion inhibition mechanism.

The electrochemical corrosion studies of mild steel in various concentration of *Carica papaya* leaves extract yellow (CPLE yellow) in 1 M HCl were carried out using AUTOLAB PGSTAT 204N instrument, piloted by Nova software. The electrochemical measurements were carried out in a three-electrode cell made up of the mild steel sample as the working electrode, while the saturated silver/silver chloride and platinum wire were utilized as reference and as counter electrodes respectively. The working electrode was immersed in test solutions 1M HCl solutions with or without *Carica papaya* leaves extract for 30 minutes until a stable open circuit potential was achieved. The working electrodes were prepared by attaching an insulated copper wire to one face of the sample using an aluminium conducting tape and cold mounting it with epoxy resin. The potentiodynamic polarization measurements were carried out using a scan rate of 1.0 mV/s at a potential initiated at -250mV to +250mV with respect to OCP. After each experiment, the electrolyte and the test sample were replaced. The linear Tafel segments of the anodic and cathodic curves were extrapolated to corrosion potential to obtain the corrosion densities (i_{corr}^0 and i_{corr}) in place of corrosion rates (C_R^0 and C_R) in Eq. (2).

3. Results & Discussions

3.1 FTIR Spectral Analysis of CPLE (Yellow)

FTIR characterization of the CPLE (yellow) was performed to identify the functional groups present in it, while that of the corrosion products is to ascertain that inhibition has taken place due to interaction/adsorption between the mild steel surface and the inhibition extract. The FTIR spectra of the inhibitor extract and the corrosion products of the specimen are shown in Figures 1a and 1b. From the results obtained, the bonded O – H stretching in phenol 3389.52cm^{-1} was shifted to 3282.68cm^{-1} , C=O stretch of carbonyl at 1714.92cm^{-1} was shifted to 1712.52cm^{-1} , C-O stretch of ester at 1083.25cm^{-1} was shifted to 1117.62cm^{-1} , C=C stretch at 1454.44cm^{-1} was shifted to 1462.36cm^{-1} , N – O stretch of nitro molecule at 1376.59cm^{-1} was shifted to 1377.00cm^{-1} and the C-H stretch corresponding to carboxylic acid group at 2922.84cm^{-1} was shifted to 2922.45cm^{-1} . The shift in the frequencies indicates that there are significant changes between the metallic substrate and the inhibitor. Moreover, a band of 1103.13cm^{-1} corresponding to C-O stretching of ether and Methyl C-H at 1462.36cm^{-1} observed in the FTIR spectral disappeared, suggesting that these bands must have been utilized in the adsorption of the inhibition extract onto the mild steel substrate [11-13]. These changes resulted in the formation of a protective film barrier on the mild steel substrate [14].

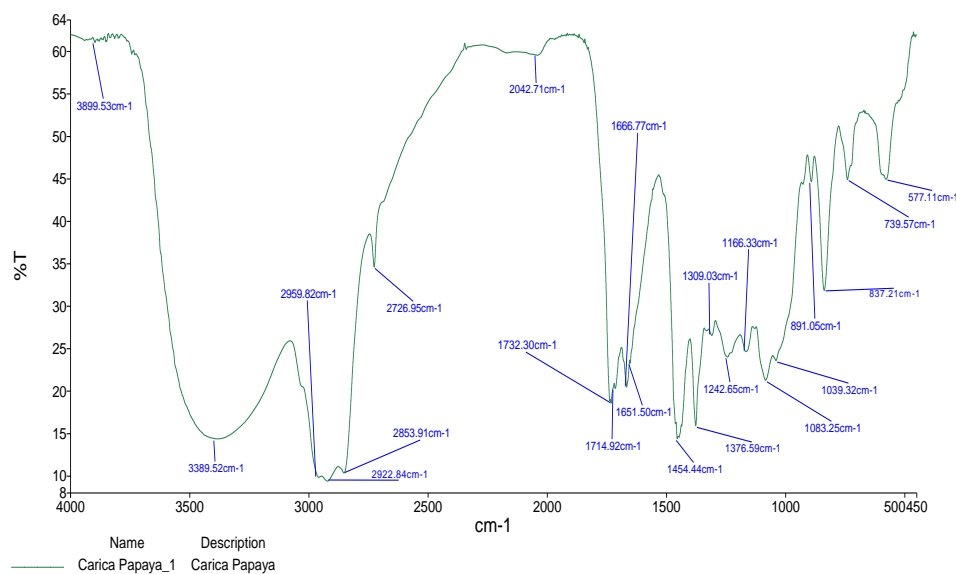


Figure 1a: FT-IR spectrum of HCl extract of *Carica papaya* leaves

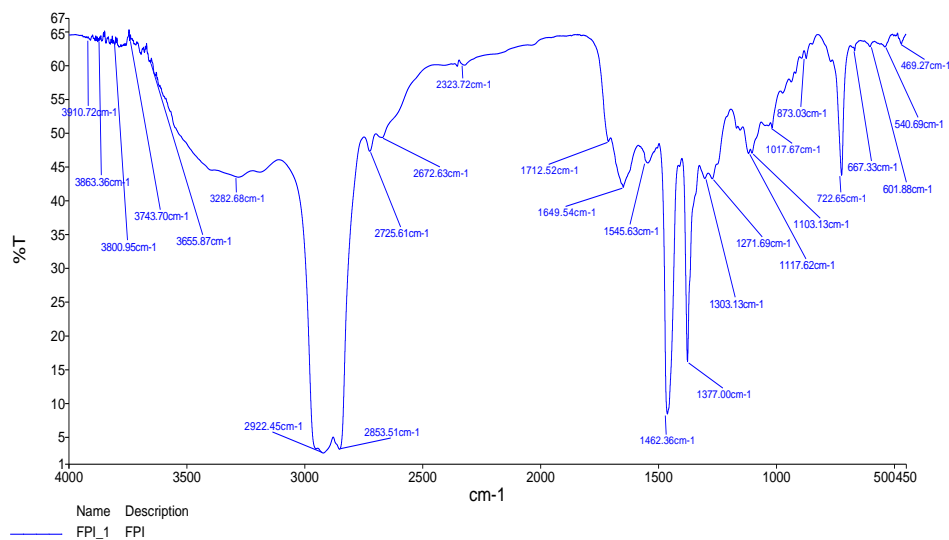


Figure 1b: FT-IR spectrum of corrosion products of MS in the presence of HCl extract of *Carica papaya* leaves

3.2 Gravimetric measurements

The gravimetric monitoring of corrosion rate (C_R) and inhibitors efficiency (I.E %) is a versatile tool because of the simplicity of the method and this has been employed by several researchers [15-18]. The plot of the variation in mass loss of the mild steel substrates in the absence and presence of varying concentrations CPLE (yellow) as a function of exposure time at 30°C and different extract concentrations is shown in Fig. 2. The C_R and I.E % values obtained from the weight loss experiment at varying concentration of CPLE (yellow) in 1M HCL solution are also shown in Table 1. The results showed that the mass loss increased with increase in exposure time in the blank solution. However, the addition of the inhibitor extracts resulted in a considerable decrease in the mass loss of mild steel substrate in comparison with the blank solution. The reduction is attributed to the adsorption of the extract active constituents (heterocyclic compounds) on the mild steel substrate as revealed by some notable changes in the FTIR spectral analysis. The adsorption of the extract active constituents as was observed indicates the formation of a protective layer which prevents charge and mass flow between the mild steel and the aggressive solution [3]. This can also be due to the fact that the extract active principles are known to combine with the mild steel corrosion products to form a passive film, thus protecting the material from further attack by the HCl solution [19].

Moreover, the C_R as indicated in Table 1 decreases noticeably with increase in inhibitor concentration, that is, the inhibition efficiency (IE) increases with increase in the concentration inhibitor extract. The progressive increase of the extract shows greater reduction of corrosion rate, given maximum inhibitive efficiency of 94.68% at 0.5g L⁻¹ at 30°C. The inhibitive effects of the inhibitor is attributed mainly to the presence of hetero atoms such as O, N, S and carbonyl rings with π bands in their constituents which was

in tandem with the FTIR results. Hence, the *Carica papaya* leaves extract (yellow), CPLE (yellow) in this regard, acted as an efficient inhibitor for the corrosion of mild steel in 1 M HCl solution.

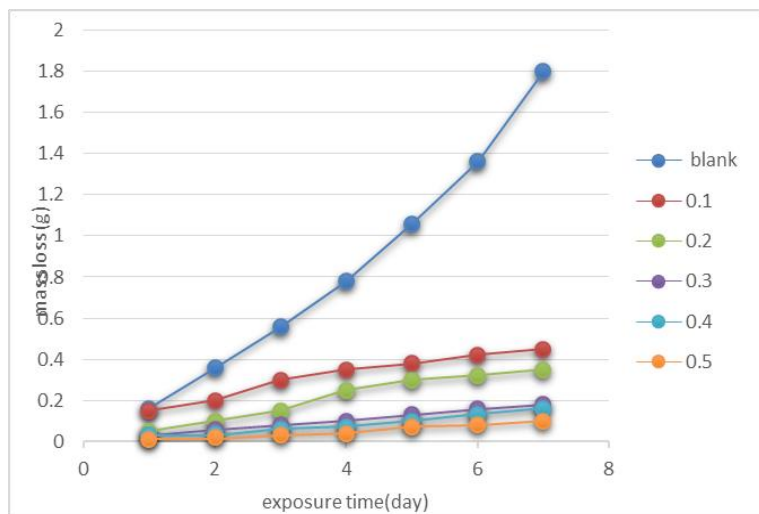


Figure 2: Mass loss as a function of time for mild steel in 1M HCl in the absence/presence of CPLE (yellow).

3.3 Electrochemical measurements

3.3.1 LPR measurement

The values of the polarization resistance (P_R) obtained from linear polarization studies are listed in Table 1. The values of P_R shows a gradual and spontaneous increase with increase in CPLE and reaches its maximum at 0.5 g L^{-1} concentration (917.3Ω) in comparison to the blank (47.64Ω). Thus, the increase in the polarization resistance in the presence of CPLE (yellow) suggests that a non-conducting adsorbed film is formed at the mild steel acid interface.

3.3.2 Potentiodynamic polarization measurement

Potentiodynamic polarization plots shown in Fig, (3-8) characterizes the behaviour of mild steel with blank solution and varying concentration of CPLE (yellow) at 30°C in 1M HCl acid solution. Electrochemical kinetic parameters associated with polarization measurements such as anodic and cathodic Tafel constants (β_a and β_c), corrosion potential (E_{corr}), and corrosion current density (i_{corr}) and percentage of inhibition efficiency were obtained and are indicated in Table 1. It is revealed from Figs (3-8) that in the presence of inhibitors both the anodic metallic dissolution and cathodic hydrogen evolution curves shift towards the lower current density. An inspection of the data in Table 1 reveals that as CPLE (yellow) were added, the value of i_{corr} decreases significantly due to the inhibitor molecules which form a blocking barrier on the surface by decreasing the sites of the metal surface of the corrosion causing

inactivation. This is purely physisorption phenomenon (adsorption) which involves a retardation of anodic reactions in the process.

Table 1: Corrosion parameters obtained from potentiodynamic polarization and linear polarization data of mild steel in 1M HCl in the presence of different concentrations of CPLE (yellow) at 30°C

Gravimetric measurement (weight loss) 24hrs immersion				Potentiodynamic polarization and linear polarization resistance data							
S/N	Conc.	C _R mm/yr	I.E %	E _{CORR} (V)	I _{CORR} (A)	b _a v/dec	b _c v/dec	C _R mm/yr	I.E%	P _R (Ω)	I.E %
1	Blank	0.1881	-	-0.6816	9.926E -05	0.026181	0.018646	1.1534	-	47.64	-
2	0.1	0.1763	6.27	-0.5658	7.1032E-05	0.017185	0.019318	0.8149	28.4	56.320	15.41
3	0.2	0.0587	68.79	-0.5239	6.4847E-05	0.016166	0.018696	0.7535	34.7	58.061	17.94
4	0.3	0.0530	71.82	-0.5186	1.823E -05	0.018792	0.021694	0.2118	81.6	239.89	80.14
5	0.4	0.0353	81.20	-0.5890	7.7249E-06	0.019819	0.022375	0.0898	92.2	590.72	91.94
6	0.5	0.0100	94.68	-0.9746	3.8824E-06	0.015804	0.017043	0.0451	96.1	917.30	94.80

Also the value of E_{corr} shifts significantly towards more negative direction, with 0.5 g L⁻¹ concentration given -0.9246V compared to the blank given a value of -0.6816V. Moreover, the largest displacement in E_{corr} value observed at a concentration of 0.5g L⁻¹ is 0.456V (456mV) which is greater than 0.085V (85mV). If the value of E_{corr} shifts beyond 85mV, an inhibitor is designated as an anodic or cathodic type [6, 20]. The Tafel slopes, β_a and β_c, show slight variations in the presence of the extract, suggest that the inhibitive effects take place via a simple blocking of existing anodic and cathodic sites on the metal surface [21]. Hence, the above studies which is the same trend with the gravimetric measurements proposed that CPLE (yellow) acts as an efficient mixed-type inhibitor. A green extract that shows both physisorption and chemisorption phenomena will result in a higher efficiency of inhibition compared to the individual physisorption or chemisorption mechanism [22, 23].

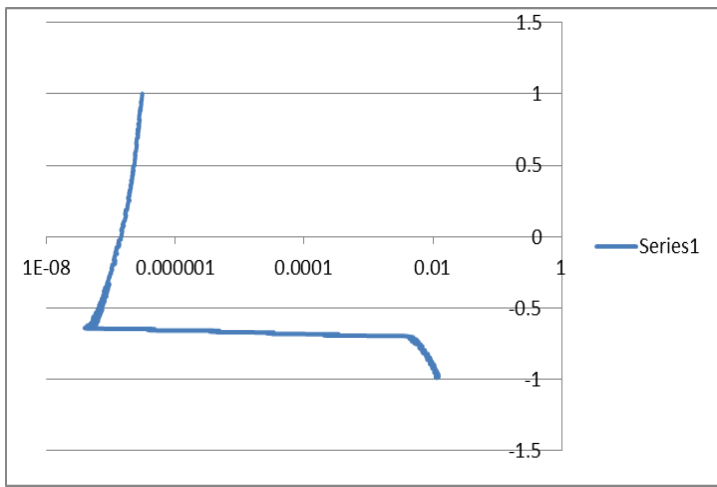


Fig. 3: Tafel plot of MS immersed in 1M HCl without CPLE (yellow)

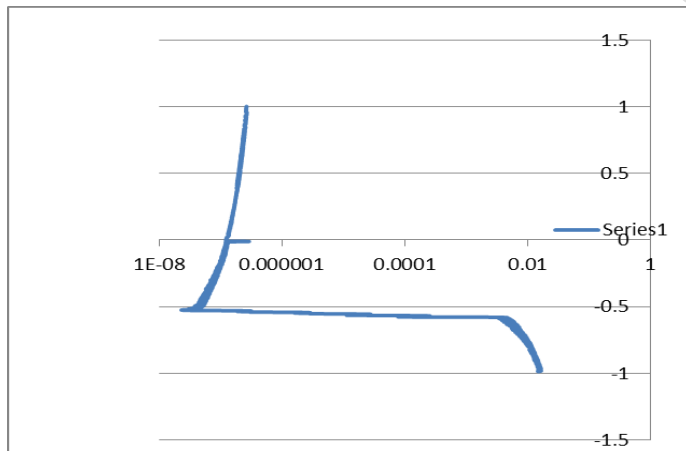


Fig. 4: Tafel plot of MS immersed in 1M HCl with 0.1g L⁻¹ CPLE (yellow) at 30°C

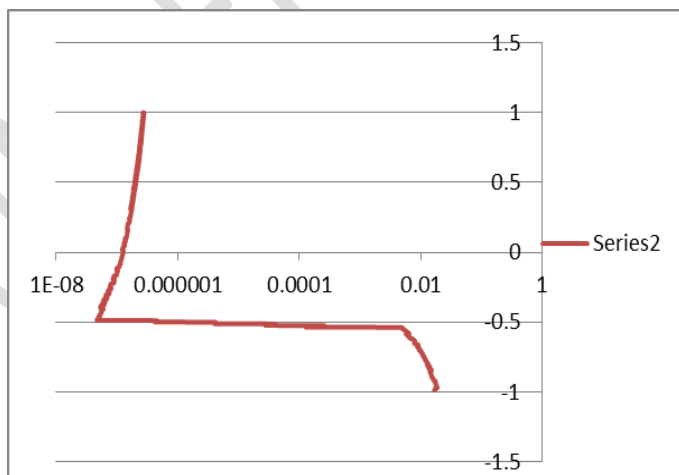


Fig. 5: Tafel plot of MS immersed in 1M HCl with 0.2g L⁻¹ CPLE (yellow) at 30°C

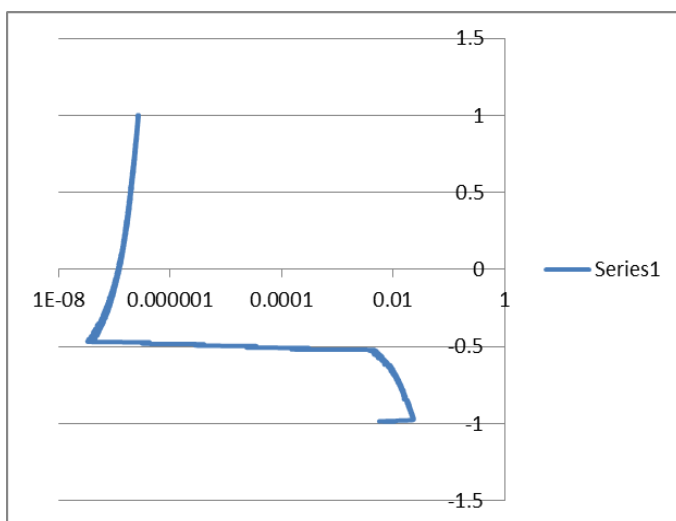


Fig. 6: Tafel plot of MS immersed in 1M HCl with 0.3g L⁻¹ CPLE (yellow) at 30°C

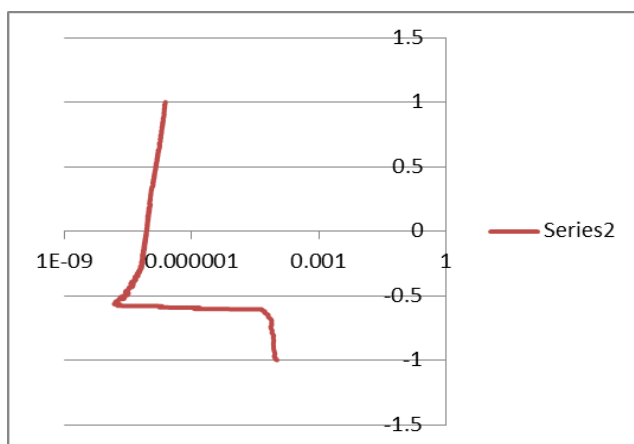


Fig. 7: Tafel plot of MS immersed in 1M HCl with 0.4g L⁻¹ CPLE (yellow) at 30°C

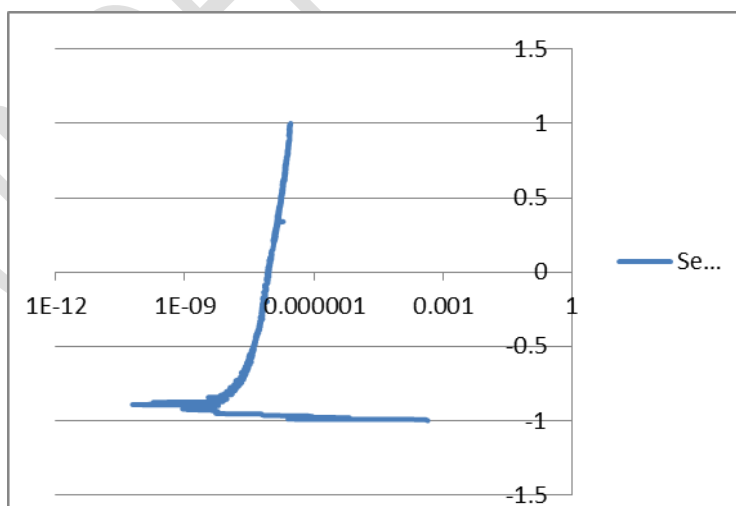


Fig. 8: Tafel plot of MS immersed in 1M HCl with 0.5g L⁻¹ CPLE (yellow) at 30°C

Table 2: Adsorption parameters of ethanolic extract of CPLE (yellow) on the mild steel in 1M HCl at 30°C using potentiodynamic polarization

Time hr	Conc. $C_{inh}(g\ l^{-1})$	θ	$\log \theta$	θ/C	$\log \theta/C$	$\log C$	$1-\theta$	$\log(1-\theta)$	$(\theta/1-\theta)$	$\log \theta/1-\theta$
24	Blank	-	-	-	-	-	-	-	-	-
	0.1	0.284	-0.5467	2.840	0.4533	-1.000	0.716	-0.1451	0.3966	-0.4016
	0.2	0.347	-0.4597	1.735	0.2393	-0.699	0.653	-0.1851	0.5314	-0.2746
	0.3	0.816	-0.0883	2.720	0.4346	-0.5229	0.184	-0.7352	4.4348	0.6469
	0.4	0.922	-0.0353	2.305	0.3627	-0.3979	0.078	-1.1079	11.8205	1.0726
	0.5	0.961	-0.0173	1.922	0.2838	-0.3010	0.039	-1.4089	24.6410	1.3917

3.4 Adsorption isotherms

In corrosion studies, further information required to elucidate the adsorption mechanism between the inhibitor molecules and the surface of metallic substrate can be obtained from adsorption isotherm. The data were made to fit into Langmuir, Temkin, Freundlich, El-Awady, and Flory – Huggins isotherms, but the R^2 values for each isotherm model were used to verify the most suitable model. From the correlation ($R^2=0.9986$) obtained, the El-Awady's isotherm model was found to be the best that describes the adsorption mechanism of Carica papaya extract (yellow) on mild steel in hydrochloric acid solution. Hence, El-Awady's adsorption isotherm is appropriate for evaluating the adsorption equilibrium constant, K_{ads} .

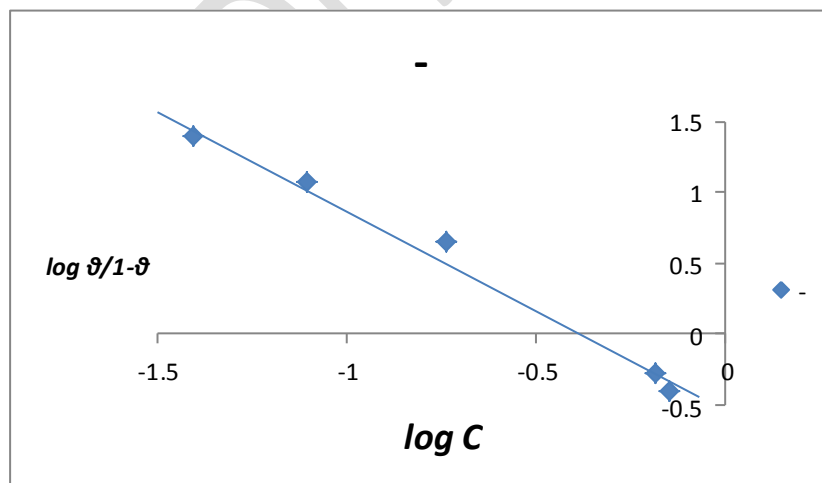


Fig. 9: El- Awady's isotherm

3.5 Thermodynamic parameters

Free energy of adsorption (ΔG_{ads}) can be calculated, thus using the equation

$$\Delta G_{ads} = -RT \ln(55.5K_{ads}) \quad (5)$$

where R is the molar gas constant, T is the temperature and 55.5 is the molar concentration of water in solution. The value K_{ads} calculated from the intercept of the linear graph is related to the standard free energy of adsorption, ΔG_{ads} as shown in equation 5 above. In literature, the values of ΔG_{ads} less than -20KJ/mol signify physical adsorption, which was consistent with electrostatic interaction between charged molecules and a charged metal [24, 25]. The ΔG_{ads} value calculated using the El-Awady's isotherm plot was found to be $-14.9\text{KJ}\cdot\text{mol}^{-1}$, an indication of physisorption (adsorption) phenomenon. The value of ΔG_{ads} is found to be negative, indicating that the adsorption is spontaneous.

4. Conclusions

Experimental analysis of the corrosion inhibition properties of Carica papaya leaves extract (yellow) CPLE (yellow) showed the constituents to be an efficient inhibitor in the acidic medium at 30°C, giving a maximum inhibition efficiency of 94.68% and 96.1% from weight loss and potentiodynamic polarization methods respectively. The significant changes as observed in the FTIR spectral analysis suggested that some adsorption over the mild steel surface had taken place. Moreover, the adsorption mechanism was found to obey the El-Awady's isotherm. Thermodynamic evaluation deduced revealed a physisorption with the mild steel surface and spontaneous adsorption of CPLE (yellow). The environmentally benign inhibitor could as well find possible applications as chemical cleaning in industries.

References

1. Oke, G. O.; Aluko, A. O. & Sanya, T. O. (2018): Inhibitive potential of Datura stramonium leaf extract on the corrosion behaviour of mild steel in 1M HCl acidic solution, Leonardo Journal of Sciences, Issue 32, January-June, (pp. 76-92).
2. Yaro, A. S.; Khadom, A. A. & Wael, R. K. (2013) : Apricot juice as green corrosion inhibitor of mild steel in phosphoric acid, Alexandria Eng. J. 52 (1), (pp129-135).
- 3a. Alaneme, K. K.; Olusegun, S. J. & Adelowo, O. (2015a). Corrosion inhibition and absorption mechanism studies of Hunteria umbellata seed husk extracts on mild steel immersed in acidic solutions. Alexandria Engineering Journal, (pp. 1-9).
- 3b. Alaneme, K. K.; Daramola, Y.; Olusegun, S. J. & Afolabi, A. (2015b): Corrosion inhibition and absorption characteristics of rice husk extracts on mild steel immersed in 1M H₂SO₄ and HCl solutions. International Journal of Electrochemical Science, (pp.3553-3567).

4. Muthukrishnan, P.; Jeyaprabha, B. & Prakash, P. (2014): Mild steel corrosion inhibition by aqueous extract of *Hyptis suaveolens* leaves, *International Journal of Industrial Chemistry*, 1, Article 5, (pp1-11).
5. Abiola, O. K. & James, A. O. (2010): The effects of Aloe Vera extract on corrosion and kinetics of corrosion process of zinc in HCl solution, *Corros. Sci.* 52 (2), (pp.661-664).
6. Al-Moghrabi, R. S.; Abdel-Gaber, A. M. and Rahal, H. T. (2018): A comparative study on the inhibitive effect of *Crataegus oxyacantha* and *Prunus avium* plant leaf extracts on the corrosion of mild steel in hydrochloric acid solution, *International Journal of Industrial Chemistry*, 9, (pp.255-263).
7. Ji, G., Anjum, S., Sundaram & Prakash, R. (2015): *Musa paradisiac* peel extract as green corrosion inhibitor for mild steel in HCl solution, *Corros. Sci.* 90, (pp.107-117).
8. Mourya, P. Banerjee, S. and Singh, M. M. (2014): Corrosion inhibition of mild steel in acidic solution by *Tagetes erecta* (Marigold flower) extract as a green inhibitor, *Corros. Sci.* 85, (pp. 352-363).
9. Zhang, W., Li, H.-J.; Chen, L.; Zhang, S.; Ma, Y.; Ye, C.; Zhou, Y.; Pang, B.; & Wu, Y. -C. (2020): Fructan from *Polygonatum crytonema* Hua as an eco-friendly corrosion inhibitor for mild steel in HCl media. *Carbohydr. Polym.* 238, (pp. 116216).
10. ASTM NACE/ASTMG31-12a 2012, Standard Guide for Laboratory Immersion Corrosion Testing of Metals, ASTM International, West Conshohocken, PA
11. Deyab, M. A. and Guibal, E. (2020): Enhancement of Corrosion resistance of the cooling systems in desalination plants by green inhibitor. *Sci Rep*, 10, (pp. 4812).
12. Awe, F. E., Idris, S. O., Abdulwahab, M. & Oguzie, E. E. (2015): Theoretical and experimental inhibitive properties of mild steel in HCl by ethanolic extract of *Boscia senegalensis*, *Cogent Chemistry*, 1, (pp. 1-14).
13. Gualdron, A. E., Becerra, E. N., Pena, D. Y., Gunerrez, J. C. & Becerra, H. Q. (2013): Inhibitory effect of *Encalyptus* and *Lappia Alba* essential oils on the corrosion of mild steel in hydrochloric acid, *Mater Environ Sci.* 4 (1), (pp. 143-158).
14. Emori, W., Zhang, R. H.; Okafor, P. C.; Zhang, X-W; He, T.; Wei, K.; Lin, X-W; Chang, C. R. (2020): Adsorption and Corrosion Inhibition performance of multi-phytoconstituents from *Dioscorea septenloba* on carbon steel in acidic media: characterization, experimental and theoretical studies. *Colloids surf. Physicochem Eng. Asp.*, 590, (pp.124534).
15. Anyiam, C. K.; Ogbobe, O.; Oguzie, E. E.; Madufor, I. C.; Nwanonyi, S. C.; Onuegbu, G. C.; Obasi, H. C.; Chidiebere, M. A. (2020): Corrosion inhibition of galvanized steel in hydrochloric acid medium by a physically modified starch. *SN Appl. Sci.* 2, (pp. 520).
16. Ogunleye, O. O.; Arinkoola, A. O.; Elleta, O. A.; Agbede, O. O.; Osho, Y. A.; Morakinyo, A. F.; Hamed, J. O. (2020): Green corrosion inhibition and adsorption characteristics of *Luffa Cylindrica* leaf extract on mild steel in hydrochloric acid environment, *Heliyon*, 6, (pp. 03205).

- 17.Nnanna, I.,Nnanna, G.,Nnakaife, J.,Ekekwe, N.& Eti, P.(2016): Aqueous extracts of *Pentaclethra Macrophylla* Bentham Roots as Eco-friendly Corrosion Inhibition of mild steel in 0.5M KOH medium, *International Journal of Materials Chemistry*, 6 (1), (pp. 12-18).
- 18a.Alaneme, K. K. Osasona, B.,Okotete, E.,Olusegun, S. J., & Donatus,U.(2016a). Corrosion inhibition behaviour of *biden pilosa* extract on aluminium matrix composites in 1 HCl solution. *The Journal of the Association of Professional Engineers of Trinidad and Tobago*; Vol. 44; No. 2.(pp. 35-42)
- 18b.Alaneme, K. K., Olusegun, S. J. & Alo, A. (2016b). Corrosion inhibitory properties of elephant grass (*Pennisetum purpureum*) extract on mild steel corrosion in 1M HCl solution. *Alexandria Engineering Journal* ,(pp. 1-8).
- 19.Alaneme, K. K., & Olusegun, S. J.(2012): Corrosion Inhibition performance of lignin extract of sun flower (*Tithonia diversifolia*) on medium carbon low alloy steel immersed in H₂SO₄ solution, *Leonardo J. Sci.* 20 (11), (pp. 59-70).
- 20.Ansari, K. R.,& Quraishi, M. A.(2015): Effect of three component (aniline-formaldehyde and piperazine) polymers on mild steel in hydrochloric acid medium, *J. Assoc. Arab Univ. Basic Appl. Sci.* 18, (pp. 12-18).
- 21.Shukla, S. K.,Quraishi, M. A., & Ebenso, E. E.(2011): Adsorption and corrosion inhibition properties of cefadroxil on mild steel in hydrochloric acid. *Int J ElectrochemSci* 6. (pp.2912–2931).
- 22.Deoghani, A.;Bahlakeh, G.; Ramezanzaeh, M.(2020): Potential Role of a novel green eco-friendly inhibitor in corrosion inhibition of mild steel in HCl solution: Detailed macro/micro-scale experimental and computational explorations. *Constr. Build. Mater.*, 245, (pp.1164-84).
- 23.Haddadi, S. A.; Alibakhshi, E.; Bahlakeh, G.; Ramezanzadeh, B.;Mahdavian, M.(2019): A detailed atomic level computational and electrochemical exploration of the *Juglans regia* green fruit shell extract as a sustainable and highly efficient green corrosion inhibitor for mild steel in 3.5wt.% NaCl solutions. *J. Mol. Liq.*, 284, (pp. 682-699).
- 24.Prabhu, D., Prabhu, P. R.;Rao, R.(2020): Thermodynamics, adsorption and response surface methodology investigation of the corrosion inhibition of aluminium by *Terminalia chebula* Ritz. Extract in H₃PO₄, *Chemical Papers*, <https://doi.org/10.1007/s11696-020-01318-8>.
- 25.Hussin, M. H.; Kassim, J. M.; Razali, N. N.; & Nasshorudin, D.(2016): The effect of *Tinospora crispa* extracts as a natural mild steel corrosion inhibitor in 1M HCl solution. *Arab J. Chem.*, 9, (pp. S616-S624).