

Original Research Article

Functional pH-responsive Poly(Styrene-Co-2-[(diethylamino)methyl]-4-formyl-6-methoxy-phenyl acrylate) Copolymers for Grafting Tryptophan

Abstract

Vanillin or 4-hydroxy-3-methoxy benzaldehyde has been used for preparing tertiary amine cationic monomer. The monomer has been used as pH-responsive and the functional aldehyde group was used for the formation of Schiff base. The new monomer was abbreviated by DEAMVA and investigated using chemical analysis e.g. ^1H NMR, ^{13}C NMR and FT IR all data were in logic case. The copolymerization of Styrene with 10 and 25 mol % of DEAMVA has been implemented by free radical polymerization. The copolymers have been chemically and physically evaluated e.g. ^1H NMR, FTIR, GPC, and DSC. Post polymerization modification of copolymer with 25mol% (III b) was fabricated via immobilization with Tryptophan, and has also been investigated by the same instrument used lately. Moreover, the responsive property of the posted polymer to pH has also been tested by UV-vis. Spectroscopy.

Comment [MF1]: No abbreviation here like (DEAMVA) full name should be written

Comment [MF2]: Same as above

Keywords: Functional polymer; pH-responsive; Styrene; Vanillin; Amino acid; Post Polymerization modifications

1. Introduction

Smart pH-responsive polymers are kind of polyelectrolytes that have acidic or basic groups in their main chain and either can donate or withdraw protons in response to changes in pH of media [1, 2]. The charge along the polymer chain is responsible for the electrostatic repulsion that increases in the hydrodynamic volume of the polymer molecules [3, 4]. Such kind of transition between tightly coiled and swollen state is affected by any condition that modify

the electrostatic repulsion, e.g. pH, ionic strength, and type of counter ions. The transition state from collapsed into expanded was explained by changes in the osmotic pressure exerted by mobile counter ions and has been neutralized the network charges [2]. Many applications for pH-responsive polymers with the greatest interest in biomedicine e.g. Drug delivery systems and Gene carriers [5-11].

Comment [MF3]: 7 references for one sentence , should be reduced
Make your language more accurate

In the last few decades many scientists were looking for green alternatives of styrene monomer due to its disadvantages like, hazardous air pollutants and emitting during metering mixing process and curing; moreover, the unreacted styrene continues to be released from composites during life cycle [12]. They focused their research in the renewable resources e.g. cellulose, starch, natural oil...etc. they have been performed as alternative to produce bio-based monomers [13]. The lignin produced from Vanillin becoming relatively easily accessible; still there are only a handful of reports on attempts to utilize vanillin as monomers for bio-based polymer synthesis [14, 15]. The chemical modifications on vanillin have implemented attributed to the presence of both aldehyde and hydroxyl active groups [2, 16]. It exposed to dimerization and polymerization process via electrochemical reductive with horseradish peroxidase [17].

Comment [MF4]: Rewrite

Schiff's base was used in the coordination chemistry and was found to be stable under redox conditions [18]. Recently, vanillin was used to form Schiff bases [19]. Their biological activities have been widely reported in many publications [20-24]; the most useful articles by Yuan et al., they used Schiff base as a stimuli-responsive linker in the polymer chain [25]. The imine linkage is pH-responsive [26, 27]. Moreover; the complexes formation of the imine have also been used to achieve the pH-responsiveness of the linker [28-33]. Several articles have reported "click reaction" as linkers for many bio-based molecules [34-36]. In this work, we fabricated new pH-responsive polystyrene copolymers from vanillin as renewable resource. The aldehyde group was used for posting biomolecule by Schiff base.

Comment [MF5]: Language

Comment [MF6]: Language

Comment [MF7]: The aim of this work is not clear

2. Experimental

2.1. Material

(AIBN Acrōs) 2,2'azobis(isobutyronitrile) was recrystallized from methanol, acryloyl chloride (98% Merck), vanillin (99% Acrōs), styrene (99% Acrōs), triethylamine (Merck), tryptophan (97 % Acrōs). Toluene, dichloromethane, tetrahydrofuran, and diethylether were distilled. Other chemicals were used as purchased.

2.2. Instruments

Bruker AV 500 spectrometer was used to record ^1H and ^{13}C NMR spectra in CDCl_3 or DMSO-d^6 at 500 MHz and 125 MHz. FT IR Vertex 70 Fourier transform infrared instrument for recording IR spectra. The Molecular weights (M) and dispersity (D) were analysed by size exclusion chromatography (SEC). Chloroform was used as eluent (containing of 0.1 vol% triethylamine). UV/vis spectroscopy (Perkin Elmer Lambda 45) was used to estimate the concentration of amino acid in post-polymer. The pH of polymer solution was in THF and measured by pH-meter model VWR pH100. Perkin Elmer Differential Scanning Calorimeter (DSC) Pyris 1 was used for the glass temperature T_g of solid polymers at heating and cooling rate of 5 °C/min.

2.3. Synthesis of Monomer

2.3.1. Synthesis of 2-[(diethylamino)methyl]-4-formyl-6-methoxy-phenyl acrylate (DEMAVA) [20].

Step1: Synthesis of 3-[(diethylamino) methyl]-4-hydroxy-5-methoxybenzaldehyde [20]

10g (0.065 mol) of vanillin, (4-hydroxy-3-methoxy benzaldehyde), 10g (0.33 mol) of formaldehyde and 10g of diethylamine (0.136 mol) were dissolved in 150 mL ethanol in 250 mL round bottomed flask fitted with reflux condenser. They were refluxed in oil bath at 90-100 °C for 3h. The mixture allowed cooling to room temperature. The solvent was removed under reduced pressure to collect the product. Yield %: 97%. Physical state: Yellowish white solid.

^1H NMR (500 MHz, CDCl_3): δ (ppm) = 1.18(t, 6H, 12- CH_3), 1.26(br., s, 1H, 8-OH), 2.73(q, 4H, 11- CH_2), 3.92(s, 2H, 9- CH_2), 3.94(s, 3H, 7- CH_3), 7.25, 7.34(dd, 2H, $^4J = 1.6$, 3,3'-Ar-CH, 10- NH^+), 9.77(s, 1H, 1-CHO).

^{13}C -NMR (125 MHz, CDCl_3): δ (ppm) = 10.82 (2C, 12- CH_3), 46.35 (2C, 11- CH_2), 55.85 (1C, 10- CH_2), 56.01 (1C, 8- CH_3), 109.68 (1C, 4'-Ar-CH), 120.84 (1C, 4-Ar-CH), 125.75 (1C, 5-Ar-C), 127.99 (1C, 3-Ar-CH), 148.65 (1C, 6-Ar-CH), 154.87 (1C, 7-Ar-C), 191.65 (1C, 2-C=O).

IR (KBr): ν (cm^{-1}): 2987 (s) (CH_2 , CH_3), 1650 (s) (2-C=O), 1706 (s) (7-C=O), 820- 868 (m) (Ar-CH).

Step2: Synthesis of 2-[(diethylamino) methyl]-4-formyl-6-methoxyphenyl acrylate [20]

13.9g (0.058 mol) of 3-[(diethylamino) methyl]-4-hydroxy-5-methoxybenzaldehyde (**I**) was dissolved in 200 mL dry CH_2Cl_2 in two neck flask fitted with argon balloon. During stirring 12.3g (0.12 mol) of TEA was added. The reaction mixture allowed cooling in ice bath to 0-

Comment [MF8]: DMSO- d^6 has been identified as a solvent for HNMR while, CDCl_3 was used

Comment [MF9]: Rewrite

5°C. After cooling, 5.4g (0.059 mol)acryloyl chloride was added drop wise. The yellowish suspension was stirred at 5°C for 1h, and then allowed to stir at RT for 6 h. The precipitate was filtered and solvent was evaporated under reduced pressure. The product was extracted by CH₂Cl₂ and wash three times with 100ml distilled water then one time with 0.1M Na₂CO₃, and again with 100 mldistilled water, then product dried with MgSO₄ overnight. Yield %: 80%, Physical state: Orange solid.

¹H NMR (500 MHz, CDCl₃):δ(ppm) = 1.10(t, 6H,14-CH₃), 2.48 (q, 4H, 13-CH₂), 3.51 (s, 2H, 11-CH₂), 3.88 (s, 3H, 7-CH₃), 6.06 (dd, ²J = 1.3 Hz, ³J = 10.40 Hz,1H, 10a-CH), 6.37(dd, ³J = 10.40 Hz, ³J = 17.30 Hz, 1 H, 9-CH), 6.63 (dd, ²J = 1.3 Hz, ³J = 17.30 Hz, 10b-CH),7.25, 7.34 (dd, 3H, ⁴J = 1.6, ⁴J = 1.9, 3,3'- Ar-CH), 9.77 (s,1H, 1-CHO).

¹³C-NMR (125 MHz, CDCl₃):δ(ppm) =10.82 (2C, 12-CH₃), 46.35 (2C, 11-CH₂), 55.85 (1C, 10-CH₂), 56.01 (1C, 8-CH₃),109.68 (1C, 4'-Ar-CH), 120.84 (1C, 4-Ar-CH), 125.75 (1C, 5-Ar-C), 127.99 (1C, 3-Ar-CH), 148.65 (1C, 6-Ar-CH), 154.87 (1C,7-Ar-C), 191.65 (1C, 2-C=O).

IR (KBr): ν (cm⁻¹): 2987 (s) (CH₂, CH₃), 1650 (s) (2-C=O), 1706 (s) (8-C=O), 820- 868. (m) (Ar-CH).

2.4.Synthesis of Polymer

2.4.1. Synthesis of poly(Styrene-co-DEAMVA) with 10and 25 mol% of DEAMVA (2a)

A mixture of 10 and 25mol%, 1.088 g, and 2.176 g respectively of 2-[(diethylamino) methyl]-4-formyl-6-methoxyphenyl acrylate,4g (0.038mol) styreneand 10⁻³ mol% AIBN of the total mole% of monomers was dissolved in 70 mltoluene and then added to 100 ml round bottom flask. They were purged with argon for 15 min., and then heated in an oil bath at 70-80°C with continuous stirring for 6h. After cooling at room temperature followed in refrigerator,and was precipitated by solvent evaporation using rotatory evaporator.Polymer was purified by dissolved in THF, and re-precipitated in diethylether to remove the unreacted monomers and impurities. Yield %: 91%, and 82 for 10, and 25mol% respectively, Physical state: Yellowish white solid.

¹H NMR (500 MHz, CDCl₃):δ(ppm) = 0.50-2.71 (m, 9H, CH, CH₂-styrene repeating unit, 2CH₃ DEAMVA), 3.25-3.93 (m, 9H, 2CH₂, NCH₂, OCH₃ DEAMVA), 4.60-5.13 (m, 3H, CH, CH₂-DEAMVA repeating unit), 6.30-7.52(m, 6H, H-Ar), 9.75-9.97 (br., 1H, -CHO).

IR (KBr): ν (cm⁻¹): 2990(s) (CH-Aliphatic), 1720-1743 (s) (-C=O), 1134 (s) (-OCH₃).

2.4.2. Synthesis of 25mol% (2a-25) Poly(Styrene-co-DEAMVA)-post-tryptophan (2b) as a function of pH-responsive

In 50 ml round bottom flasks 1.0 g of 25mol% poly(Styrene-Co-DEAMVA) and 1.0 g of tryptophan has been dissolved in 30 ml THF. The reaction was implemented in different pH solutions pH4, pH7, pH9, pH10, pH12 by addition of NaOH and HCl. The mixtures were stirred gently for 2 h at room temperature. Solvent was removed under reduced pressure. After that the precipitate was dissolved in THF and re-precipitate in diethylether at -40 °C to remove impurities and unreacted molecules. Physical state: Brownish solid.

¹H NMR and IR of poly (Styrene-co-DEAMVA)-post-Tryptophan at pH12(IV)

¹H NMR (500 MHz, DMSO): δ (ppm) = 0.70-1.22 (m, 6H, 2CH₃, DEAMVA), 1.30-1.65 (m, 1H, CH repeating Styrene), 1.82-2.35 (m, 2H, CH₂ repeating styrene), 2.80-2.90 (m, 2H, 2NCH₂, DEAMVA), 3.30-3.40 (m, 2H, CH₂, DEAMVA), 6.10-6.34 (m, 1H, C=CH, Tryptophan), 6.80-7.85 (m, 9H, H-Ar), 8.5-8.6 (br. (s), 1H, CH=N), 9.30-9.94 (s) 1H, NH, Tryptophan).

IR (KBr): ν (cm⁻¹): 2995 (m) (CH-Aliphatic), 1663-1650 (s) (7-C=O), 1570-1560 (s) (4-CH=N), 1026-1107 (s) (8-OCH₃).

3. Results and Discussion

3.1. Synthesis of Monomer, copolymers and grafted copolymers

The chemical procedure has been described in **Scheme 1**. Monomer (**1b**) or 2-[(diethylamino)methyl]-4-formyl-6-methoxyphenyl acrylate (DEAMVA); it was prepared in two steps. The first is the preparation of (3-[(diethylamino)methyl]-4-hydroxy-5-methoxy-benzaldehyde) and has been occurred by the reaction of vanillin with diethylamine and formaldehyde according to Mannich reaction mechanism [1, 20]. The second is the preparation of 2-[(diethylamino)methyl]-4-formyl-6-methoxyphenyl acrylate (DEAMVA). It has been performed by the reaction of compound (**1a**) with acryloyl chloride and TEA to form (**1b**). They have been chemically investigated by ¹H NMR and ¹³C and FT IR. **Figure 1-3** provided all data and in logic state and has also been proved the presence of aldehyde group at 9.97 ppm and 196 ppm.


To optimize the general properties of styrene by free radical copolymerization with 10 and 25 mol% of DEAMVA were used in AIBA as initiator as **scheme 1**. The chemical structure was estimated by ¹H NMR and FT IR as shown in **Figure 4**. The ¹H NMR of copolymers **1a**,

Comment [MF10]: Language

Comment [MF11]: The full name should be used first then the symbol

2a demonstrated specific broad multiples peaks at $\delta = 0.73-1.35$ ppm of $2\text{CH}_3\text{DEAMVA}$, at $\delta = 7.08-7.62$ ppm of Ar-H of each styrene and DEAMVA, and at $\delta = 9.94$ of H-CHO of DEAMVA monomer. FTIR illustrated the presence of (C=O stretch) ester at 1745 cm^{-1} . The actual content of each monomer in the polymer main chain was detected from $^1\text{H NMR}$ spectra via the determination of the ratio of the intensity of the signals at 6.66 ppm (for H, Ar-H styrene) with signal at 9.94 ppm (for CHO of DEAMVA) as written in **Table 1**.

The aldehyde functional group in the polymer main chain was used for post-polymerization with any primary amino compound producing Schiff's base as in **Scheme 1**. The post-polymerization process was fabricated at room temperature in THF at different pH (pH4, pH7, pH9, pH10, pH12). Post-copolymer was investigated by $^1\text{H NMR}$ and FT IR. The $^1\text{H NMR}$ demonstrated the disappearance of aldehyde signal at 9.74 ppm and formation of new imino (HC=N) signal at about 8.5 ppm as in **Figure 3**. **Figure 4** showed FT IR spectra that proved the presence of imine (C=N stretch) at about 1563 cm^{-1} .

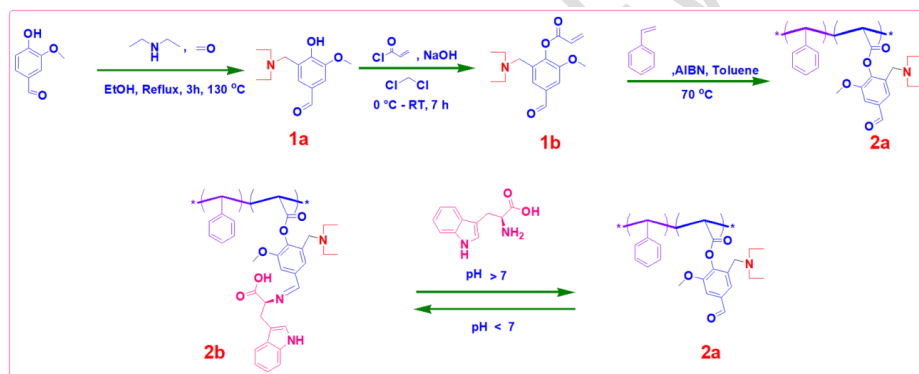

Scheme 1: Synthesis of new monomer, copolymers and post-polymer with Tryptophan.

Table 1: Yield, composition, conversion, number average molecular weight, polydispersity, and glass temperature of, Poly (*S-co*-DEAMVA) 10, 25 mole ratio of DEAMVA and Poly (*S-co*-DEAMVA)-post-try.

Polymer	Yield (%)	$^1\text{H NMR}$ DEAMVA (mol %)	Conversion (%)	M_n^a (g/mol) 10^4	\bar{D}^b	T_g^c (°C)
2a-10	91	6.35	-	44600	1.88	114
2a-25	82	17.67	-	17760	2.04	134
2b	76	-	84	15458	2.38	139

^aNumber average molecular weight,

^b Polydispersity,

^c Glass transition temperature,

^d Lower critical solution temperature.

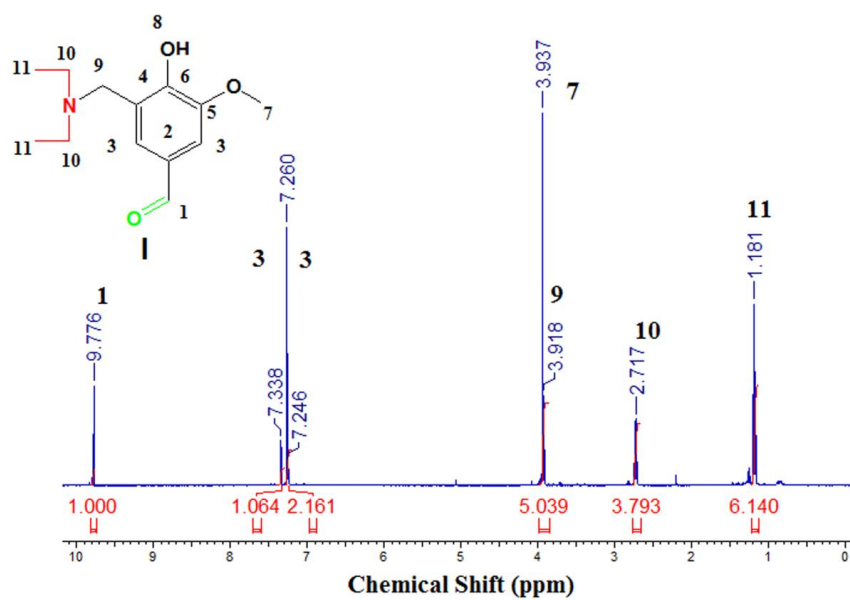


Figure 1: ¹H NMR (CDCl₃) of 2-[(diethylamino)methyl]-4-formyl-6-methoxyphenyl acrylate.

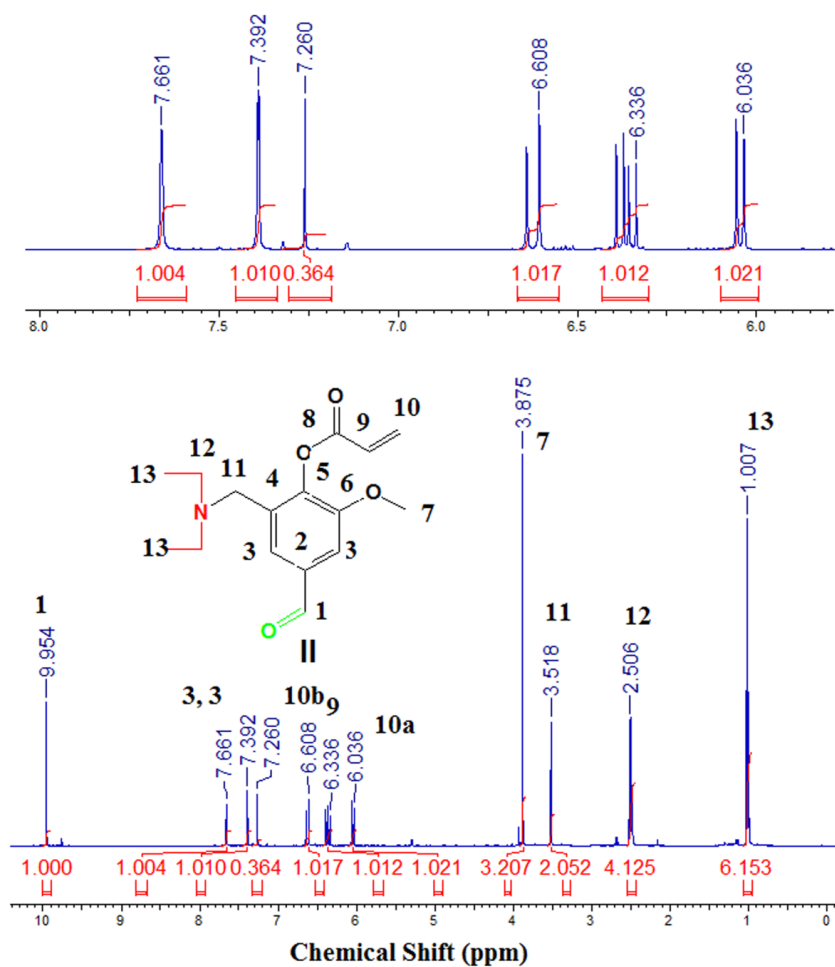


Figure 2: ^1H NMR (CDCl_3) of 2-[(diethylamino)methyl]-4-formyl-6-methoxyphenyl acrylate (DEMAVA).

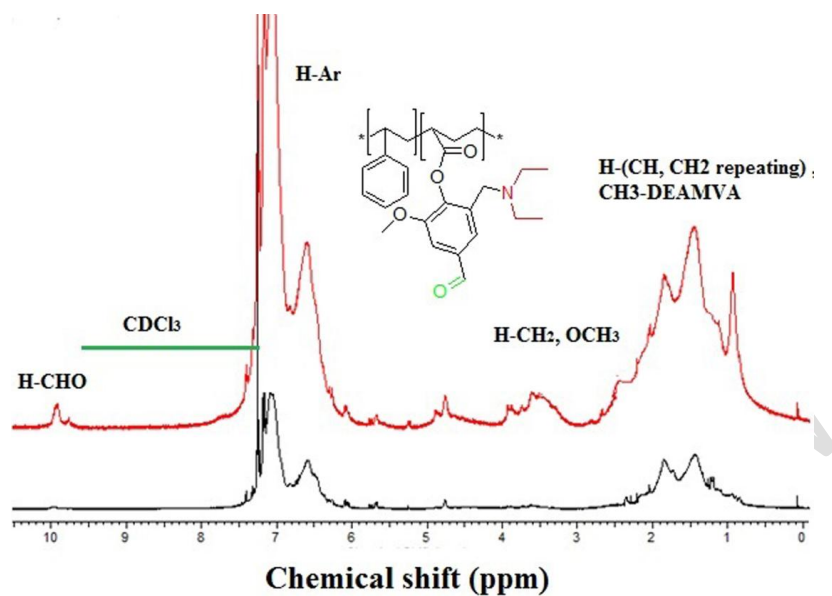


Figure 3: ^1H NMR spectra (CDCl_3) of P(S-*co*-DEAMVA) 10, 25 mole ratio of DEAMVA

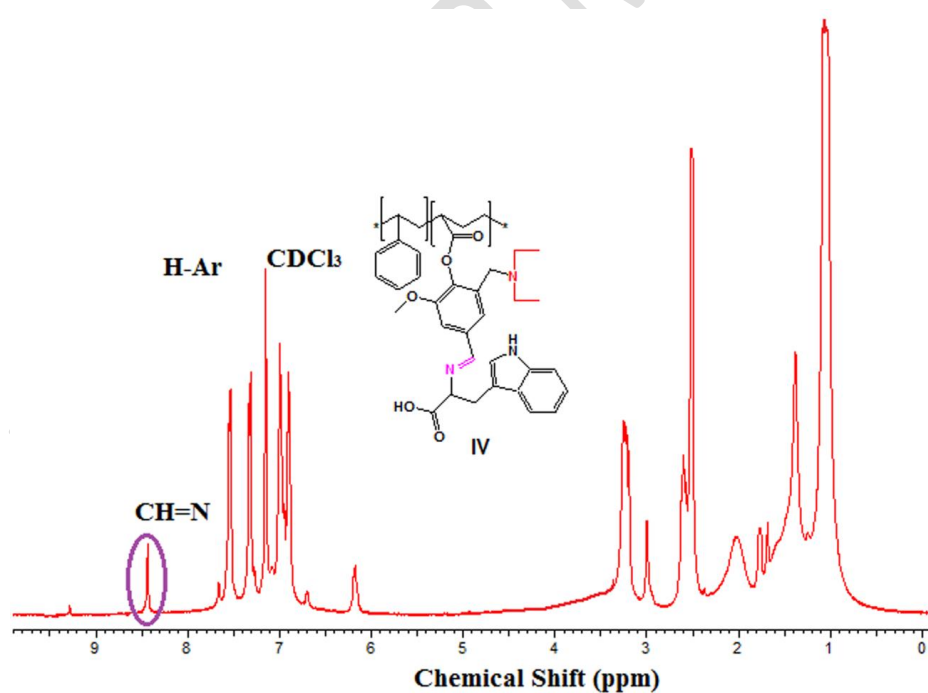


Figure 4: ^1H NMR spectra (DMSO) of P(styrene-*co*-DEAMVA)-g-Tryptophan

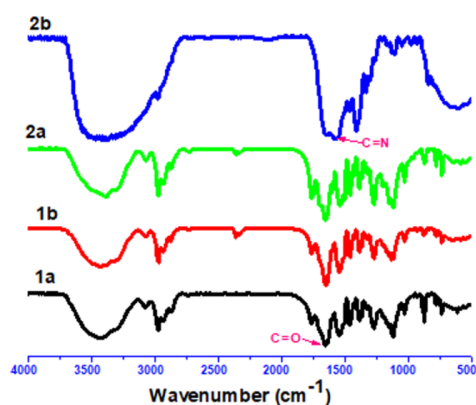


Figure 5: IR spectra KBr for DEAMV (I), DEAMVA (II), Poly (Styrene-*co*-DEAMVA) (III b) and grafted copolymers IV.

3.2. Polymer characterization

3.2.1. Molecular weight

Size exclusion chromatography was used for determination of number average molecular weight (M_n) and dispersity (D) of polymers using Polystyrene (PS) as standard in CHCl_3 . **Table 1** summarized all recorded data for all copolymers. **Figure 6** shows the relation between molecular weight and $\log M$ as recorded by GPC and demonstrated one peak, that demonstrated the disappearance of low molecular weight like monomers or impurities.

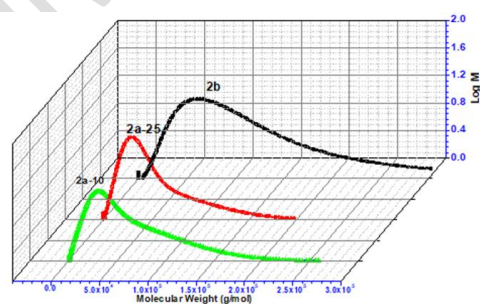


Figure 6: GPC molecular weight of copolymers

3.2.2. Conversion of poly (Styrene-Co-DEAMVA) to poly(Styrene-Co-DEAMVA)-g-tryptophan

The conversion of poly (Styrene-Co-DEAMVA) to poly (Styrene-Co-DEAMVA)-post-tryptophan by the chemical reaction, absorption was measured as function with pH at constant time (2h) for each test. The polymer solution was diluted to 10^{-3} W/V for each run.

Figure 7 illustrates the UV-vis. Spectroscopy of post reaction between poly(Styrene-Co-DEAMVA) with tryptophan. We noticed the disappearance of C=O aldehyde group at 250-270 nm and formation of new bond at 340-380 nm of C=N imine linkage. The formation of imino linkage has increased with increasing the pH value starting with pH5 which showed about zero absorbance and has been increased gradually till the highest value of absorbance pH12. **Figure 8** shows the relation between pH and absorbance intensity at constant time.

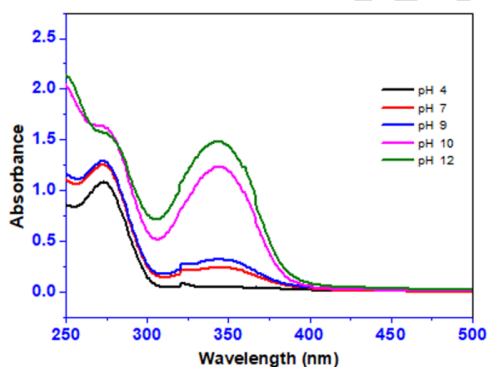


Figure 7: UV-vis. Spectroscopy for the formation of grafted poly (Styrene-Co-DEAMVA)-post-tryptophan as increasing in absorbance from pH5-pH12.

Comment [MF12]: in UV-Vis spectra cannot be indicated the function group

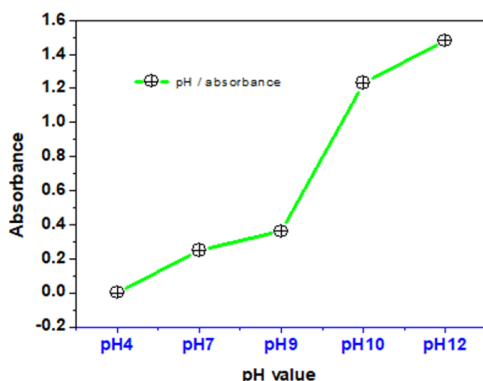


Figure 8: Relation between pH values and absorbance

3.2.3. Glass transition temperature

The glass transition temperature (T_g) was measured for all polymers. It was detected by Differential Scanning Calorimeter at heating rate 5 °C/min. It was recorded as the mid-point inflection in the thermogram. They have been tabulated in **Table 1** for copolymers and post-copolymer. a single T_g for each sample, which indicating the formation of random copolymers as shown in **Figure 9**[36]. The T_g of the homo-polystyrene(PS) showed at 100°C[37]. Copolymerization with DEAMVA change the hydrophobic and hydrophilic groups demonstrated in aromatic and tertiary amine respectively that increased T_g , which attributed to decrease in the spacing and therefore increasing in the interaction between polymer chains producing lesser flexibility and T_g of the polymer increased [36]. By introducing post molecule in copolymer (**2b**) main chain has directly influenced on raising the T_g due to the steric hindrance of aromatic molecule.

Comment [MF13]: what is the benefit, what is the effect of pH

Comment [MF14]: needs accuracy

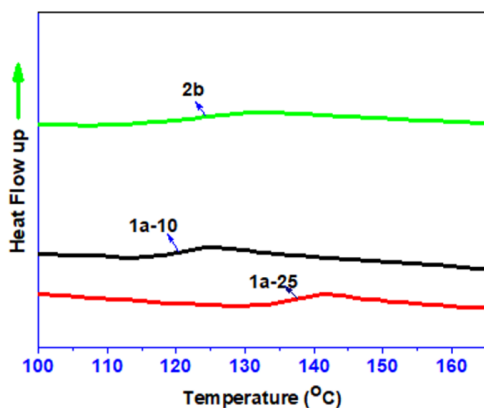


Figure 9: DSC shows the T_g of copolymers and grafted copolymer

4. Conclusion

We prepared functional polystyrene copolymers. The pH-responsive monomers have tertiary amine and aldehyde groups, and were prepared in two steps. We used free radical polymerization of styrene with two mole ratios of new monomer was for fabricating copolymers. The post-polymerization was created by the reaction of aldehyde group with primary amine. Tryptophan was used post-polymerization. The uv.vis. Spectroscopy was used for detecting the post-polymer formation through the Schiff base absorption at different pH values. The highest absorption at pH12 and lowest at pH4 have been observed.

Comment [MF15]: re- write

COMPETING INTERESTS DISCLAIMER:

Authors have declared that no competing interests exist. The products used for this research are commonly and predominantly use products in our area of research and country. There is absolutely no conflict of interest between the authors and producers of the products because we do not intend to use these products as an avenue for any litigation but for the advancement of knowledge. Also, the research was not funded by the producing company rather it was funded by personal efforts of the authors.

5. References

1. Abdelaty, M SA. (2018) Poly(*N*-isopropylacrylamide-*co*-2-((diethylamino)methyl)-4 formyl-6-methoxyphenylacrylate) Environmental Functional Copolymers: Synthesis, Characterizations, and Grafting with Amino Acids. *Biomolecules*, 8, 138; doi:10.3390/biom8040138

Comment [MF16]: volume should be in one style

2. Abdelaty MSA, Kuckling D (2016) Synthesis and Characterization of New Functional Photo Cross-Linkable Smart Polymers Containing Vanillin Derivatives. *Gels* 2: 1-13. doi:10.3390/gels2010003.
3. Sato E, Masuda Y, Kadota J, Nishiyama T, Horibe H (2015) Dual stimuli-responsive homopolymers: Thermo- and photo-responsive properties of coumarin-containing polymers in organic solvents. *EurPolym J* 69: 605–615. doi:10.1016/j.eurpolymj.2015.05.023
4. Abdelaty, M SA. (2018) Environmental Functional Photo-Cross-Linked Hydrogel Bilayer Thin Films from Vanillin. *J Polym Environ.* , 26, 2243–2256. DOI: 10.1007/s10924-017-1126-y
5. Abdelaty, M S A. (2021) Trends in the Phase Separation Temperature Optimization of a Functional and Thermo-pH Responsive Terpolymer of Poly (N-isopropylacrylamide-co-N-(2-(dimethylamino)ethyl) Acrylamide-co-vanillin Acrylate). *J Polym Environ.* <https://doi.org/10.1007/s10924-021-02096-4>
6. Abdelaty, MSA. (2018) Preparation and Characterization of New Environmental Functional Polymers Based on Vanillin and N-isopropylacrylamide for Post Polymerization. *J Polym Environ.* , 26, 636–646. DOI.org/10.1007/s10924-017-0960-2
7. KocakG, TuncerC, and BüttinV, (2017) pH-Responsive polymers. *Polym. Chem.*8: 144-176. DOI:10.1039/C6PY01872F
8. Bazban-S S, Hasani-Sadradadi M, Karkhaneh A, Serpooshan V, Jacob KI, Moshaverinia A, Mahmoudi M (2017) Revisiting structure-property relationship of pH-responsive polymers for drug delivery applications. *J Control Release.* 10,46-63. doi:10.1016/j.jconrel.2017.02.021
9. Ankit K, Carlo M and Hyo-Jick C (2017) Smart Microparticles with a pH-responsive Macropore for Targeted Oral Drug Delivery. *Scientific Reports.* 7 : 3059 -3067 doi:10.1038/s41598-017-03259-x
10. Lin L, WenDong Y, YueFeng R, XiaoYang L and JianQing G (2017) *Journal Drug Delivery.* 24: 569-581 <https://doi.org/10.1080/10717544.2017.1279238>
11. Jing X, Anqi L, Jianshu L (2017) Advances in pH-Sensitive Polymers for Smart Insulin Delivery. *Macromol. Rapid Commun.*, 38: 1700413 1-14. DOI: 10.1002/marc.201700413
12. Chen G, Hoffman AS (1995) Graft copolymers that exhibit temperature-induced phase transition over a wide range of pH. *Nature*373:49–52. doi:10.1038/373049a0

Comment [MF17]: volume should be in one style

Comment [MF18]: same as above

Comment [MF19]: you should be chosen between J or Journal

Comment [MF20]: J or Journal

13. Hoffman AS, Stayton PS, Bulmus V (2000) Really smart bioconjugates of smart polymers and receptor proteins. *J Biomed Mater Res* 52:577-586. doi: 10.1002/1097-4636(20001215)52
14. Abdelaty, M.S.A (2021) Poly(N-isopropylacrylamide-co-2-((diethylamino)methyl)-4-methylphenyl acrylate) thermo-ph responsive copolymer: trend in the lower critical solution temperature optimization of Poly (N-isopropylacrylamide). *J Polym Res* 28, 213. <https://doi.org/10.1007/s10965-021-02574-2>
15. Abdelaty, M.S.A (2019) Influence of vanillin acrylate and 4 acetylphenyl acrylate hydrophobic functional monomers on phase separation of N isopropylacrylamide environmental terpolymer: fabrication and characterization. *Polym. Bull.*, DOI 10.1007/s00289-019-02890-0
16. Fache M, Darroman E, Besse V, Auvergne R, Sylvain Caillol, S, Boutevina B (2014) Vanillin, a promising biobased building-block for monomer synthesis. *Green Chem* 16:1987-1998. doi: 10.1039/C3GC42613K
17. Ananda S A, Bernard W, Ashfaque R, (2012) Vanillin based polymers: I. An electrochemical route to polyvanillin. *Green Chem* 14:2395-2397. doi: 10.1039/C2GC35645G
18. Ananda S A, Ashfaque R (2012) Vanillin-Based Polymers-part II: Synthesis of Schiff Base Polymers of Divanillin and Their Chelation with Metal Ions. *ISRN Polymer Science* 1:1-5. doi:10.5402/2012/532171
19. Abdelaty, M.S.A (2018) Environmental Functional Photo-cross-linked Hydrogel Bilayer Thin films From Vanillin (Part 2): Temperature responsive layer A, Functional, Temperature and pH layer B. *Polym. Bull.*, 11, 4837–4858. DOI: 10.1007/s00289-018-2297-y.
20. Abdelaty, M.S.A. (2018) Preparation and Characterization of Environmental Functional Poly(Styrene-Co-2-[(Diethylamino)Methyl]-4-Formyl-6-Methoxy-Phenyl Acrylate) Copolymers for Amino Acid Post Polymerization. *Open Journal of Polymer Chemistry*. 8, 41-55. <https://doi.org/10.4236/ojpchem.2018.83005>
21. Firdaus M, Meier MAR (2013) Renewable copolymers derived from vanillin and fatty acid derivatives. *EurPolym J* 49:156–166. doi:10.1016/j.eurpolymj.2012.10.017
22. MialonLVanderhenst R, Pemba AG, Miller SA (2011) Polyalkylenehydroxybenzoates (PAHBs): Biorenewable Aromatic/Aliphatic Polyesters from Lignin. *Macromol Rapid Commun* 32:1386–1392. doi: 10.1002/marc.201100242

23. Abdelaty, M.S.A., and Kuckling D. (2018) Poly (N-Isopropyl Acrylamide-Co-Vanillin Acrylate) Dual Responsive Functional Copolymers for Grafting Biomolecules by Schiff's Base Click Reaction. *Open Journal of Organic Polymer Materials*. 8,15-32. DOI: 10.4236/ojopm.2018.82002
24. Abdelaty, MSA (2019) Layer by Layer Photo-Cross-Linked Environmental Functional hydrogel Thin Films Based on Vanillin: Part 3. *J Polym Environ*. DOI: 10.1007/s10924-019-01421-2
25. Abdelaty, MSA and Kuckling, D (2016) Synthesis and Characterization of New Functional Photo Cross-Linkable Smart Polymers Containing Vanillin Derivatives. *Gels*, 2: 1-13. DOI:10.3390/gels2010003
26. Abdelaty, M S A. (2021) a facile Method for the Preparation of Hydrophilic-Hydrophobic Functional Thermo-pH Responsive Terpolymers Based on Poly(NIPAAm-co-DMAA-co-DMAMVA) and Post-Polymerization *J Polym Environ*. DOI: 10.1007/s10924-021-02117-2
27. Zhou L, Cai Z, Yuan J, Kang Y, Yuan W, Shen D (2011) Multifunctional hybrid magnetite nanoparticles with pH-responsivity, superparamagnetism and fluorescence. *PolymInt* 60:1303-1308.doi: 10.1002/pi.3081
28. Lyas G, Burak A, Serkan K, Oguz Y S, Emel Y and Selahattin S(2017) Synthesis of imine bond containing insoluble polymeric ligand and its transition metal complexes, structural characterization and catalytic activity on esterification reaction. *Designed Monomers and Polymers*,1, 441-448, DOI: 10.1080/15685551.2017.1332139
29. Etika KC, Cox MA, Grunlan JC (2010) Tailored dispersion of carbon nanotubes in water with pH-responsive polymers. *Polymer* 51:1761-1770. doi: 10.1016/j.polymer.2010.02.024
30. Oda Y, Kanaoka S, Aoshima S (2010) Synthesis of dual pH/temperature-responsive polymers with amino groups by living cationic polymerization. *J PolymSci Part A PolymChem* 48:1207-1213.doi: 10.1002/pola.23882
31. Yan Q, Zhou R, Fu C, Zhang H, Yin Y, Yuan J (2011) CO₂-Responsive Polymeric Vesicles that Breathe. *AngewChem Int. Ed* 50:4923.doi: 10.1002/anie.201100708
32. Dondoni A, Marra A (2012) Recent applications of thiol-ene coupling as a click process for glycoconjugation. *ChemSoc Rev* 41:573-586. doi: 10.1039/C1CS15157F
33. Fu R, Fu G (2011) Polymeric nanomaterials from combined click chemistry and controlled radical polymerization. *PolymChem* 2:465-475. doi: 10.1039/C0PY00174K

34. Franc G, Kakkar AK (2010) Click” methodologies: efficient, simple and greener routes to design dendrimers. *ChemSoc Rev* 39:1536-1544. doi: 10.1039/B913281N
35. Iha RK, Wooley KL, Nyström AM, Burke DJ, Kade MJ, Hawker CJ (2009) Applications of orthogonal "click" chemistries in the synthesis of functional soft materials. *Chem Rev* 109:5620-5686.doi: 10.1021/cr900138t
36. Gupta S, Kuckling D, kretschmer K, Choudhary V, Adler HJ (2007) Synthesis and characterization of stimuli-sensitive micro- and nanohydrogel based on photocrosslinkable poly(dimethylaminoethylmethacrylate). *Journal of polymer science Part A Polymer Chemistry* 45:669-679.doi: 10.1002/pola.21846
37. Mark, James E. (2009) *Polymer data handbook* (2nd Edition). Oxford University Press. ISSN 978-0-19-518101-2