

# PROPERTIES OF SUSTAINABLE CONCRETE CONTAINING LIMESTONE: A REVIEW

**Keywords:** Limestone; cement; concrete; strength; workability; compressive strength; modulus of elasticity.

**Abstract** – The most frequently used building material on this planet is concrete. Concrete is the supreme user of natural resources as a result of its widespread use as construction material. Cement production produces significant amount of greenhouse emissions. The protection of environment has become challenging in many developing countries, 7-8% of CO<sub>2</sub> is produced by the cement industry that causes huge damage to the environment. In concrete production, and limestone can be a partial alternative to cement. The limestone waste is transported and disposed in landfills. The disposal of limestone waste material in the open areas is causing several problems. In this study, the properties of concrete incorporating limestone waste are reviewed. Workability, compressive strength, split tensile strength, flexural strength, modulus of elasticity, and durability are among qualities of limestone waste concrete that have been discussed in this study. The cement was replaced by limestone waste in the ratio of 25% to 30% in concrete By limiting the waste of limestone in the concrete, cement content can be reduced, which turns into an eco-friendly solution.

## 1. Introduction

The most rapidly expanding industry around the globe is the construction industry, which consumes most of the natural resources [1]. Cement is an important building ingredient since it is utilized as a binder in the creation of mortar [2]. Cement production, on the other hand, results in the release of greenhouse gases into the atmosphere [3-5]. According to studies, every ton of cement produced emits roughly half ton of carbon dioxide, which is a considerable quantity contributing in 5% of total man-made CO<sub>2</sub> emissions, with India accounting for nearly 7-8% of

overall carbon dioxide emissions [6,7]. In industries, waste production is unavoidable; nevertheless, by using industrial waste as a partial substitution for conventional cement, it is possible of constructing low-carbon system having lower embodied energy of production. From the previous decades the stone sector has amplified speedily due to huge infrastructural developments. In India production of stone is very huge lodging third position in the world and Rajasthan stocks about 50% of its productions. Limestone is made after the stone has been sawed and polished to the desired dimension [8]. The mining operations produce a lot of trash, with only half of the limestone being acquired [9]. The blocks of stone generate slurry during processing in gang saws, which are combined with the limestone solid to produce a limestone slurry [10, 11]. By addressing the problem of uncontrollable fine slurry powder disposal in the soil, the use of limestone waste in concrete will greatly reduce environmental pollution [12]. Due to massive infrastructural expansions, the stone sector has grown fast in the previous two decades with new technologies [13]. The annual production of the stone in India is enormous, with Rajasthan accounting for over half of the total [14].

### **1.1 Benefit of the limestone contained in concrete mix**

At present moment, cement in concrete is considered to be the greatest significant building material [15]. Despite of its widespread use in the construction industry for more than a century, low compressive strength, low tensile and flexural strength, poor bonding, porosity and permeability, poor resistance to acid and other hostile chemical, weak elastic modulus, shrinkage, and flexibility are just a few of the defects [16-19]. Mechanical measures, like adding reinforcement and mineral admixtures like fly ash, lime, and slag, can improve the compressive, tensile, and flexural strength of cement concrete [20-22]. Lime has been employed as a binding ingredient for structural purpose since prehistoric times [23]. In various nation, powder of limestone is commonly utilized as filling material in concrete [24]. Lime is abundantly available in nature and it is also not very expensive [25]. Concrete's workability can be improved by adding limestone powder [26].

### **1.2 Impact of limestone powder on the environment**

Limestone dust created by large operations of quarry that not only utilizes valuable land but also causes a lot of environmental issues [27, 28]. Lime dust disposal and utilization are two topics that are now attracting attention Mining is done using open cast method, which is used on both big and small scales [29]. The limestone produced is mostly used for the manufacturing of

cement, lime, and edible lime [30]. According to scientific studies, limestone mining has a number of negative environmental consequences, including losing of forest by deforestation, contamination of water, air and land, diminution of flora and fauna, biodiversity being reduced, soil erosion, unsteadiness of rock masses, variations in the landscape, and deprivation of land used for agriculture [31-33]. The effect of mining on various resources like water, soil, and air quality, as well as forest degradation and contamination of water are summarized and investigated [34]. The government has now implemented many policies that impact the overall influence of mining of limestone. The policies recommend that stakeholders and cement plant owners should pay a close attention to the environmental challenges that exist in zone [35, 36]. Efficient management initiatives of resources of water, forest and soil must be undertaken for preventing additional loss of cover of forest and top layer of soil, as well as declining of the quality of water, degradation of soil, noise and air pollution [37].

## 2. Workability of concrete

### 2.1. Slump

Concrete workability, which is computed by slump test, compaction factor test, etc. is an important quality in the manufacturing of concrete. Alexandra et al. [38] measured the value of slump and compaction factor of limestone for a constant w/c ratio of 0.35 for 0, 10, 20, 30, and 40% replacement of cement by limestone slurry respectively. Fig.1 shows that as the fraction of lime **cement replaced by limestone slurry increases there is an increase in the compaction factor.**

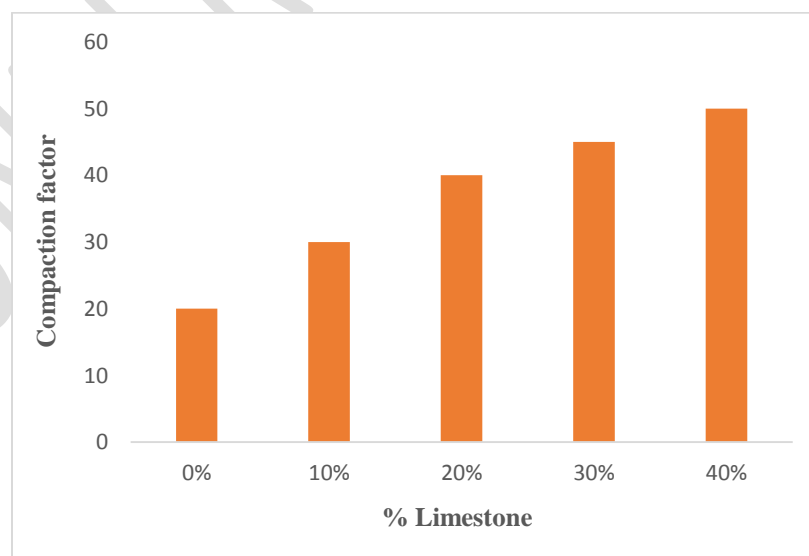


Fig. 1. Workability test results [38]

Mohammad et al. [39] investigated the slump and compaction factor of concrete made with limestone powder for a water cement ratio of 0.45. The slump and compaction factor were measured for substitution of limestone powder by cement at level of 0%, 20%, 30%, and 40%. With the limestone powder fineness, the slump value got increased and the compaction factor dropped with the increase in percentage of cement been replaced by the powder of limestone.

Skender et al. [40] supported an experiment for determining the workability of concrete specimens with replacement of limestone powder with the replacement level of 0%, 10%, and 15%, 20%, 25%, 30% and 35% used to replace cement. While, 0% to 40% limestone powder was used for substituting the fine aggregates. The results depict that with the increment in amount of cement replaced by limestone powder, the slump value got increased. Fig. 2 represents the results of workability of the concrete samples.

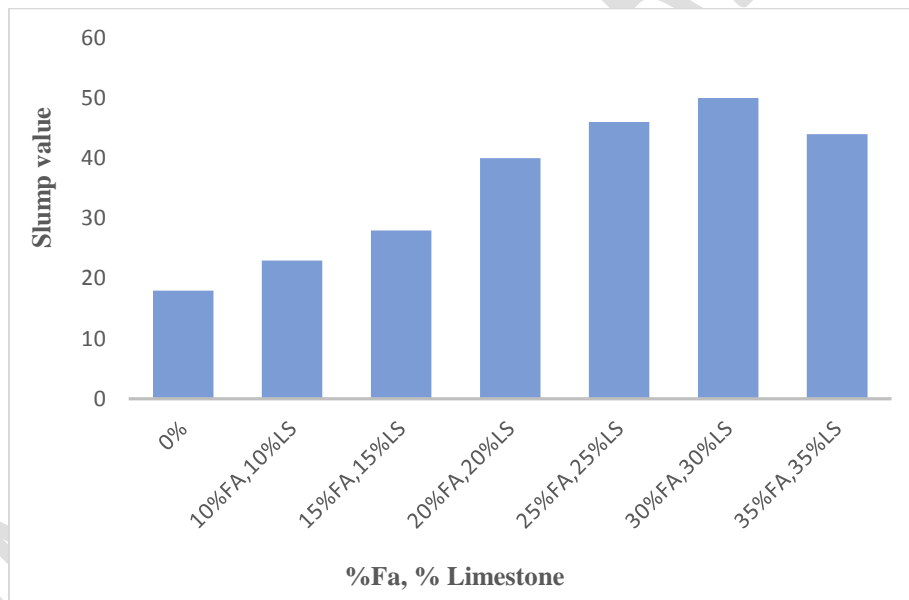


Fig. 2. Workability test results [40]

Dasilva et al. [41] measured the slump value of concrete after the cement was replaced with limestone. Concrete with water cement ratio of 0.5 was swapped in following percentages of 0%, 20%, 30%, 40% and 50%, respectively. There was an increment in the slump value and increasing in the compressive strength as the fraction of cement replaced with limestone and the water cement ratio was increased. Fig. 3 depicts the test results of workability.

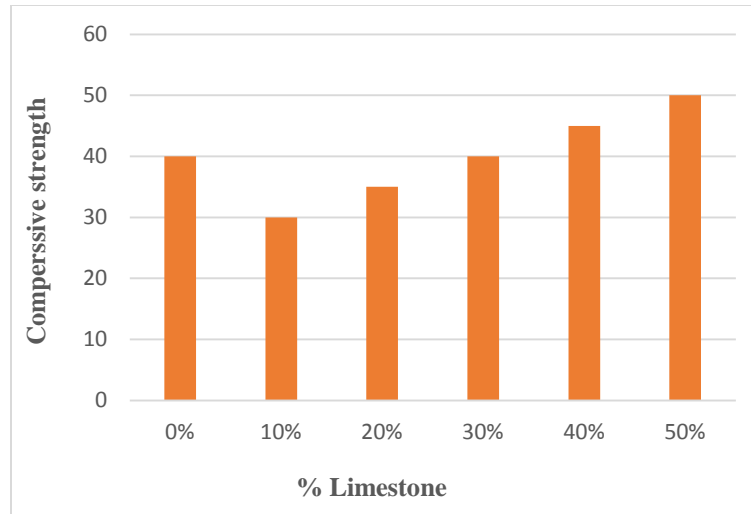


Fig. 3. Workability test results [41]

Burroughs et al. [42] conducted an experiment for regulating the concrete workability when cement was replaced by limestone in the amount of 0%, 10%, 15%, 20%, 25%, 30%, 35%, and 40%. The results concluded that the workability of concrete increased rapidly as water cement ratio got increased.

### 3. Hardened properties of concrete

The strength as well as performance of hardened concrete depend mainly on strength and performance under various types of load conditions. The main properties which come under hardened properties are shown below.

#### 3.1. Compressive strength-

Strength during compression is among the main property of concrete. Compressive strength of limestone dust concrete mixes was evaluated by several researchers.

Lollini et al. [43] carried out an experiment for calculating the strength under compression of concrete cubes replacing limestone dust at 7 and 28 days. Results of concrete depend upon the water/binder ratio. Being cured at 7 days with the dosage of binder being equal to  $300\text{kg/m}^3$  the value got enlarged. While, after 28 days of curing, the w/b ratio got reduced from 0.61 to 0.46. So, it was concluded that increase the compressive strength decreased the water/ binder ratio.

Elgalhud et al. [44] concluded that with the wet curing of 7 and 28 days having water cement ratio of 0.45, the researchers investigated the influence of strength of compression on the permeability of paste of cement and mortar concrete with limestone powder as a limited replacement for cement. The different percentages of limestone powder in the concrete by weight of Portland cement (20%, 25%, 30%, and 40%) were studied. It was reported that limestone powder up to 25% should not increase the strength of concrete and increase in the limestone powder to more than 30% directly affected the porosity of concrete thereby reducing the compressive strength. Fig. 4 represents the test results of compressive strength of the concrete.

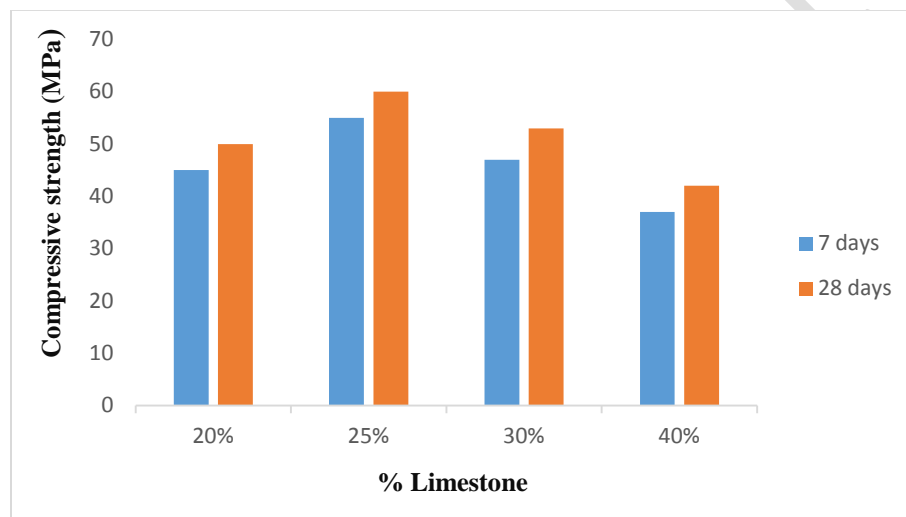


Fig.4.Compressive strength test results [44]

Li et al. [45] investigated the strength of compression of ultra-high performance concrete incorporating powder of limestone as a partial replacement of cement. The percentage of limestone powder added by weight of cement were (10%, 15%, 20%, 25%, 30% and 35%). The test was performed for M50 grade of concrete. The water cement ratios of 0.25, 0.30, and 0.35 were selected. Cube of size (100mm×100mm×100mm) was used to determine the compressive strength for a period of 7, 28, and 90 days of curing. It was discovered that swapping cement with the powder of limestone increased the strength of concrete. The optimal dosage of replacement was found to be 30% as shown in Fig. 5.

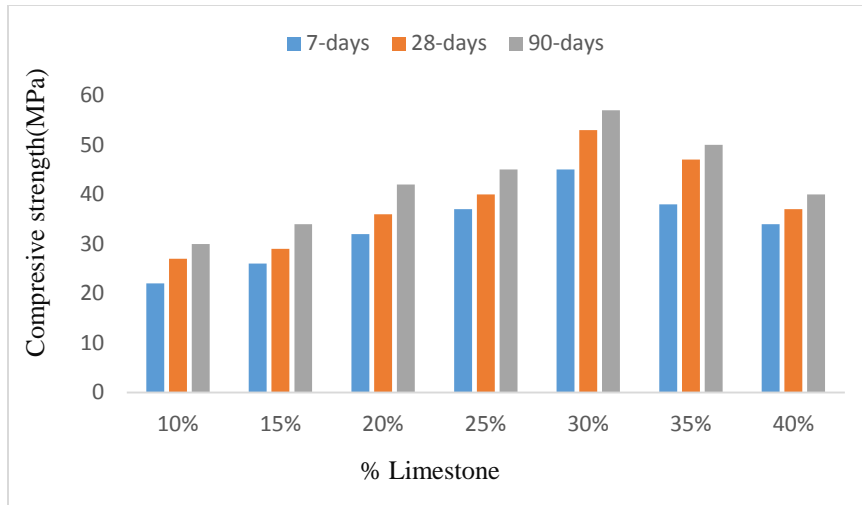


Fig.5. Compressive strength results [45]

Meddah et al. [46] analyzed compressive strength tests for M25 and M30 grade of concrete by limestone slurry at the replacement ratio of 10%, 20%, 30% and 40% for 7 and 28 days of curing. It was concluded that the limestone powder up to 40% replacement decreases the asset of concrete and at 0.52 water cement ratio with 30% replacement provide good strength concrete as shown in Fig. 6.

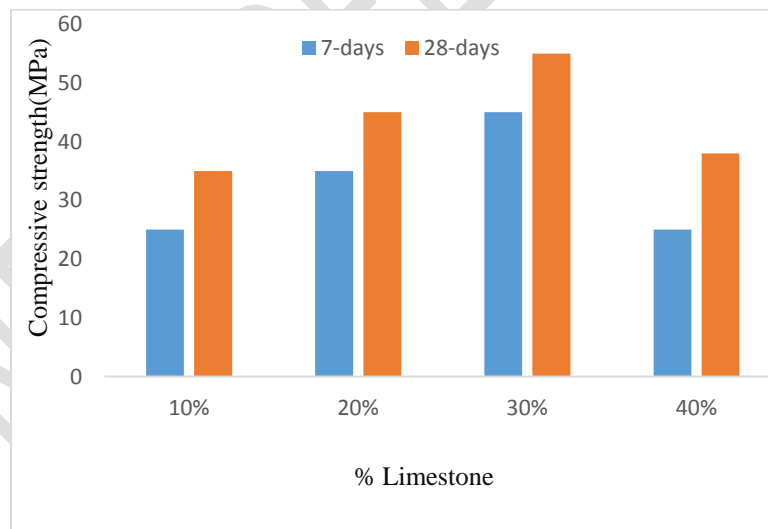


Fig. 6. Compressive strength results [46]

Mikhailova et al. [47] carried out an experiment on the strength of compression of concrete by using dolomite limestone powder. The percentage of limestone powder used varied from 0% to 30% by weight of cement and the water cement ratio was 0.5 was selected. The size of prismatic

mould that was used was (40×40×160mm). While compressive strength at 7, 14 and 28 days of curing was determined. It was decided that the increase in compressive strength, when sample contained 25% to 30% powder of limestone augmented by 16.7% and 23.5% at 14 and 28 days respectively.

The properties of concrete incorporating limestone were examined by Zatitri et al. [48] the compressive strength that was obtained varied between 50 MPa to 75 MPa for concrete having limestone as a substitution of cement with percentage of 0,10,20,30 and 40 respectively. It was noticed that a combination comprising of 20 to 30% limestone had the highest compressive strength as shown Fig. 7.

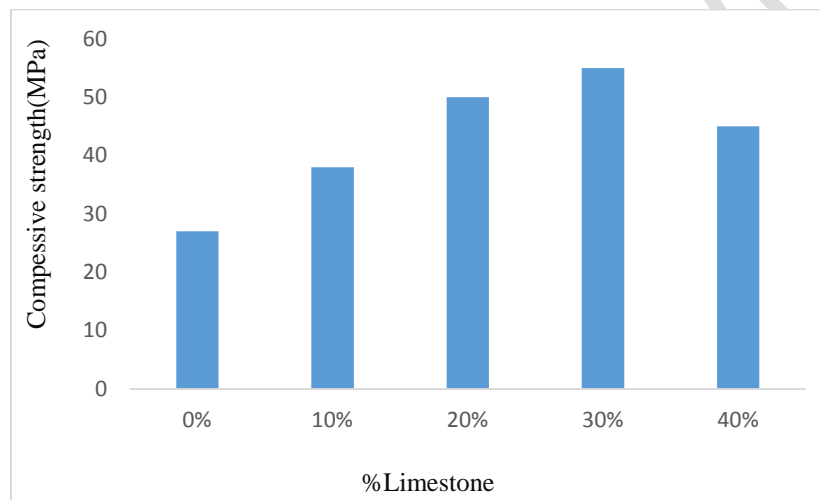


Fig.7. Compressive strength test results [48]

Characteristics of strength of compression of large quantity of fly ash concrete containing limestone were studied by Yoshitake et al. [49] the strength of compression was depicted to be maximum in sample of concrete containing 30% limestone as a partial substitution of cement at the ages of 7, 28, and 91 days.

### 3.2 .Tensile strength

Largest load sustained by a material without shattering while it is strong, divided by original cross section area of the material, is referred to as tensile strength.

Zhou et al. [50] deliberated the tensile strength of the limestone as partial replacement of the cement. They substituted limestone powder for cement in a ratio of 0% to 50%. At less than 30%

cement replacement with limestone powder, greatest split tensile strength was recorded. Fig. 8 depicts the findings of their research.

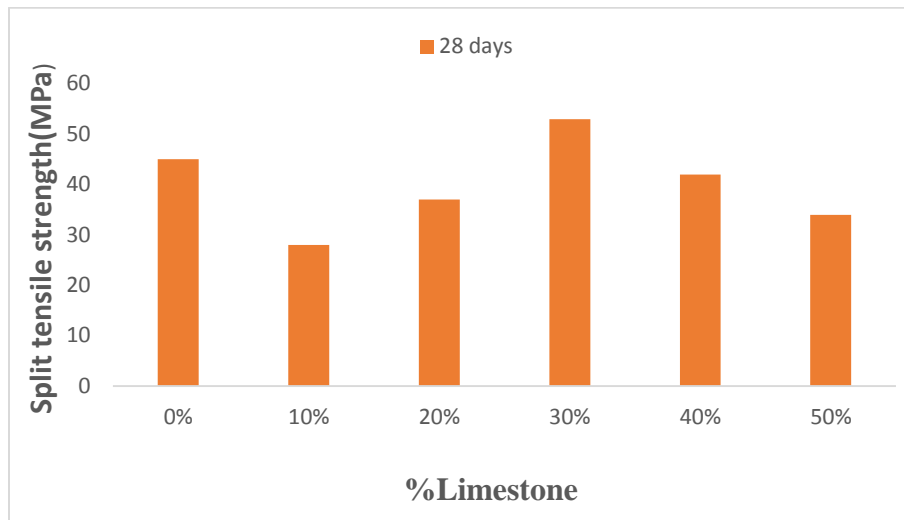


Fig. 8 Split tensile strength test results [50]

Zenggi et al. [51] investigated the properties of large volume powdered limestone of concrete. With curing of 28 days the water cement ratio was 0.4. While replacement ratios were 20%, 25%, 30% and 35%. When 25 to 30% of cement was substituted with limestone powder, the maximum split tensile strength was found. Results of their finding are represented in Fig. 9.

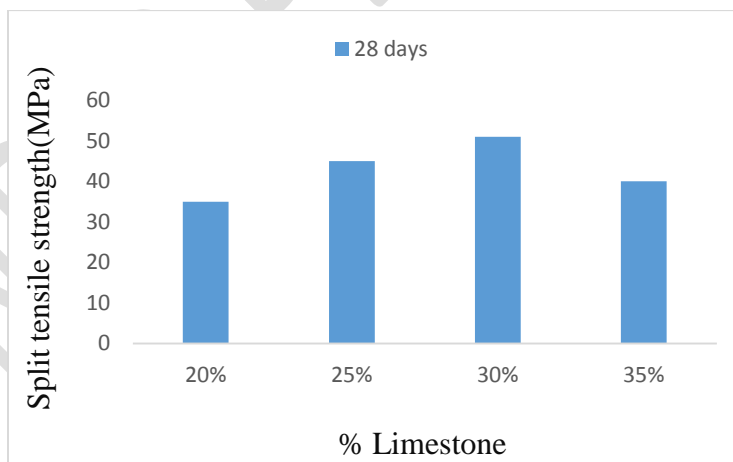


Fig.9. Split tensile strength test results [51]

Wang et al. [52] tested the tensile strength of the concrete comprising powder of limestone. It was replaced cement with powdered limestone having proportions of 10%, 20%, and 30%. At 20% cement replacement with limestone powder, the greatest split tensile strength was recorded.

Varhen et al. [53] examined the effect of switching the cement by filler of limestone. It was discovered that there was an upsurge in the percentage of filler of limestone at a limit of 30% with cement. Also, the split tensile strength was increased in concrete containing replacement of 25% to 30 %.

Turk et al. [54] premeditated the tensile strength of powdered limestone of grade M30. It was replaced by silica sand with limestone powder in the proportion of 25%, 50% and 75% for curing of 3, 28, 90 days. Supreme tensile strength was detected at 25% to 50% of silica sand replacement with limestone powder. Fig. 10 represents the test results.

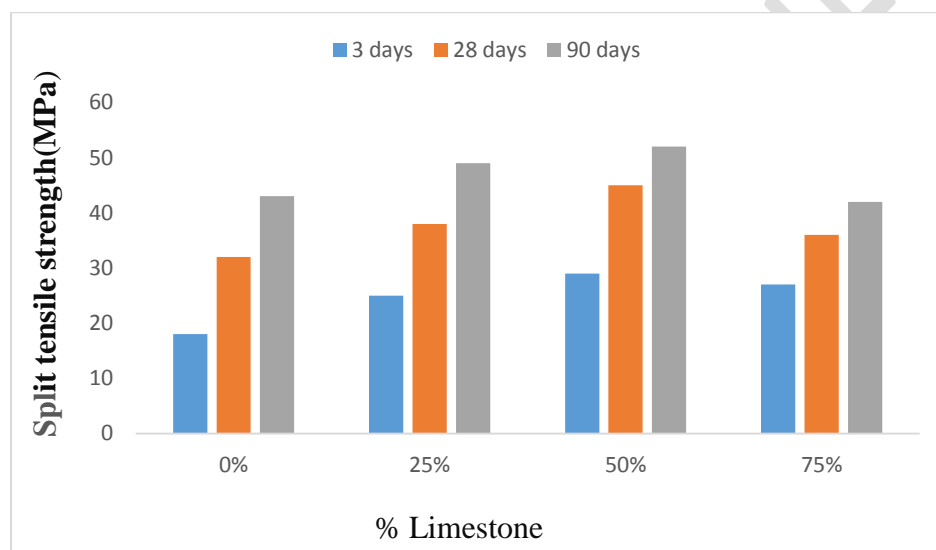


Fig.10. Split tensile strength test results [54]

Sua-iam et al. [55] used the combination of both limestone powder as well as rice husk ash by partially replacing the cement. The combination of concrete containing 30% limestone powder with 50% to 70% rice husk ash had the highest tensile strength.

### 3.3. Flexural strength

Flexural strength which is a measurement of tensile strength of concrete is used to determine the ability of an unreinforced concrete beam or slab to counterattack the failure during bending.

Acharya et al. [56] investigated the flexural strength of concrete which improved with the addition of limestone quantity leading to sustainable construction. Mix of Portland pozzolana cement containing 30% of limestone showed the highest flexural strength in the mix of concrete.

Coo et al. [57] steered an investigation to determine the flexural strength of limestone concrete. It was found that the value of flexural strength of concrete containing limestone increased with time. The results showed that when limestone powder was replaced up to 30% with cement it showed a higher value than the conventional concrete.

Hesami et al. [58] analyzed the flexural strength tests for 0%, 20%, 30%, 40% and 50% for 7 as well as 28 days of curing. It was reported that flexural strength rose up to 30 % by substituting limestone powder in concrete with cement. At 30% replacement, the ultimate flexural strength was found to be 83 KN. Fig. 11 demonstrates that by increasing the amount of powdered limestone in concrete the flexural strength was reduced.

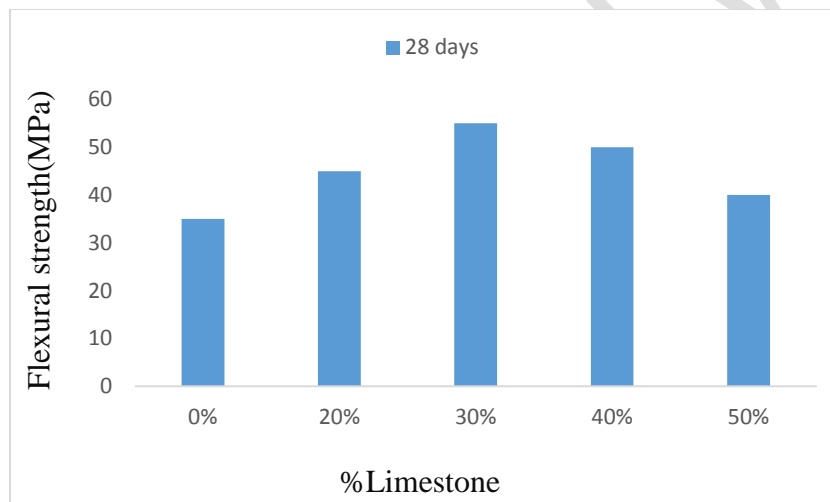


Fig. 11. Flexural strength test results [58]

Huang et al. [59] inspected the properties of ultra-high performance concrete with admixing cementitious material such as limestone powder and fly ash. Flexural strength increased when limestone concentration was increased and fly ash content decreased according to the researchers.

Shaker et al. [60] investigated the flexural strength of concrete with 10%, 20%, 30%, and 40% replacement of powdered limestone as a substitution for cement. The test results are represented in Fig. 12 according to the test results 30% limestone powder showed maximum flexural

strength. The sample of 30% limestone powder demonstrated an 80% improvement in flexural strength of the concerning control mix.

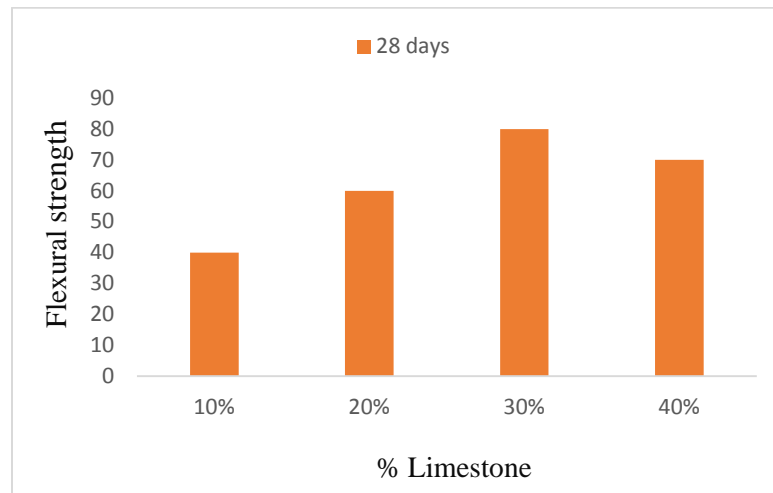


Fig.12.Flexural strength test results [60]

Ibrahim et al. [61] replaced cement with limestone in the ratios of 0%, 20%, 30% 40% and 50% in concrete. It was found that the strength of flexure in concrete is maximum for 30% of limestone replacement by cement.

### 3.4. Modulus of elasticity –

When stress is applied to an object its elastic modulus is a measurement of its resistance for being deformed.

Shen et al. [62] examined the elasticity modulus of concrete with powdered limestone and silica fume. The results showed that the elasticity and time had been increased for 25% powdered limestone and 10% silica fume.

Mohammad et al. [63] studied the elasticity modulus of limestone concrete of grade M30. The cement was replaced with limestone in the proportion of 10%, 15%, 20%, 25% and 30%. The maximum modulus of elasticity was observed at 25% of cement replacement with limestone. Results of their finding are represented in Fig.13.

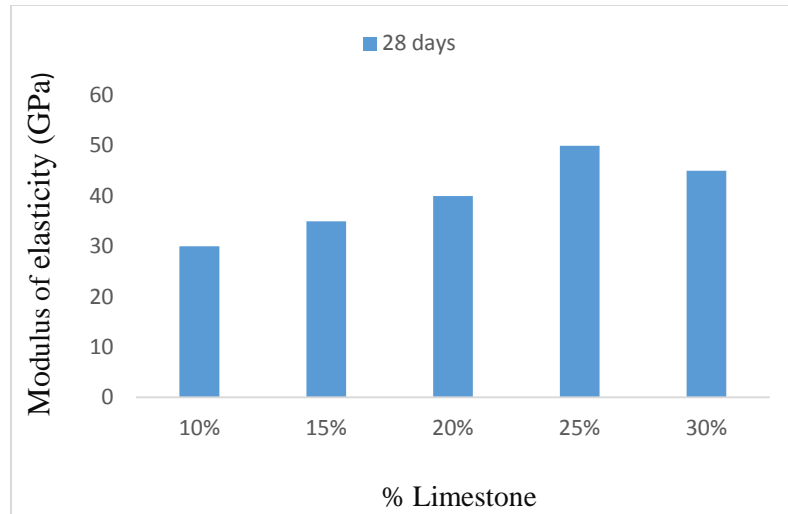


Fig. 13. Modulus of elasticity test results [63]

Revani et al. [64] investigated the elasticity modulus of concrete comprising powdered limestone. The percentage of powdered limestone added by the weight of cement was 10%, 15%, 20%, 25%, and 30%. The modulus of elasticity was calculated using the w/c ratio of 0.35, 0.40 and 0.45 after 7, 14 and 28 days of curing. It was discovered that by replacing 25% of cement with powdered limestone flexibility of concrete was improved as shown in Fig. 14.

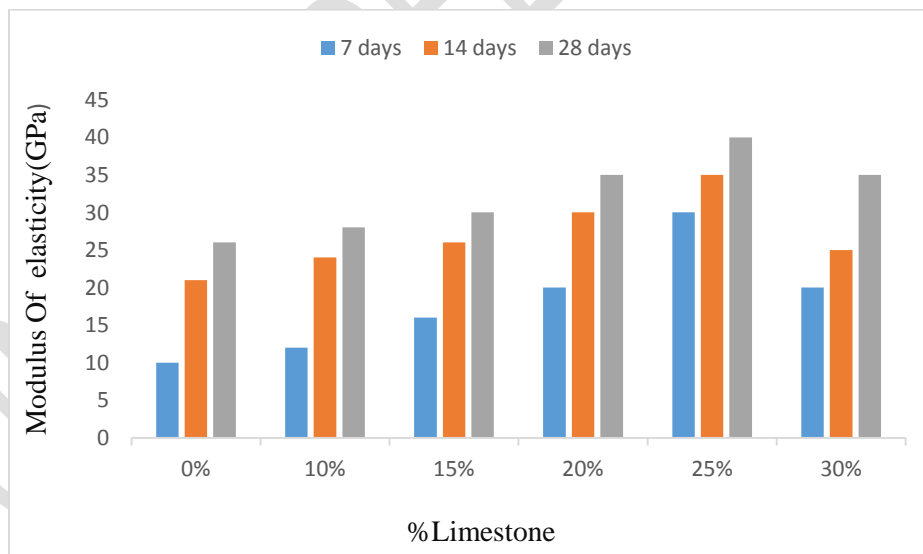


Fig. 14. Modulus of elasticity test results [64]

Silva and Brito [65] inspected the elasticity modulus of self-compacting concrete including powdered limestone as a fraction all stand by for cement. It was found an upsurge in the values of modulus of elasticity with powdered limestone of 0% to 30%. Maximum modulus of elasticity was found at 30% replacement after that it decreased.

### 3.5. Durability-

The ability of concrete to resist the wearing and deterioration is termed as durability of concrete.

Palm et al. [66] carried out a permeability test to check durability of concrete with limestone powder as a substituent for cement. An increase in durability was observed in the concrete containing 30% to 35% limestone powder at 0.35 w/c ratio for 28 days. The trial of 30% limestone powder demonstrated highest durability.

Mostofinejad et al. [67] investigated long-term durability of limestone concrete. The quantity of powdered limestone in the cement was 0% to 30% by weight, with water cement ratio of 0.45 and the micro silica and slag content was 10% to 15% by weight. The addition of limestone enhanced durability. The concrete containing 15 to 25% limestone powder showed the highest durability.

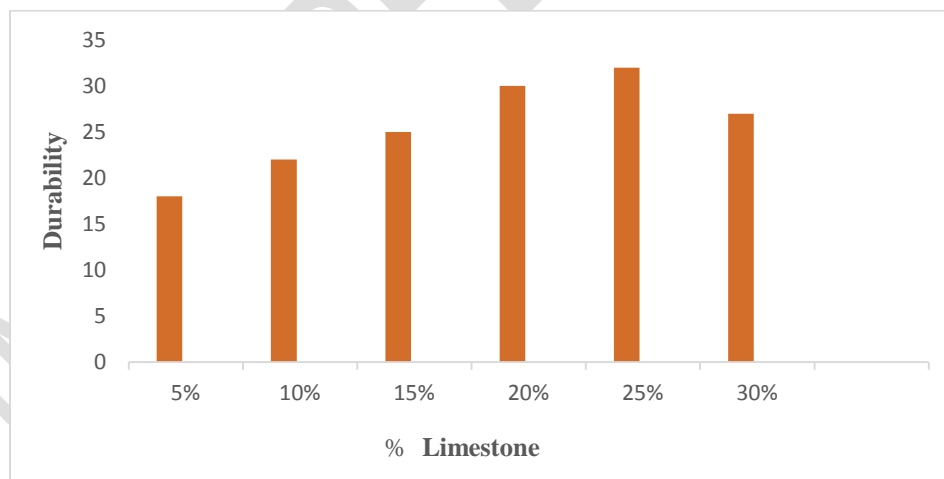


Fig.15. Permeability test results [67]

Elhundiapani et al. [68] incorporated the use of limestone powder in concrete. The researchers observed that 25% limestone and 10% clay imparted the highest durability with an increase in the substitution percentage of limestone.

Proge et al. [69] examined the use of limestone in the percentage of 0%, 10%, 20%, 30% and 40% that replaced cement in concrete. It was found that the durability of concrete was maximum when 30% of limestone was replaced by cement. Fig. 15 shows the representation of the test values.

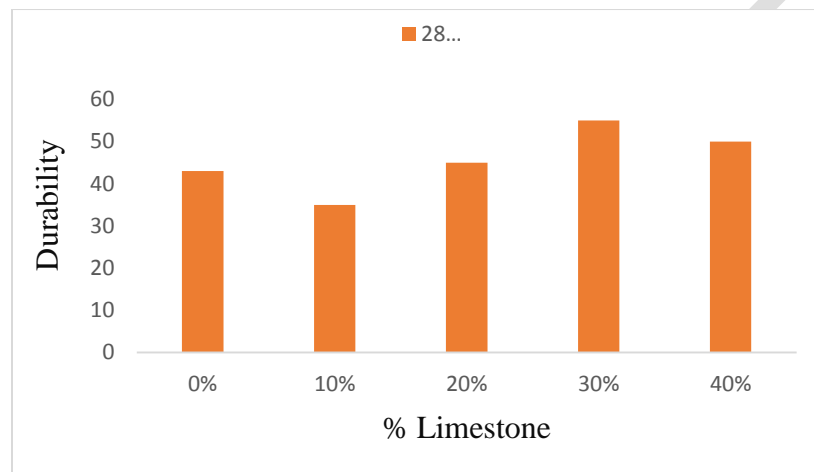


Fig.16 Permeability test results [69]

Shaker et al. [70] examined the durability of concrete that was tested by the means of limestone as a partial substitution for cement at levels of 10%, 20% and 30% of cement. The durability was found to be maximum at 30% replacement.

## 5. Concluding Remarks

Construction activities must now take into account sustainability. Several investigations on various materials to replace cement in concrete have been undertaken in the past. The impact of limestone slurry on concrete qualities like freshness, mechanical strength, and durability is discussed in this study. A review of limestone slurry and its impact on concrete as a cement substitute has been attempted.

The following conclusions can be derived from the researcher's work on using limestone slurry as a partial substitute for cement in concrete production:

- Based on a number of study articles, results subjected to various limestone slurry percentages in concrete, it can be concluded that the optimum utilization of limestone slurry shall be 25 to 30% by the mass of cement in concrete.
- The fresh properties of limestone concrete had different results, according to most of the researchers there was an increase in workability 20% to 30%.
- From the above study, researchers concluded that there was an increment in compressive strength with the increase in limestone quantity up to 30%, after that, as the percentage of limestone in concrete increased the strength got reduced.
- As the proportions of limestone increased to a certain limit, the split tensile strength increased. Optimum replacement of cement was around 30 percent by limestone after that strength decreased.
- The various studies showed that there was an enhancement in flexural strength just like compressive strength up to 30% of limestone content, after that limit it also got reduced as limestone content enhanced in concrete.
- Modulus of elasticity of concrete increased up to 25% when limestone was utilized to partially substitute cement.
- From the above study, researchers concluded that there was an increment in the durability of concrete up to 25 to 30% replacement of limestone.

Concrete with limestone as a substitute is a sustainable construction material that decreases pollution as well as disposal-related issues which is harmful to the environment. The optimum substitution level of cement with limestone was found to be 25-30%. Concrete's mechanical as well as durability properties were amended by utilizing limestone.

#### **Reference-**

1. Agrawal, Y., Gupta, T., Siddique, S., & Sharma, R. K. (2021). Potential of dolomite industrial waste as construction material: a review. *Innovative Infrastructure Solutions*, 6(4), 1-15.
2. Chouhan, D. S., Agrawal, Y., Gupta, T., & Sharma, R. K. (2017). Utilization of Granite Slurry Waste in Concrete: A. *Indian Journal of Science and Technology*, 10, 6.
3. Kanyal, K. S., Agrawal, Y., & Gupta, T. (2021). Properties of Sustainable Concrete Containing Red Mud: A Review. *Journal of Scientific Research and Reports*, 15-26.

4. Siddique, S., Jang, J. G., & Gupta, T. (2021). Developing marble slurry as supplementary cementitious material through calcination: Strength and microstructure study. *Construction and Building Materials*, 293, 123474.
5. Saxena, R., Gupta, T., Sharma, R. K., & Yadav, S. (2022). Influence of Incorporating Industrial Byproducts/Wastes on Mechanical Properties and Durability Characteristics of Self-Consolidating Concrete: A Review. *Recent Trends in Industrial and Production Engineering*, 185-196.
6. Shrimali, A., Chauhan, D. S., Gupta, T., & Sharma, R. K. (2017). Behavior of concrete utilizing recycled aggregate—A review. *Int. j. eng. res. appl*, 7(1), 72-79.
7. Agrawal, Y., Gupta, T., Sharma, R., Panwar, N. L., & Siddique, S. (2021). A Comprehensive Review on the Performance of Structural Lightweight Aggregate Concrete for Sustainable Construction. *Construction Materials*, 1(1), 39-62.
8. Sharma, D., Agrawal, Y., Gupta, T., & Sharma, R. (2021). A Review of the Hardened Properties of Eco-Friendly Concrete Containing Ground Granulated Blast-furnace Slag. *Journal of Scientific Research and Reports*, 37-49.
9. Baruah, R., Saxena, R., Gupta, T., & Sharma, R. (2020). A Review of the Hardened Properties of Eco-Friendly Concrete Containing Rice Husk Ash.
10. Saxena, R., Gupta, T., Sharma, R. K., & Panwar, N. L. (2021). Influence of granite waste on mechanical and durability properties of fly ash-based geopolymer concrete. *Environment, Development and Sustainability*, 1-25.
11. Rajawat, D., Siddique, S., Shrivastava, S., Chaudhary, S., & Gupta, T. (2018). Influence of fine ceramic aggregates on the residual properties of concrete subjected to elevated temperature. *Fire and Materials*, 42(7), 834-842.
12. Khan, M. S. H., Nguyen, Q. D., & Castel, A. (2018). Carbonation of Limestone calcined clay cement concrete. In *Calcined Clays for Sustainable Concrete* (pp. 238-243). Springer, Dordrecht.
13. Pillai, R. G., Gettu, R., Santhanam, M., Rengaraju, S., Dhandapani, Y., Rathnarajan, S., & Basavaraj, A. S. (2019). Service life and life cycle assessment of reinforced concrete systems with limestone calcined clay cement (LC3). *Cement and Concrete Research*, 118, 111-119.
14. Rakhimova, N. R., Rakhimov, R. Z., Naumkina, N. I., Khuzin, A. F., & Osin, Y. N. (2016). Influence of limestone content, fineness, and composition on the properties and microstructure of alkali-activated slag cement. *Cement and Concrete Composites*, 72, 268-274.

15. Yang, H., Liang, D., Deng, Z., & Qin, Y. (2018). Effect of limestone powder in manufactured sand on the hydration products and microstructure of recycled aggregate concrete. *Construction and Building Materials*, 188, 1045-1049.
16. Mo, L., Zhang, F., Deng, M., Jin, F., Al-Tabbaa, A., & Wang, A. (2017). Accelerated carbonation and performance of concrete made with steel slag as binding materials and aggregates. *Cement and Concrete Composites*, 83, 138-145.
17. Moon, G. D., Oh, S., Jung, S. H., & Choi, Y. C. (2017). Effects of the fineness of limestone powder and cement on the hydration and strength development of PLC concrete. *Construction and Building Materials*, 135, 129-136.
18. Panesar, D. K., Aqel, M., Rhead, D., & Schell, H. (2017). Effect of cement type and limestone particle size on the durability of steam cured self-consolidating concrete. *Cement and Concrete Composites*, 80, 175-189.
19. Shadkam, H. R., Dadsetan, S., Tadayon, M., Sanchez, L. F., & Zakeri, J. A. (2017). An investigation of the effects of limestone powder and Viscosity Modifying Agent in durability-related parameters of self-consolidating concrete (SCC). *Construction and Building Materials*, 156, 152-160.
20. Tahersima, M., & Tikalsky, P. (2017). Finite element modeling of hydration heat in a concrete slab-on-grade floor with limestone blended cement. *Construction and Building Materials*, 154, 44-50.
21. Shafigh, P., Nomeli, M. A., Alengaram, U. J., Mahmud, H. B., & Jumaat, M. Z. (2016). Engineering properties of lightweight aggregate concrete containing limestone powder and high volume fly ash. *Journal of cleaner production*, 135, 148-157.
22. Tufail, M., Shahzada, K., Gencturk, B., & Wei, J. (2017). Effect of elevated temperature on mechanical properties of limestone, quartzite, and granite concrete. *International Journal of Concrete Structures and Materials*, 11(1), 17-28.
23. Tu, Z., Guo, M. Z., Poon, C. S., & Shi, C. (2016). Effects of limestone powder on CaCO<sub>3</sub> precipitation in CO<sub>2</sub> cured cement pastes. *Cement and Concrete Composites*, 72, 9-16.
24. Yamei, H., & Lihua, W. (2017). Effect of particle shape of limestone manufactured sand and natural sand on concrete. *Procedia Engineering*, 210, 87-92.
25. Elçi, H., Türk, N., & İşintek, İ. (2015). Limestone dimension stone quarry waste properties for concrete in Western Turkey. *Arabian Journal of Geosciences*, 8(10), 8951-8961.

26. Alhozaimy, A. M. (2009). Effect of absorption of limestone aggregates on strength and slump loss of concrete. *Cement and Concrete Composites*, 31(7), 470-473.
27. Bentz, D. P., Ardani, A., Barrett, T., Jones, S. Z., Lootens, D., Peltz, M. A., ... & Weiss, W. J. (2015). Multi-scale investigation of the performance of limestone in concrete. *Construction and Building Materials*, 75, 1-10.
28. El-Hassan, H., & Shao, Y. (2015). Early carbonation curing of concrete masonry units with Portland limestone cement. *Cement and Concrete Composites*, 62, 168-177.
29. Fares, G. (2015). Effect of slump cone orientation on the slump flow time (T50) and stability of sustainable self-compacting concrete containing limestone filler. *Construction and Building Materials*, 77, 145-153.
30. Alexander, M. G. (2013). Durability performance potential and strength of blended Portland limestone cement concrete. *Cement and Concrete Composites*, 39, 115-121.
31. Tsivilis, S., Chaniotakis, E., Batis, G., Meletiou, C., Kasselouri, V., Kakali, G., ... & Psimadas, C. (1999). The effect of clinker and limestone quality on the gas permeability, water absorption, and pore structure of limestone cement concrete. *Cement and concrete composites*, 21(2), 139-146.
32. Sotiriadis, K., Nikolopoulou, E., & Tsivilis, S. (2012). Sulfate resistance of limestone cement concrete exposed to combined chloride and sulfate environment at low temperature. *Cement and Concrete Composites*, 34(8), 903-910.
33. Fares, G. (2015). Effect of slump cone orientation on the slump flow time (T50) and stability of sustainable self-compacting concrete containing limestone filler. *Construction and Building Materials*, 77, 145-153.
34. Esping, O. (2008). Effect of limestone filler BET (H<sub>2</sub>O)-area on the fresh and hardened properties of self-compacting concrete. *Cement and Concrete Research*, 38(7), 938-944.
35. Chen, J. J., Kwan, A. K. H., & Jiang, Y. (2014). Adding limestone fines as cement paste replacement to reduce water permeability and sorptivity of concrete. *Construction and Building Materials*, 56, 87-93.
36. Celik, K., Jackson, M. D., Mancio, M., Meral, C., Emwas, A. H., Mehta, P. K., & Monteiro, P. J. (2014). High-volume natural volcanic pozzolan and limestone powder as partial

- replacements for portland cement in self-compacting and sustainable concrete. *Cement and concrete composites*, 45, 136-147.
37. Li, C., Jiang, L., & Li, S. (2020). Effect of limestone powder addition on threshold chloride concentration for steel corrosion in reinforced concrete. *Cement and Concrete Research*, 131, 106018.
38. Alexandra, C., Bogdan, H., Camelia, N., & Zoltan, K. (2018). Mix design of self-compacting concrete with limestone filler versus fly ash addition. *Procedia Manufacturing*, 22, 301-308.
39. Mohammed, M. K., Al-Hadithi, A. I., & Mohammed, M. H. (2019). Production and optimization of eco-efficient self-compacting concrete SCC with limestone and PET. *Construction and Building Materials*, 197, 734-746.
40. Shaker, F., Rashad, A., & Allam, M. (2018). Properties of concrete incorporating locally produced Portland limestone cement. *Ain Shams Engineering Journal*, 9(4), 2301-2309.
41. Da Silva, P. R., & De Brito, J. (2015). Experimental study of the porosity and microstructure of self-compacting concrete (SCC) with binary and ternary mixes of fly ash and limestone filler. *Construction and Building Materials*, 86, 101-112.
42. Burroughs, J. F., Shannon, J., Rushing, T. S., Yi, K., Gutierrez, Q. B., & Harrelson, D. W. (2017). Potential of finely ground limestone powder to benefit ultra-high performance concrete mixtures. *Construction and Building Materials*, 141, 335-342.
43. Lollini, F., Redaelli, E., & Bertolini, L. (2014). Effects of portland cement replacement with limestone on the properties of hardened concrete. *Cement and Concrete Composites*, 46, 32-40.
44. Elgallud, A. A., Dhir, R. K., & Ghataora, G. (2016). Limestone addition effects on concrete porosity. *Cement and Concrete Composites*, 72, 222-234.
45. Li, P. P., Brouwers, H. J. H., Chen, W., & Yu, Q. (2020). Optimization and characterization of high-volume limestone powder in sustainable ultra-high performance concrete. *Construction and Building Materials*, 242, 118112.
46. Meddah, M. S., Lmbachiya, M. C., & Dhir, R. K. (2014). Potential use of binary and composite limestone cement in concrete production. *Construction and Building Materials*, 58, 193-205.
47. Mikhailova, O., Yakovlev, G., Maeva, I., & Senkov, S. (2013). Effect of dolomite limestone powder on the compressive strength of concrete. *Procedia Engineering*, 57, 775-780.

48. Zatiri R, Bederina M, Bouziani T, Makhloufi Z, Hadjoudja M. Development of high performances concrete based on the addition of ground dune sand and limestone rock using the mixture design modeling approach. *Construction and Building Materials*. 2014 Jun 16; 60:8-16.
49. Yoshitake I, Wong H, Ishida T, Nassif AY. Thermal stress of high volume fly-ash (HVFA) concrete made with limestone aggregate. *Construction and Building Materials*. 2014 Nov 30; 71:216-25.
50. Zhou, W., Li, L., Liu, S. H., Vinh, T. D., & Liu, X. H. (2017). Hydration properties and thermal analysis of cement-based materials containing limestone powder. *Journal of Central South University*, 24(12), 2932-2939.
51. Zhang, Z., Wang, Q., & Chen, H. (2016). Properties of high-volume limestone powder concrete under standard curing and steam-curing conditions. *Powder Technology*, 301, 16-25.
52. Wang, Q., Yang, J., & Chen, H. (2017). Long-term properties of concrete containing limestone powder. *Materials and Structures*, 50(3), 1-13.
53. Varhen, C., Dilonardo, I., de Oliveira Romano, R. C., Pileggi, R. G., & de Figueiredo, A. D. (2016). Effect of the substitution of cement by limestone filler on the rheological behavior and shrinkage of micro concrete. *Construction and building materials*, 125, 375-386.
54. Turk, K., & Demirhan, S. (2017). Effect of limestone powder on the rheological, mechanical, and durability properties of ECC. *European Journal of Environmental and Civil Engineering*, 21(9), 1151-1170.
55. Sua-iam, G., Sokrai, P., & Makul, N. (2016). Novel ternary blends of Type 1 Portland cement, residual rice husk ash, and limestone powder to improve the properties of self-compacting concrete. *Construction and Building Materials*, 125, 1028-1034.
56. Acharya, P. K., & Patro, S. K. (2016). Acid resistance, sulfate resistance, and strength properties of concrete containing ferrochrome ash (FA) and lime. *Construction and building materials*, 120, 241-250.
57. Coo, M., & Pheeraphan, T. (2016). Effect of sand, fly ash, and limestone powder on preplaced aggregate concrete mechanical properties and reinforced beam shear capacity. *Construction and Building Materials*, 120, 581-592.

58. Hesami, S., Modarres, A., Soltaninejad, M., & Madani, H. (2016). Mechanical properties of roller compacted concrete pavement containing coal waste and limestone powder as partial replacements of cement. *Construction and Building Materials*, *111*, 625-636.
59. Huang, W., Kazemi-Kamyab, H., Sun, W., & Scrivener, K. (2017). Effect of cement substitution by limestone on the hydration and microstructural development of ultra-high performance concrete (UHPC). *Cement and Concrete Composites*, *77*, 86-101.
60. Shaker, F., Rashad, A., & Allam, M. (2018). Properties of concrete incorporating locally produced Portland limestone cement. *Ain Shams Engineering Journal*, *9*(4), 2301-2309.
61. Ibrahim, M., & Issa, M. (2016). Evaluation of chloride and water penetration in concrete with cement containing limestone and IPA. *Construction and Building Materials*, *129*, 278-288.
62. Mohammadi, I., & South, W. (2016). The influence of the higher limestone content of General Purpose cement according to high-strength concrete test results and construction field data. *Materials and Structures*, *49*(11), 4621-4636.
63. Rezvani, M., & Proske, T. (2017). Influence of chemical-mineralogical properties of limestone on the shrinkage behavior of cement paste and concrete made of limestone-rich cement. *Construction and Building Materials*, *157*, 818-828.
64. Silva, P., & De Brito, J. (2017). Experimental study of the mechanical properties and shrinkage of self-compacting concrete with binary and ternary mixes of fly ash and limestone filler. *European Journal of Environmental and Civil Engineering*, *21*(4), 430-453.
65. Palm, S., Proske, T., Rezvani, M., Hainer, S., Müller, C., & Graubner, C. A. (2016). Cement with a high limestone content—Mechanical properties, durability, and ecological characteristics of the concrete. *Construction and building materials*, *119*, 308-318.
66. Mostofinejad, D., Nosouhian, F., & Nazari-Monfared, H. (2016). Influence of magnesium sulfate concentration on the durability of concrete containing micro-silica, slag, and limestone powder using durability index. *Construction and Building Materials*, *117*, 107-120.
67. Dhandapani, Y., Sakthivel, T., Santhanam, M., Gettu, R., & Pillai, R. G. (2018). Mechanical properties and durability performance of concretes with Limestone Calcined Clay Cement (LC3). *Cement and Concrete Research*, *107*, 136-151.

69. Proske, T., Rezvani, M., Palm, S., Müller, C., & Graubner, C. A. (2018). Concretes are made of efficient multi-composite cement with slag and limestone. *Cement and Concrete Composites*, 89, 107-119.
70. Shaker, F., Rashad, A., & Allam, M. (2018). Properties of concrete incorporating locally produced Portland limestone cement. *Ain Shams Engineering Journal*, 9(4), 2301-2309.

UNDER PEER REVIEW